




U. S. STEEL PRODUCTS CO.  
POCKET COMPANION



FOR

ENGINEERS, ARCHITECTS AND BUILDERS

CONTAINING

USEFUL INFORMATION AND TABLES

APPERTAINING TO THE USE OF

STEEL

MANUFACTURED BY

CARNEGIE STEEL COMPANY

PITTSBURGH, PA.

Copyright 1916 by  
CARNEGIE STEEL COMPANY  
Pittsburgh, Pa.

18th Edition, January 1, 1916.

**T**HIS, the Eighteenth Edition of the Carnegie Pocket Companion, contains the revised data of the sixteenth edition.

Since 1903, the date of the fifteenth edition, there have been many changes in the art of bridge and building construction with the extension of the use of steel into other lines than those covered by that edition. The endeavor in the sixteenth and subsequent issues has been to eliminate obsolete forms of construction, to revise the forms retained from the fifteenth edition so as to make them conformable to present standard practice, and to incorporate with the matter so retained such information on the newer lines of manufacture as would be of interest to engineers, architects, and builders.

This book differs from the sixteenth edition in the addition of tables of standard punching in flanges of beams and channels and in the extension of the tables of extreme sizes of plates to include nickel steel. The sizes of channels, bulb angles, checkered plates, merchant bars, etc. have been revised. A new line of supplementary beam sections has been substituted for that shown in the previous issues and, in addition, tables and data are included on a new line of bulb angle sections rolled in accordance with British Standards. Further, the A. S. T. M. Specifications appear in the forms adopted at their latest revision.

From the large number of rolled shapes which we manufacture, we have selected for illustration in the profiles and tables such as are deemed most suitable for use in bridge, building, locomotive, car, and ship construction. A complete list of all the sections rolled on the structural, plate, bar and rail mills of the Carnegie Steel Company, together with tables of weights and other data in regard to these products, is given in our Shape Book, Fifth Edition.



CARNEGIE STEEL COMPANY

AMERICAN SOCIETY FOR TESTING MATERIALS

PHILADELPHIA, PA., U. S. A.

AFFILIATED WITH THE

INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS

STANDARD SPECIFICATIONS

FOR

STRUCTURAL STEEL FOR BRIDGES

SERIAL DESIGNATION: A7-15.

The specifications for this material are issued under the fixed designation A 7; the final number indicates the year of original issue or, in the case of revision, the year of latest revision.

ADOPTED, 1901; REVISED, 1905, 1909, 1913, 1914, 1915.

1. **Steel Castings.** The Standard Specifications for Steel Castings (Serial Designation A-27) adopted by the American Society for Testing Materials shall govern the purchase of steel castings for bridges. Unless otherwise specified, Class B castings, medium grade, shall be used.

I. MANUFACTURE

2. **Process.** The steel shall be made by the open-hearth process.

II. CHEMICAL PROPERTIES AND TESTS

3. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition:

	STRUCTURAL STEEL				RIVET STEEL			
Phosphorus	Acid.....	not over	0.06	per cent	not over	0.04	per cent	
	Basic.....	" "	0.04	" "	" "	0.04	" "	
Sulphur	.....	" "	0.05	" "	" "	.045	" "	

## STANDARD SPECIFICATIONS

4. **Ladle Analyses.** An analysis to determine the percentages of carbon, manganese, phosphorus and sulphur shall be made by the manufacturer from a test ingot taken during the pouring of each melt, a copy of which shall be given to the purchaser or his representative. This analysis shall conform to the requirements specified in sec. 3.

5. **Check Analyses.** Analyses may be made by the purchaser from finished material representing each melt, in which case an excess of 25 per cent above the requirements specified in sec. 3 shall be allowed.

### III. PHYSICAL PROPERTIES AND TESTS

6. **Tension Tests.** (a) The material shall conform to the following requirements as to tensile properties:

Properties Considered	Structural Steel	Rivet Steel
Tensile strength . . . . . lb. per sq. inch	55,000-65,000 <sup>a</sup>	46,000-56,000
Yield point, min. . . . . lb. per sq. inch	0.5 tens. str. 1,500,000 <sup>b</sup>	0.5 tens.str. 1,500,000
Elongation in 8 inches, min. . . . . per cent	tens. str. 22	tens. str. 22
Elongation in 2 inches, min. . . . . per cent		

<sup>a</sup> See par. (b).

<sup>b</sup> See sec. 7.

(b) In order to meet the required minimum tensile strength of full-size annealed eye bars, the purchaser may determine the tensile strength to be obtained in specimen tests, the range shall not exceed 14,000 lb. per sq. inch and the maximum shall not exceed 74,000 lb. per sq. inch. The material shall conform to the requirements as to physical properties other than that of tensile strength, specified in sec. 6, 7 and 8 (b).

(c) The yield point shall be determined by the drop of the beam of the testing machine.

7. **Modifications in Elongation.** (a) For structural steel over  $\frac{3}{4}$  inch in thickness, a deduction of 1 from the percentage of elongation in 8 inches specified in sec. 6 (a) shall be made for each increase of  $\frac{1}{8}$  inch in thickness above  $\frac{3}{4}$  inch to a minimum of 18 per cent.

(b) For structural steel under  $\frac{5}{16}$  inch in thickness, a deduction of 2.5 from the percentage of elongation in 8 inches specified in sec. 6 (a) shall be made for each decrease of  $\frac{1}{16}$  inch in thickness below  $\frac{5}{16}$  inch.

# CARNEGIE STEEL COMPANY

8. **Bend Tests.** (a) The test specimen for plates, shapes and bars, except as specified in par. (b), (c) and (d), shall bend cold through 180 degrees without cracking on the outside of the bent portion, as follows: For material  $\frac{3}{4}$  inch or under in thickness, flat on itself; for material over  $\frac{3}{4}$  inch to and including  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to the thickness of the specimen; and for material over  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to twice the thickness of the specimen.

(b) The test specimen for eye-bar flats shall bend cold through 180 degrees without cracking on the outside of the bent portion as follows: For material  $\frac{3}{4}$  inch or under in thickness, around a pin the diameter of which is equal to the thickness of the specimen; for material over  $\frac{3}{4}$  inch to and including  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to twice the thickness of the specimen; and for material over  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to three times the thickness of the specimen.

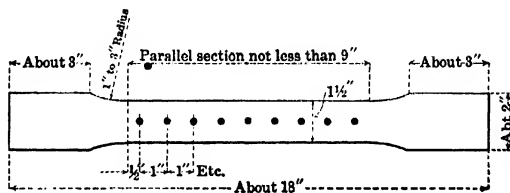


FIGURE 1.

(c) The test specimen for pins, rollers and other bars, when prepared as specified in sec. 9 (e), shall bend cold through 180 degrees around a 1-inch pin without cracking on the outside of the bent portion.

(d) The test specimen for rivet steel shall bend cold through 180 degrees flat on itself without cracking on the outside of the bent portion.

9. **Test Specimens.** (a) Tension-and bend test specimens shall be taken from rolled steel in the condition in which it comes from the rolls, except as specified in par. (b).

(b) Tension-and bend test specimens for pins and rollers shall be taken from the finished bars, after annealing when annealing is specified.

## STANDARD SPECIFICATIONS

(c) Tension-and bend test specimens for plates, shapes and bars, except as specified in par. (d), (e) and (f), shall be of the full thickness of material as rolled. They may be machined to the form and dimensions shown in fig. 1, or with both edges parallel; except that bend-test specimens for eye-bar flats may have three rolled sides.

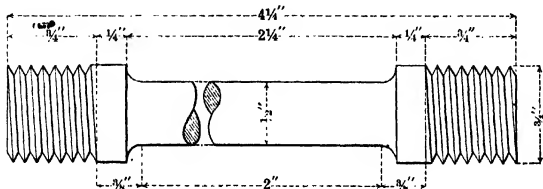


FIGURE 2.

(d) Tension-and bend test specimens for plates, and tension test specimens for eye-bar flats, over  $1\frac{1}{2}$  inch in thickness may be machined to a thickness or diameter of at least  $\frac{3}{4}$  inch for a length of at least 9 inches.

(e) Tension test specimens for pins, rollers and bars (except eye-bar flats) over  $1\frac{1}{2}$  inch in thickness or diameter may be of the form and dimensions shown in fig. 2. Bend test specimens may be 1 by  $\frac{1}{2}$  inch in section. The axis of the specimen shall be located at any point midway between the center and surface and shall be parallel to the axis of the bar.

(f) Tension-and bend test specimens for rivet steel shall be of the full-size section of bars as rolled.

10. **Number of Tests.** (a) One tension-and one bend test shall be made from each melt; except that if material from one melt differs  $\frac{3}{8}$  inch or more in thickness, one tension-and one bend test shall be made from both the thickest and the thinnest material rolled.

(b) If any test specimen shows defective machining or develops flaws, it may be discarded and another specimen substituted.

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 6(a) and any part of the fracture is more than  $\frac{3}{4}$  inch from the center of the gage length of a 2 inch specimen or is outside the middle third of the gage length of an 8-inch specimen, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

# CARNEGIE STEEL COMPANY

## IV. PERMISSIBLE VARIATIONS IN WEIGHT AND GAGE

11. **Permissible Variations.** The cross-section or weight of each piece of steel shall not vary more than 2.5 per cent from that specified; except in the case of sheared plates, which shall be covered by the following permissible variations to apply to single plates:

### (a) When Ordered to Weight.—

For plates 12½ pounds per sq. foot or over:

Under 100 inches in width, 2.5 per cent above or below the specified weight;

100 inches in width or over, 5 per cent above or below the specified weight.

For plates under 12½ pounds per sq. foot:

Under 75 inches in width, 2.5 per cent above or below the specified weight;

75 to 100 inches, exclusive, in width, 5 per cent above or 3 per cent below the specified weight;

100 inches in width or over, 10 per cent above or 3 per cent below the specified weight.

### (b) When Ordered to Gage.—

The thickness of each plate shall not vary more than 0.01 inch under that ordered.

An excess over the nominal weight corresponding to the dimensions on the order shall be allowed for each plate, if not more than that shown in the following table, one cubic inch of rolled steel being assumed to weigh 0.2833 pound:

Thickness Ordered, Inches	Nominal Weight, Pounds per Square Foot	ALLOWABLE EXCESS EXPRESSED AS PERCENTAGE OF NOMINAL WEIGHT For Width of Plate as follows:						
		Under 50 in.	50 in. to 70 in. excl.	70 in. or over	Under 75 in.	75 in. to 100 in. excl.	100 in. to 115 in. excl.	115 in. or over
⅜ to ⅝	5.10 to 6.37	10	15	20	..	..	..	..
⅝ to ⅞	6.37 to 7.6	8.5	12.5	17	..	..	..	..
⅞ to 1	7.65 to 10.20	7	10	15	..	..	..	..
1	10.20	..	..	..	10	14	18	..
1 ⅛	12.75	..	..	..	8	12	16	..
1 ¼	15.30	..	..	..	7	10	13	17
1 ½	17.85	..	..	..	6	8	10	13
1 ⅝	20.40	..	..	..	5	7	9	12
1 ¾	22.95	..	..	..	4.5	6.5	8.5	11
2	25.50	..	..	..	4	6	8	10
Over 2	.....	..	..	..	3.5	5	6.5	9

## STANDARD SPECIFICATIONS

### V. FINISH

12. **Finish.** The finished material shall be free from injurious defects and shall have a workmanlike finish.

### VI. MARKING

13. **Marking.** The name or brand of the manufacturer and the melt number shall be legibly stamped or rolled on all finished material, except that rivet and lattice bars and other small sections shall, when loaded for shipment, be properly separated and marked for identification. The identification marks shall be legibly stamped on the end of each pin and roller. The melt number shall be legibly marked, by stamping, if practicable, on each test specimen.

### VII. INSPECTION AND REJECTION

14. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the material ordered. The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the material is being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

15. **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 5 shall be reported within five working days from the receipt of samples.

(b) Material which shows injurious defects subsequent to its acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

16. **Rehearing.** Samples tested in accordance with sec. 5, which represent rejected material, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.

CARNEGIE STEEL COMPANY

AMERICAN SOCIETY FOR TESTING MATERIALS

PHILADELPHIA, PA., U. S. A.

AFFILIATED WITH THE

INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS

STANDARD SPECIFICATIONS

FOR

STRUCTURAL STEEL FOR BUILDINGS

SERIAL DESIGNATION: A9-14.

The specifications for this material are issued under the fixed designation A 9; the final number indicates the year of original issue or, in the case of revision, the year of last revision.

ADOPTED, 1901; REVISED, 1909, 1913, 1914.

I. MANUFACTURE

1. **Process.** (a) Structural steel, except as noted in par. (b), may be made by the bessemer-or the open-hearth process.

(b) Rivet steel, and steel for plates or angles over  $\frac{3}{4}$  inch in thickness which are to be punched, shall be made by the open-hearth process.

II. CHEMICAL PROPERTIES AND TESTS

2. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition:

	STRUCTURAL STEEL	RIVET STEEL
Phosphorus	Bessemer... not over 0.10 per cent	.....
	{ Open-hearth " " 0.06 " "	not over 0.06 per cent
Sulphur	.....	0.045 " "

## STANDARD SPECIFICATIONS

**3. Ladle Analyses.** An analysis to determine the percentages of carbon, manganese, phosphorus and sulphur shall be made by the manufacturer from a test ingot taken during the pouring of each melt, a copy of which shall be given to the purchaser or his representative. This analysis shall conform to the requirements specified in sec. 2.

**4. Check Analyses.** Analyses may be made by the purchaser from finished material representing each melt, in which case an excess of 25 per cent above the requirements specified in sec. 2 shall be allowed.

### III. PHYSICAL PROPERTIES AND TESTS

**5. Tension Tests.** (a) The material shall conform to the following requirements as to tensile properties:

Properties Considered	Structural Steel	Rivet Steel
Tensile strength . . . . . lb. per sq. inch	55,000-65,000	46,000-56,000
Yield point, min. . . . . lb. per sq. inch	0.5 tens. str.	0.5 tens. str.
Elongation in 8 inches, min. . . . . per cent	$\frac{1,400,000}{\text{tens. str.}}$	$\frac{1,400,000}{\text{tens. str.}}$
Elongation in 2 inches, min. . . . . per cent	22	.....

<sup>a</sup> See sec. 6.

(b) The yield point shall be determined by the drop of the beam of the testing machine.

**6. Modifications in Elongation.** (a) For structural steel over  $\frac{3}{4}$  inch in thickness, a deduction of 1 from the percentage of elongation in 8 inches specified in sec. 5 (a) shall be made for each increase of  $\frac{1}{8}$  inch in thickness above  $\frac{3}{4}$  inch to a minimum of 18 per cent.

(b) For structural steel under  $\frac{5}{16}$  inch in thickness, a deduction of 2.5 from the percentage of elongation in 8 inches specified in sec. 5 (a) shall be made for each decrease of  $\frac{1}{16}$  inch in thickness below  $\frac{5}{16}$  inch.

**7. Bend Tests.** (a) The test specimen for plates, shapes and bars, except as specified in par. (b) and (c), shall bend cold through 180 degrees without cracking on the outside of the bent portion, as follows: For material  $\frac{3}{4}$  inch or under in thickness, flat on itself; for material over  $\frac{3}{4}$  inch to and including  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to the thickness of the specimen; and for material over  $1\frac{1}{4}$  inch in thickness, around



# CARNEGIE STEEL COMPANY

a pin the diameter of which is equal to twice the thickness of the specimen.

(b) The test specimen for pins, rollers and other bars, when prepared as specified in sec. 8 (e), shall bend cold through 180 degrees around a 1-inch pin without cracking on the outside of the bent portion.

(c) The test specimen for rivet steel shall bend cold through 180 degrees flat on itself without cracking on the outside of the bent portion.

8. Test Specimens. (a) Tension-and bend test specimens shall be taken from rolled steel in the condition in which it comes from the rolls, except as specified in par. (b).

(b) Tension-and bend test specimens for pins and rollers shall be taken from the finished bars, after annealing when annealing is specified.

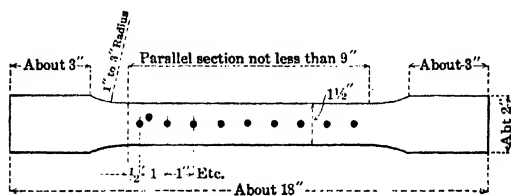


FIGURE 1.

(c) Tension-and bend test specimens for plates, shapes and bars, except as specified in par. (d), (e) and (f), shall be of the full thickness of material as rolled; and may be machined to the form and dimensions shown in fig. 1, or with both edges parallel.

(d) Tension-and bend test specimens for plates over  $1\frac{1}{2}$  inch in thickness or diameter may be machined to a thickness or diameter of at least  $\frac{3}{4}$  inch for a length of at least 9 inches.

(e) Tension test specimens for pins, rollers and bars over  $1\frac{1}{2}$  inch in thickness or diameter may be of the form and dimensions shown in fig. 2. Bend test specimens may be 1 by  $\frac{1}{2}$  inch in section. The axis of the specimens shall be located at any point midway between the center and surface and shall be parallel to the axis of the bar.

(f) Tension-and bend test specimens for rivet steel shall be of the full-size section of bars as rolled.

## STANDARD SPECIFICATIONS

9. **Number of Tests.** (a) One tension-and one bend test shall be made from each melt; except that if material from one melt differs  $\frac{3}{8}$  inch or more in thickness, one tension-and one bend test shall be made from both the thickest and the thinnest material rolled.

(b) If any test specimen shows defective machining or develops flaws, it may be discarded and another specimen substituted.

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 5 (a) and any part of the fracture is more than  $\frac{3}{4}$  inch from the center of the gage length of a 2 inch specimen or is outside the middle third of the gage length of an 8 inch specimen, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

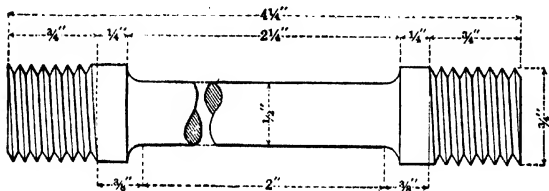


FIGURE 2.

### IV. PERMISSIBLE VARIATIONS IN WEIGHT AND GAGE

10. **Permissible Variations.** The cross-section or weight of each piece of steel shall not vary more than 2.5 per cent from that specified; except in the case of sheared plates, which shall be covered by the following permissible variations to apply to single plates:

(a) **When Ordered to Weight.**—

For plates  $12\frac{1}{2}$  pounds per sq. foot or over:

Under 100 inches in width, 2.5 per cent above or below the specified weight;

100 inches in width or over, 5 per cent above or below the specified weight.

For plates under  $12\frac{1}{2}$  pounds per sq. foot:

Under 75 inches in width, 2.5 per cent above or below the specified weight;

75 to 100 inches, exclusive, in width, 5 per cent above or 3 per cent below the specified weight;

100 inches in width or over, 10 per cent above or 3 per cent below the specified weight.

# CARNEGIE STEEL COMPANY

## (b) When Ordered to Gauge.—

The thickness of each plate shall not vary more than 0.01 inch under that ordered.

An excess over the nominal weight corresponding to the dimensions on the order shall be allowed for each plate, if not more than that shown in the following table, one cubic inch of rolled steel being assumed to weigh 0.2833 pound:

Thickness Ordered, Inches	Nominal Weight, Pounds per Square Foot	ALLOWABLE EXCESS EXPRESSED AS PERCENTAGE OF NOMINAL WEIGHT For Width of Plate as follows:						
		Under 50 in.	50 in. to 70 in. excl.	70 in. or over	Under 75 in.	75 in. to 100 in. excl.	100 in. to 115 in. excl.	115 in. or over
$\frac{1}{8}$ to $\frac{5}{16}$	5.10 to 6.37	10	15	20	..	..	..	..
$\frac{5}{16}$ to $\frac{3}{8}$	6.37 to 7.65	8.5	12.5	17	..	..	..	..
$\frac{3}{8}$ to $\frac{1}{2}$	7.65 to 10.20	7	10	15	..	..	..	..
$\frac{1}{2}$	10.20	..	..	..	10	14	18	..
$\frac{5}{8}$	12.75	..	..	..	8	12	16	..
$\frac{3}{4}$	15.30	..	..	..	7	10	13	17
$\frac{7}{8}$	17.85	..	..	..	6	8	10	13
$\frac{1}{2}$	20.40	..	..	..	5	7	9	12
$\frac{9}{16}$	22.95	..	..	..	4.5	6.5	8.5	11
$\frac{5}{8}$	25.50	..	..	..	4	6	8	10
Over $\frac{5}{8}$	.....	..	..	..	3.5	5	6.5	..

## V. FINISH

11. **Finish.** The finished material shall be free from injurious defects and shall have a workmanlike finish.

## VI. MARKING

12. **Marking.** The name or brand of the manufacturer and the melt number shall be legibly stamped or rolled on all finished material, except that rivet and lattice bars and other small sections shall, when loaded for shipment, be properly separated and marked for identification. The identification marks shall be legibly stamped on the end of each pin and roller. The melt number shall be legibly marked, by stamping, if practicable, on each test specimen.

## VII. INSPECTION AND REJECTION

13. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the material ordered.

## STANDARD SPECIFICATIONS

The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the material is being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

14 **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 4 shall be reported within five working days from the receipt of samples.

(b) Material which shows injurious defects subsequent to its acceptance at the manufacturer's works will be rejected and the manufacturer shall be notified.

15. **Rehearing.** Samples tested in accordance with sec. 4, which represent rejected material, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.

**CARNEGIE STEEL COMPANY**

**AMERICAN SOCIETY FOR TESTING MATERIALS**

PHILADELPHIA, PA., U. S. A.

AFFILIATED WITH THE

**INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS**

**STANDARD SPECIFICATIONS**

FOR

**STRUCTURAL STEEL FOR LOCOMOTIVES**

SERIAL DESIGNATION: A10-14.

The specifications for this material are issued under the fixed designation A 10; the final number indicates the year of original issue or, in the case of revision, the year of last revision.

ADOPTED, 1912; REVISED, 1913, 1914.

1. **Basis of Purchase.** These specifications apply to shapes, plates (except boiler and firebox plates) and bars over  $\frac{1}{8}$  inch in thickness.

**I. MANUFACTURE**

2. **Process.** The steel shall be made by the open-hearth process.

**II. CHEMICAL PROPERTIES AND TESTS**

3. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition:

Phosphorus.....	not over 0.05 per cent
Sulphur.....	" " 0.05 " "

4. **Ladle Analyses.** An analysis to determine the percentages of carbon, manganese, phosphorus and sulphur shall be made by the manufacturer from a test ingot taken during the pouring of each melt, a copy of which shall be given to the purchaser or his repre-

## STANDARD SPECIFICATIONS

sentative. This analysis shall conform to the requirements specified in sec. 3.

5. **Check Analyses.** Analyses may be made by the purchaser from finished material representing each melt, which shall conform to the requirements specified in sec. 3.

### III. PHYSICAL PROPERTIES AND TESTS

6. **Tension Tests.** (a) The material shall conform to the following requirements as to tensile properties:

Tensile strength.....	lb. per sq. inch	55,000-65,000
Yield point, min.....	lb. per sq. inch	0.5 tens. str.
Elongation in 8 inches, min.....	per cent	1,500,000 tens. str.

See sec. 7.

(b) The yield point shall be determined by the drop of the beam of the testing machine.

7. **Modifications in Elongation.** (a) For material over  $\frac{3}{4}$  inch in thickness, a deduction of 1 from the percentage of elongation specified in sec. 6 (a) shall be made for each increase of  $\frac{1}{8}$  inch in thickness above  $\frac{3}{4}$  inch, to a minimum of 18 per cent.

(b) For material under  $\frac{5}{16}$  inch in thickness, a deduction of 2.5 from the percentage of elongation in 8 inches specified in sec. 6 (a) shall be made for each decrease of  $\frac{1}{16}$  inch in thickness below  $\frac{5}{16}$  inch.

8. **Bend Tests.** The test specimen shall bend cold through 180 degrees without cracking on the outside of the bent portion, as follows: For material  $\frac{3}{4}$  inch or under in thickness, flat on itself; for material over  $\frac{3}{4}$  inch to and including  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to the thickness of the specimen; and for material over  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to twice the thickness of the specimen.

9. **Test Specimens.** (a) Tension and bend test specimens shall be taken from the finished rolled material.

(b) Tension and bend test specimens, except as specified in par. (c), shall be of the full thickness of material as rolled; and may be machined to the form and dimensions shown in fig. 1, or with both edges parallel.

(c) Tension and bend test specimens for plates and bars over  $1\frac{1}{2}$  inch in thickness or diameter may be machined to a thickness or diameter of at least  $\frac{3}{4}$  inch for a length of at least 9 inches.

## CARNEGIE STEEL COMPANY

10. **Number of Tests.** (a) One tension-and one bend test shall be made from each melt; except that if material from one melt differs  $\frac{3}{8}$  inch or over in thickness, one tension-and one bend test shall be made from both the thickest and the thinnest material rolled. Shapes less than 1 sq. inch in section, and bars less than  $\frac{1}{2}$  sq. inch in section, need not be subjected to a tension test.

(b) If any test specimen shows defective machining or develops flaws, it may be discarded and another specimen substituted.

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 6 (a) and any part of the fracture is outside the middle third of the gage length, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

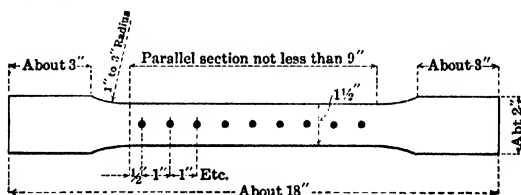


FIGURE 1

### IV. PERMISSIBLE VARIATIONS IN WEIGHT AND GAGE.

11. **Permissible Variations.** The cross-section or weight of each piece of steel shall not vary more than 2.5 per cent from that specified, except in the case of sheared plates, which shall be covered by the following permissible variations to apply to single plates:

(a) **When Ordered to Weight—**

For plates  $12\frac{1}{2}$  pounds per sq. foot or over:

- Under 100 inches in width, 2.5 per cent above or below the specified weight;
- 100 inches in width or over, 5 per cent above or below the specified weight.

For plates under  $12\frac{1}{2}$  pounds per sq. foot:

- Under 75 inches in width, 2.5 per cent above or below the specified weight;
- 75 to 100 inches, exclusive, in width, 5 per cent above or 3 per cent below the specified weight;
- 100 inches in width or over, 10 per cent above or 3 per cent below the specified weight.

## STANDARD SPECIFICATIONS

### (b) When Ordered to Gage.—

The thickness of each plate shall not vary more than 0.01 inch under that ordered.

An excess over the nominal weight corresponding to the dimensions on the order shall be allowed for each plate, if not more than that shown in the following table, one cubic inch of rolled steel being assumed to weigh 0.2833 pound:

Thickness Ordered, Inches	Nominal Weight, Pounds per Square Foot	ALLOWABLE EXCESS EXPRESSED AS PERCENTAGE OF NOMINAL WEIGHT For Width of Plate as follows:						
		Under 50 in.	50 in. to 70 in. excl.	70 in. or over	Under 75 in.	75 in. to 100 in. excl.	100 in. to 115 in. excl.	115 in. or over
$\frac{1}{8}$ to $\frac{5}{16}$	5.10 to 6.37	10	15	20	..	..	..	..
$\frac{5}{16}$ to $\frac{3}{8}$	6.37 to 7.65	8.5	12.5	17	..	..	..	..
$\frac{3}{8}$ to $\frac{1}{2}$	7.65 to 10.20	7	10	15	..	..	..	..
$\frac{1}{2}$	10.20	..	..	..	10	14	18	..
$\frac{5}{8}$	12.75	..	..	..	8	12	16	..
$\frac{3}{4}$	15.30	..	..	..	7	10	13	17
$\frac{7}{8}$	17.85	..	..	..	6	8	10	13
$\frac{1}{4}$	20.40	..	..	..	5	7	9	12
$\frac{5}{16}$	22.95	..	..	..	4.5	6.5	8.5	11
$\frac{3}{8}$	25.50	..	..	..	4	6	8	10
Over $\frac{3}{8}$	.....	..	..	..	3.5	5	6.5	9

## V. FINISH

12. **Finish.** The finished material shall be free from injurious defects and shall have a workmanlike finish.

## VI. MARKING

13. **Marking.** The name or brand of the manufacturer and the melt number shall be legibly stamped or rolled on all finished material, except that small sections shall, when loaded for shipment, be properly separated and marked for identification. The melt number shall be legibly marked, by stamping, if practicable, on each test specimen.

## VII. INSPECTION AND REJECTION

14. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the material ordered.



## CARNEGIE STEEL COMPANY

The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the material is being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

15. **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 5 shall be reported within five working days from the receipt of samples.

(b) Material which shows injurious defects subsequent to its acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

16. **Rehearing.** Samples tested in accordance with sec. 5, which represent rejected material, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.

## STANDARD SPECIFICATIONS

### AMERICAN SOCIETY FOR TESTING MATERIALS

PHILADELPHIA, PA., U. S. A.

AFFILIATED WITH THE

INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS

## STANDARD SPECIFICATIONS

FOR

### STRUCTURAL STEEL FOR CARS

SERIAL DESIGNATION: A11-14.

The specifications for this material are issued under the fixed designation A 11; the final number indicates the year of original issue or, in the case of revision, the year of last revision.

ADOPTED, 1914.

1. **Basis of Purchase.** These specifications apply to shapes, plates and bars over  $\frac{1}{8}$  inch in thickness.

#### I. MANUFACTURE

2. **Process.** The steel shall be made by the open-hearth process.

#### II. CHEMICAL PROPERTIES AND TESTS

3. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition:

STRUCTURAL STEEL AND PLATES FOR COLD FLANGING				RIVET STEEL			
Phosphorus	Acid.....	not over	0.06	per cent	not over	0.04	per cent
	Basic.....	" "	0.04	" "	" "	0.04	" "
Sulphur.....	" "	" "	0.05	" "	" "	0.045	" "

## CARNEGIE STEEL COMPANY

4. **Ladle Analyses.** An analysis to determine the percentages of carbon, manganese, phosphorus and sulphur shall be made by the manufacturer from a test ingot taken during the pouring of each melt, a copy of which shall be given to the purchaser or his representative. This analysis shall conform to the requirements specified in sec. 3.

5. **Check Analyses.** Analyses may be made by the purchaser from finished material representing each melt, in which case an excess of 25 per cent above the requirements specified in sec. 3 shall be allowed.

### III. PHYSICAL PROPERTIES AND TESTS

6. **Tension Tests.** (a) The material shall conform to the following requirements as to physical properties:

Properties Considered	Structural Steel	Rivets, and Plates for Cold Flanging
Tensile strength . . . . . lb. per sq. inch	50,000-65,000	48,000-58,000
Yield point, min. . . . . lb. per sq. inch	0.5 tens. str.	0.5 tens. str.
Elongation in 8 inches, min. . . . . per cent	$\frac{1,500,000}{\text{tens. str.}}$	$\frac{1,500,000}{\text{tens. str.}}$

<sup>1</sup> See sec. 7.

(b) The yield point shall be determined by the drop of the beam of the testing machine.

7. **Modifications in Elongation.** (a) For material over  $\frac{3}{4}$  inch in thickness, a deduction of 1 from the percentage of elongation specified in sec. 6 (a) shall be made for each increase of  $\frac{1}{8}$  inch in thickness above  $\frac{3}{4}$  inch, to a minimum of 18 per cent.

(b) For material under  $\frac{5}{16}$  inch in thickness, a deduction of 2.5 from the percentage of elongation in 8 inches specified in sec. 6 (a) shall be made for each decrease of  $\frac{1}{16}$  inch in thickness below  $\frac{5}{16}$  inch.

8. **Bend Tests.** (a) The test specimen for structural steel shall bend cold through 180 degrees without cracking on the outside of the bent portion, as follows: For material  $\frac{3}{4}$  inch or under in thickness, flat on itself; for material over  $\frac{3}{4}$  inch to and including  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to the thickness of the specimen; and for material over  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to twice the thickness of the specimen.

## STANDARD SPECIFICATIONS

(b) The test specimen for rivet steel and plates for cold flanging shall bend cold through 180 degrees flat on itself without cracking on the outside of the bent portion.

9. **Test Specimens.** (a) Tension-and bend test specimens shall be taken from the finished rolled material.

(b) Tension-and bend test specimens, except as specified in par. (c), shall be of the full thickness of material as rolled; and may be machined to the form and dimensions shown in fig. 1, or with both edges parallel.

(c) Tension-and bend test specimens for plates and bars over  $1\frac{1}{2}$  inch in thickness or diameter may be machined to a thickness or diameter of at least  $\frac{3}{4}$  inch for a length of at least 9 inches.

10. **Number of Tests.** (a) One tension-and one bend test shall be made from each melt; except that if material from one melt differs  $\frac{3}{8}$  inch or more in thickness, one tension-and one bend test shall be made from both the thickest and the thinnest material rolled. Shapes less than 1 sq. inch in section, and bars, except rivet rods, less than  $\frac{1}{2}$  sq. inch in section, need not be subjected to a tension test.

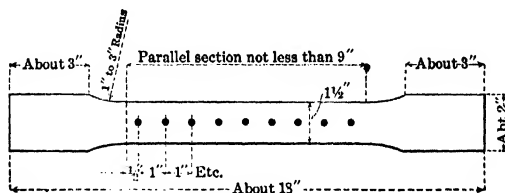


FIGURE 1.

(b) If any test specimen shows defective machining or develops flaws, it may be discarded and another specimen substituted.

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 6 (a) and any part of the fracture is outside the middle third of the gage length, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

## IV. PERMISSIBLE VARIATIONS IN WEIGHT AND GAGE

11. **Permissible Variations.** The cross-section or weight of each piece of steel shall not vary more than 2.5 per cent from that specified; except in the case of sheared plates, which shall be covered by the following permissible variations to apply to single plates:

# CARNEGIE STEEL COMPANY

## (a) When Ordered to Weight.—

For plates  $12\frac{1}{2}$  pounds per sq. foot or over:

Under 100 inches in width, 2.5 per cent above or below the specified weight;

100 inches in width or over, 5 per cent above or below the specified weight.

For plates under  $12\frac{1}{2}$  pounds per sq. foot:

Under 75 inches in width, 2.5 per cent above or below the specified weight;

75 to 100 inches, exclusive, in width, 5 per cent above or 3 per cent below the specified weight;

100 inches in width or over, 10 per cent above or 3 per cent below the specified weight.

## (b) When Ordered to Gage.—

The thickness of each plate shall not vary more than 0.01 inch under that ordered.

An excess over the nominal weight corresponding to the dimensions on the order shall be allowed for each plate, if not more than that shown in the following table, one cubic inch of rolled steel being assumed to weigh 0.2833 pound:

Thickness Ordered, Inches	Nominal Weight, Pounds per Square Foot	ALLOWABLE EXCESS EXPRESSED AS PERCENTAGE OF NOMINAL WEIGHT For Width of Plate as follows:						
		Under 50 in.	50 in. to 70 in. excl.	70 in. or over	Under 75 in.	75 in. to 100 in. excl.	100 in. to 115 in. excl.	115 in. or over
$\frac{1}{8}$ to $\frac{5}{32}$	5.10 to 6.37	10	15	20	..	..	..	..
$\frac{5}{32}$ to $\frac{3}{16}$	6.37 to 7.65	8.5	12.5	17	..	..	..	..
$\frac{3}{16}$ to $\frac{1}{4}$	7.65 to 10.20	7	10	15	..	..	..	..
$\frac{1}{4}$	10.20	..	..	..	10	14	18	..
$\frac{5}{16}$	12.75	..	..	..	8	12	16	..
$\frac{3}{8}$	15.30	..	..	..	7	10	13	17
$\frac{7}{16}$	17.85	..	..	..	6	8	10	13
$\frac{1}{2}$	20.40	..	..	..	5	7	9	12
$\frac{9}{16}$	22.95	..	..	..	4.5	6.5	8.5	11
$\frac{5}{8}$	25.50	..	..	..	4	6	8	10
Over $\frac{5}{8}$	.....	..	..	..	3.5	5	6.5	9

## V. FINISH

12. **Finish.** The finished material shall be free from injurious defects and shall have a workmanlike finish.

## STANDARD SPECIFICATIONS

### VI. MARKING

13. **Marking.** The name or brand of the manufacturer and the melt number shall be legibly rolled or stamped on all finished material, except that rivet bars and other small sections shall, when loaded for shipment, be properly separated and marked for identification. The melt number shall be legibly marked, by stamping, if practicable, on each test specimen.

### VII. INSPECTION AND REJECTION

14. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the material ordered. The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the material is being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

15. **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 5 shall be reported within five working days from the receipt of samples.

(b) Material which shows injurious defects subsequent to its acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

16. **Rehearing.** Samples tested in accordance with sec. 5, which represent rejected material, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.

CARNEGIE STEEL COMPANY

AMERICAN SOCIETY FOR TESTING MATERIALS  
PHILADELPHIA, PA., U. S. A.  
AFFILIATED WITH THE  
INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS

STANDARD SPECIFICATIONS

FOR

STRUCTURAL STEEL FOR SHIPS

SERIAL DESIGNATION: A12-14.

The specifications for this material are issued under the fixed designation A 12; the final number indicates the year of original issue or, in the case of revision, the year of last revision.

ADOPTED, 1901; REVISED, 1909, 1913, 1914.

I. MANUFACTURE

1. **Process.** The steel shall be made by the open-hearth process.

II. CHEMICAL PROPERTIES AND TESTS

2. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition:

Phosphorus	{Acid.....	not over 0.06 per cent
	{Basic.....	" " 0.04 " "
Sulphur	.....	" " 0.05 " "

3. **Ladle Analyses.** An analysis to determine the percentages of carbon, manganese, phosphorus and sulphur shall be made by the manufacturer from a test ingot taken during the pouring of each melt, copy of which shall be given to the purchaser or his representative. This analysis shall conform to the requirements specified in sec. 2.

## STANDARD SPECIFICATIONS

4. **Check Analyses.** Analyses may be made by the purchaser from finished material representing each melt, in which case an excess of 25 per cent above the requirements specified in sec. 2 shall be allowed.

### III. PHYSICAL PROPERTIES AND TESTS

5. **Tension Tests.** (a) The material shall conform to the following requirements as to tensile properties:

Tensile strength.....	lb. per sq. inch	58,000-68,000
Yield point, min.....	lb. per sq. inch	0.5 tens. str.
Elongation in 8 inches, min.....	per cent	$\frac{1,500,000}{\text{tens. str.}}$
See sec. 6.		

(b) The yield point shall be determined by the drop of the beam of the testing machine.

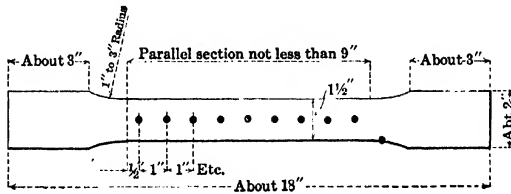


FIGURE 1.

6. **Modifications in Elongation.** (a) For material over  $\frac{3}{4}$  inch in thickness, a deduction of 1 from the percentage of elongation specified in sec. 5 (a) shall be made for each increase of  $\frac{1}{8}$  inch in thickness above  $\frac{3}{4}$  inch, to a minimum of 18 per cent.

(b) For material  $\frac{1}{4}$  inch or under in thickness, the elongation shall be measured on a gage length of 24 times the thickness of the specimen.

7. **Bend Tests.** The test specimen shall bend cold through 180 degrees without cracking on the outside of the bent portion, as follows: For material  $\frac{3}{4}$  inch or under in thickness, around a pin the diameter of which is equal to the thickness of the specimen, for material over  $\frac{3}{4}$  inch to and including  $1\frac{1}{4}$  inch in thickness around a pin the diameter of which is equal to  $1\frac{1}{2}$  times the thickness of the specimen; and for material over  $1\frac{1}{4}$  inch in thickness, around a pin the diameter of which is equal to twice the thickness of the specimen.



## CARNEGIE STEEL COMPANY

8. **Test Specimens.** (a) Tension and bend test specimens shall be taken from the finished rolled material, and shall not be annealed or otherwise treated, except as specified in par. (b).

(b) Tension and bend test specimens for material which is to be annealed or otherwise treated before use, shall be cut from properly annealed or similarly treated short lengths of the full section of the piece.

(c) Tension and bend test specimens, except as specified in par. (d), shall be of the full thickness of material as rolled; and may be machined to the form and dimensions shown in fig. 1, or with both edges parallel.

(d) Tension and bend test specimens for plates and bars over  $1\frac{1}{2}$  inch in thickness or diameter may be machined to a thickness or diameter of at least  $\frac{3}{4}$  inch for a length of at least 9 inches.

9. **Number of Tests.** (a) One tension and one bend test shall be made from each melt; except that if material from one melt differs  $\frac{3}{8}$  inch or more in thickness, one tension and one bend test shall be made from both the thickest and the thinnest material rolled.

(b) If any test specimen shows defective machining or develops flaws, it may be discarded and another specimen substituted.

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 5 (a) and any part of the fracture is outside the middle third of the gage length, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

## IV. PERMISSIBLE VARIATIONS IN WEIGHT AND GAGE

10. **Permissible Variations.** The cross-section or weight of each piece of steel shall not vary more than 2.5 per cent from that specified; except in the case of sheared plates, which shall be covered by the following permissible variations to apply to single plates:

(a) **When Ordered to Weight.—**

For plates  $12\frac{1}{2}$  pounds per sq. foot or over:

Under 100 inches in width, 2.5 per cent above or below the specified weight;

100 inches in width or over, 5 per cent above or below the specified weight.

## STANDARD SPECIFICATIONS

For plates under 12½ pounds per sq. foot:

Under 75 inches in width, 2.5 per cent above or below the specified weight;

75 to 100 inches, exclusive, in width, 5 per cent above or 3 per cent below the specified weight;

100 inches in width or over, 10 per cent above or 3 per cent below the specified weight.

### (b) When Ordered to Gage.—

The thickness of each plate shall not vary more than 0.01 inch under that ordered.

An excess over the nominal weight corresponding to the dimensions on the order shall be allowed for each plate, if not more than that shown in the following table, one cubic inch of rolled steel being assumed to weigh 0.2833 pound:

Thickness Ordered, Inches	Nominal Weight, Pounds per Square Foot	ALLOWABLE EXCESS EXPRESSED AS PERCENTAGE OF NOMINAL WEIGHT For Width of Plate as follows:						
		Under 50 in.	50 in. to 70 in. excl.	70 in. or over	Under 75 in.	75 in. to 100 in. excl.	100 in. to 115 in. excl.	115 in. or over
½ to ¾	5.10 to 6.37	10	15	20	..	..	..	..
¾ to 1	6.37 to 7.65	8.5	12.5	17	..	..	..	..
1 to 1¼	7.65 to 10.20	7	10	15	..	..	..	..
1¼	10.20	..	..	..	10	14	18	..
1½	12.75	..	..	..	8	12	16	..
1¾	15.30	..	..	..	7	10	13	17
2	17.85	..	..	..	6	8	10	13
2¼	20.40	..	..	..	5	7	9	12
2½	22.95	..	..	..	4.5	6.5	8.5	11
2¾	25.50	..	..	..	4	6	8	10
Over 2¾	.....	..	..	..	3.5	5	6.5	9

## V. FINISH

11. **Finish.** The finished material shall be free from injurious defects and shall have a workmanlike finish.

## VI. MARKING

12. **Marking.** The name or brand of the manufacturer and the melt number shall be legibly rolled or stamped on all finished material. The melt number shall be legibly stamped on each test specimen.

## CARNEGIE STEEL COMPANY

### VII. INSPECTION AND REJECTION

13. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the material ordered. The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the material is being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

14. **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 4 shall be reported within five working days from the receipt of samples.

(b) Material which shows injurious defects subsequent to its acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

15. **Rehearing.** Samples tested in accordance with sec. 4, which represent rejected material, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.



## STANDARD SPECIFICATIONS

### AMERICAN SOCIETY FOR TESTING MATERIALS

PHILADELPHIA, PA., U. S. A.

AFFILIATED WITH THE

INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS

## STANDARD SPECIFICATIONS

FOR

### RIVET STEEL FOR SHIPS

SERIAL DESIGNATION: A13-14.

The specifications for this material are issued under the fixed designation A 13; the final number indicates the year of original issue or, in the case of revision, the year of last revision.

ADOPTED, 1901; REVISED, 1909, 1913, 1914.

#### *A. Requirements for Rolled Bars.*

#### I. MANUFACTURE

1. **Process.** The steel shall be made by the open-hearth process.

#### II. CHEMICAL PROPERTIES AND TESTS

2. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition:

Phosphorus	Acid.....	not over 0.06 per cent
	Basic.....	" " 0.04 " "
Sulphur.....	" " 0.045 " "	

3. **Ladle Analyses.** An analysis to determine the percentages of carbon, manganese, phosphorus and sulphur shall be made by the manufacturer from a test ingot taken during the pouring of each melt, a copy of which shall be given to the purchaser or his repre-

## CARNEGIE STEEL COMPANY

sentative. This analysis shall conform to the requirements specified in sec. 2.

4. **Check Analyses.** Analyses may be made by the purchaser from finished bars representing each melt, in which case an excess of 25 per cent above the requirements specified in sec. 2 shall be allowed.

### III. PHYSICAL PROPERTIES AND TESTS

5. **Tension Tests.** (a) The bars shall conform to the following requirements as to tensile properties:

Tensile strength.....	lb. per sq. inch	55,000-65,000
Yield point, min.....	lb. per sq. inch	0.5 tens. str.
Elongation in 8 inches, min.....	per cent	$\frac{1,500,000}{\text{tens. str.}}$
See sec. 6.		

(b) The yield point shall be determined by the drop of the beam of the testing machine.

6. **Modifications in Elongation.** For bars over  $\frac{3}{4}$  inch in diameter, a deduction of 1 from the percentage of elongation specified in sec. 5 (a) shall be made for each increase of  $\frac{1}{8}$  inch in diameter above  $\frac{3}{4}$  inch.

7. **Bend Tests.** The test specimen shall bend cold through 180 degrees flat on itself without cracking on the outside of the bent portion.

8. **Test Specimens.** Tension and bend test specimens shall be of the full-size section of bars as rolled.

9. **Number of Tests.** (a) Two tension and two bend tests shall be made from each melt, each of which shall conform to the requirements specified; except that if bars from one melt differ  $\frac{3}{8}$  inch or more in diameter, one tension and one bend test shall be made from both the greatest and the least diameters rolled.

(b) If any test specimen develops flaws, it may be discarded and another specimen substituted.

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 5 (a) and any part of the fracture is outside the middle third of the gage length, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

## STANDARD SPECIFICATIONS

### IV. PERMISSIBLE VARIATIONS IN GAGE

10. **Permissible Variations.** The gage of bars 1 inch or under in diameter shall not vary more than 0.01 inch from that specified; the gage bars over 1 inch to and including 2 inches in diameter shall not vary more than  $\frac{1}{64}$  inch under nor more than  $\frac{1}{32}$  inch over that specified.

### V. FINISH

11. **Finish.** The finished bars shall be free from injurious defects and shall have a workmanlike finish.

### VI. MARKING

12. **Marking.** Rivet bars shall, when loaded for shipment, be properly separated and marked with the name or brand of the manufacturer and the melt number for identification. The melt number shall be legibly marked on each test specimen.

### VII. INSPECTION AND REJECTION

13. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the bars ordered. The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the bars are being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

14. **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 4 shall be reported within five working days from the receipt of samples.

(b) Bars which show injurious defects subsequent to their acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

15. **Rehearing.** Samples tested in accordance with sec. 4, which represent rejected bars, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.

## CARNEGIE STEEL COMPANY

### *B. Requirements for Rivets.*

#### I. PHYSICAL PROPERTIES AND TESTS

16. **Test Certificate of Rolled Bars.** A copy of the results of tension tests of the rolled bars from which the rivets were made shall be furnished for each lot of rivets.

17. **Tension Tests.** If the test certificate required in sec. 16 cannot be furnished, the rivets shall conform to the requirements as to tensile properties specified in sec. 5 and 6, except that the elongation shall be measured on a gage length as great as the length of the rivets tested will permit.

18. **Bend Tests.** The rivet shank shall bend cold through 180 degrees flat on itself, as shown in fig. 1, without cracking on the outside of the bent portion.



FIGURE 1.




FIGURE 2.

19. **Flattening Tests.** The rivet head shall flatten, while hot, to a diameter  $2\frac{1}{2}$  times the diameter of the shank, as shown in fig. 2, without cracking at the edges.

20. **Number of Tests.** (a) When required in accordance with sec. 17, one tension test shall be made from each size in each lot of rivets offered for inspection.

(b) Three bend-and three flattening tests shall be made from each size in each lot of rivets offered for inspection, each of which shall conform to the requirements specified.

#### II. WORKMANSHIP AND FINISH

21. **Workmanship.** The rivets shall be true to form, concentric, and shall be made in a workmanlike manner.

22. **Finish.** The finished rivets shall be free from injurious defects.

## **STANDARD SPECIFICATIONS**

### **III. INSPECTION AND REJECTION**

23. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the rivets ordered. The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the rivets are being furnished in accordance with these specifications. All tests and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

24. **Rejection.** Rivets which show injurious defects subsequent to their acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.



CARNEGIE STEEL COMPANY

AMERICAN SOCIETY FOR TESTING MATERIALS

PHILADELPHIA, PA., U. S. A.

AFFILIATED WITH THE

INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS

STANDARD SPECIFICATIONS

FOR

BOILER AND FIREBOX STEEL

SERIAL DESIGNATION: A30-14.

The specifications for this material are issued under the fixed designation A 30; the final number indicates the year of original issue or, in the case of revision, the year of last revision.

ADOPTED, 1901; REVISED, 1909, 1912, 1913, 1914.

1. **Grades.** These specifications cover two grades of steel for boilers, namely: flange and firebox.

I. MANUFACTURE

2. **Process.** The steel shall be made by the open-hearth process.

II. CHEMICAL PROPERTIES AND TESTS

3. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition:

	FLANGE		FIREBOX	
		per cent		per cent
Carbon.....		" "	0.12-0.25	" "
Manganese.....	0.30-0.60	" "	0.30-0.50	" "
Phosphorus {	Acid..... not over 0.05	" "	not over 0.04	" "
{	Basic..... " " 0.04	" "	" " 0.035	" "
Sulphur.....	" " 0.05	" "	" " 0.04	" "
Copper.....		" "	" " 0.05	" "

## STANDARD SPECIFICATIONS

4. **Ladle Analyses.** An analysis shall be made by the manufacturer from a test ingot taken during the pouring of each melt, a copy of which shall be given to the purchaser or his representative. This analysis shall conform to the requirements specified in sec. 3.

5. **Check Analyses.** Analyses may be made by the purchaser from a broken tension test specimen representing each plate as rolled, which shall conform to the requirements specified in sec. 3.

### III. PHYSICAL PROPERTIES AND TESTS

6. **Tension Tests.** (a) The material shall conform to the following requirements as to tensile properties:

	PLATE	FIREBOX
Tensile strength . . . . . lb. per sq. inch	55,000-65,000	52,000-62,000
Yield point, min. . . . . lb. per sq. inch	0.5 tens. str.	0.5 tens. str.
Elongation in 8 inches, min. . . per cent	1,500,000 tens. str.	1,500,000 tens. str.

See sec. 7.

(b) The yield point shall be determined by the drop of the beam of the testing machine.

7. **Modifications in Elongation.** (a) For material over  $\frac{3}{4}$  inch in thickness, a deduction of 0.5 from the percentages of elongation specified in sec. 6 (a) shall be made for each increase of  $\frac{1}{8}$  inch in thickness above  $\frac{3}{4}$  inch.

(b) For material  $\frac{1}{4}$  inch or under in thickness, the elongation shall be measured on a gage length of 24 times the thickness of the specimen.

8. **Bend Tests.** (a) *Cold-bend Tests.*—The test specimen shall bend cold through 180 degrees without cracking on the outside of the bent portion, as follows: For material 1 inch or under in thickness, flat on itself; and for material over 1 inch in thickness, around a pin the diameter of which is equal to the thickness of the specimen.

(b) *Quench-bend Tests.*—The test specimen, when heated to a light cherry red as seen in the dark (not less than 1200° F.) and quenched at once in water the temperature of which is between 80° and 90° F., shall bend through 180 degrees without cracking on the outside of the bent portion, as follows: For material 1 inch or under in thickness, flat on itself; and for material over 1 inch in thickness, around a pin the diameter of which is equal to the thickness of the specimen.

# CARNEGIE STEEL COMPANY

9. **Homogeneity Tests.** For firebox steel, a sample taken from a broken tension test specimen shall not show any single seam or cavity more than  $\frac{1}{4}$  inch long, in either of the three fractures obtained in the test for homogeneity, which shall be made as follows: The specimen shall be either nicked with a chisel or grooved on a machine, transversely, about  $\frac{1}{16}$  inch deep, in three places about 2 inches apart. The first groove shall be made 2 inches from the square end; each succeeding groove shall be made on the opposite side from the preceding one. The specimen shall then be firmly held in a vise, with the first groove about  $\frac{1}{4}$  inch above the jaws, and the projecting end broken off by light blows of a hammer, the bending being away from the groove. The specimen shall be broken at the other two grooves in the same manner. The object of this test is to open and render visible to the eye any seams due to failure to weld up or to interposed foreign matter, or any cavities due to gas bubbles in the ingot. One side of each fracture shall be examined and the lengths of the seams and cavities determined, a pocket lens being used if necessary.

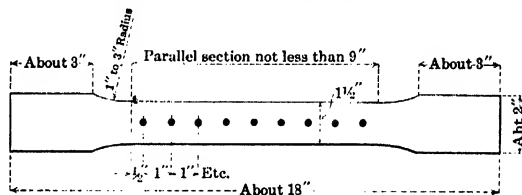


FIGURE 1.

10. **Test Specimens.** Tension and bend test specimens shall be taken from the finished rolled material. They shall be of the full thickness of material as rolled, and shall be machined to the form and dimensions shown in fig. 1; except that bend test specimens may be machined with both edges parallel.

11. **Number of Tests.** (a) One tension-, one cold-bend-, and one quench-bend test shall be made from each plate as rolled.

(b) If any test specimen shows defective machining or develops flaws, it may be discarded and another specimen substituted.

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 6 (a) and any part of the fracture is outside the middle third of the gage length, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

## STANDARD SPECIFICATIONS

### IV. PERMISSIBLE VARIATIONS IN WEIGHT AND GAGE

#### 12. Permissible Variations. *When Ordered to Gage.*—

The thickness of each plate shall not vary more than 0.01 inch under that ordered.

An excess over the nominal weight corresponding to the dimensions on the order shall be allowed for each plate, if not more than that shown in the following table, one cubic inch of rolled steel being assumed to weigh 0.2833 pound:

Thickness Ordered, Inches	Nominal Weight, Pounds per Square Foot	ALLOWABLE EXCESS EXPRESSED AS PERCENTAGE OF NOMINAL WEIGHT For Width of Plate as follows:						
		Under 50 in.	50 in. to 70 in. excl.	70 in. or over	Under 75 in.	75 in. to 100 in. excl.	100 in. to 115 in. excl.	115 in. or over
$\frac{1}{8}$ to $\frac{5}{16}$	5.10 to 6.37	10	15	20	..	..	..	..
$\frac{5}{16}$ to $\frac{3}{8}$	6.37 to 7.65	8.5	12.5	17	..	..	..	..
$\frac{3}{8}$ to $\frac{1}{2}$	7.65 to 10.20	7	10	15	..	..	..	..
$\frac{1}{2}$	10.20	..	..	..	10	14	18	..
$\frac{5}{8}$	12.75	..	..	..	8	12	16	..
$\frac{3}{4}$	15.30	..	..	..	7	10	13	17
$\frac{7}{8}$	17.85	..	..	..	6	8	10	13
$\frac{1}{4}$	20.40	..	..	..	5	7	9	12
$\frac{5}{16}$	22.95	..	..	..	4.5	6.5	8.5	11
$\frac{3}{8}$	25.50	..	..	..	4	6	8	10
Over $\frac{3}{8}$	.....	..	..	..	3.5	5	6.5	9

### V. FINISH

13. **Finish.** The finished material shall be free from injurious defects and shall have a workmanlike finish.

### VI. MARKING

14. **Marking.** The name or brand of the manufacturer, melt or slab number, grade, and lowest tensile strength for its grade specified in sec. 6 (a), shall be legibly stamped on each plate. The melt or slab number shall be legibly stamped on each test specimen.

### VII. INSPECTION AND REJECTION

15. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the material ordered.

## CARNEGIE STEEL COMPANY

The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the material is being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

16. **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 5 shall be reported within five working days from the receipt of samples.

(b) Material which shows injurious defects subsequent to its acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

17. **Rehearing.** Samples tested in accordance with sec. 5, which represent rejected material, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.

## STANDARD SPECIFICATIONS

### AMERICAN SOCIETY FOR TESTING MATERIALS

PHILADELPHIA, PA., U. S. A.

AFFILIATED WITH THE

INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS

## STANDARD SPECIFICATIONS

FOR

### BOILER RIVET STEEL

SERIAL DESIGNATION: A31-14.

The specifications for this material are issued under the fixed designation A 31; the final number indicates the year of original issue or, in the case of revision, the year of last revision.

ADOPTED, 1901; REVISED, 1909, 1912, 1913, 1914.

#### *A. Requirements for Rolled Bars.*

#### I. MANUFACTURE

1. **Process.** The steel shall be made by the open-hearth process.

#### II. CHEMICAL PROPERTIES AND TESTS

2. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition:

Manganese.....	0.30-0.50 per cent
Phosphorus.....	not over 0.04 " "
Sulphur.....	" " 0.045 " "

3. **Ladle Analyses.** An analysis to determine the percentages of carbon, manganese, phosphorus and sulphur shall be made by the manufacturer from a test ingot taken during the pouring of each melt, a copy of which shall be given to the purchaser or his repre-

## CARNEGIE STEEL COMPANY

sentative. This analysis shall conform to the requirements specified in sec. 2.

4. **Check Analyses.** Analyses may be made by the purchaser from finished bars representing each melt, which shall conform to the requirements specified in sec. 2.

### III. PHYSICAL PROPERTIES AND TESTS

5. **Tension Tests.** (a) The bars shall conform to the following requirements as to tensile properties:

Tensile strength.....	lb. per sq. inch	45,000-55,000
Yield point, min.....	lb. per sq. inch	0.5 tens. str.
Elongation in 8 inches, min.....	per cent	1,500,000
but not to exceed 30 per cent.		tens. str.

(b) The yield point shall be determined by the drop of the beam of the testing machine.

6. **Bend Tests.** (a) *Cold-bend Tests.*—The test specimen shall bend cold through 180 degrees flat on itself without cracking on the outside of the bent portion.

(b) *Quench-bend Tests.*—The test specimen, when heated to a light cherry red as seen in the dark (not less than 1200° F.) and quenched at once in water the temperature of which is between 80° and 90° F., shall bend through 180 degrees flat on itself without cracking on the outside of the bent portion.

7. **Test Specimens.** Tension and bend test specimens shall be of the full-size section of bars as rolled.

8. **Number of Tests.** (a) Two tension-, two cold-bend-, and two quench-bend tests shall be made from each melt, each of which shall conform to the requirements specified.

(b) If any test specimen develops flaws, it may be discarded and another specimen substituted.

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 5 (a) and any part of the fracture is outside the middle third of the gage length, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

### IV. PERMISSIBLE VARIATIONS IN GAGE

9. **Permissible Variations.** The gage of each bar shall not vary more than 0.01 inch from that specified.

## STANDARD SPECIFICATIONS

### V. WORKMANSHIP AND FINISH

10. **Workmanship.** The finished bars shall be circular within 0.01 inch.

11. **Finish.** The finished bars shall be free from injurious defects and shall have a workmanlike finish.

### VI. MARKING

12. **Marking.** Rivet bars shall, when loaded for shipment, be properly separated and marked with the name or brand of the manufacturer and the melt number for identification. The melt number shall be legibly marked on each test specimen.

### VII. INSPECTION AND REJECTION

13. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the bars ordered. The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the bars are being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

14. **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 4 shall be reported within five working days from the receipt of samples.

(b) Bars which show injurious defects subsequent to their acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

15. **Rehearing.** Samples tested in accordance with sec. 4, which represent rejected bars, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.

### *B. Requirements for Rivets.*

#### I. PHYSICAL PROPERTIES AND TESTS

16. **Tension Tests.** The rivets, when tested, shall conform to the requirements as to tensile properties specified in sec. 5, except that the elongation shall be measured on a gage length not less



## CARNEGIE STEEL COMPANY

than four times the diameter of the rivet.

17. **Bend Tests.** The rivet shank shall bend cold through 180 degrees flat on itself, as shown in fig. 1, without cracking on the outside of the bent portion.

18. **Flattening Tests.** The rivet head shall flatten, while hot, to a diameter  $2\frac{1}{2}$  times the diameter of the shank, as shown in fig. 2, without cracking at the edges.



FIGURE 1.




FIGURE 2.

19. **Number of Tests.** (a) When specified, one tension test shall be made from each size in each lot of rivets offered for inspection.

(b) Three bend-and three flattening tests shall be made from each size in each lot of rivets offered for inspection, each of which shall conform to the requirements specified.

## II. WORKMANSHIP AND FINISH

20. **Workmanship.** The rivets shall be true to form, concentric, and shall be made in a workmanlike manner.

21. **Finish.** The finished rivets shall be free from injurious defects.

## III. INSPECTION AND REJECTION

22. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the rivets ordered. The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the rivets are being furnished in accordance with these specifications. All tests and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

23. **Rejection.** Rivets which show injurious defects subsequent to their acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

## STANDARD SPECIFICATIONS

### AMERICAN SOCIETY FOR TESTING MATERIALS

PHILADELPHIA, PA., U. S. A.

AFFILIATED WITH THE

INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS

## STANDARD SPECIFICATIONS

FOR

### STRUCTURAL NICKEL STEEL

SERIAL DESIGNATION: A8-14.

The specifications for this material are issued under the fixed designation A 8; the final number indicates the year of original issue or, in the case of revision, the year of last revision.

ADOPTED, 1912; REVISED, 1913, 1914.

#### I. MANUFACTURE

1. **Process.** The steel shall be made by the open-hearth process.
2. **Discard.** A sufficient discard shall be made from each ingot intended for eye bars to secure freedom from injurious piping and undue segregation.

#### II. CHEMICAL PROPERTIES AND TESTS

3. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition.

STRUCTURAL STEEL				RIVET STEEL			
Carbon.....	not over	0.45	per cent	not over	0.30	per cent	
Manganese.....	" "	0.70	" "	" "	0.60	" "	
Phosphorus { Acid.....	" "	0.05	" "	" "	0.04	" "	
{ Basic.....	" "	0.04	" "	" "	0.03	" "	
Sulphur.....	" "	0.05	" "	" "	0.45	" "	
Nickel.....	not under	3.25	" "	not under	3.25	" "	

## CARNEGIE STEEL COMPANY

4. **Ladle Analyses.** An analysis shall be made by the manufacturer from a test ingot taken during the pouring of each melt, a copy of which shall be given to the purchaser or his representative. This analysis shall conform to the requirements specified in sec. 3.

5. **Check Analyses.** Analyses may be made by the purchaser from finished material representing each melt, which shall conform to the requirements specified in sec. 3.

### III. PHYSICAL PROPERTIES AND TESTS

6. **Tension Tests.** (a) The material shall conform to the following requirements as to tensile properties:

Properties Considered	Rivet Steel	Plates, Shapes and Bars	Eye Bars and Rollers, <i>c</i> Unannealed	Eye Bars <i>a</i> and Pins, <i>c</i> Annealed
Tensile strength, lb. per sq. inch	70,000-80,000	85,000-100,000	95,000-110,000	90,000-105,000
Yield point, min., lb. per sq. inch	45,000	50,000	55,000	52,000
Elongation in 8 inches, min., per cent	1,500,000 tens. str.	1,500,000 <sup>b</sup> tens. str.	1,500,000 <sup>b</sup> tens. str.	20
Elongation in 2 inches, min., per cent	.....	.....	16	20
Reduction of area, min., per cent	40	25	25	35

<sup>a</sup> Tests of annealed specimens of eye bars shall be made for information only

<sup>b</sup> See sec. 7.

<sup>c</sup> Elongation shall be measured in 2 inches.

(b) The yield point shall be determined by the drop of the beam of the testing machine.

7. **Modifications in Elongations.** For plates, shapes and unannealed bars over 1 inch in thickness, a deduction of 1 from the percentage of elongation specified in sec. 6 (a) shall be made for each increase of  $\frac{1}{8}$  inch in thickness above 1 inch, to a minimum of 14 per cent.

8. **Character of Fracture.** All broken tension test specimens shall show either a silky or a very fine granular fracture, of uniform color, and free from coarse crystals.

9. **Bend Tests.** (a) The test specimen for plates, shapes and bars shall bend cold through 180 degrees without cracking on the outside of the bent portion, as follows: For material  $\frac{3}{4}$  inch or under in thickness, around a pin the diameter of which is equal to the thickness of the specimen; and for material over  $\frac{3}{4}$  inch in

## STANDARD SPECIFICATIONS

thickness, around a pin the diameter of which is equal to twice the thickness of the specimen.

(b) The test specimen for pins and rollers shall bend cold through 180 degrees around a 1-inch pin without cracking on the outside of the bent portion.

(c) The test specimen for rivet steel shall bend cold through 180 degrees flat on itself without cracking on the outside of the bent portion.

10. **Drift Tests.** Punched rivet holes pitched two diameters from a planed edge shall stand drifting until the diameter is enlarged 50 per cent, without cracking the metal.

11. **Test Specimens.** (a) Tension-and bend test specimens shall be taken from the finished material. Specimens for pins shall be taken after annealing.

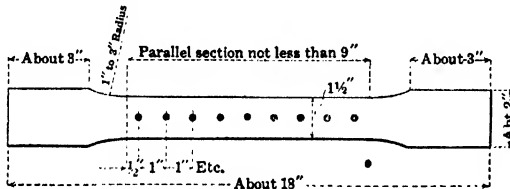


FIGURE 1.

(b) Tension-and bend test specimens for plates, shapes and bars, except as specified in par. (c), shall be of the full thickness of material as rolled. They may be machined to the form and dimensions shown in fig. 1, or with both edges parallel; except that bend test specimens shall not be less than 2 inches in width, and that bend test specimens for eye-bar flats may have three rolled sides.

(c) Tension-and bend test specimens for plates and bars (except eye-bar flats) over  $1\frac{1}{2}$  inch in thickness or diameter may be machined to a thickness or diameter of at least  $\frac{3}{4}$  inch for a length of at least 9 inches.

(d) The axis of tension-and bend test specimens for pins and rollers shall be 1 inch from the surface and parallel to the axis of the bar. Tension test specimens shall be of the form and dimensions shown in fig. 2. Bend test specimens shall be 1 by  $\frac{1}{2}$  inch in section.

(e) Tension-and bend test specimens for rivet steel shall be of the full-size section of bars as rolled.

## CARNEGIE STEEL COMPANY

**12. Number of Tests.** (a) One tension-and one bend test shall be made from each melt; except that if material from one melt differs  $\frac{3}{8}$  inch or more in thickness, one tension-and one bend test shall be made from both the thickest and the thinnest material rolled.

(b) If any test specimen shows defective machining or develops flaws, it may be discarded and another specimen substituted.

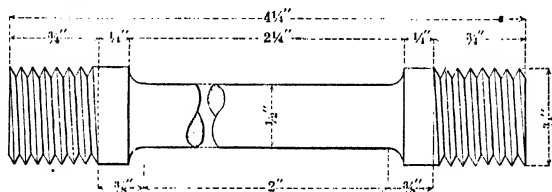


FIGURE 2.

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 6 (a) and any part of the fracture is more than  $\frac{3}{4}$  inch from the center of the gage length of a 2-inch specimen or is outside the middle third of the gage length of an 8-inch specimen, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

### IV. PERMISSIBLE VARIATIONS IN WEIGHT AND GAGE

**13. Permissible Variations.** The cross-section or weight of each piece of steel shall not vary more than 2.5 per cent from that specified; except in the case of sheared plates, which shall be covered by the following permissible variations to apply to single plates:

(a) **When Ordered to Weight.**—

For plates  $12\frac{1}{2}$  pounds per sq. foot or over:

Under 100 inches in width, 2.5 per cent above or below the specified weight;

100 inches in width or over, 5 per cent above or below the specified weight.

For plates under  $12\frac{1}{2}$  pounds per sq. foot:

Under 75 inches in width, 2.5 per cent above or below the specified weight;

75 to 100 inches, exclusive, in width, 5 per cent above or 3 per cent below the specified weight;

100 inches in width or over, 10 per cent above or 3 per cent below the specified weight.

## STANDARD SPECIFICATIONS

### (b) When Ordered to Gage.—

The thickness of each plate shall not vary more than 0.01 inch under that ordered.

An excess over the nominal weight corresponding to the dimensions on the order shall be allowed for each plate, if not more than that shown in the following table, one cubic inch of rolled steel being assumed to weigh 0.2833 pounds:

Thickness Ordered, Inches	Nominal Weight, Pounds per Square Foot	ALLOWABLE EXCESS EXPRESSED AS PERCENTAGE OF NOMINAL WEIGHT For Width of Plate as follows:						
		Under 50 in.	50 in. to 70 in. excl.	70 in. or over	Under 75 in.	75 in. to 100 in. excl.	100 in. to 115 in. excl.	115 in. or over
$\frac{1}{8}$ to $\frac{5}{16}$	5.10 to 6.37	10	15	20	..	..	..	..
$\frac{5}{16}$ to $\frac{3}{8}$	6.37 to 7.65	8.5	12.5	17	..	..	..	..
$\frac{3}{8}$ to $\frac{1}{2}$	7.65 to 10.20	7	10	15	..	..	..	..
$\frac{1}{2}$	10.20	..	..	..	10	14	18	..
$\frac{5}{8}$	12.75	..	..	..	8	12	16	..
$\frac{3}{4}$	15.30	..	..	..	7	10	13	17
$\frac{7}{8}$	17.85	..	..	..	6	8	10	13
$1\frac{1}{8}$	20.40	..	..	..	5	7	9	12
$\frac{1}{4}$	22.95	..	..	..	4.5	6.5	8.5	11
$\frac{1}{2}$	25.50	..	..	..	4	6	8	10
Over $\frac{3}{4}$	.....	..	..	..	3.5	5	6.5	9

## V. FINISH

14. **Finish.** The finished material shall be free from injurious defects and shall have a workmanlike finish.

## VI. MARKING

15. **Marking.** The name or brand of the manufacturer and the melt number shall be legibly stamped or rolled on all finished material, except that rivet and lattice bars and other small sections shall, when loaded for shipment, be properly separated and marked for identification. The identification marks shall be legibly stamped on the end of each pin and roller. The melt number shall be legibly marked, by stamping, if practicable, on each test specimen.

## VII. INSPECTION AND REJECTION

16. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the material ordered.

## CARNEGIE STEEL COMPANY

The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the material is being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

17. **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 5 shall be reported within five working days from the receipt of samples.

(b) Material which shows injurious defects subsequent to its acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

18. **Rehearing.** Samples tested in accordance with sec. 5, which represent rejected material, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.

### VIII. FULL-SIZE TESTS

19. **Test of Eye Bars.** (a) Full-size tests of annealed eye bars shall conform to the following requirements as to tensile properties:

Tensile strength.....	lb. per sq. inch	85,000-100,000
Yield point, min.....	lb. per sq. inch	48,000
Elongation in 18 ft., min.....	per cent	10
Reduction of area, min.....	per cent	30

(b) The yield point shall be determined by the halt of the gage of the testing machine.

## STANDARD SPECIFICATIONS

AMERICAN SOCIETY FOR TESTING MATERIALS

PHILADELPHIA, PA., U. S. A.

AFFILIATED WITH THE

INTERNATIONAL ASSOCIATION FOR TESTING MATERIALS

## STANDARD SPECIFICATIONS

FOR

### BILLET STEEL

### CONCRETE REINFORCEMENT BARS

SERIAL DESIGNATION: A15-14.

The specifications for this material are issued under the fixed designation A 15; the final number indicates the year of original issue or, in the case of revision, the year of last revision.

ADOPTED, 1911; REVISED, 1912, 1913, 1914.

1. **Classes.** (a) These specifications cover three classes of billet steel concrete reinforcement bars, namely: plain, deformed and cold-twisted.

(b) Plain and deformed bars are of three grades, namely: structural steel, intermediate and hard.

2. **Basis of Purchase.** (a) The structural steel grade shall be used unless otherwise specified.

(b) If desired, cold-twisted bars may be purchased on the basis of tests of the hot-rolled bars before twisting, in which case such tests shall govern and shall conform to the requirements specified for plain bars of structural steel grade.

#### I. MANUFACTURE

3. **Process.** (a) The steel may be made by the bessemer-or the open-hearth process.



## CARNEGIE STEEL COMPANY

(b) The bars shall be rolled from new billets. No rerolled material will be accepted.

4. **Cold-twisted Bars.** Cold-twisted bars shall be twisted cold with one complete twist in a length not over 12 times the thickness of the bar.

### II. CHEMICAL PROPERTIES AND TESTS

5. **Chemical Composition.** The steel shall conform to the following requirements as to chemical composition:

Phosphorus	Bessemer.....	not over 0.10 per cent
	Open-hearth.....	" " 0.05 " "

6. **Ladle Analyses.** An analysis to determine the percentages of carbon, manganese, phosphorus and sulphur, shall be made by the manufacturer from a test ingot taken during the pouring of each melt, a copy of which shall be given to the purchaser or his representative. This analysis shall conform to the requirements specified in sec. 5.

7. **Check Analyses.** Analyses may be made by the purchaser from finished bars representing each melt of open-hearth steel, and each melt, or lot of ten tons, of bessemer steel, in which case an excess of 25 per cent above the requirements specified in sec. 5 shall be allowed.

### III. PHYSICAL PROPERTIES AND TESTS

8. **Tension Tests.** (a) The bars shall conform to the following requirements as to tensile properties:

TENSILE PROPERTIES

Properties Considered	Plain Bars			Deformed Bars			Cold-twisted Bars
	Structural-Steel Grade	Intermediate Grade	Hard Grade	Structural-Steel Grade	Intermediate Grade	Hard Grade	
Tensile strength, lb. per sq. inch	55,000 to 70,000	70,000 to 85,000	80,000 min.	55,000 to 70,000	70,000 to 85,000	80,000 min.	Recorded only
Yield point, min. lb. per sq. inch	33,000	40,000	50,000	33,000	40,000	50,000	55,000
Elongation in 8 inches, min. per cent	1,400,000 <sup>a</sup> tens. str.	1,300,000 <sup>a</sup> tens. str.	1,200,000 <sup>a</sup> tens. str.	1,250,000 <sup>a</sup> tens. str.	1,125,000 <sup>a</sup> tens. str.	1,000,000 <sup>a</sup> tens. str.	5

<sup>a</sup> See sec. 9.

## STANDARD SPECIFICATIONS

(b) The yield point shall be determined by the drop of the beam of the testing machine.

9. **Modifications in Elongation.** (a) For plain and deformed bars over  $\frac{3}{4}$  inch in thickness or diameter, a deduction of 1 from the percentages of elongation specified in sec. 8 (a) shall be made for each increase of  $\frac{1}{8}$  inch in thickness or diameter above  $\frac{3}{4}$  inch.

(b) For plain and deformed bars under  $\frac{7}{16}$  inch in thickness or diameter, a deduction of 1 from the percentages of elongation specified in sec. 8 (a) shall be made for each decrease of  $\frac{1}{16}$  inch in thickness or diameter below  $\frac{7}{16}$  inch.

10. **Bend Tests.** The test specimen shall bend cold around a pin without cracking on the outside of the bent portion, as follows:

BEND-TEST REQUIREMENTS

Thickness or Diameter of Bar	Plain Bars			Deformed Bars			Cold-twisted Bars
	Structural-Steel Grade	Inter-mediate Grade	Hard Grade	Structural-Steel Grade	Inter-mediate Grade	Hard Grade	
Under $\frac{3}{4}$ inch	180 deg. d=t	180 deg. d=2t	180 deg. d=3t	180 deg. d=t	180 deg. d=3t	180 deg. d=4t	180 deg. d=2t.
$\frac{3}{4}$ inch or over	180 deg. d=t	90 deg. d=2t	90 deg. d=3t	180 deg. d=2t	90 deg. d=3t	90 deg. d=4t	180 deg. d=3t

EXPLANATORY NOTE: d = the diameter of pin about which the specimen is bent;  
t = the thickness or diameter of the specimen.

11. **Test Specimens.** (a) Tension-and bend test specimens for plain and deformed bars shall be taken from the finished bars, and shall be of the full thickness or diameter of bars as rolled; except that the specimens for deformed bars may be machined for a length of at least 9 inches, if deemed necessary by the manufacturer to obtain uniform cross-section.

(b) Tension-and bend test specimens for cold-twisted bars shall be taken from the finished bars, without further treatment; except as specified in sec. 2 (b).

12. **Number of Tests.** (a) One tension-and one bend test shall be made from each melt of open-hearth steel, and from each melt, or lot of ten tons, of bessemer steel; except that if material from one melt differs  $\frac{3}{8}$  inch or more in thickness or diameter, one tension-and one bend test shall be made from both the thickest and the thinnest material rolled.

(b) If any test specimen shows defective machining or develops flaws, it may be discarded and another specimen substituted.

## CARNEGIE STEEL COMPANY

(c) If the percentage of elongation of any tension test specimen is less than that specified in sec. 8 (a) and any part of the fracture is outside the middle third of the gage length, as indicated by scribe scratches marked on the specimen before testing, a retest shall be allowed.

### IV. PERMISSIBLE VARIATIONS IN WEIGHT

13. **Permissible Variations.** The weight of any lot of bars shall not vary more than 5 per cent from the theoretical weight of that lot.

### V. FINISH

14. **Finish.** The finished bars shall be free from injurious defects and shall have a workmanlike finish.

### VII. INSPECTION AND REJECTION

15. **Inspection.** The inspector representing the purchaser shall have free entry, at all times while work on the contract of the purchaser is being performed, to all parts of the manufacturer's works which concern the manufacture of the bars ordered. The manufacturer shall afford the inspector, free of cost, all reasonable facilities to satisfy him that the bars are being furnished in accordance with these specifications. All tests (except check analyses) and inspection shall be made at the place of manufacture prior to shipment, unless otherwise specified, and shall be so conducted as not to interfere unnecessarily with the operation of the works.

16. **Rejection.** (a) Unless otherwise specified, any rejection based on tests made in accordance with sec. 7 shall be reported within five working days from the receipt of samples.

(b) Bars which show injurious defects subsequent to their acceptance at the manufacturer's works will be rejected, and the manufacturer shall be notified.

17. **Rehearing.** Samples tested in accordance with sec. 7, which represent rejected bars, shall be preserved for two weeks from the date of the test report. In case of dissatisfaction with the results of the tests, the manufacturer may make claim for a rehearing within that time.

## GENERAL INSTRUCTIONS FOR ORDERING

### ORDERING MATERIAL

#### GENERAL INSTRUCTIONS

Structural steel for bridges, buildings and ships, steel reinforcement bars and open hearth boiler plate and rivet steel are rolled to permissible variations given in the specifications which precede. In cases of design which require close fitting, allowance should be made for such rolling variations so as to insure ample clearance between abutting or interfitting surfaces.

All dimensions given on profiles are theoretical. Wherever the profile applies to more than one weight of section, the dimensions are for the minimum weight.

Weights of rails are given per lineal yard of section, but unless otherwise indicated, all other weights are per lineal foot. Sections having but one weight specified can be rolled only to the weight given.

Structural Beams, H-Beams, Structural Channels, Shipbuilding Channels, Bulb Angles, Bulb Beams, United States Steel Sheet Piling, Tees and Zees should be ordered to weight per foot; Angles may be ordered either to weight per foot or to thickness.

Orders for Plates should specify all dimensions in inches.


Orders for Rounds, Squares and other Bar Mill Products should specify width and thickness in inches and the length in feet and inches.

Rails, Ties and other track accessories should be ordered by section number and not by the weight per foot. The section number should also be specified on orders for all other sections.

The Association of American Steel Manufacturers has recommended certain angle sections as standard for bridge, car, ship and general building construction, and quicker deliveries can be obtained by ordering these standard sizes and weights. Angles not standard are marked "special" on the profile pages.

In the calculation of the areas and weights of the various sections herein shown, the fillets have been disregarded in accordance with the rules of the Association of American Steel Manufacturers.

# CARNEGIE STEEL COMPANY

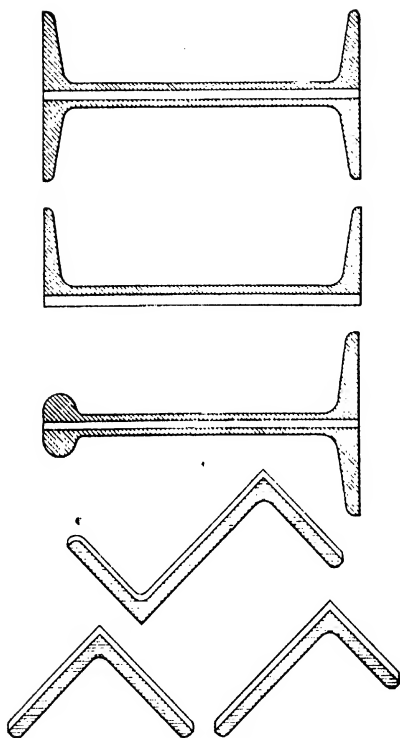

The above figures show the method of increasing the sectional areas and weights of structural shapes. Cross hatched portions represent the minimum sections and the blank portions the added areas.

In the case of Channels, I-Beams and Bulb Beams, the enlargement of the section adds an equal amount to the thickness of the web and the width of the flanges. In the case of Angles and Zees, the effect of spreading the rolls is slightly to increase the length of the legs. No general statement can be made with regard to Bulb Angles, in the rolling of which different methods are in use.


Inasmuch as the roll passes are modified in the wear of the rolls, the actual dimensions will not always conform to the theoretical, even in the case of the minimum weight sections. Designers and detailers of structural work should arrange for ample clearances.

# COMMON DIMENSIONS FOR BEAMS AND CHANNELS


## BEAMS AND CHANNELS

### COMMON DIMENSIONS

#### STRUCTURAL BEAMS

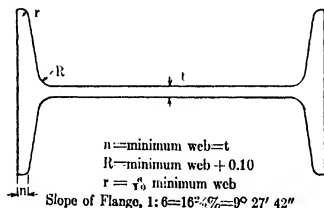

#### STRUCTURAL CHANNELS

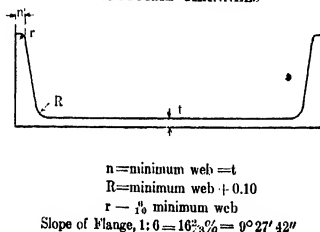

All dimensions are in inches and apply only to the minimum weight Beams or Channels.

Dimensions given for Structural Beams are those adopted in 1896, by the Association of American Steel Manufacturers and apply to all Beam Sections shown on the pages which follow, except the American Standard Beam Sections B 1, B 2 and B 3, Beam Sections B 24 and B 81, and Supplementary Beams, B 61 to B 68, inclusive.


The dimensions of the Supplementary Beams cannot be readily reduced to exact formulas. With the exception of the 27-inch beam, B 61, dimensions are based on those of the 12-inch beam, B 66, which, in turn, has been adopted in the light of mill experience; from these dimensions they vary by the addition or subtraction of successive differences.

Slope of flange of Supplementary Beams, B 61 to B 68, inclusive, is uniformly 1:11 =  $9\frac{1}{11}\%$  =  $5^\circ 11' 40''$ .

Dimensions shown for Structural Channels are those adopted by the Association of American Steel Manufacturers and apply to all Structural Channel Sections except C 20.

# CARNEGIE STEEL COMPANY

## STRUCTURAL BEAMS

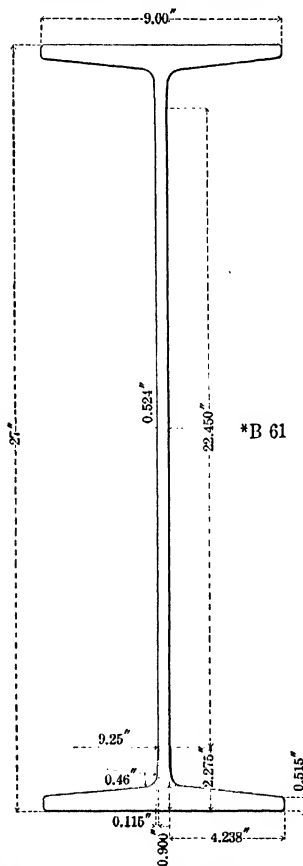


Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
*B 61	27	90.0	9.00	9	0.524	$17\frac{1}{32}$

\* Supplementary Beam.

# BEAMS

## STRUCTURAL BEAMS—Continued

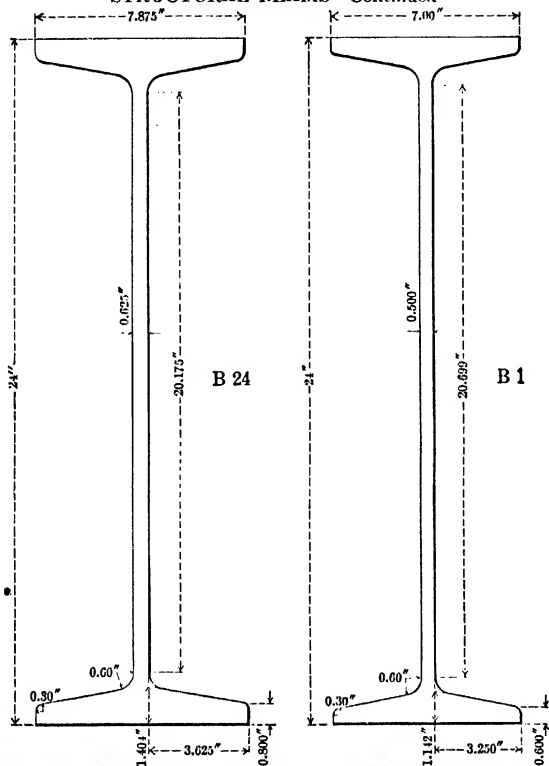


Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
B 24	24	115.0	8.000	8	0.750	$\frac{3}{4}$
		110.0	7.938	$7\frac{1}{8}$	0.688	$\frac{11}{16}$
		105.0	7.875	$7\frac{7}{8}$	0.625	$\frac{5}{8}$
		100.0	7.254	$7\frac{1}{4}$	0.754	$\frac{3}{4}$
B 1	24	95.0	7.193	$7\frac{3}{16}$	0.693	$\frac{11}{16}$
		90.0	7.131	$7\frac{1}{8}$	0.631	$\frac{5}{8}$
		85.0	7.070	$7\frac{1}{16}$	0.570	$\frac{9}{16}$
		80.0	7.000	7	0.500	$\frac{1}{2}$



CARNEGIE STEEL COMPANY

STRUCTURAL BEAMS—Continued

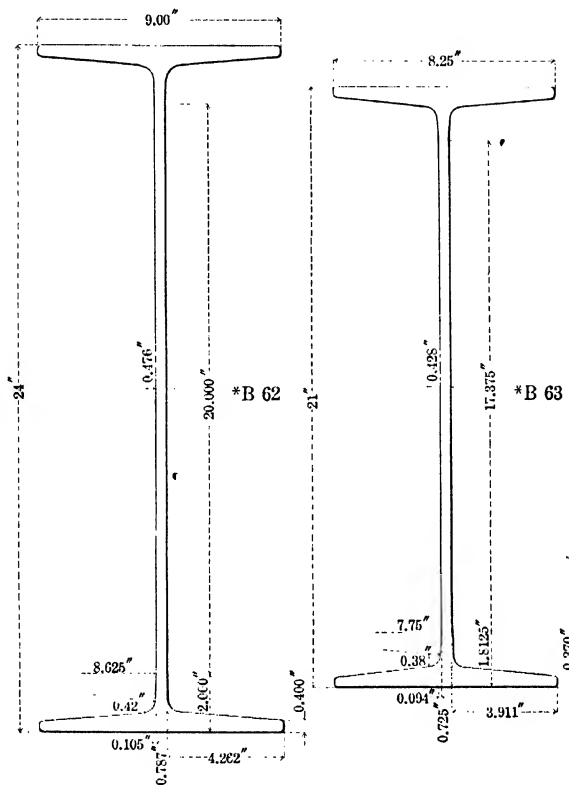


Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
*B 62	24	74	9.00	9	0.476	$1\frac{1}{2}$
*B 63	21	60.5	8.25	$8\frac{1}{4}$	0.428	$2\frac{3}{4}$

\* Supplementary Beam.

# BEAMS


## STRUCTURAL BEAMS—Continued

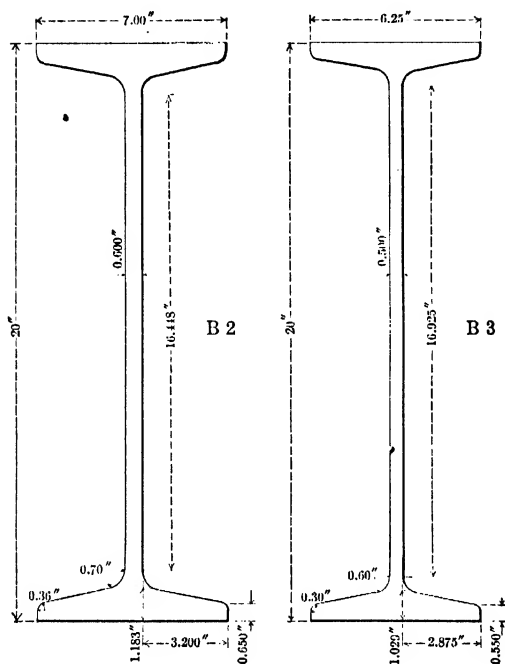

Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
B 2	20	100.0	7.284	$7\frac{3}{8}$	0.884	$\frac{7}{8}$
		95.0	7.210	$7\frac{1}{4}$	0.810	$\frac{3}{4}$
		90.0	7.137	$7\frac{1}{8}$	0.737	$\frac{3}{4}$
		85.0	7.063	$7\frac{1}{8}$	0.663	$\frac{3}{4}$
		80.0	7.000	7	0.600	$\frac{3}{4}$
B 3	20	75.0	6.399	$6\frac{3}{8}$	0.649	$\frac{3}{4}$
		70.0	6.325	$6\frac{1}{4}$	0.575	$\frac{3}{4}$
		65.0	6.250	$6\frac{1}{4}$	0.500	$\frac{3}{4}$

CARNEGIE STEEL COMPANY

STRUCTURAL BEAMS—Continued

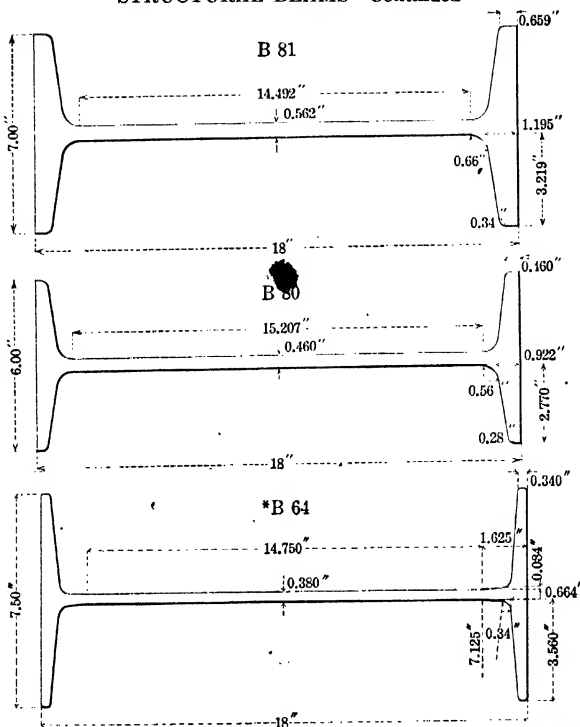


Section Index	Depth of Beam, Inches	Weight Per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
B 81	18	90.0	7.245	7 <sup>1</sup> / <sub>4</sub>	0.807	13 <sup>1</sup> / <sub>16</sub>
		85.0	7.163	7 <sup>5</sup> / <sub>32</sub>	0.725	23 <sup>3</sup> / <sub>32</sub>
		80.0	7.082	7 <sup>5</sup> / <sub>16</sub>	0.644	41 <sup>1</sup> / <sub>16</sub>
		75.0	7.000	7	0.562	9 <sup>1</sup> / <sub>16</sub>
B 80	18	70.0	6.259	6 <sup>1</sup> / <sub>16</sub>	0.719	23 <sup>3</sup> / <sub>32</sub>
		65.0	6.177	6 <sup>1</sup> / <sub>16</sub>	0.637	41 <sup>1</sup> / <sub>16</sub>
		60.0	6.095	6 <sup>9</sup> / <sub>32</sub>	0.555	9 <sup>1</sup> / <sub>16</sub>
		55.0	6.000	6	0.460	29 <sup>5</sup> / <sub>16</sub>
*B 64	18	48.0	7.500	7 <sup>1</sup> / <sub>2</sub>	0.380	3 <sup>1</sup> / <sub>8</sub>

\*Supplementary Beam.

# BEAMS

## STRUCTURAL BEAMS—Continued

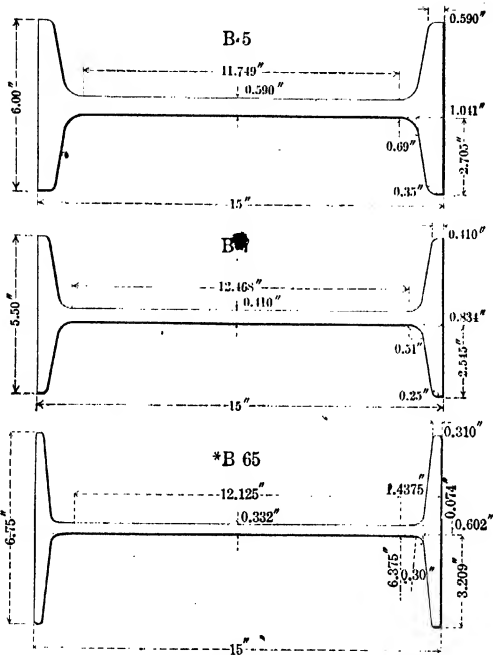


Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
B 5	15	75.0	6.292	6 19/64	0.882	7/8
		70.0	6.194	6 9/16	0.784	25/32
		65.0	6.096	6 5/32	0.686	11/16
		60.0	6.000	6	0.590	19/32
B 7	15	55.0	5.746	5 3/4	0.656	21/32
		50.0	5.648	5 1/16	0.558	9/16
		45.0	5.550	5 5/16	0.460	29/64
		42.0	5.500	5 1/2	0.410	13/32
*B 65	15	37.5	6.750	6 3/4	0.332	21/64

\* Supplementary Beam.

CARNEGIE STEEL COMPANY

STRUCTURAL BEAMS—Continued

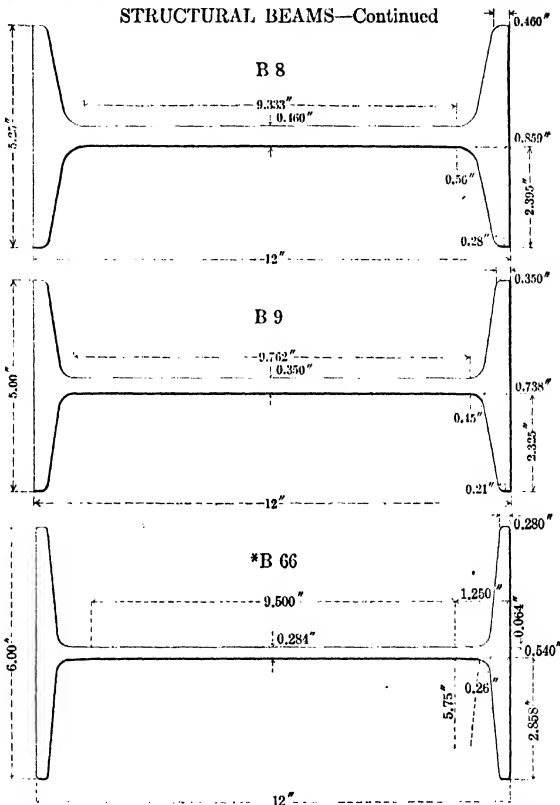


Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
B 8	12	55.0	5.611	5 <sup>39</sup> / <sub>64</sub>	0.821	5 <sup>3</sup> / <sub>16</sub>
		50.0	5.489	5 <sup>31</sup> / <sub>64</sub>	0.699	4 <sup>5</sup> / <sub>16</sub>
		45.0	5.366	5 <sup>23</sup> / <sub>64</sub>	0.576	3 <sup>7</sup> / <sub>16</sub>
		40.0	5.250	5 <sup>1</sup> / <sub>4</sub>	0.400	2 <sup>3</sup> / <sub>16</sub>
B 9	12	35.0	5.086	5 <sup>1</sup> / <sub>2</sub>	0.436	7 <sup>1</sup> / <sub>16</sub>
		31.5	5.000	5	0.350	1 <sup>1</sup> / <sub>2</sub>
*B 66	12	28.0	6.000	6	0.284	1 <sup>1</sup> / <sub>2</sub>

\* Supplementary Beam.

# BEAMS

## STRUCTURAL BEAMS—Continued

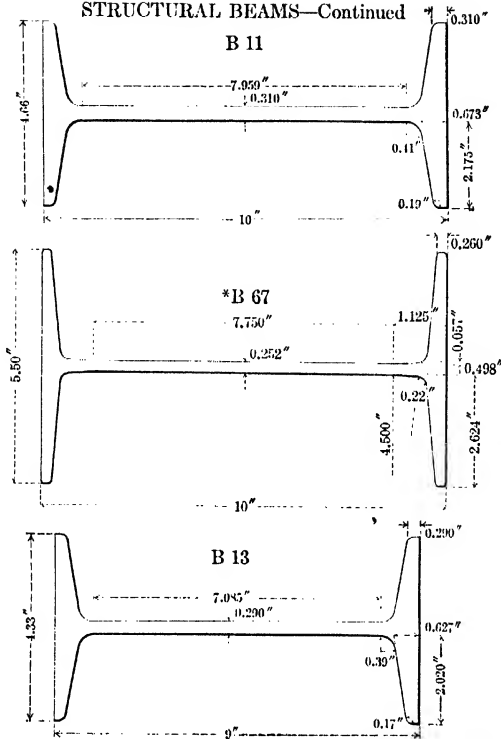


Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
B 11	10	40.0	5.099	$5\frac{3}{32}$	0.749	$\frac{3}{4}$
		35.0	4.952	$4\frac{1}{16}$	0.602	$\frac{23}{64}$
		30.0	4.805	$4\frac{13}{16}$	0.455	$\frac{29}{64}$
		25.0	4.660	$4\frac{21}{32}$	0.310	$\frac{5}{16}$
*B 67	10	22.25	5.500	$5\frac{1}{4}$	0.252	$\frac{1}{4}$
		35.0	4.772	$4\frac{49}{64}$	0.732	$\frac{47}{64}$
B 13	9	30.0	4.609	$4\frac{39}{64}$	0.569	$\frac{9}{16}$
		25.0	4.446	$4\frac{29}{64}$	0.406	$\frac{13}{32}$
		21.0	4.330	$4\frac{21}{64}$	0.290	$\frac{19}{64}$

\* Supplementary Beam.

# CARNEGIE STEEL COMPANY

## STRUCTURAL BEAMS—Continued

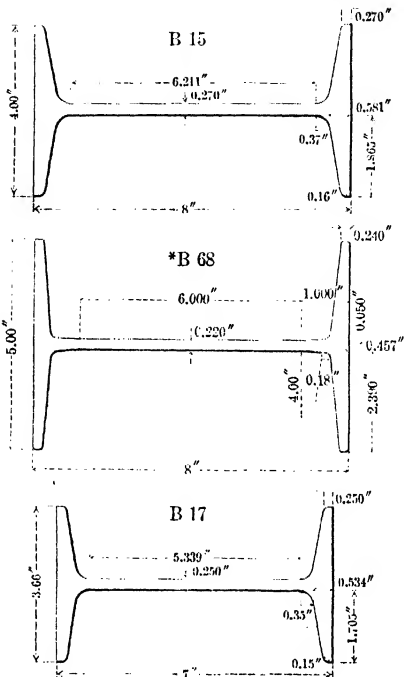


Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
B 15	8	25.5	4.271	$4\frac{17}{64}$	0.541	$35\frac{1}{64}$
		23.0	4.179	$4\frac{11}{64}$	0.449	$29\frac{61}{64}$
		20.5	4.087	$4\frac{3}{32}$	0.357	$23\frac{51}{64}$
		18.0	4.000	4	0.270	$17\frac{1}{64}$
*B 68	8	17.5	5.000	5	0.220	$7\frac{1}{32}$
B 17	7	20.0	3.868	$3\frac{7}{8}$	0.458	$29\frac{61}{64}$
		17.5	3.763	$3\frac{19}{64}$	0.353	$23\frac{61}{64}$
		15.0	3.660	$3\frac{21}{32}$	0.250	$16\frac{1}{4}$

\*Supplementary Beam.

# BEAMS

## STRUCTURAL BEAMS—Concluded

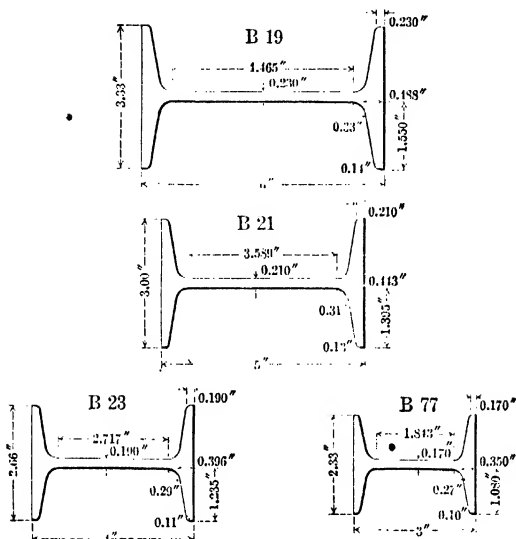


Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
B 19	6	17.25	3.575	$3\frac{37}{64}$	0.475	$\frac{3}{4}$
		14.75	3.452	$3\frac{37}{64}$	0.352	$\frac{3}{8}$
		12.25	3.330	$3\frac{31}{64}$	0.230	$\frac{3}{8}$
B 21	5	14.75	3.294	$3\frac{17}{64}$	0.504	$\frac{1}{2}$
		12.25	3.147	$3\frac{1}{64}$	0.357	$\frac{3}{8}$
		9.75	3.000	3	0.210	$\frac{3}{8}$
B 23	4	10.5	2.880	$2\frac{7}{8}$	0.410	$\frac{1}{2}$
		9.5	2.807	$2\frac{1}{8}$	0.337	$\frac{3}{8}$
		8.5	2.733	$2\frac{1}{8}$	0.263	$\frac{3}{8}$
		7.5	2.660	$2\frac{1}{8}$	0.190	$\frac{3}{8}$
B 77	3	7.5	2.521	$2\frac{3}{8}$	0.361	$\frac{3}{8}$
		6.5	2.423	$2\frac{3}{8}$	0.263	$\frac{3}{8}$
		5.5	2.330	$2\frac{1}{8}$	0.170	$\frac{3}{8}$



# CARNEGIE STEEL COMPANY

## H-BEAMS

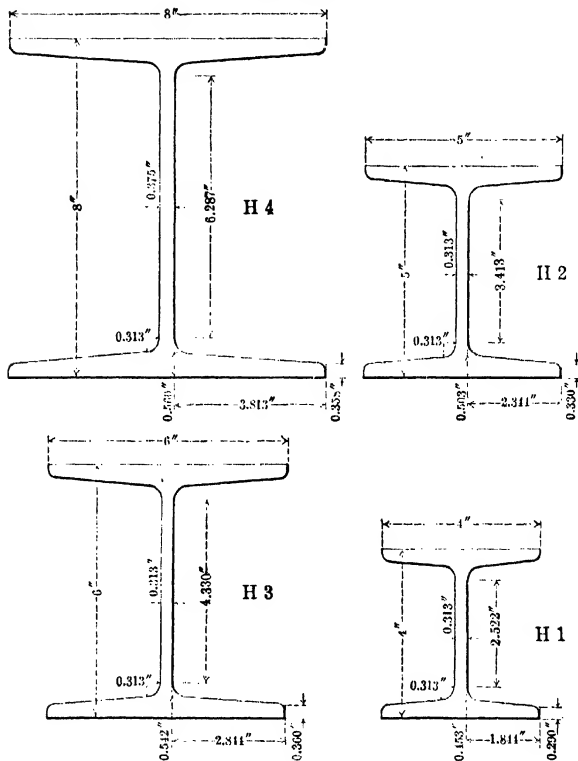


Section Index	Depth of Beam, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
H 4	8	34.0	8.000	8	0.375	$\frac{3}{8}$
H 3	6	23.8	6.000	6	0.313	$\frac{1}{4}$
H 2	5	18.7	5.000	5	0.313	$\frac{1}{4}$
H 1	4	13.6	4.000	4	0.313	$\frac{1}{4}$

H-Beams shown on this sheet are particularly adapted for use in inside mine timbering. Full information as to their properties and uses is given in separate pamphlets entitled "Steel Mine Timbers."

# BULB SECTIONS

## BULB BEAMS

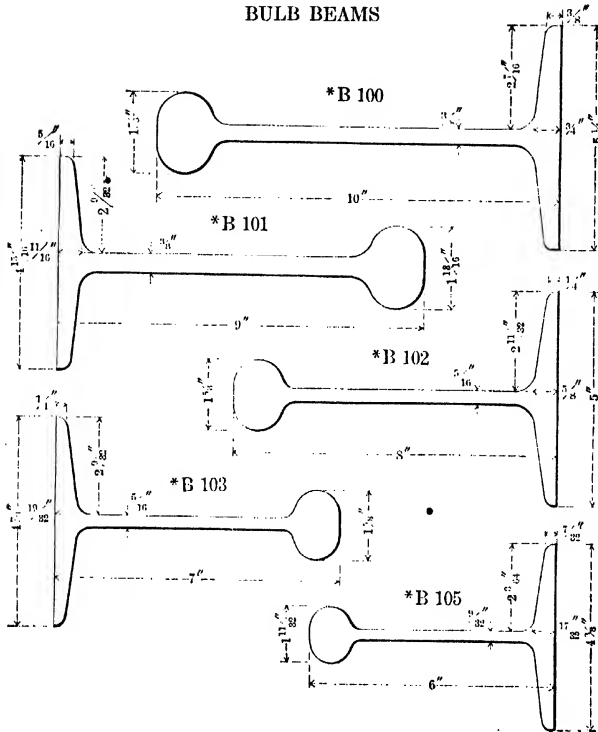


Section Index	Depth, Inches	Flange Width, Inches		Web Thickness, Inches		Weight per Foot, Pounds	Increase in web and width for each additional pound per foot
		Decimal	Fractional	Decimal	Fractional		
*B 100	10	5.500	5 1/2	0.625	5/8	36.6	0.029"
		5.250	5 1/4	0.375	3/8	28.1	
*B 101	9	5.125	5 1/8	0.563	9/16	30.1	0.033"
		4.938	4 15/16	0.375	3/8	24.3	
*B 102	8	5.156	5 5/16	0.469	15/32	24.2	0.037"
		5.000	5	0.313	5/16	20.0	
*B 103	7	5.094	5 3/32	0.531	17/32	23.3	0.042"
		4.875	4 7/8	0.313	5/16	18.1	
*B 105	6	4.524	4 17/32	0.430	7/16	17.2	0.049"
		4.375	4 3/4	0.281	9/32	14.0	

\*Furnished only by special arrangement.

CARNEGIE STEEL COMPANY

SHIP BUILDING BULB ANGLES

British Standard Sections

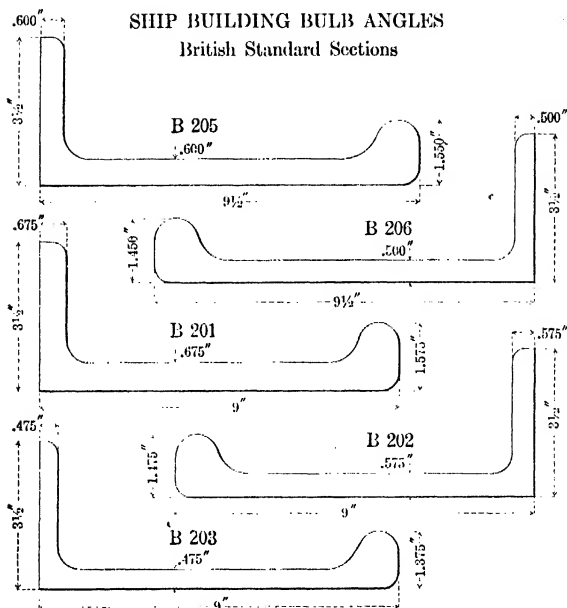


Section Index	Depth, Inches		Flange Width, Inches		Web Thickness, Inches		Weight per Foot, Pounds
	Decimal	Fractional	Decimal	Fractional	Decimal	Fractional	
*B 205	9.500	9 1/2	3.500	3 1/2	0.025	5/8	29.7
					0.000	15/32	28.8
					0.575	27/41	27.8
					0.550	25/44	26.9
					0.525	17/32	25.7
*B 206	9.500	9 1/2	3.500	3 1/2	0.500	1/2	24.7
					0.475	15/32	23.8
					0.450	29/64	22.8
					0.675	43/64	30.4
					0.650	21/32	29.5
*B 201	9.000	9	3.500	3 1/2	0.625	5/8	28.6
					0.600	19/32	27.7
					0.575	27/41	26.6
					0.550	25/44	25.7
					0.525	17/32	24.8
*B 202	9.000	9	3.500	3 1/2	0.500	1/2	23.9
					0.475	15/32	22.7
					0.450	29/64	21.8
					0.425	27/64	20.9
					0.400	13/32	20.0

\*Furnished only by special arrangement.

# BULB SECTIONS

## SHIP BUILDING BULB ANGLES

British Standard Sections

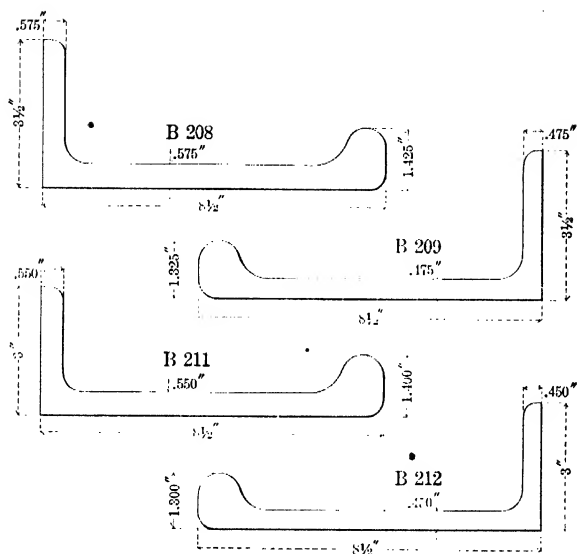


Section Index	Depth, Inches		Flange Width, Inches		Web Thickness, Inches		Weight per Foot, Pounds
	Decimal	Fractional	Decimal	Fractional	Decimal	Fractional	
*B 208	8.500	8 1/2	3.500	3 1/2	.575	27/64	25.3
					.550	25/64	24.1
					.525	17/32	23.5
					.500	1/2	22.7
*B 209	8.500	8 1/2	3.500	3 1/2	.475	15/32	21.6
					.450	29/64	20.7
					.425	27/64	19.8
					.400	13/32	18.9
*B 211	8.500	8 1/2	3.000	3	.575	27/64	24.3
					.550	25/64	23.4
					.525	17/32	22.6
					.500	1/2	21.7
*B 212	8.500	8 1/2	3.000	3	.475	15/32	20.7
					.450	29/64	19.8
					.425	27/64	19.0
					.400	13/32	18.1

\*Furnished only by special arrangement.

**CARNEGIE STEEL COMPANY**

**SHIP BUILDING BULB ANGLES**  
British Standard Sections

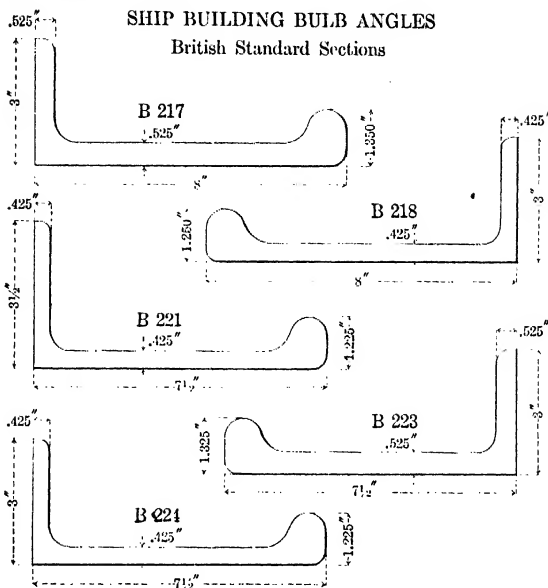


Section Index	Depth, Inches		Flange Width, Inches		Web Thickness, Inches		Weight per Foot, Pounds
	Decimal	Fractional	Decimal	Fractional	Decimal	Fractional	
*B 217	8.000	8	3.000	3	0.575	$\frac{37}{64}$	23.1
					0.550	$\frac{35}{64}$	22.2
					0.525	$\frac{17}{32}$	21.4
					0.500	$\frac{1}{2}$	20.6
*B 218	8.000	8	3.000	3	0.475	$\frac{15}{32}$	19.6
					0.450	$\frac{29}{64}$	18.8
					0.425	$\frac{27}{64}$	18.0
					0.400	$\frac{13}{32}$	17.2
*B 221	7.500	7 1/2	3.500	3 1/2	0.475	$\frac{15}{32}$	19.4
					0.450	$\frac{29}{64}$	18.6
					0.425	$\frac{27}{64}$	17.8
					0.400	$\frac{13}{32}$	17.0
*B 223	7.500	7 1/2	3.000	3	0.525	$\frac{17}{32}$	20.3
					0.500	$\frac{1}{2}$	19.6
					0.475	$\frac{15}{32}$	18.8
					0.450	$\frac{29}{64}$	18.0
*B 224	7.500	7 1/2	3.000	3	0.425	$\frac{27}{64}$	17.1
					0.400	$\frac{13}{32}$	16.3
					0.375	$\frac{3}{8}$	15.6
					0.350	$\frac{11}{32}$	14.8

\*Furnished only by special arrangement.

# BULB SECTIONS

## SHIP BUILDING BULB ANGLES

British Standard Sections

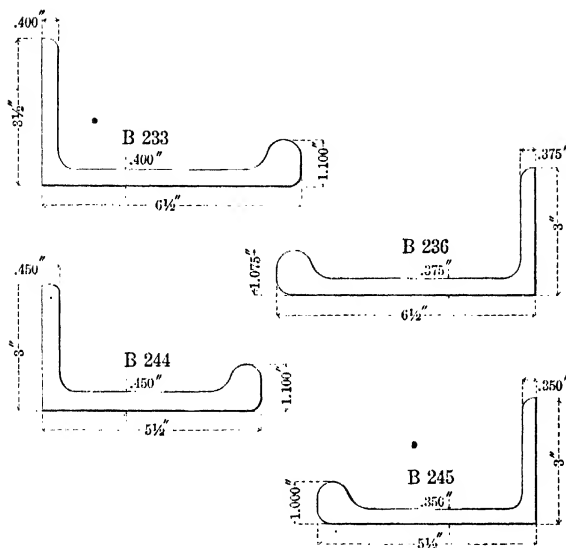


Section Index	Depth, Inches		Flange Width, Inches		Web Thickness, Inches		Weight per Foot, Pounds
	Decimal	Fractional	Decimal	Fractional	Decimal	Fractional	
*B 233	6.500	6 1/2	3.500	3 1/2	0.125	27/64	15.7
					0.400	18/32	15.0
					0.375	3/8	14.3
					0.350	11/32	13.6
*B 236	6.500	6 1/2	3.000	3	0.425	27/64	15.0
					0.400	18/32	14.3
					0.375	3/8	13.6
					0.350	11/32	12.9
*B 244	5.500	5 1/2	3.000	3	0.500	1/2	15.1
					0.475	15/32	14.5
					0.450	29/64	13.9
					0.425	27/64	13.4
*B 245	5.500	5 1/2	3.000	3	0.400	18/32	12.5
					0.375	3/8	11.9
					0.350	11/32	11.3
					0.325	21/64	10.7

\*Furnished only by special arrangement.

CARNEGIE STEEL COMPANY

SHIP BUILDING BULB ANGLES

Miscellaneous Sections

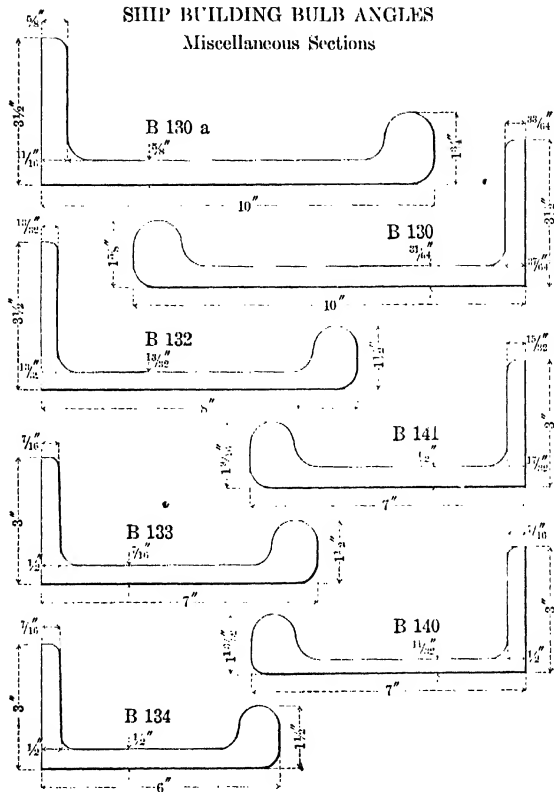


Section Index	Depth, Inches		Flange Width, Inches		Web Thickness, Inches		Weight per Foot, Pounds
	Decimal	Fractional	Decimal	Fractional	Decimal	Fractional	
*B 130a	10.000	10	3.500	3 1/2	0.625	5/8	32.0
*B 130	10.000	10	3.500	3 1/2	0.484	11/16	26.6
*B 132	8.000	8	3.500	3 1/2	0.406	13/32	19.3
*B 141	7.000	7	3.000	3	0.500	1/2	20.0
*B 133	7.000	7	3.000	3	0.438	7/16	18.3
*B 140	7.000	7	3.000	3	0.344	11/32	16.1
*B 134	6.000	6	3.000	3	0.500	1/2	17.3

\*Furnished only by special arrangement.

# BULB SECTIONS

## SHIP BUILDING BULB ANGLES

### Miscellaneous Sections




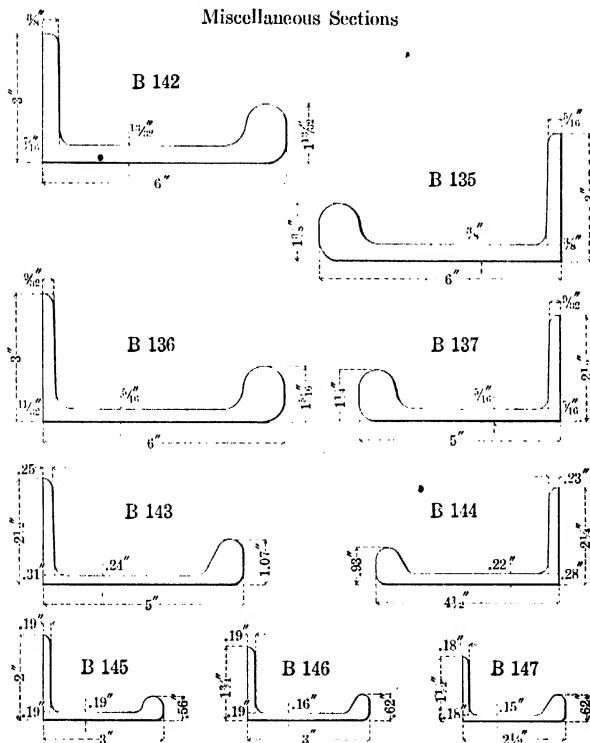


Section Index	Depth, Inches		Flange Width, Inches		Web Thickness, Inches		Weight per Foot, Pounds
	Decimal	Fractional	Decimal	Fractional	Decimal	Fractional	
*B 142	6.000	6	3.000	3	0.406	13/32	15.0
*B 135	6.000	6	3.000	3	0.375	3/8	13.8
*B 136	6.000	6	3.000	3	0.313	5/16	12.4
*B 137	5.000	5	2.500	2 1/2	0.313	5/16	10.0
*B 143	5.000	5	2.500	2 1/2	0.240	1/4	8.3
*B 144	4.500	4 1/2	2.250	2 1/4	0.220	7/32	6.7
*B 145	3.000	3	2.000	2	0.190	3/16	3.60
*B 146	3.000	3	1.750	1 3/4	0.160	5/32	3.25
*B 147	2.500	2 1/2	1.500	1 1/2	0.150	5/32	2.66

\*Furnished only by special arrangement.



**CARNEGIE STEEL COMPANY**  
**CAR BUILDING BULB ANGLES**

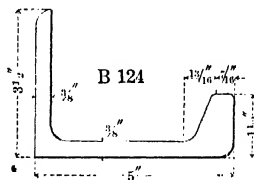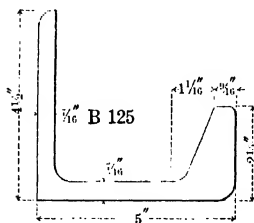


Section Index	Depth, Inches		Flange Width, Inches		Web Thickness, Inches		Weight per Foot, Pounds
	Decimal	Fractional	Decimal	Fractional	Decimal	Fractional	
*B 125	5.000	5	4.500	4 1/2	0.438	7/16	19.3
*B 124	5.000	5	3.500	3 1/2	0.375	3/8	13.2
*B 122	4.000	4	3.500	3 1/2	0.500	1/2	14.3
*B 123	4.000	4	3.500	3 1/2	0.375	3/8	11.9

\*Furnished only by special arrangement.

# CHANNELS



## STRUCTURAL CHANNELS

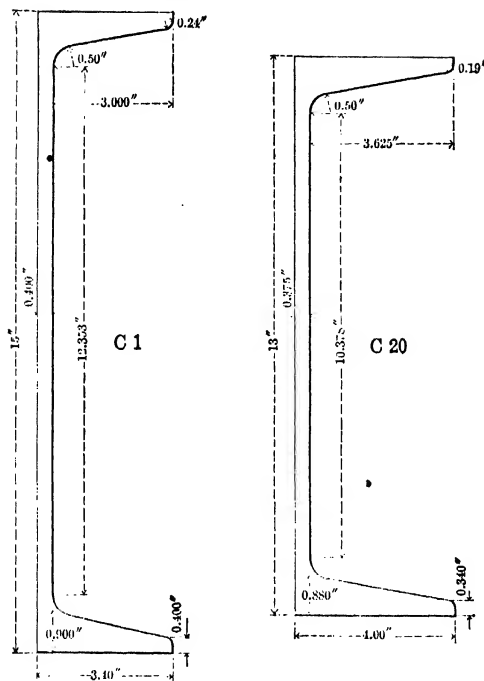

Section Index	Depth of Channel, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
C 1	15	55.0	3.818	3 1/4	0.818	13/16
		50.0	3.720	3 3/4	0.720	23/32
		45.0	3.622	3 3/8	0.622	5/8
		40.0	3.524	3 1/2	0.524	17/32
		35.0	3.426	3 1/2	0.426	27/64
		33.0	3.400	3 1/2	0.400	13/16
C 20	13	50.0	4.416	4 1/4	0.791	51/64
		45.0	4.303	4 1/4	0.678	47/64
		40.0	4.190	4 1/8	0.565	9/16
		37.0	4.122	4 1/8	0.497	15/32
		35.0	4.077	4 1/8	0.452	29/64
		32.0	4.000	4	0.375	3/8

CARNEGIE STEEL COMPANY




STRUCTURAL CHANNELS—Continued

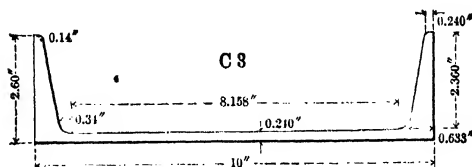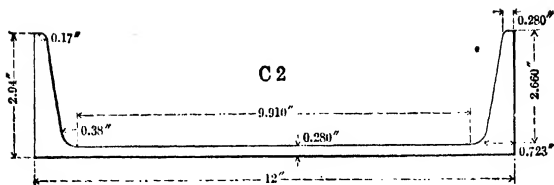

Section Index	Depth of Channel, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
C 2	12	40.0	3.418	$3\frac{11}{16}$	0.758	$\frac{11}{16}$
		35.0	3.296	$3\frac{11}{16}$	0.636	$\frac{11}{16}$
		30.0	3.173	$3\frac{11}{16}$	0.513	$\frac{11}{16}$
		25.0	3.050	$3\frac{3}{4}$	0.390	$\frac{11}{16}$
		20.5	2.940	$2\frac{1}{2}$	0.280	$\frac{3}{8}$
C 3	10	35.0	3.183	$3\frac{7}{8}$	0.823	$\frac{11}{16}$
		30.0	3.036	$3\frac{1}{2}$	0.676	$\frac{11}{16}$
		25.0	2.889	$2\frac{7}{8}$	0.529	$\frac{11}{16}$
		20.0	2.742	$2\frac{1}{2}$	0.382	$\frac{9}{16}$
		15.0	2.600	$2\frac{1}{8}$	0.240	$\frac{1}{4}$

# CHANNELS





## STRUCTURAL CHANNELS—Continued

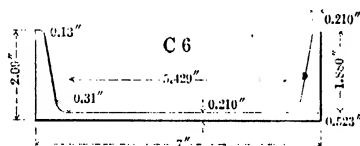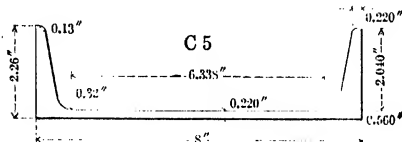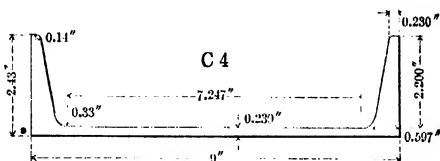

Section Index	Depth of Channel, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
C 4	9	25.0	2.815	$2\frac{1}{8}$	0.615	$\frac{3}{8}$
		20.0	2.652	$2\frac{1}{2}$	0.452	$\frac{3}{8}$
		15.0	2.488	$2\frac{1}{4}$	0.288	$\frac{3}{8}$
		13.25	2.430	$2\frac{1}{8}$	0.230	$\frac{1}{4}$
C 5	8	21.25	2.622	$2\frac{5}{8}$	0.582	$\frac{3}{8}$
		18.75	2.530	$2\frac{1}{2}$	0.490	$\frac{3}{8}$
		16.25	2.430	$2\frac{1}{8}$	0.390	$\frac{3}{8}$
		13.75	2.347	$2\frac{1}{4}$	0.307	$\frac{3}{8}$
		11.25	2.260	$2\frac{1}{4}$	0.220	$\frac{3}{8}$
C 6	7	19.75	2.513	$2\frac{1}{4}$	0.633	$\frac{1}{2}$
		17.25	2.408	$2\frac{1}{4}$	0.528	$\frac{1}{2}$
		14.75	2.303	$2\frac{1}{4}$	0.423	$\frac{1}{2}$
		12.25	2.198	$2\frac{1}{4}$	0.318	$\frac{1}{2}$
		9.75	2.090	$2\frac{1}{4}$	0.210	$\frac{1}{2}$

# CARNEGIE STEEL COMPANY


## STRUCTURAL CHANNELS—Concluded

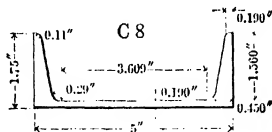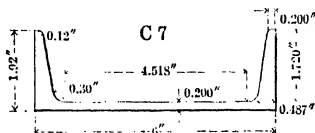

Section Index	Depth of Channel, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
C 7	6	15.5	2.283	$2\frac{1}{8}$	0.563	$\frac{9}{16}$
		13.0	2.160	$2\frac{1}{4}$	0.440	$\frac{7}{16}$
		10.5	2.038	$2\frac{1}{8}$	0.318	$\frac{1}{4}$
		8.0	1.920	$1\frac{3}{4}$	0.200	$\frac{1}{4}$
C 8	5	11.5	2.037	$2\frac{1}{8}$	0.477	$\frac{3}{4}$
		9.0	1.890	$1\frac{7}{8}$	0.330	$\frac{1}{2}$
		6.5	1.750	$1\frac{3}{4}$	0.190	$\frac{1}{8}$
C 9	4	7.25	1.725	$1\frac{3}{4}$	0.325	$\frac{1}{2}$
		6.25	1.652	$1\frac{3}{4}$	0.252	$\frac{1}{4}$
		5.25	1.580	$1\frac{3}{4}$	0.180	$\frac{1}{8}$
C 72	3	6.0	1.602	$1\frac{3}{4}$	0.362	$\frac{3}{4}$
		5.0	1.504	$1\frac{3}{4}$	0.264	$\frac{1}{2}$
		4.0	1.410	$1\frac{3}{4}$	0.170	$\frac{1}{4}$

# CHANNELS




## SHIP BUILDING CHANNELS

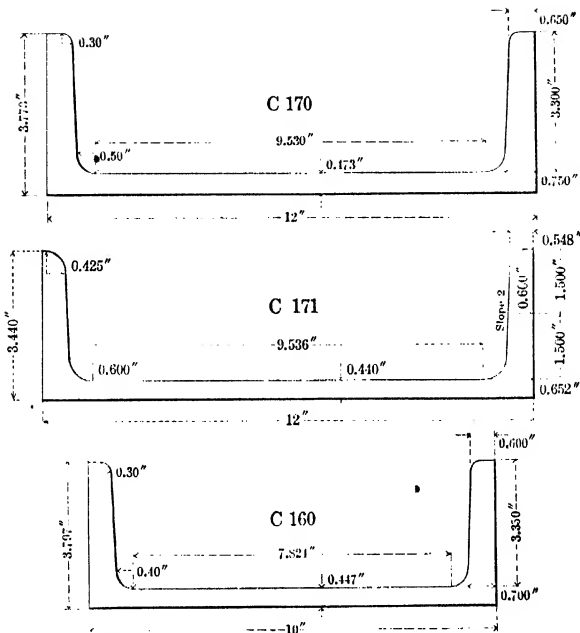

Section Index	Depth of Channel, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
C 170	12	50.0	4.140	4 <sup>9</sup> / <sub>64</sub>	0.810	27 <sup>3</sup> / <sub>32</sub>
		48.4	4.100	4 <sup>9</sup> / <sub>32</sub>	0.800	27 <sup>1</sup> / <sub>16</sub>
		46.3	4.050	4 <sup>3</sup> / <sub>64</sub>	0.750	24
		44.3	4.000	4	0.700	21 <sup>1</sup> / <sub>16</sub>
		40.0	3.895	3 <sup>57</sup> / <sub>64</sub>	0.595	19 <sup>3</sup> / <sub>32</sub>
		35.0	3.773	3 <sup>49</sup> / <sub>64</sub>	0.473	15 <sup>1</sup> / <sub>16</sub>
C 171	12	40.8	3.700	3 <sup>15</sup> / <sub>64</sub>	0.700	22 <sup>1</sup> / <sub>16</sub>
		37.2	3.610	3 <sup>39</sup> / <sub>64</sub>	0.610	19 <sup>1</sup> / <sub>16</sub>
		32.7	3.500	3 <sup>1</sup> / <sub>2</sub>	0.500	16
		30.2	3.440	3 <sup>3</sup> / <sub>8</sub>	0.440	14 <sup>1</sup> / <sub>16</sub>
C 160	10	40.0	4.091	4 <sup>3</sup> / <sub>32</sub>	0.741	24 <sup>1</sup> / <sub>16</sub>
		36.9	4.000	4	0.650	21 <sup>1</sup> / <sub>16</sub>
		34.4	3.925	3 <sup>59</sup> / <sub>64</sub>	0.575	18 <sup>5</sup> / <sub>16</sub>
		31.8	3.850	3 <sup>27</sup> / <sub>32</sub>	0.500	16
		30.0	3.797	3 <sup>5</sup> / <sub>16</sub>	0.447	14 <sup>9</sup> / <sub>16</sub>

CARNEGIE STEEL COMPANY




SHIP BUILDING CHANNELS--Continued

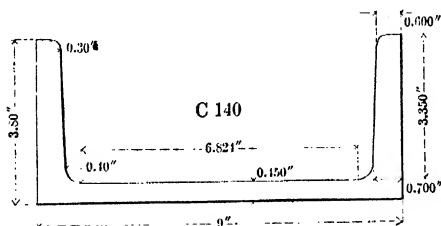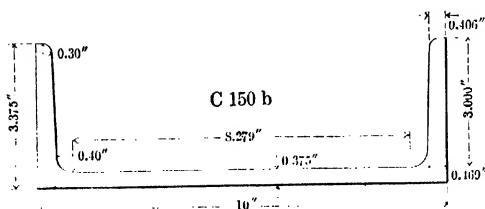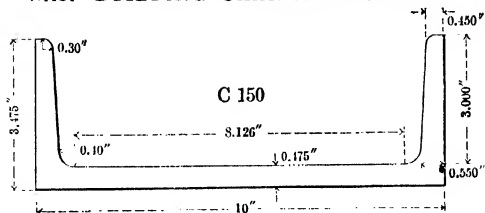

Section Index	Depth of Channel, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
C 150	10	33.2	3.675	3 11/16	0.675	11/16
		30.6	3.600	3 11/16	0.600	19/32
		28.9	3.550	3 35/64	0.550	35/64
		27.2	3.500	3 1/2	0.500	1/2
		26.4	3.475	3 13/32	0.475	15/32
C 150b	10	28.5	3.575	3 37/64	0.575	37/64
		26.0	3.500	3 1/2	0.500	1/2
		24.3	3.450	3 29/64	0.450	29/64
		22.6	3.400	3 13/32	0.400	13/32
		21.7	3.375	3 3/8	0.375	3/8
C 140	9	35.5	4.025	4 1/8	0.675	11/16
		34.7	4.000	4	0.650	21/32
		34.7	3.900	3 29/32	0.550	35/64
		28.6	3.800	3 51/64	0.450	29/64

# CHANNELS

## SHIP BUILDING CHANNELS—Continued

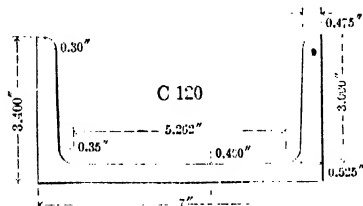
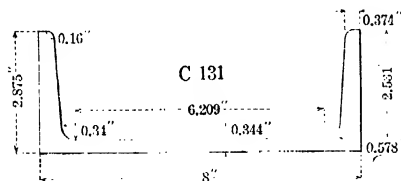
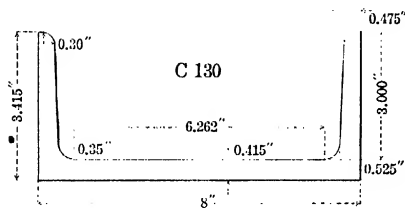


Section Index	Depth of Channel, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
C 130	8	27.2	3.625	$3\frac{1}{8}$	0.625	$\frac{5}{8}$
		26.5	3.600	$3\frac{19}{32}$	0.600	$\frac{39}{64}$
		25.2	3.550	$3\frac{37}{64}$	0.550	$\frac{35}{64}$
		23.8	3.500	$3\frac{1}{2}$	0.500	$\frac{1}{2}$
		21.5	3.415	$3\frac{27}{64}$	0.415	$\frac{27}{64}$
C 131	8	21.0	3.000	3	0.469	$\frac{15}{32}$
		17.6	2.875	$2\frac{7}{8}$	0.344	$\frac{11}{32}$
		24.5	3.600	$3\frac{19}{32}$	0.600	$\frac{19}{32}$
C 120	7	23.3	3.550	$3\frac{35}{64}$	0.550	$\frac{35}{64}$
		22.1	3.500	$3\frac{1}{2}$	0.500	$\frac{1}{2}$
		20.9	3.450	$3\frac{29}{64}$	0.450	$\frac{29}{64}$
		19.7	3.400	$3\frac{13}{32}$	0.400	$\frac{13}{32}$



CARNEGIE STEEL COMPANY



SHIP BUILDING CHANNELS—Continued

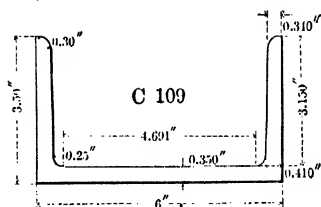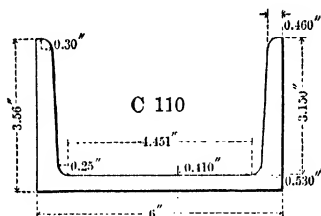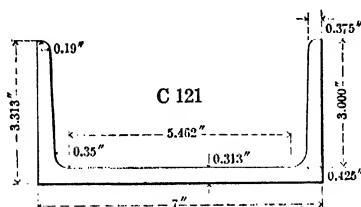





Section Index	Depth of Channel, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
C 121	7	21.9	3.575	$3\frac{37}{64}$	0.575	$\frac{37}{64}$
		18.6	3.438	$3\frac{7}{16}$	0.438	$\frac{7}{16}$
		16.5	3.350	$3\frac{11}{32}$	0.350	$\frac{11}{32}$
		15.6	3.313	$3\frac{5}{16}$	0.313	$\frac{5}{16}$
C 110	6	21.5	3.685	$3\frac{11}{16}$	0.535	$\frac{17}{32}$
		19.0	3.560	$3\frac{9}{16}$	0.410	$\frac{13}{32}$
C 109	6	15.0	3.500	$3\frac{1}{2}$	0.350	$\frac{11}{32}$

# CHANNELS

## SHIP BUILDING CHANNELS—Concluded

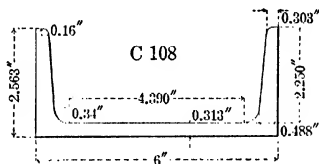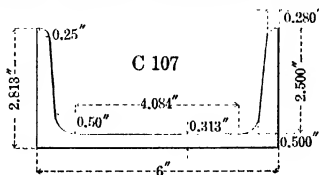

## CAR CHANNELS—STRUCTURAL SIZES

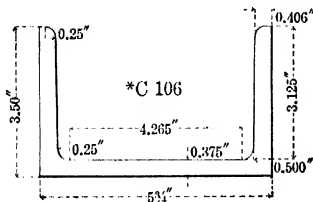


Section Index	Depth of Channel, Inches	Weight per Foot, Pounds	Flange Width, Inches		Web Thickness, Inches	
			Decimal	Fractional	Decimal	Fractional
C 107	6	18.1	3.063	31/16	0.563	9/16
		13.0	2.813	273/16	0.313	5/16
C 108	6	17.0	2.781	225/32	0.531	17/32
		12.5	2.563	259/16	0.313	5/16
*C 106	5 3/4	17.0	3.500	3 1/2	0.375	3/8
*C 200	4	13.6	2.500	2 1/2	0.500	1/2
*C 220	4	10.1	2.087	23/16	0.394	25/64
*C 190	3	7.1	1.984	153/64	0.250	1/4

\* Furnished only by special arrangement.

# CARNEGIE STEEL COMPANY

## EQUAL ANGLES

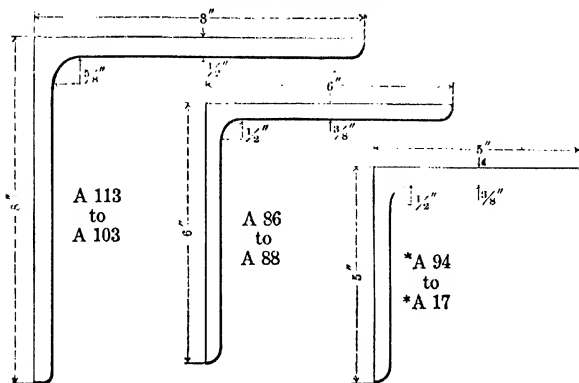


Section Index	Size, Inches	Thickness, Inches	Weight per Foot, Pounds
A 113	8 x 8	1 1/2	56.9
A 112	8 x 8	1 1/16	54.0
A 111	8 x 8	1	51.0
A 110	8 x 8	3/4	48.1
A 109	8 x 8	7/8	45.0
A 108	8 x 8	13/16	42.0
A 107	8 x 8	1 1/8	38.9
A 106	8 x 8	1 1/16	35.8
A 105	8 x 8	5/8	32.7
A 104	8 x 8	11/16	29.6
A 103	8 x 8	1 1/2	26.4
A 86	6 x 6	1	37.4
A 87	6 x 6	1 1/16	35.3
A 1	6 x 6	1 1/8	33.1
A 2	6 x 6	3/4	31.0
A 3	6 x 6	7/8	28.7
A 4	6 x 6	1 1/8	26.5
A 5	6 x 6	5/8	24.2
A 6	6 x 6	1 1/16	21.9
A 7	6 x 6	1 1/8	19.6
A 8	6 x 6	1 1/2	17.2
A 88	6 x 6	3/4	14.0
*A 94	5 x 5	1	30.6
*A 95	5 x 5	1 1/16	28.9
*A 9	5 x 5	3/4	27.2
*A 10	5 x 5	7/8	25.4
*A 11	5 x 5	1 1/8	23.6
*A 12	5 x 5	1 1/16	21.8
*A 13	5 x 5	5/8	20.0
*A 14	5 x 5	1 1/8	18.1
*A 15	5 x 5	1 1/16	16.2
*A 16	5 x 5	3/4	14.3
*A 17	5 x 5	1 1/2	12.3

\*Special, see page 55.

# ANGLES

## EQUAL ANGLES—Continued





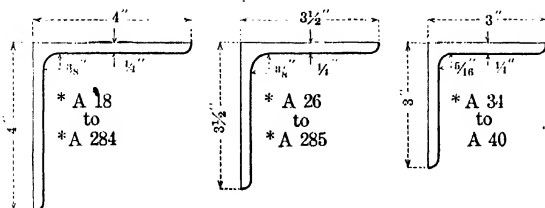


Section Index	Size, Inches	Thickness, Inches	Weight per Foot, Pounds
*A 18	4 x 4	1/4	19.9
A 19	4 x 4	3/4	18.5
A 20	4 x 4	1 1/4	17.1
A 21	4 x 4	5/8	15.7
A 22	4 x 4	3/8	14.3
A 23	4 x 4	1/2	12.8
A 24	4 x 4	7/16	11.3
A 25	4 x 4	3/8	9.8
A 30	4 x 4	5/16	8.2
*A 284	4 x 4	1/4	6.6
*A 26	3 1/2 x 3 1/2	1/4	17.1
*A 27	3 1/2 x 3 1/2	3/4	16.0
*A 28	3 1/2 x 3 1/2	1 1/4	14.8
A 29	3 1/2 x 3 1/2	5/8	13.6
A 30	3 1/2 x 3 1/2	3/8	12.4
A 31	3 1/2 x 3 1/2	1/2	11.1
A 32	3 1/2 x 3 1/2	7/16	9.8
A 33	3 1/2 x 3 1/2	3/8	8.5
A 39	3 1/2 x 3 1/2	5/16	7.2
*A 285	3 1/2 x 3 1/2	1/4	5.8
*A 34	3 x 3	5/8	11.5
*A 35	3 x 3	3/4	10.4
A 36	3 x 3	1 1/2	9.4
A 37	3 x 3	7/8	8.3
A 38	3 x 3	3/4	7.2
A 39	3 x 3	5/8	6.1
A 40	3 x 3	1/4	4.9

\* Special, see page 55.

# CARNEGIE STEEL COMPANY

## EQUAL ANGLES—Concluded




Section Index	Size, Inches	Thickness, Inches	Weight per Foot, Pounds
*A 46	2 1/2 x 2 1/2	1/2	7.7
A 47	2 1/2 x 2 1/2	5/8	6.8
A 48	2 1/2 x 2 1/2	3/4	5.9
A 49	2 1/2 x 2 1/2	7/8	5.0
A 50	2 1/2 x 2 1/2	1	4.1
A 100	2 1/2 x 2 1/2	5/8	3.07
*A 504	2 1/2 x 2 1/2	3/8	2.08
*A 56	2 x 2	7/8	5.3
A 57	2 x 2	3/4	4.7
A 58	2 x 2	5/8	3.92
A 59	2 x 2	1/2	3.19
A 60	2 x 2	3/8	2.44
*A 506	2 x 2	1/4	1.65
*A 61	1 3/4 x 1 3/4	7/8	4.6
*A 62	1 3/4 x 1 3/4	3/4	3.99
*A 63	1 3/4 x 1 3/4	5/8	3.39
*A 64	1 3/4 x 1 3/4	1/2	2.77
*A 65	1 3/4 x 1 3/4	3/8	2.12
*A 507	1 3/4 x 1 3/4	1/4	1.44
*A 66	1 1/2 x 1 1/2	3/4	3.35
A 67	1 1/2 x 1 1/2	5/8	2.86
A 68	1 1/2 x 1 1/2	1/2	2.34
A 69	1 1/2 x 1 1/2	3/8	1.80
A 102	1 1/2 x 1 1/2	1/4	1.23
*A 70	1 1/4 x 1 1/4	5/8	2.33
*A 71	1 1/4 x 1 1/4	3/4	1.92
*A 72	1 1/4 x 1 1/4	5/8	1.48
*A 73	1 1/4 x 1 1/4	3/8	1.01
*A 78	1 x 1	1/2	1.49
*A 79	1 x 1	3/8	1.16
*A 80	1 x 1	1/4	0.80

\* Special, see page 55.

# ANGLES

## UNEQUAL ANGLES

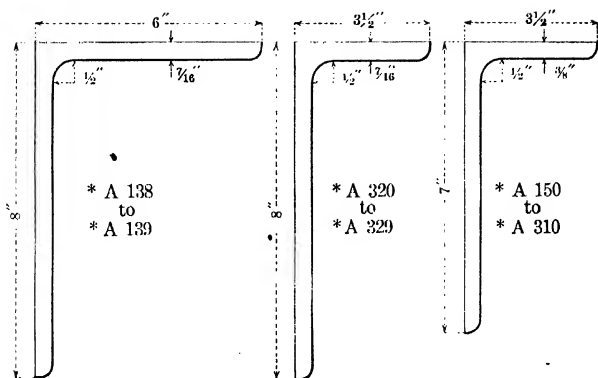


Section Index	Size, Inches	Thickness, Inches	Weight per Foot, Pounds
*A 138	8 x 6	1	44.2
*A 137	8 x 6	1 1/8	41.7
*A 136	8 x 6	1 1/4	39.1
*A 135	8 x 6	1 3/8	36.5
*A 134	8 x 6	1 1/2	33.8
*A 133	8 x 6	1 5/8	31.2
*A 132	8 x 6	1 3/4	28.5
*A 131	8 x 6	1 7/8	25.7
*A 130	8 x 6	2	23.0
*A 139	8 x 6	1 1/8	20.2
*A 320	8 x 3 1/2	1	35.7
*A 321	8 x 3 1/2	1 1/8	33.7
*A 322	8 x 3 1/2	1 1/4	31.7
*A 323	8 x 3 1/2	1 3/8	29.6
*A 324	8 x 3 1/2	1 1/2	27.5
*A 325	8 x 3 1/2	1 5/8	25.3
*A 326	8 x 3 1/2	1 3/4	23.2
*A 327	8 x 3 1/2	1 7/8	21.0
*A 328	8 x 3 1/2	2	18.7
*A 329	8 x 3 1/2	1 1/8	16.5
*A 150	7 x 3 1/2	1	32.3
*A 151	7 x 3 1/2	1 1/8	30.5
*A 152	7 x 3 1/2	1 1/4	28.7
*A 153	7 x 3 1/2	1 3/8	26.8
*A 154	7 x 3 1/2	1 1/2	24.9
*A 155	7 x 3 1/2	1 5/8	23.0
*A 156	7 x 3 1/2	1 3/4	21.0
*A 157	7 x 3 1/2	1 7/8	19.1
*A 158	7 x 3 1/2	2	17.0
*A 159	7 x 3 1/2	1 1/8	15.0
*A 310	7 x 3 1/2	1 1/4	13.0

\* Special, see page 55.

CARNEGIE STEEL COMPANY

UNEQUAL ANGLES—Continued

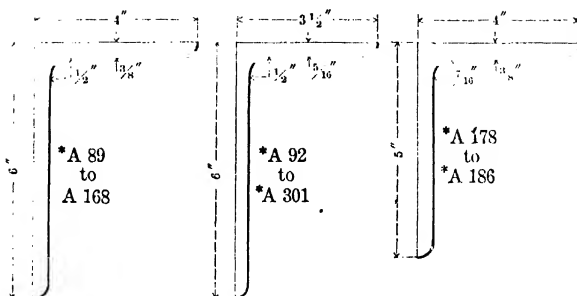


Section Index	Size, Inches	Thickness, Inches	Weight per Foot, Pounds
*A 89	6 x 4	1	30.6
*A 91	6 x 4	1/8	28.9
A 160	6 x 4	1/8	27.2
A 161	6 x 4	1/8	25.4
A 162	6 x 4	1/8	23.6
A 163	6 x 4	1/8	21.8
A 164	6 x 4	1/8	20.0
A 165	6 x 4	1/8	18.1
A 166	6 x 4	1/8	16.2
A 167	6 x 4	1/8	14.3
A 168	6 x 4	1/8	12.3
*A 92	6 x 3 1/2	1	28.9
*A 93	6 x 3 1/2	1/8	27.3
A 169	6 x 3 1/2	1/8	25.7
A 170	6 x 3 1/2	1/8	24.0
A 171	6 x 3 1/2	1/8	22.4
A 172	6 x 3 1/2	1/8	20.6
A 173	6 x 3 1/2	1/8	18.9
A 174	6 x 3 1/2	1/8	17.1
A 175	6 x 3 1/2	1/8	15.3
A 176	6 x 3 1/2	1/8	13.5
A 177	6 x 3 1/2	1/8	11.7
*A 301	6 x 3 1/2	1/8	9.8
*A 178	5 x 4	3/8	24.2
*A 179	5 x 4	1/4	22.7
*A 180	5 x 4	1/4	21.1
*A 181	5 x 4	1/4	19.5
*A 182	5 x 4	1/4	17.8
*A 183	5 x 4	1/4	16.2
*A 184	5 x 4	1/4	14.5
*A 185	5 x 4	1/4	12.8
*A 186	5 x 4	1/4	11.0

\* Special, see page 55.

# ANGLES

## UNEQUAL ANGLES—Continued

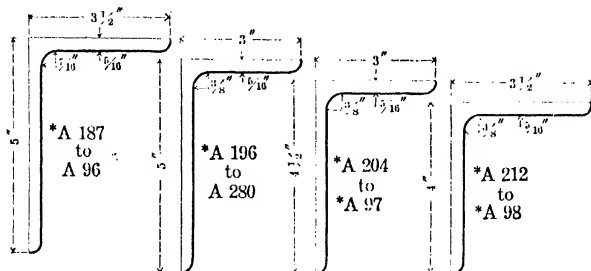


Section Index	Size, Inches	Thickness, Inches	Weight per Foot, Pounds
*A 187	5 x 3 1/2	7/8	22.7
*A 188	5 x 3 1/2	1 1/4	21.3
A 189	5 x 3 1/2	3/4	19.8
A 190	5 x 3 1/2	1 1/4	18.3
A 191	5 x 3 1/2	3/8	16.8
A 192	5 x 3 1/2	1 1/4	15.2
A 193	5 x 3 1/2	1 1/2	13.6
A 194	5 x 3 1/2	1 1/4	12.0
A 195	5 x 3 1/2	3/8	10.4
A 96	5 x 3 1/2	1 1/4	8.7
*A 196	5 x 3	1 1/4	19.9
*A 197	5 x 3	3/4	18.5
A 198	5 x 3	1 1/4	17.1
A 199	5 x 3	3/8	15.7
A 200	5 x 3	1 1/4	14.3
A 201	5 x 3	1 1/2	12.8
A 202	5 x 3	1 1/4	11.3
A 203	5 x 3	3/8	9.8
A 280	5 x 3	1 1/4	8.2
*A 204	4 1/2 x 3	1 1/4	18.5
*A 205	4 1/2 x 3	3/4	17.3
*A 206	4 1/2 x 3	1 1/4	16.0
*A 207	4 1/2 x 3	3/8	14.7
*A 208	4 1/2 x 3	1 1/4	13.3
*A 209	4 1/2 x 3	1 1/2	11.9
*A 210	4 1/2 x 3	1 1/4	10.6
*A 211	4 1/2 x 3	3/8	9.1
*A 97	4 1/2 x 3	1 1/4	7.7
*A 212	4 x 3 1/2	1 1/4	18.5
*A 213	4 x 3 1/2	3/4	17.3
*A 214	4 x 3 1/2	1 1/4	16.0
*A 215	4 x 3 1/2	3/8	14.7
*A 216	4 x 3 1/2	1 1/4	13.3
*A 217	4 x 3 1/2	1 1/2	11.9
*A 218	4 x 3 1/2	1 1/4	10.6
*A 219	4 x 3 1/2	3/8	9.1
*A 98	4 x 3 1/2	1 1/4	7.7

\*Special, see page 55.



# CARNEGIE STEEL COMPANY

## UNEQUAL ANGLES—Continued

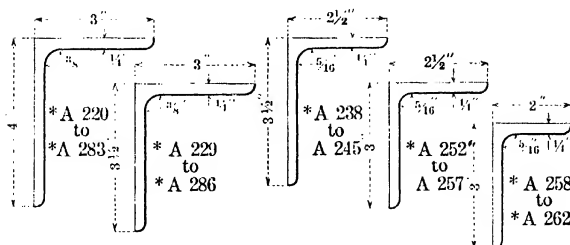


Section Index	Size, Inches	Thickness Inches	Weight per Foot, Pounds
*A 220	4 x 3	13/16	17.1
*A 221	4 x 3	13/16	16.0
*A 222	4 x 3	13/16	14.8
A 223	4 x 3	13/16	13.6
A 224	4 x 3	13/16	12.4
A 225	4 x 3	13/16	11.1
A 226	4 x 3	13/16	9.8
A 227	4 x 3	13/16	8.5
A 228	4 x 3	13/16	7.2
*A 283	4 x 3	13/16	5.8
*A 229	3 1/2 x 3	13/16	15.8
*A 230	3 1/2 x 3	13/16	14.7
*A 231	3 1/2 x 3	13/16	13.6
*A 232	3 1/2 x 3	13/16	12.5
A 233	3 1/2 x 3	13/16	11.4
A 234	3 1/2 x 3	13/16	10.2
A 235	3 1/2 x 3	13/16	9.1
A 236	3 1/2 x 3	13/16	7.9
A 237	3 1/2 x 3	13/16	6.6
*A 286	3 1/2 x 3	13/16	5.4
*A 238	3 1/2 x 2 1/2	13/16	12.5
*A 239	3 1/2 x 2 1/2	13/16	11.5
*A 240	3 1/2 x 2 1/2	13/16	10.4
A 241	3 1/2 x 2 1/2	13/16	9.4
A 242	3 1/2 x 2 1/2	13/16	8.3
A 243	3 1/2 x 2 1/2	13/16	7.2
A 244	3 1/2 x 2 1/2	13/16	6.1
A 245	3 1/2 x 2 1/2	13/16	4.9
*A 252	3 x 2 1/2	13/16	9.5
*A 253	3 x 2 1/2	13/16	8.5
A 254	3 x 2 1/2	13/16	7.6
A 255	3 x 2 1/2	13/16	6.6
A 256	3 x 2 1/2	13/16	5.6
A 257	3 x 2 1/2	13/16	4.5
*A 258	3 x 2	13/16	7.7
*A 259	3 x 2	13/16	6.8
*A 260	3 x 2	13/16	5.9
*A 261	3 x 2	13/16	5.0
*A 262	3 x 2	13/16	4.1

\*Special, see page 56.

# ANGLES

## UNEQUAL ANGLES—Concluded

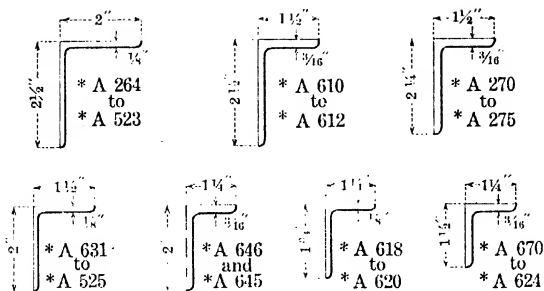


Section Index	Size, Inches	Thickness, Inches	Weight per Foot, Pounds
*A 264	2 1/2 x 2	1/2	6.8
*A 265	2 1/2 x 2	5/8	6.1
A 266	2 1/2 x 2	3/8	5.3
A 267	2 1/2 x 2	1/4	4.5
A 268	2 1/2 x 2	1/4	3.62
A 269	2 1/2 x 2	3/16	2.75
*A 523	2 1/2 x 2	1/8	1.86
*A 610	2 1/2 x 1 1/2	1/2	3.92
*A 611	2 1/2 x 1 1/2	5/8	3.19
*A 612	2 1/2 x 1 1/2	3/8	2.44
*A 270	2 1/2 x 1 1/2	1/2	5.6
*A 271	2 1/2 x 1 1/2	5/8	5.0
*A 272	2 1/2 x 1 1/2	3/8	4.4
*A 273	2 1/2 x 1 1/2	1/4	3.66
*A 274	2 1/2 x 1 1/2	1/4	2.98
*A 275	2 1/2 x 1 1/2	3/16	2.28
*A 631	2 x 1 1/2	3/8	3.99
*A 614	2 x 1 1/2	1/4	3.39
*A 615	2 x 1 1/2	1/4	2.77
*A 616	2 x 1 1/2	1/8	2.12
*A 525	2 x 1 1/2	3/16	1.44
*A 646	2 x 1 1/4	1/4	2.55
*A 645	2 x 1 1/4	1/8	1.96
*A 618	1 3/4 x 1 1/4	1/4	2.34
*A 619	1 3/4 x 1 1/4	1/8	1.80
*A 620	1 3/4 x 1 1/4	3/16	1.23
*A 670	1 1/2 x 1 1/4	1/4	2.59
*A 623	1 1/2 x 1 1/4	1/8	2.13
*A 624	1 1/2 x 1 1/4	3/16	1.64

\* Special, see page 55.

# CARNEGIE STEEL COMPANY


## EQUAL TEES

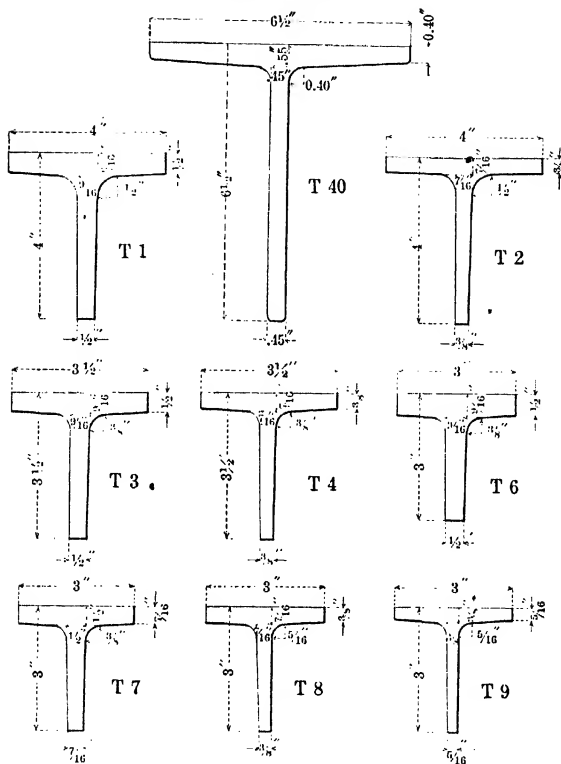

Section Index	Size, Inches		Thickness, Inches		Weight per Foot, Pounds
	Flange	Stem	Flange	Stem	
T 40	6 1/2	6 1/2	0.40 to 0.55	0.45	19.8
T 1	4	4	1/2 to 5/16	1/2 to 5/16	13.5
T 2	4	4	3/8 to 1/2	3/8 to 1/2	10.5
T 3	3 1/2	3 1/2	1/2 to 5/16	1/2 to 5/16	11.7
T 4	3 1/2	3 1/2	3/8 to 1/2	3/8 to 1/2	9.2
T 6	3	3	1/2 to 5/16	1/2 to 5/16	9.9
T 7	3	3	1/2 to 1/2	1/2 to 1/2	8.9
T 8	3	3	3/8 to 1/2	3/8 to 1/2	7.8
T 9	3	3	5/16 to 3/8	5/16 to 3/8	6.7

# TEES






## EQUAL TEES—Concluded

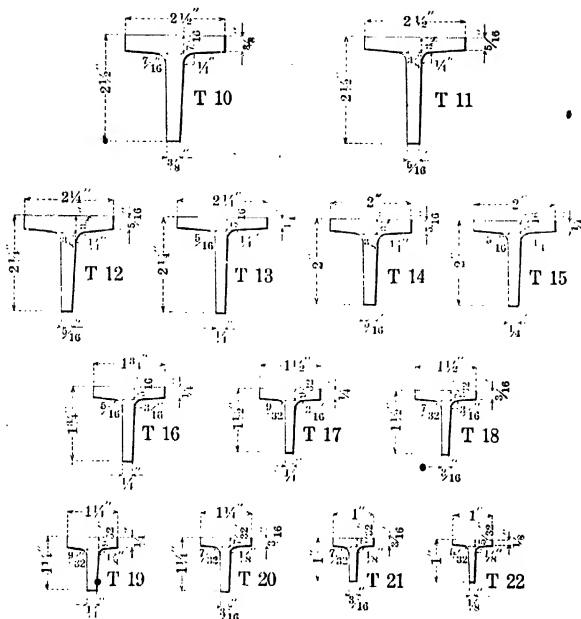

Section Index	Size, Inches		Thickness, Inches		Weight per Foot, Pounds
	Flange	Stem	Flange	Stem	
T 10	2½	2½	⅜ to ⅞	⅜ to ⅞	6.4
T 11	2¼	2¼	⅞ to ⅝	⅞ to ⅝	5.5
T 12	2¼	2¼	⅞ to ⅝	⅞ to ⅝	4.9
T 13	2¼	2¼	⅞ to ⅝	⅞ to ⅝	4.1
T 14	2	2	⅞ to ⅝	⅞ to ⅝	4.3
T 15	2	2	⅞ to ⅝	⅞ to ⅝	3.56
T 16	1¾	1¾	⅞ to ⅝	⅞ to ⅝	3.09
T 17	1¾	1¾	⅞ to ⅝	⅞ to ⅝	2.47
T 18	1½	1½	⅞ to ⅝	⅞ to ⅝	1.94
T 19	1¾	1¾	⅞ to ⅝	⅞ to ⅝	2.02
T 20	1¾	1¾	⅞ to ⅝	⅞ to ⅝	1.59
T 21	1	1	⅞ to ⅝	⅞ to ⅝	1.25
T 22	1	1	⅞ to ⅝	⅞ to ⅝	0.89

CARNEGIE STEEL COMPANY


UNEQUAL TEES




Section Index	Size, Inches		Thickness, Inches		Weight per Foot, Pounds
	Flange	Stem	Flange	Stem	
T 50	5	3	1/2 to 7/8	1 1/2 to 3/4	13.4
T 51	5	2 1/4	3/8 to 7/8	1/4 to 1 1/4	10.9
T 52	4 1/2	3 1/4	7/8 to 1 1/8	1 1/4 to 3/4	15.7
T 54	4 1/2	3	3/8 to 7/8	3/8 to 7/8	9.8
T 53	4 1/2	3	7/8 to 3/4	1/4 to 3/4	8.4

# TEES


## UNEQUAL TEES—Continued




T 56




T 55

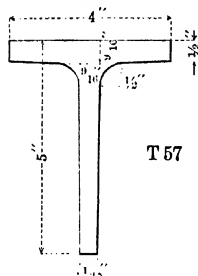


T 57

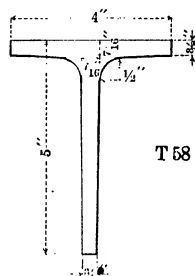

T 58

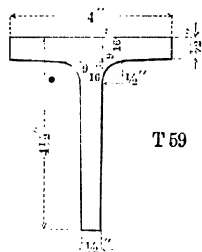

T 59








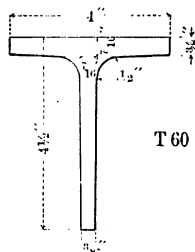


T 60

Section Index	Size, Inches		Thickness, Inches		Weight per Foot, Pounds
	Flange	Stem	Flange	Stem	
T 56	4 1/2	2 1/2	3/8 to 7/16	3/8 to 7/16	9.2
T 55	4 1/2	2 1/2	7/16 to 3/8	7/16 to 3/8	7.8
T 57	4	5	1/2 to 5/8	1/2 to 5/8	15.3
T 58	4	5	3/8 to 7/16	3/8 to 7/16	11.9
T 59	4	4 1/2	1/2 to 7/16	1/2 to 7/16	14.4
T 60	4	4 1/2	3/8 to 7/16	3/8 to 7/16	11.2

# CARNEGIE STEEL COMPANY


## UNEQUAL TEES—Continued



Section Index	Size, Inches		Thickness, Inches		Weight per Foot, Pounds
	Flange	Stem	Flange	Stem	
T 61	4	3	3/8 to 7/8	3/8 to 7/8	9.2
T 44	4	3	7/8 to 3/4	7/8 to 3/4	7.8
T 62	4	2 1/2	3/8 to 7/8	3/8 to 7/8	8.5
T 63	4	2 1/2	7/8 to 3/8	7/8 to 3/8	7.2
T 64	4	2	3/8 to 7/8	3/8 to 7/8	7.8
T 65	4	2	7/8 to 3/8	7/8 to 3/8	6.7
T 66	3 1/2	4	1/2 to 7/8	1/2 to 7/8	12.6
T 67	3 1/2	4	3/8 to 7/8	3/8 to 7/8	9.8

# TEES

## UNEQUAL TEES—Continued









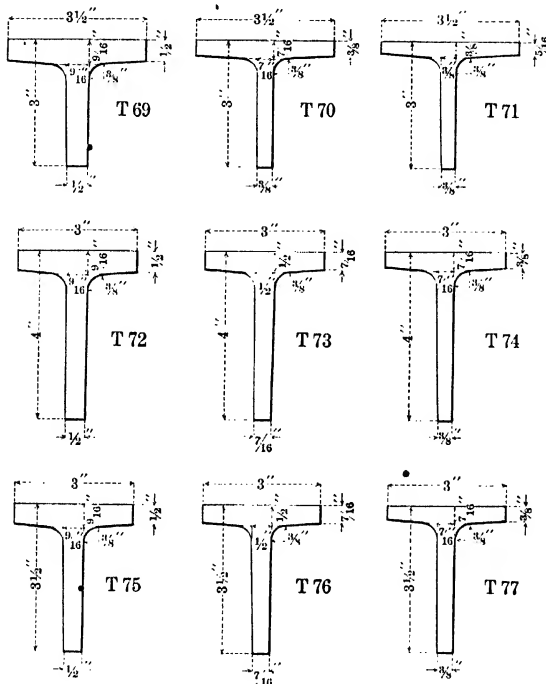


Section Index	Size, Inches		Thickness, Inches		Weight per Foot, Pounds
	Flange	Stem	Flange	Stem	
T 69	$3\frac{1}{2}$	3	$\frac{1}{2}$ to $\frac{1}{16}$	$\frac{1}{2}$ to $\frac{1}{16}$	10.8
T 70	$3\frac{1}{2}$	3	$\frac{3}{8}$ to $\frac{1}{16}$	$\frac{3}{8}$ to $\frac{1}{16}$	8.5
T 71	$3\frac{1}{2}$	3	$\frac{1}{16}$ to $\frac{3}{8}$	$\frac{3}{8}$	7.5
T 72	3	4	$\frac{1}{2}$ to $\frac{1}{16}$	$\frac{1}{2}$ to $\frac{1}{16}$	11.7
T 73	3	4	$\frac{1}{16}$ to $\frac{1}{2}$	$\frac{1}{16}$ to $\frac{1}{2}$	10.5
T 74	3	4	$\frac{3}{8}$ to $\frac{1}{16}$	$\frac{3}{8}$ to $\frac{1}{16}$	9.2
T 75	3	$3\frac{1}{2}$	$\frac{1}{2}$ to $\frac{1}{16}$	$\frac{1}{2}$ to $\frac{1}{16}$	10.8
T 76	3	$3\frac{1}{2}$	$\frac{1}{16}$ to $\frac{1}{2}$	$\frac{1}{16}$ to $\frac{1}{2}$	9.7
T 77	3	$3\frac{1}{2}$	$\frac{3}{8}$ to $\frac{1}{16}$	$\frac{3}{8}$ to $\frac{1}{16}$	8.5



# CARNEGIE STEEL COMPANY

## UNEQUAL TEES—Concluded




Section Index	Size, Inches		Thickness, Inches		Weight per Foot, Pounds
	Flange	Stem	Flange	Stem	
T 78	3	2 1/2	3/8 to 1/2	3/8 to 1/2	7.1
T 79	3	2 1/2	3/8 to 3/4	3/8 to 3/4	6.1
T 82	2 1/2	2	3/8 to 1/2	3/8 to 1/2	7.1
T 83	2 1/2	2	3/8 to 3/4	3/8 to 3/4	6.1
T 86	2 1/2	1 1/4	3/8 to 1/2	3/8 to 1/2	2.87
T 87	2	1 1/2	3/8 to 1/2	3/8 to 1/2	3.09
T 519	1 1/2	2	3/8 to 1/2	3/8 to 1/2	2.45
T 605	1 1/2	1 1/4	3/8 to 1/2	3/8 to 1/2	1.25
*T 603	1 1/4	3/8	No. 9	3/8 to No. 7	0.88

\* Furnished only by special arrangement.


# TEES

## MISCELLANEOUS TEES


\* T 154




\* T 156



\* T 157



\* T 158




Section Index	Size, Inches		Thickness, Inches		Weight per Foot, Pounds
	Flange	Stem	Flange	Stem	
*T 154	4 1/2	1 7/8	See cut	1/4 to 1/8	7.0
*T 156	4	3	See cut	1/4 to 1/2	11.3
*T 157	3 1/2	2 1/4	See cut	1/8 to 1/4	7.3
*T 158	3	2 1/4	See cut	1/8 to 1/4	7.0

\* Furnished only by special arrangement.

# CARNEGIE STEEL COMPANY


## ZEES

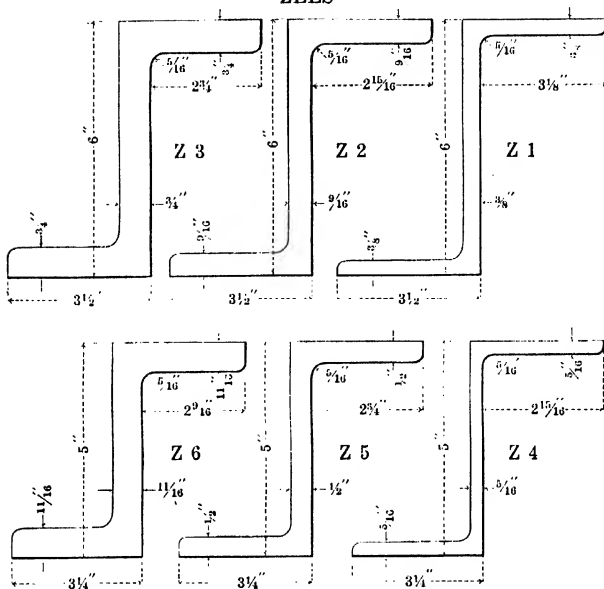

Section Index	Size, Inches			Thickness, Inches	Weight per Foot, Pounds
	Flange	Web	Flange		
Z 3	3 $\frac{1}{8}$	6 $\frac{1}{8}$	3 $\frac{5}{8}$	$\frac{7}{8}$	34.6
	3 $\frac{9}{16}$	6 $\frac{1}{16}$	3 $\frac{9}{16}$	$\frac{11}{16}$	32.0
	3 $\frac{1}{2}$	6	3 $\frac{1}{2}$	$\frac{5}{8}$	29.4
Z 2	3 $\frac{5}{8}$	6 $\frac{1}{8}$	3 $\frac{1}{8}$	$\frac{11}{16}$	28.1
	3 $\frac{9}{16}$	6 $\frac{1}{16}$	3 $\frac{1}{16}$	$\frac{5}{8}$	25.4
	3 $\frac{1}{2}$	6	3 $\frac{1}{2}$	$\frac{9}{16}$	22.8
Z 1	3 $\frac{5}{8}$	6 $\frac{1}{8}$	3 $\frac{5}{8}$	$\frac{1}{2}$	21.1
	3 $\frac{9}{16}$	6 $\frac{1}{16}$	3 $\frac{9}{16}$	$\frac{7}{8}$	18.4
	3 $\frac{1}{2}$	6	3 $\frac{1}{2}$	$\frac{3}{4}$	15.7
Z 6	3 $\frac{3}{8}$	5 $\frac{1}{8}$	3 $\frac{3}{8}$	$\frac{11}{16}$	28.4
	3 $\frac{9}{16}$	5 $\frac{1}{16}$	3 $\frac{9}{16}$	$\frac{3}{4}$	26.0
	3 $\frac{1}{4}$	5	3 $\frac{1}{4}$	$\frac{11}{16}$	23.7
Z 5	3 $\frac{3}{8}$	5 $\frac{1}{8}$	3 $\frac{3}{8}$	$\frac{5}{8}$	22.6
	3 $\frac{9}{16}$	5 $\frac{1}{16}$	3 $\frac{9}{16}$	$\frac{1}{2}$	20.2
	3 $\frac{1}{4}$	5	3 $\frac{1}{4}$	$\frac{1}{2}$	17.9
Z 4	3 $\frac{3}{8}$	5 $\frac{1}{8}$	3 $\frac{3}{8}$	$\frac{7}{8}$	16.4
	3 $\frac{9}{16}$	5 $\frac{1}{16}$	3 $\frac{9}{16}$	$\frac{3}{4}$	14.0
	3 $\frac{1}{4}$	5	3 $\frac{1}{4}$	$\frac{9}{16}$	11.6

# ZEES

## ZEES—Concluded



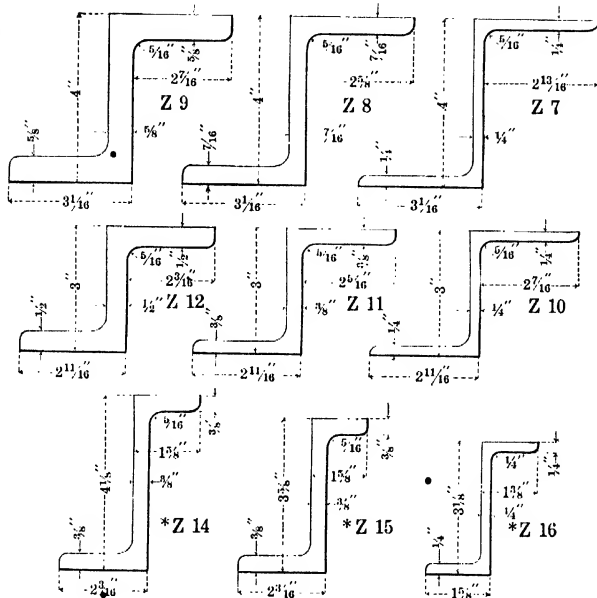


Section Index	Size, Inches			Thickness, Inches	Weight per Foot, Pounds
	Flange	Web	Flange		
Z 9	3 7/16	4 1/8	3 3/8	3/8	23.0
	3 1/8	4 1/8	3 1/8	3/8	20.9
	3 1/8	4	3 1/8	3/8	18.9
Z 8	3 3/8	4 1/8	3 3/8	3/8	18.0
	3 1/8	4 1/8	3 1/8	3/8	15.9
	3 1/8	4	3 1/8	3/8	13.8
Z 7	3 3/8	4 1/8	3 3/8	3/8	12.5
	3 1/8	4 1/8	3 1/8	3/8	10.3
	3 1/8	4	3 1/8	3/8	8.2
Z 12	2 3/4	3 1/8	2 3/4	3/8	14.3
	2 1/4	3	2 1/4	3/8	12.6
Z 11	2 3/4	3 1/8	2 3/4	3/8	11.5
	2 1/4	3	2 1/4	3/8	9.8
Z 10	2 3/4	3 1/8	2 3/4	3/8	8.5
	2 1/4	3	2 1/4	3/8	6.7
*Z 14	1 5/8	4 1/8	2 3/8	3/8	9.2
*Z 15	1 5/8	3 3/8	2 3/8	3/8	8.6
*Z 16	1 3/8	3 3/8	1 5/8	3/8	4.8

\* Furnished only by special arrangement.

CARNEGIE STEEL COMPANY

UNITED STATES STEEL SHEET PILING

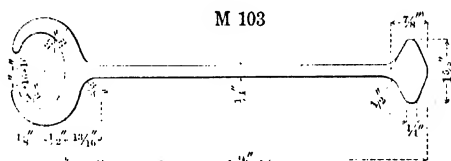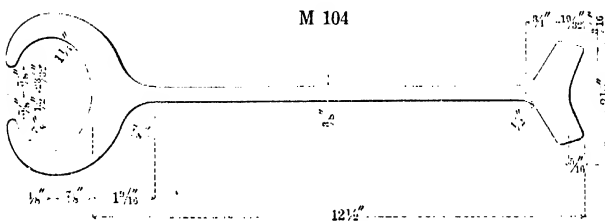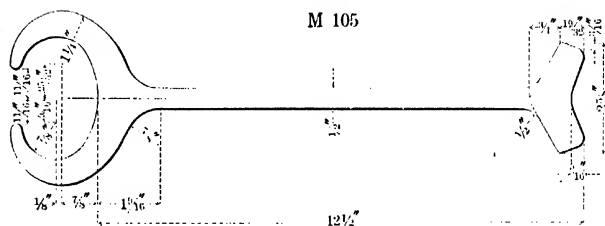


Section Index	Width, Inches	Web Thickness, Inches	Weight per Foot, Pounds
M 105	12 1/2	1/2	43
M 104	12 1/2	3/4	38
M 103	9	1/4	16

This Company manufactures Friestedt Interlocking Channel Bar Piling and Symmetrical Interlock Channel Bar Piling in addition to United States Steel Sheet Piling. Full information as to the properties and uses of these sections is given in a separate pamphlet entitled "Steel Sheet Piling."

# FLOOR PLATES

## TROUGH PLATES

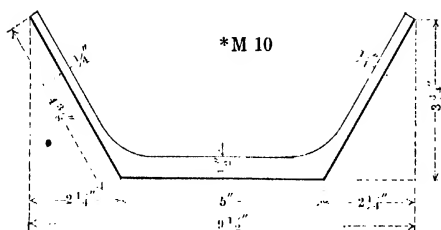

## CORRUGATED PLATES





Section Index	Width, Inches	Depth, Inches	Thickness, Inches	Weight per Foot, Pounds
*M 14	9 1/2	3 3/4	3/16	23.2
*M 13	9 1/2	3 3/4	1/10	21.4
*M 12	9 1/2	3 3/4	5/8	19.7
*M 11	9 1/2	3 3/4	9/10	18.0
*M 10	9 1/2	3 3/4	1/2	16.3
*M 35	12 3/16	2 7/8	1/2	23.7
*M 34	12 3/16	2 3/16	7/10	20.8
*M 33	12 3/16	2 3/4	3/8	17.8
*M 32	8 3/4	1 5/8	3/8	12.0
*M 31	8 3/4	1 9/16	5/10	10.1
*M 30	8 3/4	1 1/2	1/4	8.1

\*Furnished only by special arrangement.

# CARNEGIE STEEL COMPANY

## CHECKERED PLATE

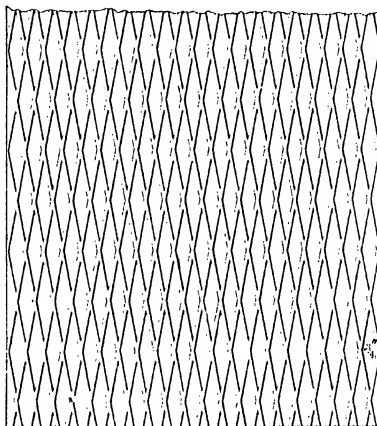

Section at Rib

Section Index	Thickness, Inches	Width and Length, Inches			Weight per Square Foot, Pounds
		6 to 11 $\frac{7}{8}$	12 to 48	48 $\frac{1}{8}$ to 60	
M 54	$\frac{1}{2}$	120	240	240	21.4
M 53	$\frac{7}{16}$	120	240	240	18.9
M 52	$\frac{3}{8}$	120	240	240	16.3
M 51	$\frac{5}{16}$	120	240	240	13.8
M 50	$\frac{1}{4}$	120	240	240	11.2
M 49	$\frac{3}{16}$	120	180		8.7

Checkered plates of greater lengths than shown in the above table may be submitted for special consideration.

# FLAT ROLLED STEEL

## RECTANGULAR AND CIRCULAR PLATES—Carbon Steel

SHEARED PLATES, THREE-SIXTEENTH INCHES AND UNDER, EXTREME SIZES

Thickness, Inches, B. W. G.	Weight, Lbs. per Sq. Ft.	Widths and Lengths in Inches						Diameter, Inches
		74	72	70	68	66	64	
$\frac{3}{16}$	7.65	200	220	240	250	270	320	375
No. 8	6.73		200	210	216	230	260	280
No. 9	6.01			160	170	190	220	240
No. 10	5.47				144	170	200	230
$\frac{1}{8}$	5.10					140	150	160
No. 11	*See Note					140	150	160
No. 12	*See Note					120	130	144
Thickness, Inches, B. W. G.	Weight, Lbs. per Sq. Ft.	54	48	42	36	30	24	Diameter, Inches
$\frac{3}{16}$	7.65	400	400	400	375	375	400	77
No. 8	6.73	300	310	350	350	350	340	74
No. 9	6.01	280	300	310	330	330	280	70
No. 10	5.47	210	260	270	300	300	260	68
$\frac{1}{8}$	5.10	200	220	230	260	260	260	66
No. 11	*See Note	200	220	230	260	260	260	66
No. 12	*See Note	180	200	220	240	240	240	64

Rectangular Plates  $\frac{3}{16}$ " thick, over 74" wide and Circular Plates  $\frac{3}{16}$ " thick, over 77" diameter can be furnished to gauge only and only under certain conditions. Such sizes should be submitted for special consideration.

\*Plates lighter than  $\frac{1}{8}$ " should be specified to gauge only, as it is not practicable to furnish such light plates to weight.

Plates of greater dimensions than shown in above table, may be submitted for special consideration.

## RECTANGULAR UNIVERSAL PLATES—Carbon Steel

UNIVERSAL MILL PLATES, ONE-FOURTH INCH AND OVER, EXTREME SIZES

Thick- ness, Inches	Weight, Lbs. per Sq. Ft.	Widths and Lengths in Inches											
		48-46	45-41	40-36	35-31	30-26	25-20	19-17	16-15	14-12	11	10-6	$\frac{1}{4}$
$\frac{1}{4}$	10.20								1020	1020	1020	540	540
$\frac{5}{16}$	12.75	1020	1020	1140	1260	1320	1320	1080	1080	1080	600	600	
$\frac{3}{8}$	15.30	1200	1200	1320	1380	1380	1380	1080	1080	1080	900	810	
$\frac{7}{16}$	17.85	1320	1320	1380	1380	1380	1380	1080	1080	1080	900	810	
$\frac{1}{2}$	20.40	1380	1380	1380	1380	1380	1380	1080	1080	1080	1020	840	
$\frac{9}{16}$	22.95	1380	1380	1380	1380	1380	1380	1080	1080	1080	1020	840	
$\frac{5}{8}$	25.50	1380	1380	1380	1380	1380	1380	1080	1080	1080	1020	840	
$\frac{3}{4}$	30.60	1353	1357	1363	1372	1380	1380	1080	1080	1080	900	810	
$\frac{7}{8}$	35.70	1160	1163	1169	1177	1188	1203	1080	1080	1080	900	810	
1	40.80	1015	1018	1023	1030	1039	1052	1080	1080	1080	900	840	
$1\frac{1}{8}$	45.90	903	905	910	916	924	936	1080	1080	1080	840	810	
$1\frac{1}{4}$	51.00	812	814	818	824	832	842	1071	1080	1080	840	840	
$1\frac{3}{8}$	56.10	738	740	744	749	756	766	973	1080	1080	840	840	
$1\frac{1}{2}$	61.20	677	679	682	687	693	702	892	1050	1080	840	840	
$1\frac{5}{8}$	66.30	625	626	629	634	640	648	823	978	1080	840	840	
$1\frac{3}{4}$	71.40	580	581	584	588	594	601	765	908	1038	720	720	
$1\frac{7}{8}$	76.50	541	543	545	549	554	561	714	847	968	660	720	
2	81.60	507	509	511	515	519	526	669	794	907	600	720	

Plates of greater dimensions than shown in above table, may be submitted for special consideration.



# CARNEGIE STEEL COMPANY

## RECTANGULAR AND CIRCULAR PLATES—Carbon Steel

### SHEARED PLATES, ONE-FOURTH INCH AND OVER, EXTREME SIZES

Thick- ness, Inches	Weight, Lbs. per Sq. Ft.	Widths and Lengths in Inches										Diam., Inches
		132	126	120	114	108	102	96	90	84	78	
$\frac{1}{4}$	10.20				175	250	280	300	330	375	400	115
$\frac{5}{16}$	12.75			240	270	320	360	380	420	440	460	120
$\frac{3}{8}$	15.30	180	240	270	320	365	380	410	450	500	550	132
$\frac{7}{16}$	17.85	200	270	300	360	370	410	430	460	510	550	132
$\frac{1}{2}$	20.40	210	270	320	365	400	450	480	510	550	580	134
$\frac{9}{16}$	22.95	210	270	330	373	420	470	500	530	570	600	134
$\frac{5}{8}$	25.50	240	300	350	390	450	500	520	540	600	620	134
$1\frac{1}{16}$	28.05	210	300	360	420	450	500	520	540	600	620	134
$\frac{3}{4}$	30.60	240	300	360	400	450	490	520	540	600	620	134
$1\frac{3}{16}$	33.15	210	300	310	385	410	490	510	530	600	620	134
$\frac{7}{8}$	35.70	240	300	330	375	440	480	510	530	600	620	134
1	40.80	240	300	300	310	410	460	500	530	580	600	134
$1\frac{1}{8}$	45.90	240	300	300	330	410	440	450	500	550	580	132
$1\frac{1}{4}$	51.00	230	270	300	310	380	400	420	490	530	550	132
$1\frac{1}{2}$	61.20	210	230	260	280	330	320	340	420	440	480	132
$1\frac{3}{4}$	71.40	200	200	220	240	280	270	300	380	380	410	132
2	81.60	180	180	190	210	240	240	260	320	330	360	132
$2\frac{1}{4}$	91.80	132	160	170	190	210	210	230	280	295	320	132

Thick- ness, Inches	Weight, Lbs. per Sq. Ft.	72	66	60	54	50	48	42	36	30	24	Diam., Inches
$\frac{1}{4}$	10.20	430	475	525	530	530	530	530	530	530	530	115
$\frac{5}{16}$	12.75	480	500	560	550	575	575	550	550	550	580	120
$\frac{3}{8}$	15.30	600	600	620	620	620	620	600	580	600	600	132
$\frac{7}{16}$	17.85	600	630	630	640	640	640	600	580	600	600	132
$\frac{1}{2}$	20.40	610	630	630	640	640	640	600	580	630	600	134
$\frac{9}{16}$	22.95	620	640	640	640	640	640	600	580	630	600	134
$\frac{5}{8}$	25.50	620	640	640	640	640	640	600	580	600	600	134
$1\frac{1}{16}$	28.05	620	640	640	640	640	640	600	580	600	580	134
$\frac{3}{4}$	30.60	620	640	640	640	640	640	600	580	600	580	134
$1\frac{3}{16}$	33.15	620	640	640	640	640	640	600	580	570	550	134
$\frac{7}{8}$	35.70	620	640	640	640	640	640	600	580	550	550	134
1	40.80	600	630	630	640	640	640	580	580	520	530	134
$1\frac{1}{8}$	45.90	580	620	620	640	640	640	580	580	520	500	132
$1\frac{1}{4}$	51.00	550	600	600	600	600	600	560	560	520	450	132
$1\frac{1}{2}$	61.20	530	600	600	600	600	600	540	540	470	430	132
$1\frac{3}{4}$	71.40	450	490	550	550	550	550	540	540	430	380	132
2	81.60	400	440	480	500	500	500	500	500	400	350	132
$2\frac{1}{4}$	91.80	350	390	420	450	450	450	450	450	300	200	132

Plates 48" wide and under can also be rolled on Universal Mills.

For greater length and Universal Mill Sizes, see Universal Mill Plate Table.

Plates of greater dimensions than shown in above tables may be submitted for special consideration.

# FLAT ROLLED STEEL

## RECTANGULAR PLATES—Nickel Steel SHEARED PLATES, ONE-FOURTH INCH AND OVER, EXTREME SIZES

Thick- ness, Inches	Widths and Lengths in Inches															
	102	96	90	84	78	72	66	60	54	50	48	42	36	30	24	
$\frac{1}{4}$						240	240	260	280	280	280	280	260	260		
$\frac{5}{16}$					260	260	270	300	310	310	340	310	310	310	310	
$\frac{3}{8}$		280	310	390	420	450	500	500	500	500	480	450	450	430	430	
$\frac{7}{16}$	260	300	360	400	430	480	520	520	520	520	500	490	490	480	480	
$\frac{1}{2}$	270	320	380	420	460	485	520	520	520	520	500	490	490	480	480	
$\frac{9}{16}$	270	320	380	420	460	485	520	520	520	520	500	490	490	480	480	
$\frac{5}{8}$	270	300	355	390	410	480	520	520	520	520	500	500	500	480	450	
$\frac{11}{16}$	260	300	355	390	440	460	490	500	500	500	500	500	500	480	450	
$\frac{3}{4}$	260	300	355	390	410	450	460	500	500	500	500	500	480	480	450	
$\frac{13}{16}$	260	300	355	390	440	440	460	480	500	500	500	500	480	460	440	
$\frac{7}{8}$	260	300	355	390	440	440	460	480	480	480	480	480	480	450	440	
1	260	290	320	370	400	430	440	460	480	480	480	480	440	420	420	
$1\frac{1}{8}$	250	270	295	330	375	400	410	420	440	440	440	440	410	420	420	
$1\frac{1}{4}$	240	260	290	315	330	350	360	380	390	400	400	420	420	400	400	
$1\frac{1}{2}$	230	260	290	290	310	330	350	370	390	390	390	390	380	380	360	
$1\frac{3}{4}$	220	230	250	270	300	310	330	350	370	390	390	390	360	340	320	
2	210	230	250	260	290	295	310	330	350	370	370	370	340	320	290	


## RECTANGULAR PLATES—Nickel Steel UNIVERSAL MILL PLATES, ONE-FOURTH INCH AND OVER, EXTREME SIZES

Thick- ness, Inches	Widths and Lengths in Inches									
	48-46	45-44	40-36	35-31	30-26	25-20	19-17	16-15	14-12	11 10-6 1
$\frac{1}{4}$								660	660	660 510 510
$\frac{5}{16}$	510	510	600	660	720	780	780	780	780	600 600
$\frac{3}{8}$	720	720	780	840	960	960	1020	1020	1020	900 840
$\frac{7}{16}$	840	840	960	1020	1080	1080	1020	1020	1020	900 840
$\frac{1}{2}$	960	960	1080	1110	1200	1200	1020	1020	1020	1020 840
$\frac{9}{16}$	960	960	1080	1140	1200	1200	1020	1020	1020	1020 840
$\frac{5}{8}$	900	900	1020	1080	1140	1140	1000	1000	1020	1020 810
$\frac{3}{4}$	840	840	960	1020	1080	1080	1000	1000	1020	900 810
$\frac{7}{8}$	780	780	840	960	960	960	1000	1000	1000	900 840
1	720	750	780	816	840	900	1000	1000	1000	900 840
$1\frac{1}{8}$	640	667	693	725	744	800	1000	1000	1000	840 840
$1\frac{1}{4}$	575	600	624	652	672	720	1000	1000	1000	840 840
$1\frac{1}{2}$	525	545	567	593	600	655	970	1000	1000	810 840
$1\frac{3}{4}$	480	500	520	544	540	600	890	1000	980	810 840
$1\frac{5}{8}$	444	461	480	502	504	554	820	978	980	840 840
$1\frac{3}{4}$	410	428	445	466	480	514	765	908	980	720 720
$1\frac{7}{8}$	384	400	416	435	444	480	710	847	968	660 720
2	360	375	390	408	420	450	670	794	908	600 720

All sizes of Rectangular Nickel Steel Plates given in above tables under  $\frac{1}{2}$ " thick should be specified to gage only. Plates  $\frac{1}{2}$ " thick and over can be rolled to either gage or weight per square foot.

## CARNEGIE STEEL COMPANY

### SQUARE EDGE FLATS




$\frac{3}{8}$ " to 3", wide, x any thickness,  $\frac{1}{8}$ ", up to width.  
 Over 3" to 5", wide, x any thickness,  $\frac{1}{4}$ " to 3", inclusive.  
 Over 5" to 7", wide, x any thickness,  $\frac{1}{4}$ " to 2", inclusive.  
 Over 7" to  $7\frac{1}{2}$ ", wide, x any thickness,  $\frac{5}{16}$ " to  $1\frac{1}{2}$ ", inclusive.  
 Over  $7\frac{1}{2}$ " to 8", wide, x any thickness,  $\frac{5}{16}$ " to 1" inclusive.  
 Sizes not listed will be considered.

### NUT STEEL FLATS

All sizes of Nut Steel Flats within the range of Square Edge Flats can be furnished. Some of the smaller sizes can be furnished in coils.

### BAND EDGE FLATS



$\frac{3}{8}$ ",	wide, x No. 18 to No. 4 B. W. G.
$\frac{7}{16}$ ",	wide, x No. 19 to No. 4 B. W. G.
$\frac{1}{2}$ ",	wide, x No. 22 to No. 4 B. W. G.
$\frac{5}{16}$ " to 1",	wide, x No. 23 to No. 4 B. W. G.
$1\frac{1}{16}$ " to 2",	wide, x No. 22 to No. 4 B. W. G.
$2\frac{1}{16}$ " to 3",	wide, x No. 21 to No. 1 B. W. G.
$3\frac{1}{16}$ " to $3\frac{1}{2}$ ",	wide, x No. 20 to No. 1 B. W. G.
$3\frac{9}{16}$ " to 4",	wide, x No. 19 to No. 1 B. W. G.
$4\frac{1}{16}$ " to $4\frac{1}{2}$ ",	wide, x No. 18 to No. 1 B. W. G.
$4\frac{5}{16}$ " to $5\frac{1}{16}$ ",	wide, x No. 17 to No. 1 B. W. G.
$5\frac{1}{8}$ " to $6\frac{3}{4}$ ",	wide, x No. 16 to No. 1 B. W. G.
$6\frac{3}{16}$ " to $8\frac{5}{8}$ ",	wide, x No. 14 to No. 1 B. W. G.
$8\frac{1}{16}$ " to $9\frac{5}{8}$ ",	wide, x No. 12 to No. 1 B. W. G.
$10\frac{1}{4}$ ",	wide, x No. 12 to No. 1 B. W. G.

From  $\frac{3}{8}$ " to  $9\frac{5}{8}$ " intermediate widths can be furnished.

Over  $9\frac{5}{8}$ " in width, the size listed is the only one which is rolled, but intermediate widths will be considered.

### SKELP

All sizes within the range of Sheared Plates, Universal Mill Plates and Band Edge Flats can be furnished.

## MERCHANT BARS

### SQUARES



Size  $\frac{3}{16}$ " to 2", inclusive, advancing by 64ths.

Size  $2\frac{1}{32}$ " to  $3\frac{1}{2}$ ", inclusive, advancing by 32ds.

Size  $3\frac{9}{16}$ " to  $5\frac{1}{2}$ ", inclusive, advancing by 16ths.

Squares can also be rolled to decimal dimensions, if so arranged.

Squares  $\frac{1}{4}$ " and smaller can be furnished in coils.

### ROUND CORNERED SQUARES



Size  $\frac{1}{4}$ " to  $\frac{1}{2}$ ", inclusive, advancing by 64ths.

### ROUNDS



Diameter  $\frac{7}{32}$ " to  $1\frac{3}{4}$ ", inclusive, advancing by 64ths.

Diameter  $1\frac{25}{32}$ " to  $3\frac{1}{2}$ ", inclusive, advancing by 32ds.

Diameter  $3\frac{9}{16}$ " to 7", inclusive, advancing by 16ths.

Rounds can also be rolled to decimal dimensions, if so arranged.

Rounds  $\frac{7}{8}$ " and smaller can be furnished in coils.

### HALF ROUNDS



Diameter

Diameter  $\frac{5}{16}$ " to  $\frac{7}{8}$ ", inclusive, advancing by 64ths.

Diameter  $1\frac{5}{16}$ " to  $1\frac{1}{2}$ ", inclusive, advancing by 16ths.

Diameter 2",  $2\frac{1}{2}$ ", 3".

### HEXAGONS



Size  $\frac{1}{4}$ " to  $1\frac{1}{4}$ ", inclusive, advancing by 32ds.

Size  $1\frac{3}{4}$ " to  $3\frac{1}{4}$ ", inclusive, advancing by 16ths.

Size  $3\frac{3}{4}$ "

## CARNEGIE STEEL COMPANY

## AREAS OF RECTANGULAR SECTIONS

## SQUARE INCHES

Width, Inches	Thickness, Inches															
	$\frac{1}{16}$	$\frac{1}{8}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{16}$	$\frac{3}{8}$	$\frac{7}{16}$	$\frac{1}{2}$	$\frac{9}{16}$	$\frac{5}{8}$	$\frac{11}{16}$	$\frac{3}{4}$	$\frac{13}{16}$	$\frac{7}{8}$	$1\frac{1}{16}$	1
$\frac{1}{16}$	.016	.031	.047	.063	.078	.094	.109	.125	.141	.156	.172	.188	.203	.22	.23	.25
$\frac{1}{8}$	.031	.063	.094	.125	.156	.188	.219	.250	.281	.313	.344	.375	.406	.44	.47	.50
$\frac{3}{16}$	.047	.091	.111	.138	.164	.191	.218	.245	.272	.299	.326	.353	.380	.407	.434	.461
$\frac{1}{4}$	.063	.125	.188	.250	.313	.375	.438	.500	.563	.625	.688	.750	.813	.88	.94	1.00
$\frac{5}{16}$	.078	.156	.234	.313	.391	.469	.547	.625	.703	.781	.859	.938	1.016	1.09	1.17	1.25
$\frac{3}{8}$	.094	.188	.281	.375	.469	.563	.656	.750	.844	.938	1.031	1.125	1.219	1.31	1.41	1.50
$\frac{7}{16}$	.109	.219	.328	.438	.547	.656	.766	.875	.984	1.094	1.203	1.313	1.422	1.53	1.64	1.75
$\frac{1}{2}$	.125	.250	.375	.500	.625	.750	.875	1.000	1.125	1.250	1.375	1.500	1.625	1.75	1.88	2.00
$\frac{9}{16}$	.141	.281	.422	.563	.703	.844	.984	1.125	1.266	1.406	1.547	1.688	1.828	1.97	2.11	2.25
$\frac{5}{8}$	.156	.313	.469	.625	.781	.938	1.094	1.250	1.406	1.563	1.719	1.875	2.031	2.19	2.34	2.50
$\frac{11}{16}$	.172	.344	.516	.688	.859	1.031	1.203	1.375	1.547	1.719	1.891	2.063	2.234	2.41	2.58	2.75
$\frac{3}{4}$	.188	.375	.563	.750	.938	1.125	1.313	1.500	1.688	1.875	2.063	2.250	2.438	2.63	2.81	3.00
$1\frac{1}{16}$	.203	.406	.609	.813	1.016	1.219	1.422	1.625	1.828	2.031	2.234	2.438	2.641	2.84	3.06	3.25
$1\frac{1}{8}$	.219	.438	.656	.875	1.094	1.313	1.531	1.750	1.969	2.188	2.406	2.625	2.844	3.06	3.28	3.50
$1\frac{3}{16}$	.234	.469	.703	.938	1.172	1.406	1.641	1.875	2.109	2.344	2.578	2.813	3.047	3.28	3.52	3.75
$1\frac{1}{4}$	.250	.500	.750	1.000	1.250	1.500	1.750	2.000	2.250	2.500	2.750	3.000	3.250	3.50	3.75	4.00
$1\frac{5}{16}$	.266	.531	.797	1.063	1.328	1.594	1.859	2.125	2.391	2.656	2.922	3.188	3.453	3.72	3.98	4.25
$1\frac{3}{8}$	.281	.563	.844	1.125	1.406	1.688	1.969	2.250	2.531	2.813	3.094	3.375	3.656	3.94	4.22	4.50
$1\frac{7}{16}$	.297	.594	.891	1.188	1.484	1.781	2.078	2.375	2.672	2.969	3.266	3.563	3.859	4.16	4.45	4.75
$1\frac{1}{2}$	.313	.625	.938	1.250	1.563	1.875	2.188	2.500	2.813	3.125	3.438	3.750	4.063	4.38	4.69	5.00
$1\frac{9}{16}$	.328	.656	.984	1.313	1.641	1.969	2.297	2.625	2.953	3.281	3.609	3.938	4.266	4.59	4.92	5.25
$1\frac{5}{8}$	.344	.688	1.031	1.375	1.719	2.063	2.406	2.750	3.094	3.438	3.781	4.125	4.469	4.81	5.16	5.50
$1\frac{3}{4}$	.359	.719	1.078	1.438	1.797	2.156	2.516	2.875	3.234	3.594	3.953	4.313	4.672	5.03	5.39	5.75
$2\frac{1}{16}$	.375	.750	1.125	1.500	1.875	2.250	2.625	3.000	3.375	3.750	4.125	4.500	4.875	5.25	5.63	6.00
$2\frac{1}{8}$	.391	.781	1.172	1.563	1.953	2.344	2.734	3.125	3.516	3.906	4.297	4.688	5.078	5.47	5.86	6.25
$2\frac{1}{4}$	.406	.813	1.219	1.625	2.031	2.438	2.844	3.250	3.656	4.063	4.469	4.875	5.281	5.69	6.09	6.50
$2\frac{3}{16}$	.422	.844	1.266	1.688	2.109	2.531	2.953	3.375	3.797	4.219	4.641	5.063	5.484	5.91	6.33	6.75
$2\frac{1}{2}$	.438	.875	1.313	1.750	2.188	2.625	3.063	3.500	3.938	4.375	4.813	5.250	5.688	6.13	6.56	7.00
$2\frac{5}{16}$	.453	.906	1.359	1.813	2.266	2.719	3.172	3.625	4.078	4.531	4.984	5.438	5.891	6.34	6.80	7.25
$2\frac{3}{8}$	.469	.938	1.406	1.875	2.344	2.813	3.281	3.750	4.219	4.688	5.156	5.625	6.094	6.56	7.03	7.50
$2\frac{7}{16}$	.484	.969	1.453	1.938	2.422	2.906	3.381	3.875	4.359	4.841	5.328	5.813	6.297	6.78	7.27	7.75
$2\frac{1}{2}$	.500	1.000	1.500	2.000	2.500	3.000	3.500	4.000	4.500	5.000	5.500	6.000	6.500	7.00	7.50	8.00
$3\frac{1}{16}$	.516	1.031	1.547	2.063	2.578	3.094	3.609	4.125	4.641	5.156	5.672	6.188	6.703	7.22	7.73	8.25
$3\frac{1}{8}$	.531	1.063	1.594	2.125	2.656	3.188	3.719	4.250	4.781	5.313	5.844	6.375	6.906	7.44	7.97	8.50
$3\frac{3}{16}$	.547	1.094	1.641	2.188	2.734	3.281	3.828	4.375	4.922	5.469	6.016	6.563	7.109	7.66	8.20	8.75
$3\frac{1}{4}$	.563	1.125	1.688	2.250	2.813	3.375	3.938	4.500	5.063	5.625	6.188	6.750	7.313	7.88	8.44	9.00
$3\frac{5}{16}$	.578	1.156	1.734	2.313	2.891	3.469	4.047	4.625	5.203	5.781	6.359	6.938	7.516	8.09	8.67	9.25
$3\frac{3}{8}$	.594	1.188	1.781	2.375	2.969	3.563	4.156	4.750	5.344	5.938	6.531	7.125	7.719	8.31	8.91	9.50
$3\frac{7}{16}$	.609	1.219	1.828	2.438	3.047	3.656	4.266	4.875	5.484	6.094	6.703	7.313	7.922	8.53	9.14	9.75
$3\frac{1}{2}$	.625	1.250	1.875	2.500	3.125	3.750	4.375	5.000	5.625	6.250	6.875	7.500	8.125	8.75	9.38	10.00
$3\frac{9}{16}$	.641	1.281	1.922	2.563	3.203	3.844	4.484	5.125	5.766	6.406	7.047	7.688	8.328	8.97	9.61	10.25
$3\frac{5}{8}$	.656	1.313	1.969	2.625	3.281	3.938	4.594	5.250	5.906	6.563	7.219	7.875	8.531	9.19	9.84	10.50
$3\frac{3}{4}$	.672	1.344	2.016	2.688	3.359	4.031	4.703	5.375	6.047	6.719	7.391	8.063	8.734	9.41	10.08	10.75
$4\frac{1}{16}$	.688	1.375	2.063	2.750	3.438	4.125	4.813	5.500	6.188	6.875	7.563	8.250	8.938	9.63	10.31	11.00
$4\frac{1}{8}$	.703	1.406	2.109	2.813	3.516	4.219	4.922	5.625	6.328	7.031	7.734	8.438	9.141	9.84	10.55	11.25
$4\frac{3}{16}$	.719	1.438	2.156	2.875	3.594	4.313	5.031	5.750	6.469	7.188	7.906	8.625	9.344	10.06	10.78	11.50
$4\frac{1}{4}$	.734	1.469	2.203	2.938	3.672	4.406	5.141	5.875	6.609	7.344	8.078	8.813	9.547	10.28	11.02	11.75
$4\frac{3}{8}$	.750	1.500	2.250	3.000	3.750	4.500	5.250	6.000	6.750	7.500	8.250	9.000	9.750	10.50	11.25	12.00

# AREAS OF RECTANGLES

## AREAS OF RECTANGULAR SECTIONS—Continued

SQUARE INCHES

Width, Inches	Thickness, Inches															
	$\frac{1}{16}$	$\frac{1}{8}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{16}$	$\frac{3}{8}$	$\frac{7}{16}$	$\frac{1}{2}$	$\frac{9}{16}$	$\frac{5}{8}$	$\frac{11}{16}$	$\frac{3}{4}$	$\frac{13}{16}$	$\frac{7}{8}$	$1\frac{1}{16}$	1
12	.781	1.563	2.344	3.13	3.91	4.69	5.47	6.25	7.03	7.81	8.59	9.38	10.16	10.94	11.72	12.50
13	.813	1.626	2.438	3.25	4.06	4.88	5.69	6.50	7.31	8.13	8.94	9.75	10.56	11.38	12.19	13.00
13½	.844	1.688	2.531	3.38	4.22	5.06	5.91	6.75	7.59	8.44	9.28	10.13	10.97	11.81	12.66	13.50
14	.875	1.750	2.625	3.50	4.38	5.25	6.13	7.00	7.88	8.75	9.63	10.50	11.38	12.25	13.13	14.00
14½	.906	1.813	2.719	3.63	4.53	5.44	6.34	7.25	8.16	9.09	9.97	10.88	11.78	12.69	13.59	14.50
15	.938	1.875	2.813	3.75	4.69	5.63	6.56	7.50	8.44	9.38	10.31	11.25	12.19	13.13	14.06	15.00
15½	.969	1.938	2.906	3.88	4.84	5.81	6.78	7.75	8.72	9.69	10.66	11.63	12.59	13.56	14.53	15.50
16	1.000	2.000	3.000	4.00	5.00	6.00	7.00	8.00	9.00	10.00	11.00	12.00	13.00	14.00	15.00	16.00
16½	1.031	2.063	3.094	4.13	5.16	6.19	7.22	8.25	9.28	10.31	11.34	12.38	13.41	14.44	15.47	16.50
17	1.063	2.126	3.188	4.25	5.31	6.38	7.44	8.56	9.56	10.63	11.69	12.75	13.81	14.88	15.91	17.00
17½	1.094	2.188	3.281	4.38	5.47	6.56	7.66	8.75	9.84	10.94	12.03	13.13	14.22	15.31	16.41	17.50
18	1.125	2.250	3.375	4.50	5.63	6.75	7.88	9.00	10.13	11.25	12.38	13.50	14.63	15.75	16.88	18.00
18½	1.156	2.313	3.469	4.63	5.78	6.94	8.09	9.25	10.41	11.56	12.72	13.88	15.03	16.19	17.34	18.50
19	1.188	2.375	3.563	4.75	5.94	7.13	8.31	9.50	10.69	11.88	13.06	14.25	15.44	16.63	17.81	19.00
19½	1.219	2.438	3.656	4.88	6.09	7.31	8.53	9.75	10.97	12.19	13.41	14.63	15.84	17.06	18.28	19.50
20	1.250	2.500	3.750	5.00	6.25	7.50	8.75	10.00	11.25	12.50	13.75	15.00	16.25	17.50	18.75	20.00
20½	1.281	2.563	3.844	5.13	6.41	7.69	8.97	10.25	11.53	12.81	14.09	15.38	16.66	17.94	19.22	20.50
21	1.313	2.625	3.938	5.25	6.56	7.88	9.19	10.50	11.81	13.13	14.44	15.75	17.06	18.38	19.69	21.00
21½	1.344	2.688	4.031	5.38	6.72	8.06	9.41	10.75	12.09	13.44	14.78	16.13	17.47	18.81	20.16	21.50
22	1.375	2.750	4.125	5.50	6.88	8.25	9.63	11.00	12.38	13.75	15.13	16.50	17.88	19.25	20.63	22.00
22½	1.406	2.813	4.219	5.63	7.03	8.44	9.84	11.25	12.66	14.06	15.47	16.88	18.28	19.69	21.00	22.50
23	1.438	2.875	4.313	5.75	7.19	8.63	10.06	11.50	12.94	14.38	15.81	17.25	18.69	20.13	21.56	23.00
23½	1.469	2.938	4.406	5.88	7.34	8.81	10.28	11.75	13.22	14.69	16.16	17.63	19.09	20.56	22.03	23.50
24	1.500	3.000	4.500	6.00	7.50	9.00	10.50	12.00	13.50	15.00	16.50	18.00	19.50	21.00	22.50	24.00
25	1.563	3.125	4.688	6.25	7.81	9.38	10.94	12.50	14.06	15.63	17.19	18.75	20.31	21.88	23.44	25.00
26	1.625	3.250	4.875	6.50	8.13	9.75	11.38	13.00	14.63	16.25	17.88	19.50	21.13	22.75	24.38	26.00
27	1.688	3.375	5.063	6.75	8.44	10.13	11.81	13.50	15.19	16.88	18.56	20.25	21.94	23.63	25.31	27.00
28	1.750	3.500	5.250	7.00	8.75	10.50	12.25	14.00	15.75	17.50	19.25	21.00	22.75	24.50	26.25	28.00
29	1.813	3.625	5.438	7.25	9.06	10.88	12.60	14.50	16.31	18.13	19.94	21.75	23.56	25.38	27.19	29.00
30	1.875	3.750	5.625	7.50	9.38	11.25	13.13	15.00	16.88	18.75	20.63	22.50	24.38	26.25	28.13	30.00
31	1.938	3.875	5.813	7.75	9.69	11.63	13.50	15.50	17.44	19.38	21.31	23.25	25.19	27.13	29.06	31.00
32	2.000	4.000	6.000	8.00	10.00	12.00	14.00	16.00	18.00	20.00	22.00	24.00	26.00	28.00	30.00	32.00
33	2.063	4.126	6.188	8.25	10.31	12.38	14.44	16.50	18.56	20.63	22.69	24.75	26.81	28.88	30.94	33.00
34	2.125	4.250	6.375	8.50	10.63	12.75	14.88	17.00	19.13	21.25	23.38	25.50	27.63	29.75	31.88	34.00
35	2.188	4.375	6.563	8.75	10.94	13.13	15.31	17.50	19.69	21.88	24.06	26.25	28.44	30.63	32.81	35.00
36	2.250	4.500	6.750	9.00	11.25	13.50	15.75	18.00	20.25	22.50	24.75	27.00	29.25	31.50	33.75	36.00
37	2.313	4.625	6.938	9.25	11.56	13.88	16.19	18.50	20.81	23.13	25.44	27.75	30.06	32.38	34.69	37.00
38	2.375	4.750	7.125	9.50	11.88	14.25	16.63	19.00	21.38	23.75	26.13	28.50	30.88	33.25	35.63	38.00
39	2.438	4.875	7.313	9.75	12.19	14.63	17.06	19.50	21.94	24.38	26.81	29.25	31.69	34.13	36.56	39.00
40	2.500	5.000	7.500	10.00	12.50	15.00	17.50	20.00	22.50	25.00	27.50	30.00	32.50	35.00	37.50	40.00
41	2.563	5.125	7.688	10.25	12.81	15.38	17.94	20.50	23.06	25.63	28.19	30.75	33.31	35.88	38.44	41.00
42	2.625	5.250	7.875	10.50	13.13	15.75	18.38	21.00	23.63	26.25	28.88	31.50	34.13	36.75	39.38	42.00
43	2.688	5.375	8.063	10.75	13.44	16.13	18.81	21.50	24.19	26.88	29.56	32.25	34.94	37.63	40.31	43.00
44	2.750	5.500	8.250	11.00	13.75	16.50	19.25	22.00	24.75	27.50	30.25	33.00	35.75	38.50	41.25	44.00
45	2.813	5.625	8.438	11.25	14.06	16.88	19.69	22.50	25.31	28.13	30.94	33.75	36.56	39.38	42.19	45.00
46	2.875	5.750	8.625	11.50	14.38	17.25	20.13	23.00	25.88	28.75	31.63	34.50	37.38	40.25	43.13	46.00
47	2.938	5.875	8.813	11.75	14.69	17.63	20.56	23.50	26.44	29.38	32.31	35.25	38.19	41.13	44.06	47.00
48	3.000	6.000	9.000	12.00	15.00	18.00	21.00	24.00	27.00	30.00	33.00	36.00	39.00	42.00	45.00	48.00

# CARNEGIE STEEL COMPANY

## AREAS OF RECTANGULAR SECTIONS—Concluded SQUARE INCHES

Width, Inches	Thickness, Inches															
	$\frac{1}{16}$	$\frac{1}{8}$	$\frac{3}{16}$	$\frac{1}{2}$	$\frac{5}{8}$	$\frac{3}{4}$	$\frac{7}{8}$	1	1 $\frac{1}{8}$	1 $\frac{1}{4}$	1 $\frac{3}{8}$	1 $\frac{1}{2}$	1 $\frac{3}{4}$	1 $\frac{7}{8}$	2	1
49	3.06	6.13	9.19	12.25	15.31	18.38	21.44	24.50	27.56	30.63	33.69	36.75	39.81	42.88	45.94	49.00
50	3.13	6.25	9.38	12.50	15.63	18.75	21.88	25.00	28.13	31.25	34.38	37.50	40.63	43.75	46.88	50.00
51	3.19	6.38	9.56	12.75	15.94	19.13	22.31	25.50	28.69	31.88	35.06	38.25	41.44	44.63	47.81	51.00
52	3.25	6.50	9.75	13.00	16.25	19.50	22.75	26.00	29.25	32.50	35.75	39.00	42.25	45.50	48.75	52.00
53	3.31	6.63	9.94	13.25	16.56	19.88	23.19	26.50	29.81	33.13	36.44	39.75	43.06	46.38	49.69	53.00
54	3.38	6.75	10.13	13.50	16.88	20.25	23.63	27.00	30.38	33.75	37.13	40.50	43.88	47.25	50.63	54.00
55	3.44	6.88	10.31	13.75	17.19	20.63	24.06	27.50	30.94	34.38	37.81	41.25	44.69	48.13	51.56	55.00
56	3.50	7.00	10.50	14.00	17.50	21.00	24.50	28.00	31.50	35.00	38.50	42.00	45.50	49.00	52.50	56.00
57	3.56	7.13	10.69	14.25	17.81	21.38	24.94	28.50	32.06	35.63	39.19	42.75	46.31	49.88	53.44	57.00
58	3.63	7.25	10.88	14.50	18.13	21.75	25.38	29.00	32.63	36.25	39.88	43.50	47.13	50.75	54.38	58.00
59	3.69	7.38	11.06	14.75	18.44	22.19	25.81	29.50	33.19	36.88	40.56	44.25	47.91	51.63	55.31	59.00
60	3.75	7.50	11.25	15.00	18.75	22.50	26.25	30.00	33.75	37.50	41.25	45.00	48.75	52.50	56.25	60.00
61	3.81	7.63	11.44	15.25	19.06	22.88	26.69	30.50	34.31	38.13	41.94	45.75	49.56	53.38	57.19	61.00
62	3.88	7.75	11.63	15.50	19.38	23.25	27.13	31.00	34.88	38.75	42.63	46.50	50.38	54.25	58.13	62.00
63	3.94	7.88	11.81	15.75	19.69	23.63	27.56	31.50	35.44	39.38	43.31	47.25	51.19	55.13	59.06	63.00
64	4.00	8.00	12.00	16.00	20.00	24.00	28.00	32.00	36.00	40.00	44.00	48.00	52.00	56.00	60.00	64.00
65	4.06	8.13	12.19	16.25	20.31	24.38	28.44	32.50	36.56	40.63	44.69	48.75	52.81	56.88	60.94	65.00
66	4.13	8.25	12.38	16.50	20.63	24.75	28.88	33.00	37.13	41.25	45.38	49.50	53.63	57.75	61.88	66.00
67	4.19	8.38	12.56	16.75	20.94	25.13	29.31	33.50	37.69	41.88	46.06	50.25	54.44	58.63	62.81	67.00
68	4.25	8.50	12.75	17.00	21.25	25.50	29.75	34.00	38.25	42.50	46.75	51.00	55.25	59.50	63.75	68.00
69	4.31	8.63	12.94	17.25	21.56	25.88	30.19	34.50	38.81	43.13	47.44	51.75	56.06	60.38	64.69	69.00
70	4.38	8.75	13.13	17.50	21.88	26.25	30.63	35.00	39.38	43.75	48.13	52.50	56.88	61.25	65.63	70.00
71	4.44	8.88	13.31	17.75	22.19	26.63	31.06	35.50	39.94	44.38	48.81	53.25	57.69	62.13	66.56	71.00
72	4.50	9.00	13.50	18.00	22.50	27.00	31.50	36.00	40.50	45.00	49.50	54.00	58.50	63.00	67.50	72.00
73	4.56	9.13	13.69	18.25	22.81	27.38	31.94	36.50	41.06	45.63	50.19	54.75	59.31	63.88	68.44	73.00
74	4.63	9.25	13.88	18.50	23.13	27.75	32.38	37.00	41.63	46.25	50.88	55.50	60.13	64.75	69.38	74.00
75	4.69	9.38	14.06	18.75	23.44	28.13	32.81	37.50	42.19	46.88	51.56	56.25	60.94	65.63	70.31	75.00
76	4.75	9.50	14.25	19.00	23.75	28.50	33.25	38.00	42.75	47.50	52.25	57.00	61.75	66.50	71.25	76.00
77	4.81	9.63	14.44	19.25	24.06	28.88	33.69	38.50	43.31	48.13	52.94	57.75	62.56	67.38	72.19	77.00
78	4.88	9.75	14.63	19.50	24.38	29.25	34.13	39.00	43.88	48.75	53.63	58.50	63.38	68.25	73.13	78.00
79	4.94	9.88	14.81	19.75	24.69	29.63	34.56	39.50	44.44	49.38	54.31	59.25	64.19	69.13	74.06	79.00
80	5.00	10.00	15.00	20.00	25.00	30.00	35.00	40.00	45.00	50.00	55.00	60.00	65.00	70.00	75.00	80.00
81	5.06	10.13	15.19	20.25	25.31	30.38	35.44	40.50	45.56	50.63	55.69	60.75	65.81	70.88	75.94	81.00
82	5.13	10.25	15.38	20.50	25.63	30.75	35.88	41.00	46.13	51.25	56.38	61.50	66.63	71.75	76.88	82.00
83	5.19	10.38	15.56	20.75	25.94	31.13	36.31	41.50	46.69	51.88	57.06	62.25	67.44	72.63	77.81	83.00
84	5.25	10.50	15.75	21.00	26.25	31.50	36.75	42.00	47.25	52.50	57.75	63.00	68.25	73.50	78.75	84.00
85	5.31	10.63	15.94	21.25	26.56	31.88	37.19	42.50	47.81	53.13	58.44	63.75	69.06	74.38	79.69	85.00
86	5.38	10.75	16.13	21.50	26.88	32.25	37.63	43.00	48.38	53.75	59.13	64.50	69.88	75.25	80.63	86.00
87	5.44	10.88	16.31	21.75	27.19	32.63	38.06	43.50	48.94	54.38	59.81	65.25	70.69	76.13	81.56	87.00
88	5.50	11.00	16.50	22.00	27.50	33.00	38.50	44.00	49.50	55.00	60.50	66.00	71.50	77.00	82.50	88.00
89	5.56	11.13	16.69	22.25	27.81	33.38	38.94	44.50	50.06	55.63	61.19	66.75	72.31	77.88	83.44	89.00
90	5.63	11.25	16.88	22.50	28.13	33.75	39.38	45.00	50.63	56.25	61.88	67.50	73.13	78.75	84.38	90.00
91	5.69	11.38	17.06	22.75	28.44	34.13	39.81	45.50	51.19	56.88	62.56	68.25	73.94	79.63	85.31	91.00
92	5.75	11.50	17.25	23.00	28.75	34.50	40.25	46.00	51.75	57.50	63.25	69.00	74.75	80.50	86.25	92.00
93	5.81	11.63	17.44	23.25	29.06	34.88	40.69	46.50	52.31	58.13	63.94	69.75	75.56	81.38	87.19	93.00
94	5.88	11.75	17.63	23.50	29.38	35.25	41.13	47.00	52.88	58.75	64.63	70.50	76.38	82.25	88.13	94.00
95	5.94	11.88	17.81	23.75	29.69	35.63	41.56	47.50	53.44	59.38	65.31	71.25	77.19	83.13	89.06	95.00
96	6.00	12.00	18.00	24.00	30.00	36.00	42.00	48.00	54.00	60.00	66.00	72.00	78.00	84.00	90.00	96.00
97	6.06	12.13	18.19	24.25	30.31	36.38	42.44	48.50	54.56	60.63	66.69	72.75	78.81	84.88	90.94	97.00
98	6.13	12.25	18.38	24.50	30.63	36.75	42.88	49.00	55.13	61.25	67.38	73.50	79.63	85.75	91.88	98.00
99	6.19	12.38	18.56	24.75	30.94	37.13	43.31	49.50	55.69	61.88	68.06	74.25	80.44	86.63	92.81	99.00
100	6.25	12.50	18.75	25.00	31.25	37.50	43.75	50.00	56.25	62.50	68.75	75.00	81.25	87.50	93.75	100.00

## WEIGHTS OF FLAT ROLLED STEEL

## WEIGHTS OF FLAT ROLLED STEEL

POUNDS PER LINEAL FOOT

Width, Inches	Thickness, Inches															
	1/16	1/8	3/16	1/4	5/16	3/8	7/16	1/2	9/16	5/8	11/16	3/4	13/16	7/8	15/16	1
1 1/4	.053	.106	.159	.213	.27	.32	.37	.43	.48	.54	.58	.64	.69	.74	.80	.85
1 1/2	.106	.213	.319	.425	.53	.64	.74	.85	.96	1.06	1.17	1.28	1.38	1.49	1.59	1.70
1 3/4	.159	.319	.478	.638	.80	.96	1.12	1.28	1.43	1.59	1.75	1.91	2.07	2.23	2.39	2.55
2	.213	.425	.638	.850	1.06	1.28	1.49	1.70	1.91	2.13	2.34	2.55	2.76	2.98	3.19	3.40
2 1/4	.266	.531	.797	1.063	1.33	1.59	1.86	2.13	2.39	2.66	2.92	3.19	3.45	3.72	3.98	4.25
2 1/2	.319	.638	.956	1.275	1.59	1.91	2.23	2.55	2.87	3.19	3.51	3.83	4.14	4.46	4.78	5.10
2 3/4	.372	.744	1.116	1.488	1.86	2.23	2.60	2.98	3.35	3.72	4.09	4.46	4.83	5.21	5.58	5.95
3	.425	.850	1.275	1.700	2.13	2.55	2.98	3.40	3.83	4.25	4.68	5.10	5.53	5.95	6.38	6.80
3 1/4	.478	.956	1.434	1.913	2.39	2.87	3.35	3.83	4.30	4.78	5.26	5.74	6.22	6.69	7.17	7.65
3 1/2	.531	1.063	1.594	2.125	2.66	3.19	3.72	4.25	4.78	5.31	5.84	6.38	6.91	7.44	7.97	8.50
3 3/4	.584	1.169	1.753	2.338	2.92	3.51	4.09	4.68	5.26	5.84	6.43	7.01	7.60	8.18	8.77	9.35
4	.638	1.275	1.913	2.550	3.19	3.83	4.46	5.10	5.74	6.38	7.01	7.65	8.29	8.93	9.56	10.20
4 1/4	.691	1.381	2.072	2.763	3.45	4.14	4.83	5.53	6.22	6.91	7.60	8.29	8.98	9.67	10.36	11.05
4 1/2	.744	1.488	2.231	2.975	3.72	4.46	5.21	5.95	6.69	7.44	8.18	8.93	9.67	10.41	11.16	11.90
4 3/4	.797	1.591	2.391	3.188	3.98	4.78	5.58	6.38	7.17	7.97	8.77	9.56	10.36	11.16	11.95	12.75
5	.850	1.700	2.550	3.400	4.25	5.10	5.95	6.80	7.65	8.50	9.35	10.20	11.05	11.90	12.75	13.60
5 1/4	.903	1.806	2.709	3.613	4.52	5.42	6.32	7.23	8.13	9.03	9.93	10.84	11.74	12.64	13.55	14.45
5 1/2	.956	1.913	2.869	3.825	4.78	5.74	6.69	7.65	8.61	9.56	10.52	11.48	12.43	13.39	14.34	15.30
5 3/4	1.009	2.019	3.028	4.038	5.05	6.06	7.07	8.08	9.08	10.09	11.10	12.11	13.12	14.13	15.14	16.15
6	1.063	2.125	3.188	4.250	5.31	6.38	7.44	8.50	9.56	10.63	11.69	12.75	13.81	14.88	15.94	17.00
6 1/4	1.116	2.231	3.347	4.463	5.58	6.69	7.81	8.93	10.04	11.16	12.27	13.39	14.50	15.62	16.73	17.85
6 1/2	1.169	2.338	3.506	4.675	5.84	7.01	8.18	9.35	10.52	11.69	12.86	14.03	15.19	16.36	17.53	18.70
6 3/4	1.222	2.441	3.666	4.888	6.11	7.33	8.55	9.78	11.00	12.22	13.44	14.66	15.88	17.11	18.33	19.55
7	1.275	2.550	3.825	5.100	6.38	7.65	8.93	10.20	11.48	12.75	14.03	15.30	16.58	17.85	19.13	20.40
7 1/4	1.328	2.656	3.984	5.313	6.64	7.97	9.30	10.63	11.95	13.28	14.61	15.94	17.27	18.59	19.92	21.25
7 1/2	1.381	2.763	4.144	5.525	6.91	8.29	9.67	11.05	12.43	13.81	15.19	16.58	17.96	19.34	20.72	22.10
7 3/4	1.434	2.869	4.303	5.738	7.17	8.61	10.04	11.48	12.91	14.34	15.78	17.21	18.65	20.08	21.52	22.95
8	1.488	2.975	4.463	5.950	7.44	8.93	10.41	11.90	13.39	14.88	16.36	17.85	19.34	20.83	22.31	23.80
8 1/4	1.541	3.081	4.622	6.163	7.70	9.24	10.78	12.33	13.87	15.41	16.95	18.49	20.03	21.57	23.11	24.65
8 1/2	1.594	3.188	4.781	6.375	7.97	9.56	11.16	12.75	14.34	15.94	17.53	19.13	20.72	22.31	23.91	25.50
8 3/4	1.647	3.294	4.941	6.588	8.23	9.88	11.53	13.18	14.82	16.47	18.12	19.76	21.41	23.06	24.70	26.35
9	1.700	3.400	5.100	6.800	8.50	10.20	11.90	13.60	15.30	17.00	18.70	20.40	22.10	23.80	25.50	27.20
9 1/4	1.753	3.506	5.250	7.013	8.77	10.52	12.27	14.03	15.78	17.53	19.28	21.04	22.79	24.54	26.30	28.05
9 1/2	1.806	3.613	5.410	7.225	9.03	10.84	12.64	14.45	16.26	18.06	19.87	21.68	23.48	25.29	27.09	28.90
9 3/4	1.859	3.719	5.578	7.438	9.30	11.16	13.02	14.88	16.73	18.58	20.45	22.31	24.17	26.03	27.89	29.75
10	1.913	3.825	5.738	7.650	9.56	11.48	13.39	15.30	17.21	19.13	21.04	22.95	24.86	26.78	28.69	30.60
10 1/4	1.966	3.931	5.897	7.863	9.83	11.79	13.76	15.73	17.69	19.66	21.62	23.59	25.55	27.52	29.48	31.45
10 1/2	2.021	4.038	6.056	8.075	10.09	12.11	14.13	16.15	18.17	20.19	22.21	24.23	26.24	28.26	30.28	32.30
10 3/4	2.072	4.144	6.216	8.288	10.36	12.43	14.50	16.58	18.65	20.72	22.79	24.86	26.93	29.01	31.08	33.15
11	2.125	4.250	6.375	8.500	10.63	12.75	14.88	17.00	19.13	21.25	23.38	25.50	27.63	29.75	31.88	34.00
11 1/4	2.178	4.356	6.534	8.713	10.89	13.07	15.25	17.43	19.60	21.78	23.96	26.14	28.32	30.49	32.67	34.85
11 1/2	2.231	4.463	6.694	8.925	11.16	13.39	15.62	17.85	20.08	22.31	24.54	26.78	29.01	31.24	33.47	35.70
11 3/4	2.284	4.569	6.853	9.138	11.42	13.71	15.99	18.28	20.56	22.84	25.13	27.41	29.70	31.98	34.27	36.55
12	2.338	4.675	7.013	9.350	11.69	14.03	16.36	18.70	21.04	23.38	25.71	28.05	30.39	32.73	35.06	37.40
12 1/4	2.391	4.781	7.172	9.563	11.95	14.34	16.73	19.13	21.52	23.91	26.30	28.69	31.08	33.47	35.86	38.25
12 1/2	2.444	4.888	7.331	9.775	12.22	14.66	17.11	19.55	21.99	24.44	26.88	29.33	31.77	34.21	36.66	39.10
12 3/4	2.497	4.994	7.491	9.988	12.48	14.98	17.48	19.98	22.47	24.97	27.47	29.96	32.46	34.96	37.45	39.95
13	2.550	5.100	7.650	10.20	12.75	15.30	17.85	20.40	22.95	25.50	28.05	30.60	33.15	35.70	38.25	40.80



# CARNEGIE STEEL COMPANY

## WEIGHTS OF FLAT ROLLED STEEL—Continued

POUNDS PER LINEAL FOOT

Width, Inches	Thickness, Inches																		
	$\frac{1}{16}$	$\frac{1}{8}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{16}$	$\frac{3}{8}$	$\frac{7}{16}$	$\frac{1}{2}$	$\frac{9}{16}$	$\frac{5}{8}$	$1\frac{1}{16}$	$1\frac{1}{8}$	$1\frac{3}{16}$	$1\frac{1}{2}$	$1\frac{5}{8}$	$1\frac{7}{8}$	$2$	$2\frac{1}{2}$	$3$
12 $\frac{1}{2}$	2.66	5.31	7.97	10.63	13.28	15.94	18.59	21.25	23.91	26.56	29.22	31.9	34.5	37.2	39.8	42.5			
13	2.76	5.53	8.29	11.05	13.81	16.58	19.31	22.10	24.86	27.63	30.4	33.2	35.9	38.7	41.4	44.2			
13 $\frac{1}{2}$	2.87	5.74	8.61	11.48	14.34	17.21	20.08	22.95	25.82	28.69	31.6	34.4	37.3	40.2	43.0	45.9			
14	2.98	5.95	8.93	11.90	14.88	17.85	20.83	23.80	26.78	29.75	32.7	35.7	38.7	41.7	44.6	47.6			
14 $\frac{1}{2}$	3.08	6.16	9.24	12.35	15.41	18.49	21.57	24.65	27.73	30.81	33.9	37.0	40.1	43.1	46.2	49.3			
15	3.19	6.38	9.56	12.75	15.91	19.13	22.31	25.50	28.69	31.88	35.1	38.3	41.4	44.6	47.8	51.0			
15 $\frac{1}{2}$	3.29	6.59	9.88	13.18	16.47	19.70	23.06	26.35	29.64	32.94	36.2	39.5	42.8	46.1	49.4	52.7			
16	3.40	6.80	10.20	13.60	17.00	20.40	23.80	27.20	30.60	34.00	37.4	40.8	44.2	47.6	51.0	54.4			
16 $\frac{1}{2}$	3.51	7.01	10.52	14.03	17.53	21.04	24.54	28.05	31.56	35.06	38.6	42.1	45.6	49.1	52.6	56.1			
17	3.61	7.23	10.81	14.45	18.06	21.68	25.20	28.90	32.51	36.13	39.7	43.4	47.0	50.6	54.2	57.8			
17 $\frac{1}{2}$	3.72	7.44	11.16	14.88	18.59	22.31	26.03	29.75	33.47	37.19	40.9	44.6	48.3	52.1	55.8	59.5			
18	3.83	7.65	11.48	15.30	19.13	22.95	26.78	30.60	34.43	38.25	42.1	45.9	49.7	53.6	57.4	61.2			
18 $\frac{1}{2}$	3.93	7.86	11.79	15.73	19.66	23.59	27.52	31.45	35.38	39.31	43.2	47.2	51.1	55.0	59.0	62.9			
19	4.04	8.08	12.11	16.15	20.19	24.23	28.26	32.30	36.34	40.38	44.4	48.5	52.5	56.5	60.6	64.6			
19 $\frac{1}{2}$	4.14	8.29	12.43	16.58	20.72	24.86	29.01	33.15	37.29	41.44	45.6	49.7	53.9	58.0	62.2	66.3			
20	4.25	8.50	12.75	17.00	21.25	25.50	29.75	34.00	38.25	42.50	46.8	51.0	55.3	59.5	63.8	68.0			
20 $\frac{1}{2}$	4.36	8.71	13.07	17.43	21.78	26.14	30.49	34.85	39.21	43.56	47.9	52.3	56.6	61.0	65.3	69.7			
21	4.46	8.93	13.39	17.85	22.31	26.78	31.21	35.70	40.16	44.63	49.1	53.6	58.0	62.5	66.9	71.4			
21 $\frac{1}{2}$	4.57	9.11	13.71	18.28	22.84	27.41	31.98	36.55	41.12	45.69	50.3	54.8	59.4	63.9	68.5	73.1			
22	4.68	9.35	14.03	18.79	23.38	28.05	32.73	37.40	42.08	46.75	51.4	56.1	60.8	65.5	70.1	74.8			
22 $\frac{1}{2}$	4.78	9.56	14.34	19.13	23.91	28.69	33.47	38.25	43.03	47.81	52.6	57.4	62.2	66.9	71.7	76.5			
23	4.89	9.78	14.66	19.55	24.44	29.33	34.21	39.10	43.99	48.88	53.8	58.7	63.5	68.1	73.3	78.2			
23 $\frac{1}{2}$	4.99	9.99	14.98	19.98	24.97	29.96	34.96	39.95	44.91	49.91	54.9	59.9	64.9	69.9	74.9	79.9			
24	5.10	10.20	15.30	20.40	25.50	30.60	35.70	40.80	45.90	51.00	56.1	61.2	66.3	71.4	76.5	81.6			
25	5.31	10.63	15.94	21.25	26.56	31.88	37.19	42.50	47.81	53.13	58.4	63.8	69.1	74.4	79.7	85.0			
26	5.53	11.05	16.58	22.10	27.63	33.13	38.68	44.20	49.74	55.25	60.8	66.3	71.8	77.4	82.9	88.4			
27	5.74	11.48	17.21	22.95	28.69	34.43	40.16	45.90	51.64	57.38	63.1	68.9	74.6	80.3	86.1	91.8			
28	5.95	11.90	17.85	23.80	29.75	35.70	41.65	47.60	53.55	59.50	65.5	71.4	77.4	83.3	89.3	95.2			
29	6.16	12.33	18.49	24.65	30.81	36.98	43.14	49.30	55.46	61.63	67.8	74.0	80.1	86.3	92.4	98.6			
30	6.38	12.75	19.13	25.50	31.88	38.25	44.63	51.00	57.38	63.75	70.1	76.5	82.9	89.3	95.6	102.0			
31	6.59	13.18	19.76	26.35	32.91	39.55	46.11	52.70	59.29	65.88	72.5	79.1	85.6	92.2	98.8	105.4			
32	6.80	13.60	20.40	27.20	34.00	40.80	47.60	54.10	61.20	68.00	74.8	81.6	88.4	95.2	102.0	108.8			
33	7.01	14.03	21.04	28.05	35.06	42.08	49.09	56.10	63.11	70.13	77.1	84.2	91.2	98.2	105.2	112.2			
34	7.23	14.45	21.68	28.90	36.13	43.35	50.58	57.80	65.03	72.25	79.5	86.7	93.9	101.2	108.4	115.6			
35	7.44	14.88	22.31	29.75	37.19	44.63	52.06	59.50	66.91	74.38	81.8	89.3	96.7	104.1	111.6	119.0			
36	7.65	15.30	22.95	30.60	38.25	45.90	53.55	61.20	68.85	76.50	84.2	91.8	99.5	107.1	114.8	122.4			
37	7.86	15.73	23.59	31.45	39.31	47.18	55.04	62.90	70.76	78.63	86.5	94.4	102.2	110.1	117.9	125.8			
38	8.08	16.15	24.23	32.30	40.38	48.45	56.53	64.60	72.68	80.75	88.8	96.9	105.0	113.1	121.1	129.2			
39	8.29	16.58	24.86	33.15	41.44	49.73	58.01	66.30	74.59	82.88	91.2	99.5	107.7	116.0	124.3	132.6			
40	8.50	17.00	25.50	34.00	42.50	51.00	59.50	68.00	76.50	85.00	93.5	102.0	110.5	119.0	127.5	136.0			
41	8.71	17.43	26.14	34.85	43.56	52.28	60.99	69.70	78.41	87.13	95.8	104.6	113.3	122.0	130.7	139.4			
42	8.93	17.85	26.78	35.70	44.63	53.55	62.48	71.40	80.33	89.25	98.2	107.1	116.0	125.0	133.9	142.8			
43	9.14	18.28	27.41	36.55	45.69	54.83	63.90	73.10	82.24	91.38	100.5	109.7	118.8	127.9	137.1	146.2			
44	9.35	18.70	28.05	37.40	46.75	56.10	65.45	74.80	84.15	93.50	102.9	112.2	121.6	130.9	140.3	149.6			
45	9.56	19.13	28.69	38.25	47.81	57.38	66.94	76.50	86.06	95.63	105.2	114.8	124.3	133.9	143.4	153.0			
46	9.78	19.55	29.33	39.10	48.88	58.68	68.43	78.20	87.98	97.75	107.5	117.3	127.1	136.9	146.6	156.4			
47	9.99	19.98	29.96	39.95	49.94	59.93	69.91	79.90	89.89	99.88	109.9	119.9	129.8	139.8	149.8	159.8			
48	10.20	20.40	30.60	40.80	51.00	61.20	71.40	81.60	91.80	102.0	112.2	122.4	132.6	142.8	153.0	163.2			

# WEIGHTS OF FLAT ROLLED STEEL

## WEIGHTS OF FLAT ROLLED STEEL--Concluded POUNDS PER LINEAL FOOT

Width, Inches	Thickness, Inches															
	1/16	1/8	3/16	1/4	5/16	3/8	7/16	1/2	5/8	3/4	7/8	1 1/8	1 1/4	1 3/8	1 1/2	1
49	10.4	20.8	31.2	41.7	52.1	62.5	72.9	83.3	93.7	104.1	114.5	125.0	135.4	145.8	156.2	166.6
50	10.6	21.3	31.9	42.5	53.1	63.8	74.3	85.0	95.6	106.3	116.9	127.5	138.1	148.8	159.4	170.0
51	10.8	21.7	32.5	43.4	54.2	65.0	75.9	86.7	97.5	108.4	119.2	130.1	140.9	151.7	162.6	173.4
52	11.1	22.1	33.2	44.2	55.3	66.3	77.4	88.4	99.5	110.5	121.6	132.6	143.7	154.7	165.8	176.8
53	11.3	22.5	33.8	45.1	56.3	67.6	78.8	90.1	101.4	112.6	123.9	135.2	146.4	157.7	168.9	180.2
54	11.5	23.0	34.4	45.9	57.4	68.9	80.3	91.8	103.3	114.8	126.2	137.7	149.2	160.7	172.1	183.6
55	11.7	23.1	35.1	46.8	58.4	70.1	81.8	93.5	105.2	116.9	128.6	140.3	151.9	163.6	175.3	187.0
56	11.9	23.8	35.7	47.6	59.5	71.4	83.3	95.2	107.1	119.0	130.9	142.8	154.7	166.6	178.5	190.4
57	12.1	24.2	36.3	48.5	60.6	72.7	84.8	96.9	109.0	121.1	133.2	145.4	157.5	169.6	181.7	193.8
58	12.3	24.7	37.0	49.3	61.6	74.0	86.3	98.6	110.9	123.3	135.6	147.9	160.2	172.6	184.9	197.2
59	12.5	25.1	37.6	50.2	62.7	75.2	87.8	100.3	112.8	125.1	137.6	150.5	163.0	175.5	188.1	200.6
60	12.8	25.5	38.3	51.0	63.8	76.5	89.3	102.0	114.8	127.5	140.3	153.0	165.8	178.5	191.3	204.0
61	13.0	25.9	38.9	51.9	64.8	77.8	90.7	103.7	116.7	129.6	142.6	155.6	168.5	181.5	194.4	207.4
62	13.2	26.1	39.3	52.7	65.9	79.1	92.2	105.4	118.6	131.8	144.9	158.1	171.3	184.5	197.6	210.8
63	13.4	26.8	40.2	53.6	66.9	80.3	93.7	107.1	120.5	133.9	147.3	160.7	174.0	187.4	200.8	214.2
64	13.6	27.2	40.8	54.4	68.0	81.6	95.2	108.8	122.4	136.0	149.6	163.2	176.8	190.4	204.0	217.6
65	13.8	27.6	41.4	55.3	69.1	82.9	96.7	110.5	124.3	138.1	151.9	165.8	179.6	193.7	207.2	221.0
66	14.0	28.1	42.1	56.1	70.1	84.2	98.2	112.2	126.2	140.3	154.3	168.3	182.3	196.2	210.4	224.4
67	14.2	28.5	42.7	57.0	71.2	85.1	99.7	113.9	128.1	142.4	156.6	170.9	185.1	199.2	213.6	227.8
68	14.5	28.9	43.4	57.8	72.3	86.7	101.2	115.6	130.1	144.5	159.0	173.4	187.9	202.3	216.8	231.2
69	14.7	29.3	44.0	58.7	73.3	88.0	102.6	117.3	132.0	146.6	161.3	176.0	190.6	205.3	219.9	234.6
70	14.9	29.8	44.6	59.5	74.1	89.3	104.1	119.0	133.9	148.8	163.6	178.5	193.1	208.3	223.1	238.0
71	15.1	30.2	45.3	60.1	75.1	90.5	105.6	120.7	135.8	150.9	166.0	181.1	196.1	211.2	226.3	241.4
72	15.3	30.6	45.9	61.2	76.5	91.8	107.1	122.4	137.7	153.0	168.3	183.6	198.9	214.2	229.5	244.8
73	15.5	31.0	46.5	62.1	77.6	93.1	108.6	124.1	139.6	155.1	170.6	186.2	201.7	217.2	232.7	248.2
74	15.7	31.5	47.2	62.9	78.6	94.4	110.1	125.8	141.5	157.3	173.0	188.7	204.1	220.2	235.9	251.6
75	15.9	31.9	47.8	63.8	79.7	95.6	111.6	127.5	143.4	159.4	175.3	191.3	207.2	223.1	239.1	255.0
76	16.2	32.3	48.5	64.6	80.8	96.9	113.1	129.2	145.4	161.5	177.7	193.8	210.0	226.1	242.3	258.4
77	16.4	32.7	49.1	65.5	81.8	98.2	114.5	130.9	147.3	163.6	180.0	196.4	212.7	228.1	245.4	261.8
78	16.6	33.2	49.7	66.3	82.9	99.5	116.0	132.6	149.2	165.8	182.3	198.9	215.5	232.1	248.6	265.2
79	16.8	33.6	50.4	67.2	83.9	100.7	117.5	134.3	151.1	167.9	184.7	201.5	218.2	235.0	251.8	268.6
80	17.0	34.0	51.0	68.0	85.0	102.0	119.0	136.0	153.0	170.0	187.0	204.0	221.0	238.0	255.0	272.0
81	17.2	34.4	51.6	68.9	86.1	103.3	120.5	137.7	154.9	172.1	189.3	206.6	223.8	241.0	258.2	275.4
82	17.4	34.9	52.3	69.7	87.1	104.6	122.0	139.4	156.8	174.3	191.7	209.1	226.5	244.0	261.4	278.8
83	17.6	35.3	52.9	70.6	88.2	105.8	123.5	141.1	158.7	176.4	194.0	211.7	229.3	246.9	264.6	282.2
84	17.9	35.7	53.6	71.4	89.3	107.1	125.0	142.8	160.7	178.5	196.4	214.2	232.1	249.9	267.8	285.6
85	18.1	36.1	54.2	72.3	90.3	108.4	126.4	144.5	162.6	180.6	198.7	216.8	234.8	252.9	270.9	289.0
86	18.3	36.6	54.8	73.1	91.4	109.7	127.9	146.2	164.5	182.8	201.0	219.3	237.6	255.9	274.1	292.4
87	18.5	37.0	55.5	74.0	92.4	110.9	129.1	147.9	166.1	184.9	203.4	221.9	240.3	258.8	277.3	295.8
88	18.7	37.4	56.1	74.8	93.5	112.2	130.9	149.6	168.3	187.0	205.7	224.4	243.1	261.8	280.5	299.2
89	18.9	37.8	56.7	75.7	94.6	113.5	132.4	151.3	170.2	189.1	208.0	227.6	245.9	264.8	283.7	302.6
90	19.1	38.3	57.4	76.5	95.6	114.8	133.9	153.0	172.1	191.3	210.4	229.5	248.6	267.8	286.9	306.0
91	19.3	38.7	58.0	77.4	96.7	116.0	135.4	154.7	174.0	193.4	212.7	232.1	251.4	270.7	290.1	309.4
92	19.6	39.1	58.7	78.2	97.8	117.3	136.9	156.4	176.0	195.5	215.1	234.6	254.2	273.7	293.3	312.8
93	19.8	39.5	59.3	79.1	98.8	118.6	138.3	158.1	177.9	197.6	217.4	237.2	256.9	276.7	296.4	316.2
94	20.0	40.0	59.9	79.9	99.9	119.9	139.8	159.8	179.8	199.8	219.7	239.7	259.7	279.7	299.6	319.6
95	20.2	40.4	60.6	80.8	100.9	121.1	141.3	161.5	181.7	201.9	222.1	242.3	262.4	282.6	302.8	323.0
96	20.4	40.8	61.2	81.6	102.0	122.1	142.8	163.2	183.6	204.0	224.4	244.8	265.2	285.3	306.0	326.4
97	20.6	41.2	61.8	82.5	103.1	123.7	144.3	164.9	185.5	206.1	226.7	247.4	268.0	288.6	309.2	329.8
98	20.8	41.7	62.5	83.3	104.1	125.0	145.8	166.6	187.4	208.3	229.1	249.9	270.7	291.6	312.4	333.2
99	21.0	42.1	63.1	84.2	105.2	126.2	147.3	168.3	189.3	210.4	231.4	252.5	273.3	294.5	315.6	336.6
100	21.3	42.5	63.8	85.0	106.3	127.5	148.8	170.0	191.3	212.5	233.8	255.0	276.3	297.5	318.8	340.0

**CARNEGIE STEEL COMPANY**  
**SQUARE AND ROUND BARS**

**WEIGHTS AND AREAS**

Size, Inches	Weight, Lbs. per Foot		Area, Square Inches		Size, Inches	Weight, Lbs. per Foot		Area, Square Inches	
	□	○	□	○		□	○	□	○
0					3	30.60	21.03	9.000	7.069
$\frac{1}{8}$	.013	.010	.0039	.0031	$\frac{1}{8}$	31.89	25.05	9.379	7.366
$\frac{1}{4}$	.053	.012	.0156	.0123	$\frac{1}{4}$	33.20	26.08	9.766	7.670
$\frac{3}{8}$	.120	.091	.0352	.0276	$\frac{3}{8}$	34.54	27.13	10.160	7.980
$\frac{1}{2}$	.213	.167	.0625	.0491	$\frac{1}{2}$	35.91	28.21	10.563	8.296
$\frac{5}{8}$	.332	.261	.0977	.0767	$\frac{5}{8}$	37.31	29.30	10.973	8.618
$\frac{3}{4}$	.478	.376	.1406	.1105	$\frac{3}{4}$	38.73	30.42	11.391	8.946
$\frac{7}{8}$	.651	.511	.1914	.1503	$\frac{7}{8}$	40.18	31.55	11.816	9.281
$1\frac{1}{8}$	.850	.668	.2500	.1963	$1\frac{1}{8}$	41.65	32.71	12.250	9.621
$1\frac{1}{4}$	1.076	.815	.3161	.2485	$1\frac{1}{4}$	43.15	33.89	12.601	9.968
$1\frac{3}{8}$	1.328	1.013	.3906	.3068	$1\frac{3}{8}$	44.68	35.09	13.141	10.321
$1\frac{1}{2}$	1.607	1.262	.4727	.3712	$1\frac{1}{2}$	46.23	36.31	13.598	10.680
$1\frac{3}{4}$	1.913	1.502	.5625	.4418	$1\frac{3}{4}$	47.81	37.55	14.063	11.045
$1\frac{7}{8}$	2.245	1.763	.6602	.5185	$1\frac{7}{8}$	49.42	38.81	14.535	11.416
2	2.603	2.011	.7656	.6013	2	51.05	40.10	15.016	11.793
$2\frac{1}{8}$	2.988	2.347	.8789	.6903	$2\frac{1}{8}$	52.71	41.40	15.504	12.177
1	3.400	2.670	1.0000	.7854	4	51.40	42.73	16.000	12.566
$1\frac{1}{8}$	3.838	3.015	1.1289	.8866	$1\frac{1}{8}$	56.11	44.07	16.504	12.962
$1\frac{1}{4}$	4.303	3.380	1.2656	.9940	$1\frac{1}{4}$	57.85	45.44	17.016	13.364
$1\frac{3}{8}$	4.795	3.765	1.4102	1.1075	$1\frac{3}{8}$	59.62	46.83	17.535	13.772
$1\frac{1}{2}$	5.313	4.172	1.5625	1.2272	$1\frac{1}{2}$	61.41	48.23	18.063	14.186
$1\frac{3}{4}$	5.857	4.600	1.7227	1.3530	$1\frac{3}{4}$	63.23	49.66	18.598	14.607
$1\frac{7}{8}$	6.428	5.019	1.8906	1.4849	$1\frac{7}{8}$	65.08	51.11	19.141	15.033
2	7.026	5.518	2.0664	1.6230	2	66.95	52.58	19.691	15.466
$2\frac{1}{8}$	7.650	6.008	2.2500	1.7671	$2\frac{1}{8}$	68.85	54.07	20.250	15.904
$2\frac{1}{4}$	8.301	6.519	2.4414	1.9175	$2\frac{1}{4}$	70.78	55.59	20.816	16.349
$2\frac{3}{8}$	8.978	7.051	2.6406	2.0739	$2\frac{3}{8}$	72.73	57.12	21.391	16.800
$2\frac{1}{2}$	9.682	7.604	2.8477	2.2365	$2\frac{1}{2}$	74.71	58.67	21.973	17.257
$2\frac{3}{4}$	10.413	8.178	3.0625	2.4053	$2\frac{3}{4}$	76.71	60.25	22.563	17.721
$2\frac{7}{8}$	11.170	8.773	3.2852	2.5802	$2\frac{7}{8}$	78.74	61.85	23.160	18.190
3	11.953	9.388	3.5156	2.7612	3	80.80	63.46	23.766	18.665
$3\frac{1}{8}$	12.763	10.024	3.7539	2.9483	$3\frac{1}{8}$	82.89	65.10	24.379	19.147
2	13.600	10.681	4.0000	3.1416	5	85.00	66.76	25.000	19.635
$2\frac{1}{8}$	14.463	11.350	4.2539	3.3410	$2\frac{1}{8}$	87.14	68.44	25.629	20.129
$2\frac{1}{4}$	15.353	12.058	4.5156	3.5466	$2\frac{1}{4}$	89.30	70.14	26.266	20.629
$2\frac{3}{8}$	16.270	12.778	4.7852	3.7583	$2\frac{3}{8}$	91.49	71.86	26.910	21.135
$2\frac{1}{2}$	17.213	13.519	5.0625	3.9761	$2\frac{1}{2}$	93.71	73.60	27.563	21.648
$2\frac{3}{4}$	18.182	14.280	5.3477	4.2000	$2\frac{3}{4}$	95.96	75.36	28.223	22.166
$2\frac{7}{8}$	19.178	15.062	5.6406	4.4301	$2\frac{7}{8}$	98.23	77.15	28.891	22.691
3	20.201	15.866	5.9414	4.6664	3	100.53	78.95	29.566	23.221
$3\frac{1}{8}$	21.250	16.690	6.2500	4.9087	$3\frac{1}{8}$	102.85	80.78	30.250	23.758
$3\frac{1}{4}$	22.326	17.531	6.5664	5.1572	$3\frac{1}{4}$	105.20	82.62	30.941	24.301
$3\frac{3}{8}$	23.428	18.400	6.8906	5.4119	$3\frac{3}{8}$	107.58	84.49	31.641	24.850
$3\frac{1}{2}$	24.557	19.287	7.2227	5.6727	$3\frac{1}{2}$	109.98	86.38	32.348	25.406
$3\frac{3}{4}$	25.713	20.195	7.5625	5.9396	$3\frac{3}{4}$	112.41	88.29	33.063	25.967
$3\frac{7}{8}$	26.895	21.123	7.9102	6.2126	$3\frac{7}{8}$	114.87	90.22	33.785	26.535
4	28.103	22.072	8.2656	6.4918	4	117.35	92.17	34.516	27.109
$4\frac{1}{8}$	29.338	23.042	8.6289	6.7771	$4\frac{1}{8}$	119.86	94.14	35.254	27.688
3	30.600	24.033	9.0000	7.0686	6	122.40	96.13	36.000	28.274

# WEIGHTS OF BAR

## SQUARE AND ROUND BARS

### WEIGHTS AND AREAS

Size, Inches	Weight, Lbs. per Foot		Area, Square Inches		Size, Inches	Weight, Lbs. per Foot		Area, Square Inches	
	$\square$	$\circ$	$\square$	$\circ$		$\square$	$\circ$	$\square$	$\circ$
6	122.40	96.13	36.000	28.274	9	275.40	216.30	81.000	63.617
$\frac{1}{8}$	124.96	98.15	36.754	28.866	$\frac{1}{8}$	279.24	219.31	82.129	64.504
$\frac{1}{4}$	127.55	100.18	37.516	29.465	$\frac{1}{4}$	283.10	222.35	83.266	65.397
$\frac{3}{8}$	130.17	102.23	38.285	30.069	$\frac{3}{8}$	286.99	225.41	84.410	66.296
$\frac{1}{2}$	132.81	104.31	39.063	30.680	$\frac{1}{2}$	290.91	228.48	85.563	67.201
$\frac{5}{8}$	135.48	106.41	39.818	31.296	$\frac{5}{8}$	294.86	231.58	86.723	68.112
$\frac{3}{4}$	138.18	108.53	40.641	31.919	$\frac{3}{4}$	298.83	234.70	87.891	69.029
$\frac{7}{8}$	140.90	110.66	41.441	32.548	$\frac{7}{8}$	302.83	237.84	89.066	69.953
$1\frac{1}{8}$	143.65	112.82	42.250	33.183	$1\frac{1}{8}$	306.85	241.00	90.250	70.882
$1\frac{1}{4}$	146.43	115.00	43.066	33.824	$1\frac{1}{4}$	310.90	244.18	91.411	71.818
$1\frac{3}{8}$	149.23	117.20	43.891	34.472	$1\frac{3}{8}$	314.98	247.38	92.641	72.760
$1\frac{1}{2}$	152.06	119.43	44.723	35.125	$1\frac{1}{2}$	319.08	250.61	93.848	73.708
$1\frac{5}{8}$	154.91	121.67	45.563	35.785	$1\frac{5}{8}$	323.21	253.85	95.063	74.662
$1\frac{3}{4}$	157.79	123.93	46.110	36.450	$1\frac{3}{4}$	327.37	257.12	96.285	75.622
$1\frac{7}{8}$	160.70	126.22	47.266	37.122	$1\frac{7}{8}$	331.55	260.40	97.516	76.589
$2$	163.64	128.52	48.129	37.800	$2$	335.76	263.71	98.754	77.561
7	166.60	130.85	49.000	38.485	10	340.00	267.04	100.000	78.540
$\frac{1}{8}$	169.59	133.19	49.879	39.175	$\frac{1}{8}$	344.26	270.38	101.254	79.525
$\frac{1}{4}$	172.60	135.56	50.766	39.871	$\frac{1}{4}$	348.55	273.75	102.516	80.516
$\frac{3}{8}$	175.64	137.95	51.660	40.574	$\frac{3}{8}$	352.87	277.14	103.785	81.513
$\frac{1}{2}$	178.71	140.36	52.563	41.282	$\frac{1}{2}$	357.21	280.55	105.063	82.516
$\frac{5}{8}$	181.81	142.79	53.473	41.997	$\frac{5}{8}$	361.58	283.99	106.348	83.525
$\frac{3}{4}$	184.93	145.24	54.391	42.718	$\frac{3}{4}$	365.98	287.44	107.641	84.541
$\frac{7}{8}$	188.07	147.71	55.316	43.445	$\frac{7}{8}$	370.40	290.91	108.941	85.563
$1$	191.25	150.21	56.250	44.179	$1$	374.85	294.41	110.250	86.590
$1\frac{1}{8}$	194.45	152.72	57.191	44.918	$1\frac{1}{8}$	379.33	297.92	111.566	87.624
$1\frac{1}{4}$	197.68	155.26	58.141	45.664	$1\frac{1}{4}$	383.83	301.46	112.891	88.664
$1\frac{3}{8}$	200.93	157.81	59.098	46.415	$1\frac{3}{8}$	388.36	305.02	114.223	89.710
$1\frac{1}{2}$	204.21	160.39	60.063	47.173	$1\frac{1}{2}$	392.91	308.59	115.563	90.763
$1\frac{5}{8}$	207.52	162.99	61.035	47.937	$1\frac{5}{8}$	397.49	312.19	116.910	91.821
$1\frac{3}{4}$	210.85	165.60	62.016	48.707	$1\frac{3}{4}$	402.10	315.81	118.266	92.886
$1\frac{7}{8}$	214.21	168.24	63.004	49.483	$1\frac{7}{8}$	406.74	319.45	119.629	93.957
8	217.60	170.90	64.000	50.265	11	411.40	323.11	121.000	95.033
$\frac{1}{8}$	221.01	173.58	65.004	51.054	$\frac{1}{8}$	416.09	326.80	122.379	96.116
$\frac{1}{4}$	224.45	176.29	66.016	51.849	$\frac{1}{4}$	420.80	330.50	123.766	97.205
$\frac{3}{8}$	227.92	179.01	67.035	52.649	$\frac{3}{8}$	425.54	334.22	125.160	98.301
$\frac{1}{2}$	231.41	181.75	68.063	53.456	$\frac{1}{2}$	430.31	337.97	126.563	99.402
$\frac{5}{8}$	234.93	184.52	69.098	54.269	$\frac{5}{8}$	435.11	341.73	127.973	100.510
$\frac{3}{4}$	238.48	187.30	70.141	55.088	$\frac{3}{4}$	439.93	345.52	129.391	101.623
$\frac{7}{8}$	242.05	190.11	71.191	55.914	$\frac{7}{8}$	444.78	349.33	130.816	102.743
$1$	245.65	192.93	72.250	56.745	$1$	449.65	353.16	132.250	103.869
$1\frac{1}{8}$	249.28	195.78	73.316	57.583	$1\frac{1}{8}$	454.55	357.00	133.691	105.001
$1\frac{1}{4}$	252.93	198.65	74.391	58.426	$1\frac{1}{4}$	459.48	360.87	135.141	106.139
$1\frac{3}{8}$	256.61	201.54	75.473	59.276	$1\frac{3}{8}$	464.43	364.76	136.598	107.284
$1\frac{1}{2}$	260.31	204.45	76.563	60.132	$1\frac{1}{2}$	469.41	368.68	138.063	108.434
$1\frac{5}{8}$	264.04	207.38	77.660	60.994	$1\frac{5}{8}$	474.42	372.61	139.535	109.591
$1\frac{3}{4}$	267.80	210.33	78.766	61.863	$1\frac{3}{4}$	479.45	376.56	141.016	110.754
$1\frac{7}{8}$	271.59	213.31	79.879	62.737	$1\frac{7}{8}$	484.51	380.54	142.504	111.923
9	275.40	216.30	81.000	63.617	12	489.60	384.53	144.000	113.098

**CARNEGIE STEEL COMPANY**  
**COLD TWISTED SQUARE BARS**



Size, Inches	Area, Square Inches	Weight per Foot, Pounds
2	4.0000	13.600
1 7/8	3.5156	11.953
1 3/4	3.0625	10.413
1 5/8	2.6406	8.978
1 1/2	2.2500	7.650
1 3/8	1.8906	6.428
1 1/4	1.5625	5.313
1 1/8	1.2656	4.303
1	1.0000	3.400
3/4	0.8789	2.988
7/8	0.7656	2.603
1 1/16	0.6602	2.215
3/4	0.5625	1.913
1 1/16	0.4727	1.607
5/8	0.3906	1.328
3/8	0.3164	1.076
1/2	0.2500	0.850
1/4	0.1914	0.651
3/16	0.1406	0.478
5/16	0.0977	0.332
1/4	0.0625	0.213

Cold twisted bars will conform to Manufacturers' Standard Specifications, unless otherwise specified.

# CONCRETE REINFORCEMENT BARS

## DEFORMED BARS

### CUP BAR




Section Index	Size, Inches	Weight per Foot, Pounds
*M 1528	1 1/2	7.65
*M 1530	1 1/4	5.31
*M 1531	1 3/8	4.30
*M 1532	1	3.40
*M 1533	3/8	2.60
*M 1534	3/4	1.91
*M 1535	5/8	1.33
*M 1536	1/2	0.85
*M 1537	3/8	0.48

\* Furnished only by special arrangement.


# CARNEGIE STEEL COMPANY

## DEFORMED BARS—Continued

### CORRUGATED SQUARE BAR TYPE A




### CORRUGATED SQUARE BAR TYPE B




Rolled for Corrugated Bar Co.

### CORRUGATED ROUND BAR TYPE C



### CORRUGATED SQUARE BAR TYPE D



Rolled for Corrugated Bar Co.

Section Index	Size, Inches	Weight per Foot, Pounds	Section Index	Size, Inches	Weight per Foot, Pounds
Corrugated Square Bar—Type A			Corrugated Square Bar—Type B		
*M 1980	1 1/4	4.00	*M 1550	1 1/4	5.31
*M 1981	1	2.70	*M 1551	1	3.40
*M 1982	3/8	1.95	*M 1552	3/8	2.60
*M 1983	3/4	1.35	*M 1553	3/4	1.91
*M 1984	1/2	0.64	*M 1554	5/8	1.33
			*M 1555	1/2	0.85
			*M 1558	3/8	0.48
			*M 1557	1/8	0.37
			*M 1556	1/4	0.21
Corrugated Round Bar—Type C			Corrugated Square Bar—Type D		
*M 1618	1 1/4	4.21	*M 1732	1 3/4	10.48
*M 1617	1 1/8	3.41	*M 1731	1 1/2	7.69
*M 1616	1	2.69	*M 1650	1 1/4	5.35
*M 1615	3/8	2.06	*M 1651	1 1/8	4.34
*M 1614	3/4	1.52	*M 1652	1	3.43
*M 1613	5/8	1.05	*M 1653	3/8	2.64
*M 1612	9/16	0.86	*M 1654	3/4	1.94
*M 1611	1/2	0.66	*M 1655	5/8	1.35
*M 1610	3/8	0.38	*M 1656	1/2	0.86
			*M 1657	3/8	0.49
			*M 1658	1/4	0.22

\* Furnished only by special arrangement.

# CONCRETE REINFORCEMENT BARS

## DEFORMED BARS—Continued .

LUG BAR—TYPE A



LUG BAR—TYPE B



Rolled for Corrugated Bar Co.

HERRINGBONE BAR



Rolled for Corrugated Bar Co.

Section Index	Size, Inches	Weight per Foot, Pounds	Section Index	Size, Inches	Weight per Foot, Pounds
Lug Bar—Type A			Lug Bar—Type B		
*M 1578	1 1/4	5.31	*M 1648	1 1/4	5.31
*M 1577	1 3/8	4.30	*M 1647	1 3/8	4.30
*M 1576	1	3.40	*M 1646	1	3.40
*M 1575	7/8	2.60	*M 1645	7/8	2.60
*M 1574	3/4	1.91	*M 1644	3/4	1.91
*M 1573	5/8	1.33	*M 1643	5/8	1.33
*M 1572	1/2	0.85	*M 1642	1/2	0.85
*M 1579	3/16	0.65	*M 1641	3/8	0.48
*M 1571	3/8	0.48	*M 1640	1/4	0.21
*M 1570	1/4	0.21			

Herringbone Bar

Section Index	Size, Inches	Weight per Foot, Pounds
*M 1673	1 1/4	5.13
*M 1672	1 1/4	3.62
*M 1671	1	2.38
*M 1670	3/4	1.72
*M 1669	3/4	1.28
*M 1668	5/8	0.91

\* Furnished only by special arrangement.



# CARNEGIE STEEL COMPANY

## DEFORMED BARS—Continued


### HAVEMEYER SQUARE BAR



### HAVEMEYER ROUND BAR



Rolled for Concrete Steel Co.  
ELCANNES BAR



Rolled for Mr. Elie Cannies

Section Index	Size, Inches	Weight per Foot, Pounds	Section Index	Size, Inches	Weight per Foot, Pounds
Havemeyer Square Bar			Havemeyer Round Bar		
*M 1599	1 1/2	7.65			
*M 1609	1 3/8	6.43			
*M 1608	1 1/4	5.31	*M 1629	1 1/4	4.17
*M 1607	1 1/8	4.30	*M 1628	1 1/8	3.38
*M 1606	1	3.40	*M 1627	1	2.67
*M 1605	7/8	2.60	*M 1626	7/8	2.04
*M 1604	3/4	1.91	*M 1625	3/4	1.50
*M 1603	5/8	1.33	*M 1624	5/8	1.04
*M 1602	1/2	0.85	*M 1623	1/2	0.67
*M 1601	3/8	0.48	*M 1622	3/8	0.38
*M 1598	5/16	0.33	*M 1600	1/4	0.17
*M 1621	1/4	0.21			

### Elcannes Bar

Section Index	Size, Inches	Weight per Foot, Pounds
*M 1901	1 1/4	5.31
*M 1902	1 1/8	4.30
*M 1903	1	3.40
*M 1904	7/8	2.60
*M 1905	3/4	1.91
*M 1906	5/8	1.33
*M 1907	1/2	0.85
*M 1908	3/8	0.48

\*Furnished only by special arrangement.


# CONCRETE REINFORCEMENT BARS

## DEFORMED BARS—Concluded

WING BAR—TYPE A




WING BAR—TYPE B

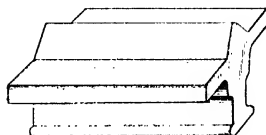

Rolled for Trussed Concrete Steel Co.

## NEW RIB BAR



Rolled for Trussed Concrete Steel Co.

Section Index	Size, Inches	Weight per Foot, Pounds	Section Index	Size, Inches	Weight per Foot, Pounds
Wing Bar—Type A			Wing Bar—Type B		
*M 1513	$\frac{3}{4}$	2.70	*M 1509	$3\frac{1}{2}$	10.2
*M 1512	$1\frac{1}{2}$	1.10	*M 1510	$2\frac{3}{4}$	6.8
			*M 1516	$2\frac{1}{4}$	4.8

## New Rib Bar


Section Index	Size, Inches	Weight per Foot, Pounds
*M 1918	$1\frac{1}{4}$	5.31
*M 1917	$1\frac{1}{8}$	4.30
*M 1916	1	3.10
*M 1915	$\frac{7}{8}$	2.60
*M 1914	$\frac{3}{4}$	1.91
*M 1913	$\frac{5}{8}$	1.33
*M 1912	$\frac{1}{2}$	0.85
*M 1911	$\frac{3}{8}$	0.48
*M 1910	$\frac{1}{4}$	0.21

\*Furnished only by special arrangement.

# CARNEGIE STEEL COMPANY


## DEFORMED BARS—Continued

### MONOTYPE BAR



Rolled for Philadelphia Steel and Wire Co.

### WING BAR



Rolled for  
Thomas Reinforcement Co.

### SLANT RIB BAR



Rolled for  
Mississippi Valley Construction Co.


Section Index	Size, Inches	Weight per Foot, Pounds	Section Index	Size, Inches	Weight per Foot, Pounds
Monotype Bar—Equivalent to Square			Monotype Bar—Equivalent to Round		
*M 2151	1 1/4	5.39	*M 2161	1 1/4	4.24
*M 2152	1 3/8	4.37	*M 2162	1 3/8	3.43
*M 2153	1	3.45	*M 2163	1	2.71
*M 2154	7/8	2.64	*M 2164	7/8	2.08
*M 2155	3/4	1.94	*M 2165	3/4	1.53
*M 2156	5/8	1.35	*M 2166	5/8	1.06
*M 2157	1/2	0.86	*M 2167	1/2	0.68
*M 2158	3/8	0.49	*M 2168	3/8	0.38
Wing Bar			Slant Rib Bar		
*M 2135	2 1/4	5.08	*M 1297	1 1/4	5.31
*M 2134	2	4.02	*M 1296	1	3.40
*M 2133	1 3/4	3.06	*M 1295	3/8	2.60
*M 2132	1 1/2	2.08	*M 1294	3/4	1.91
*M 2131	1 1/8	1.08	*M 1293	5/8	1.33
			*M 1292	1/2	0.85
			*M 1291	3/8	0.48
			*M 1290	1/4	0.21

\* Furnished only by special arrangement.


# CONCRETE REINFORCEMENT BARS

## DEFORMED BARS—Continued


SCOFIELD BAR



THACHER BAR



MONOLITH BAR



Section Index	Size, Inches	Weight per Foot, Pounds	Section Index	Size, Inches	Weight per Foot, Pounds
Scofield Bar			Thacher Bar		
		Equivalent to Round			
*M 1969	1 1/2	6.01	*M 1546	1 1/2	5.20
*M 1968	1 1/4	4.17	*M 1545	1 1/4	3.55
*M 1967	1 1/8	3.38	*M 1544	1	2.32
*M 1966	1	2.67	*M 1543	7/8	1.79
*M 1965	3/8	2.04	*M 1542	3/4	1.34
*M 1964	3/4	1.50	*M 1541	5/8	0.92
*M 1963	5/8	1.04	*M 1540	1/2	0.58
*M 1962	1/2	0.67			
*M 1961	3/8	0.38			
		Equivalent to Square			
*M 1583	5/8	1.33			
*M 1582	1/2	0.85			
*M 1581	3/8	0.48			


Monolith Bar

Section Index	Size, Inches	Weight per Foot, Pounds
*M 1500	1 1/2	7.65
*M 1508	1 1/4	5.31
*M 1507	1	3.40
*M 1517	3/4	1.91
*M 1506	5/8	1.33
*M 1505	1/2	0.85
*M 1504	3/8	0.48

\*Furnished only by special arrangement.


# CARNEGIE STEEL COMPANY

## GIRDER BAR SECTIONS

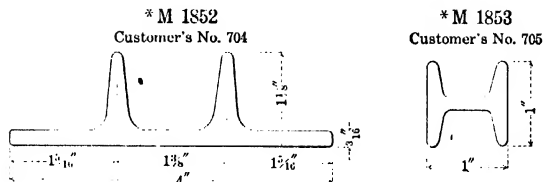


## WASHBOARD SECTION - TYPE A

**\* M 1521**



## WASHBOARD SECTION - TYPE B

**\* M 1522**




Rolled for Trussed Concrete Steel Co.

Section Index	Size, Inches	Weight per Foot, Pounds
*M 1852	4 x 1 1/8 x 3/16	4.1
*M 1853	1 x 1 x 5/16	1.52
*M 1521	6 1/2 x 3/16 x 3/16	3.20
*M 1522	6 1/2 x 5/16 x 3/16	3.95

\*Rolled only by special arrangement.

# CONCRETE REINFORCEMENT BARS

## HANGER BARS

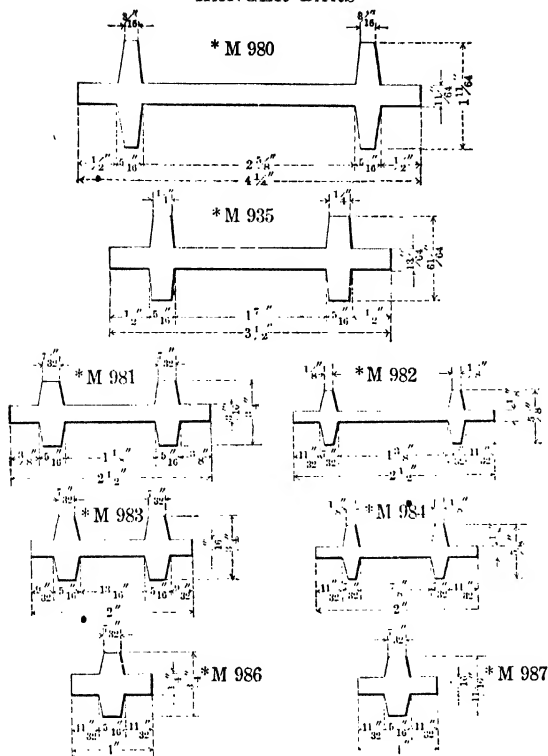


Section Index	Size, Inches	Thickness, Inches	Weight per Foot, Pounds
*M 980	4 1/4 x 1 1/4	1 1/4	5.31
	4 1/4 x 1 3/8	1 3/8	4.63
	4 1/4 x 1 1/2	1 1/2	4.18
*M 935	3 1/2 x 1 1/4	1 1/4	4.41
	3 1/2 x 1 3/8	1 3/8	3.85
*M 981	2 1/2 x 1 1/4	1 1/4	2.61
*M 982	2 1/2 x 1 3/8	1 3/8	1.65
*M 983	2 x 1 1/4	1 1/4	2.29
*M 984	2 x 1 3/8	1 3/8	1.43
*M 986	1 x 1 1/4	1 1/4	1.30
*M 987	1 x 1 3/8	1 3/8	1.09

\* Furnished only by special arrangement.

# CARNEGIE STEEL COMPANY

## CROSS TIE SECTIONS





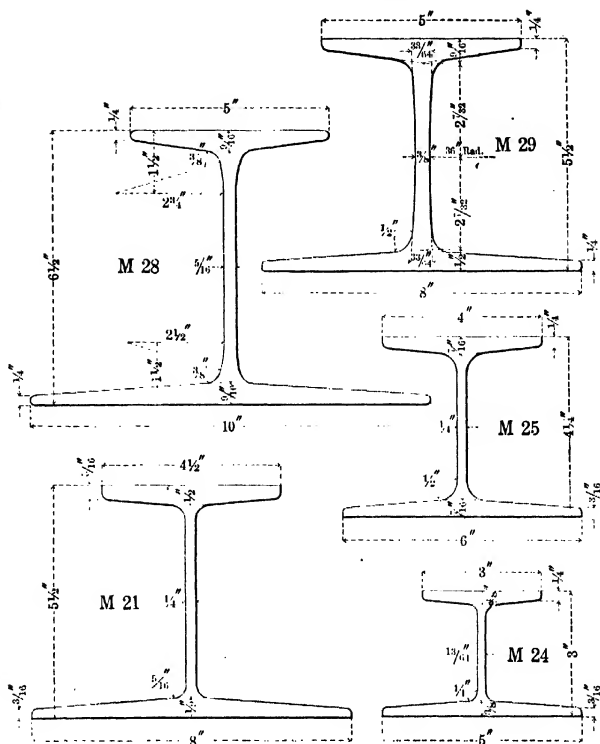


Section Index	Depth, Inches	Width of Flanges		Web Thickness, Inches	Weight per Foot, Pounds
		Top, Inches	Bottom, Inches		
M 28	6 1/2	5	10	5/16	27.8
M 29	5 1/2	5	8	3/8 to 33/64	23.5
M 21	5 1/2	4 1/2	8	1/4	20.0
M 25	4 1/4	4	6	1/4	14.5
M 24	3	3	5	13/64	9.5

Full information as to uses of steel cross ties is given in a separate pamphlet on Steel Cross Ties.

# CROSS TIES

## CROSS TIE SECTIONS—Concluded

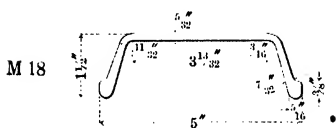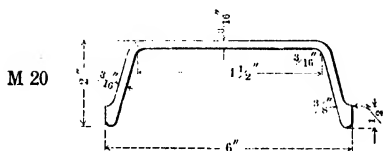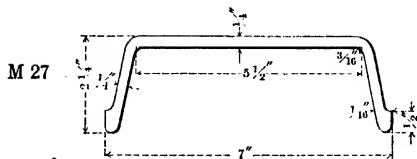


Section Index	Depth, Inches	Width, Inches	Web Thickness, Inches	Weight per Foot, Pounds
M 27	2 1/4	7	1/4	9.0
M 20	2	6	3/16	6.0
M 18	1 1/2	5	5/32	4.0
M 26	1 13/16	4 15/16	1/8	3.20
M 19	1 1/8	4	3/64	2.50

Full information as to uses of steel cross ties is given in a separate pamphlet on Steel Cross Ties.



# CARNEGIE STEEL COMPANY


## A. S. C. E. RAILS AND LIGHT RAILS



Section Index	Weight per Yard, Pounds	a	b	c	d	e	f	g	h	i	j	k	l
		In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.
10040	100	5 $\frac{3}{4}$	5 $\frac{3}{4}$	2 $\frac{3}{4}$	1 $\frac{1}{2}$	3 $\frac{1}{2}$	3 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
9040	90	5 $\frac{3}{8}$	5 $\frac{3}{8}$	2 $\frac{5}{8}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
8540	85	5 $\frac{1}{8}$	5 $\frac{1}{8}$	2 $\frac{7}{8}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
8040	80	5	5	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
7540	75	4 $\frac{1}{2}$	4 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
7040	70	4 $\frac{1}{2}$	4 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
6540	65	4 $\frac{1}{2}$	4 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
6040	60	4 $\frac{1}{2}$	4 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
5540	55	4 $\frac{1}{2}$	4 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
5040	50	3 $\frac{3}{8}$	3 $\frac{3}{8}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
4540	45	3 $\frac{1}{2}$	3 $\frac{1}{2}$	2	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
4040	40	3 $\frac{1}{2}$	3 $\frac{1}{2}$	1 $\frac{7}{8}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
3540	35	3 $\frac{1}{2}$	3 $\frac{1}{2}$	1 $\frac{3}{4}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
3040	30	3 $\frac{1}{2}$	3 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
2540	25	2 $\frac{3}{4}$	2 $\frac{3}{4}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
2040	20	2 $\frac{3}{4}$	2 $\frac{3}{4}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
1640	16	2 $\frac{3}{4}$	2 $\frac{3}{4}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
1440	14	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
1240	12	2	2	1	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
1040	10	1 $\frac{3}{4}$	1 $\frac{3}{4}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$
840	8	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$


## RAILS

## AMERICAN RAILWAY ASSOCIATION RAILS



SERIES A

Section Index	Weight Per Yard, Pounds	a	b	c	d	e	f	g	h	i	j	k	l
		In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.
10020	100	6	5 $\frac{1}{2}$	2 $\frac{3}{4}$	1 $\frac{1}{8}$	3 $\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$	2 $\frac{1}{8}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$
9020	90	5 $\frac{5}{8}$	5 $\frac{1}{8}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	3 $\frac{1}{2}$	1	1 $\frac{1}{8}$	2 $\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$
8020	80	5 $\frac{1}{8}$	4 $\frac{3}{8}$	2 $\frac{1}{2}$	1 $\frac{1}{8}$	2 $\frac{3}{4}$	$\frac{3}{2}$	$\frac{3}{4}$	2 $\frac{1}{8}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$
7020	70	4 $\frac{3}{4}$	4 $\frac{1}{4}$	2 $\frac{3}{8}$	1 $\frac{1}{4}$	2 $\frac{1}{2}$	$\frac{5}{8}$	$\frac{1}{2}$	2 $\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$
6020	60	4 $\frac{1}{2}$	4	2 $\frac{1}{4}$	1 $\frac{1}{4}$	2 $\frac{1}{4}$	$\frac{1}{2}$	$\frac{1}{2}$	2 $\frac{1}{4}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$



SERIES B

Section Index	Weight Per Yard, Pounds	a	b	c	d	e	f	g	h	i	j	k	l
		In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.
*10030	100	5 $\frac{1}{4}$	5 $\frac{3}{4}$	2 $\frac{3}{4}$	1 $\frac{1}{4}$	2 $\frac{3}{4}$	1 $\frac{1}{4}$	1 $\frac{1}{4}$	2 $\frac{3}{4}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$
*9030	90	5 $\frac{1}{8}$	4 $\frac{7}{8}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{8}$	2 $\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$
*8030	80	4 $\frac{1}{2}$	4 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	2 $\frac{1}{2}$	1	$\frac{3}{4}$	2 $\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$
*7030	70	4 $\frac{3}{8}$	4 $\frac{1}{4}$	2 $\frac{3}{8}$	1 $\frac{1}{4}$	2 $\frac{1}{4}$	$\frac{5}{8}$	$\frac{1}{2}$	2 $\frac{1}{4}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$
*6030	60	4 $\frac{1}{8}$	3 $\frac{1}{8}$	2 $\frac{3}{8}$	1 $\frac{1}{4}$	2 $\frac{1}{8}$	$\frac{3}{8}$	$\frac{1}{2}$	2 $\frac{1}{8}$	$\frac{3}{8}$	$\frac{3}{8}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$

\* Not rolled by Carnegie Steel Company.

# CARNEGIE STEEL COMPANY

## SPLICE BARS

### A. S. C. E. RAILS AND LIGHT RAILS


S 10040 to S 5540

S 5040 to S 3040

S 2540

S 2040

S 1640 to S 840

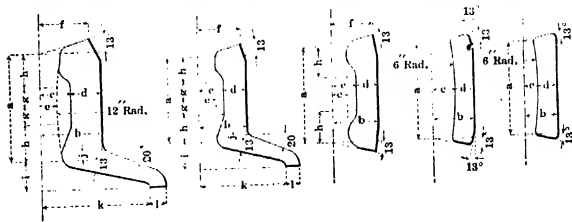


Section Index	Weight per Foot, Unfinished	a	b	c	d	e	f	g	h	i	j	k	l
	Pounds	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.
S 10040	15.80	3 5/8	1 3/4	3 3/4	7/8	1 1/2	1 3/8	1/2	1 5/8	3/8	3/8	3 1/8	1/4
S 9010	13.50	2 3/4	1 5/8	3 1/8	1 1/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 8510	12.40	2 3/4	1 3/4	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 8040	11.50	2 3/8	1 3/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 7540	10.70	2 3/8	1 3/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 7040	10.00	2 3/8	1 3/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 6540	9.20	2 3/8	1 3/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 6040	8.40	2 3/8	1 3/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 5540	7.50	2 3/8	1 3/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 5040	6.62	2 3/8	1 3/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 4540	5.80	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 4040	5.00	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 3540	4.58	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 3040	3.97	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 2540	2.20	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 2040	1.87	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 1640	1.70	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 1440	1.36	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 1240	1.36	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 1040	0.985	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8
S 840	0.747	1 3/4	1 1/8	3 1/8	3/4	1 1/2	1 1/8	1/2	1 1/2	3/8	3/8	2 1/8	3/8

Splice Bars S 10040 to S 5040, inclusive, are for A. S. C. E. Rails.  
Splice Bars S 4540 to S 840, inclusive, are for Light Rails.

# SPLICE BARS

## SPLICE BARS—Concluded


### AMERICAN RAILWAY ASSOCIATION RAILS



SERIES A


Section Index	Weight per Foot, Unfinished Pounds	a	b	c	d	e	f	g	g¹	h	i	j	k	l
		In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.
S 10020	19.04	3 3/8	1 1/2	3/4	3/4	3/4	1 3/8	1 3/8	3/4	3/4	1	1 1/2	3 3/8	7/8
S 9020	16.64	3 1/2	1 1/2	3/4	3/4	3/4	1 3/8	1 3/8	3/4	3/4	1	1 1/2	3 3/8	7/8
S 8020	13.43	2 3/4	1 1/2	3/4	3/4	3/4	1 3/8	1 3/8	3/4	3/4	1	1 1/2	2 3/4	3/4
S 7020	11.64	2 1/2	1 1/2	3/4	3/4	3/4	1 3/8	1 3/8	3/4	3/4	1	1 1/2	2 1/2	3/4
S 6020	10.63	2 1/4	1 1/2	3/4	3/4	3/4	1 3/8	1 1/2	3/4	3/4	1	1 1/2	2 1/4	3/4

S 10030



SERIES B

S 9030 to S 6030



Section Index	Weight per Foot, Unfinished Pounds	a	b	c	d	e	f	g	g¹	h	i	j	k	l
		In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.
S 10030	16.92	2 3/4	1 1/2	3/4	3/4	3/4	1 3/8	1 3/8	3/4	3/4	1	1 1/2	3 1/4	7/8
S 9030	14.42	2 3/4	1 1/2	3/4	3/4	3/4	1 3/8	1 3/8	3/4	3/4	1	1 1/2	2 3/4	3/4
S 8030	12.65	2 1/4	1 1/2	3/4	3/4	3/4	1 3/8	1 1/2	3/4	3/4	1	1 1/2	2 1/4	3/4
*S 7030	11.90	2 1/4	1 1/2	3/4	3/4	3/4	1 3/8	1 1/2	3/4	3/4	1	1 1/2	2 1/4	3/4
*S 6030	9.50	2 1/4	1 1/2	3/4	3/4	3/4	1 3/8	1 1/2	3/4	3/4	1	1 1/2	2 1/4	3/4

\*Not rolled by Carnegie Steel Company.

**CARNEGIE STEEL COMPANY**


## TABLE OF RAILS AND ACCESSORIES

Rail Section	Weight per Yard	Height of Rail	Base of Rail	Length of Space Bar	Size of Bolt	Size of Spike	One Rail Joint			Accessories for 1000 Tons of Rails			Material for One Mile of Single Track											
							Weight in Pounds	Number	Spikes	Weight in Gross Tons	Number	Spikes	Weight in Gross Tons	Number	Spikes	Weight in Gross Tons								
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	15714	17406
00040	100 57 3/4	3 3/4	1 1/2 x 3 1/2	1 1/2	1 1/2	1 1/2	9.70	95.35	2075	13190	73312	73312	848	1835	10756	326	1936	11520	1247	141	3303	16391	1	


Rails 50 pounds and over—Basis of table, 90° furnished 33 ft. and 100° not less than 31 ft. long, varying by 1 ft. feet. This 22 in. centers, 2880 tons per mile.  
 Rails 45 pounds and under—Basis of table, 90° furnished 30 ft. and 100° not less than 29 ft. long. This 24 in. centers, 2640 tons per mile.  
 Number and weight of accessories do not allow for any excess. Rails marked "C" rolled by Carnegie Steel Company.

# RAIL ACCESSORIES


## RAIL CLIPS




No. 103




No. 114

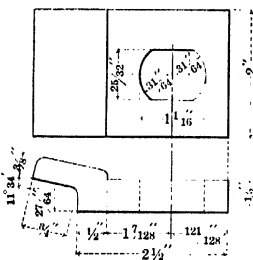

No. 118

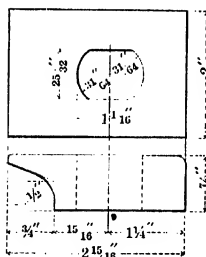

No. 10



No. 108

Rail Clip No.	Size, Inches	Weight per Foot, Pounds	Weight of Finished Clip, Pounds	Rail Section
103	2 1/4 x 2	4.4	0.64	100 to 60 lb. A. S. C. E. Rails.
114	1 1/2 x 1 1/2	2.3	0.25	50 to 20 lb. A. S. C. E. Rails.
118	2 1/2 x 2	5.65	0.85	100 to 60 lb. R. B. Rails.
104	2 1/2 x 2	7.3	1.10	100 to 60 lb. A.S.C.E. Angle Bars
108	2 1/4 x 2	4.8	0.70	Girder Rails.

Clips can be furnished with 3/8" diameter holes.

CARNEGIE STEEL COMPANY

PIPE—BLACK AND GALVANIZED

NATIONAL TUBE COMPANY STANDARD

STANDARD PIPE

Size, In.	Diameters, Inches		Thick- ness, Inches	Weight per Foot, Pounds		Threads per Inch	Couplings		
	External	Internal		Plain Ends	Threads and Couplings		Diameter, Inches	Length, Inches	Weight, Pounds
$\frac{1}{8}$	.405	.269	.068	.244	.245	27	.562	$\frac{7}{8}$	.029
$\frac{1}{4}$	.540	.364	.088	.424	.425	18	.685	1	.043
$\frac{3}{8}$	.675	.493	.091	.567	.568	18	.848	$1\frac{1}{8}$	.070
$\frac{1}{2}$	.840	.622	.109	.850	.852	14	1.024	$1\frac{1}{8}$	.116
$\frac{3}{4}$	1.050	.824	.113	1.130	1.134	14	1.281	$1\frac{1}{8}$	.209
1	1.315	1.049	.133	1.678	1.684	$11\frac{1}{2}$	1.576	$1\frac{1}{8}$	.343
$1\frac{1}{4}$	1.660	1.380	.140	2.272	2.281	$11\frac{1}{2}$	1.950	$2\frac{1}{8}$	.535
$1\frac{1}{2}$	1.900	1.610	.145	2.717	2.731	$11\frac{1}{2}$	2.218	$2\frac{1}{8}$	.743
2	2.375	2.067	.154	3.652	3.678	$11\frac{1}{2}$	2.760	$2\frac{1}{8}$	1.208
$2\frac{1}{2}$	2.875	2.469	.203	5.793	5.819	8	3.276	$2\frac{1}{8}$	1.720
3	3.500	3.068	.216	7.575	7.616	8	3.948	$3\frac{1}{8}$	2.498
$3\frac{1}{2}$	4.000	3.548	.226	9.109	9.202	8	4.591	$3\frac{1}{8}$	4.241
4	4.500	4.024	.237	10.790	10.889	8	5.091	$3\frac{1}{8}$	4.741
$4\frac{1}{2}$	5.000	4.506	.247	12.538	12.642	8	5.591	$3\frac{1}{8}$	5.241
5	5.563	5.047	.258	14.617	14.810	8	6.296	$4\frac{1}{8}$	8.091
6	6.625	6.065	.280	18.974	19.185	8	7.358	$4\frac{1}{8}$	9.554
7	7.625	7.023	.301	23.544	23.769	8	8.358	$4\frac{1}{8}$	10.932
8	8.625	8.071	.277	24.696	25.000	8	9.358	$4\frac{1}{8}$	13.905
8	8.625	7.981	.322	28.554	28.809	8	9.358	$4\frac{1}{8}$	13.905
9	9.625	8.941	.342	33.907	34.188	8	10.358	$5\frac{1}{8}$	17.236
10	10.750	10.192	.279	31.201	32.000	8	11.721	$6\frac{1}{8}$	29.877
10	10.750	10.136	.307	34.240	35.000	8	11.721	$6\frac{1}{8}$	29.877
10	10.750	10.020	.365	40.483	41.132	8	11.721	$6\frac{1}{8}$	29.877
11	11.750	11.000	.375	45.557	46.247	8	12.721	$6\frac{1}{8}$	32.550
12	12.750	12.090	.330	43.773	45.000	8	13.958	$6\frac{1}{8}$	43.098
12	12.750	12.000	.375	49.562	50.706	8	13.958	$6\frac{1}{8}$	43.098
13	14.000	13.250	.375	54.568	55.824	8	15.208	$6\frac{1}{8}$	47.152
14	15.000	14.250	.375	58.573	60.375	8	16.446	$6\frac{1}{8}$	59.493
15	16.000	15.250	.375	62.579	64.500	8	17.446	$6\frac{1}{8}$	63.294

The permissible variation in weight is 5 per cent. above and 5 per cent. below.

Furnished with threads and couplings and in random lengths unless otherwise ordered.

Taper of threads is  $\frac{3}{4}$ " diameter per foot length for all sizes.

The weight per foot of pipe with threads and couplings is based on a length of 20 feet, including the coupling, but shipping lengths of small sizes will usually average less than 20 feet.

All weights and dimensions are nominal. On sizes made in more than one weight, weight desired must be specified.

# PIPE

## PIPE—BLACK AND GALVANIZED—Concluded

NATIONAL TUBE COMPANY STANDARD

### EXTRA STRONG PIPE

### DOUBLE EXTRA STRONG PIPE

Size, In.	Diameters, Inches		Thick- ness, Inches	Weight, per Foot, Pounds	Size, In.	Diameters, Inches		Thick- ness, Inches	Weight per Foot, Pounds
	External	Internal				External	Internal		
1/8	.405	.215	.095	.314	1/2	.840	.252	.294	1.714
1/4	.540	.302	.119	.535	3/4	1.050	.434	.308	2.440
3/8	.675	.423	.126	.738	1	1.315	.599	.358	3.650
1/2	.840	.546	.147	1.087	1 1/4	1.660	.896	.382	5.214
3/4	1.050	.742	.154	1.473	1 1/2	1.900	1.100	.400	6.408
1	1.215	.957	.179	2.171	2	2.375	1.503	.436	9.029
1 1/4	1.660	1.278	.191	2.906	2 1/2	2.875	1.771	.552	13.695
1 1/2	1.900	1.500	.200	3.631	3	3.500	2.300	.600	18.583
2	2.375	1.939	.218	5.022	3 1/2	4.000	2.728	.636	22.850
2 1/2	2.875	2.323	.276	7.091	4	4.500	3.152	.674	27.541
3	3.500	2.900	.300	10.252	4 1/2	5.000	3.580	.710	32.530
3 1/2	4.000	3.364	.318	12.505	5	5.563	4.063	.750	38.552
4	4.500	3.826	.337	14.983	6	6.625	4.897	.864	53.160
4 1/2	5.000	4.290	.355	17.611	7	7.625	5.875	.875	63.079
5	5.563	4.813	.375	20.778	8	8.625	6.875	.875	72.424
6	6.625	5.761	.432	28.573					
7	7.625	6.625	.500	38.048					
8	8.625	7.625	.500	43.388					
9	9.625	8.625	.500	48.728					
10	10.750	9.750	.500	54.735					
11	11.750	10.750	.500	60.075					
12	12.750	11.750	.500	65.415					
13	14.000	13.000	.500	72.091					
14	15.000	14.000	.500	77.431					
15	16.000	15.000	.500	82.771					

Furnished with plain ends and in random lengths unless otherwise ordered.  
Permissible variation in weight, for extra strong pipe, 5 per cent. above and 5 per cent. below.  
For double extra strong pipe, 10 per cent. above and 10 per cent. below.  
All weights and dimensions are nominal.

### LARGE O. D. PIPE

Size, In.	Weight per Foot, Pounds									
	Thickness, Inches									
	1/4	3/16	1/2	3/8	1/2	3/4	1	1 1/4	1 1/2	1
14	36.713	45.082	54.568	63.371	72.091	80.726	89.279	106.134	122.654	138.842
15	39.383	49.020	58.573	68.044	77.431	86.734	95.954	114.144	132.000	149.522
16	42.053	52.357	62.579	72.716	82.771	92.742	102.629	122.154	141.345	160.202
17	44.723	55.695	66.584	77.389	88.111	98.749	109.304	130.164	150.690	170.882
18	47.393	59.032	70.589	82.061	93.451	104.757	115.979	138.174	160.035	181.562
20	65.708	78.599	91.407	104.131	116.772	129.330	154.194	178.725	202.022	
21	69.045	82.604	96.079	109.471	122.780	136.005	162.204			
22	72.383	86.609	100.752	114.811	128.787	142.680	170.215			
24		94.619	110.097	125.491	140.802	156.030	186.235			
26		102.629	119.442	136.172	152.818	169.380	202.255			
28					128.787	146.852	164.833	182.730	218.275	
30					138.132	157.532	176.848	196.081	234.296	

Furnished with plain ends and in random lengths, unless otherwise ordered.  
All weights and dimensions are nominal.




# CARNEGIE STEEL COMPANY

## SCREW THREADS

AMERICAN BRIDGE COMPANY STANDARD


BOLTS, RODS, EYE BARS, TURNBUCKLES, SLEEVE NUTS, AND CLEVISSES

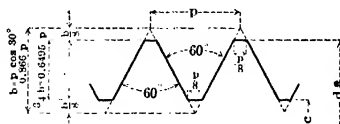

Diameter		Area		Number of Threads per Inch	Diameter		Area		Number of Threads per Inch
Total d, In.	Net, C, In.	Total Dia. d, Sq. In.	Net C, Sq. In.		Total, d, In.	Net, C, In.	Total Dia. d, Sq. In.	Net C, Sq. In.	
1/4	.185	.049	.027	20	2 1/2	2.175	4.909	3.716	4
3/8	.294	.110	.068	16	2 3/8	2.300	5.412	4.156	4
1/2	.400	.196	.126	13	2 1/2	2.425	5.910	4.619	4
5/8	.507	.307	.202	11	2 7/8	2.550	6.492	5.108	4
3/4	.620	.442	.302	10	3	2.629	7.069	5.428	3 1/2
7/8	.731	.601	.419	9	3 1/4	2.879	8.296	6.500	3 1/2
1	.838	.785	.551	8	3 1/2	3.100	9.621	7.549	3 1/4
1 1/8	.939	.991	.693	7	3 3/4	3.317	11.045	8.641	3
1 1/4	1.064	1.227	.890	7	4	3.567	12.566	9.993	3
1 3/8	1.158	1.486	1.054	6	4 1/4	3.798	14.186	11.330	2 7/8
1 1/2	1.283	1.767	1.294	6	4 1/2	4.028	15.904	12.741	2 3/4
1 3/4	1.389	2.074	1.515	5 1/2	4 3/4	4.255	17.721	14.221	2 3/4
1 7/8	1.490	2.405	1.744	5	5	4.480	19.635	15.766	2 1/2
2	1.615	2.761	2.049	5	5 1/4	4.730	21.648	17.574	2 1/2
2 1/8	1.711	3.142	2.300	4 1/2	5 1/2	4.953	23.758	19.268	2 1/2
2 1/4	1.836	3.547	2.619	4 1/2	5 3/4	5.203	25.967	21.262	2 1/2
2 1/2	1.961	3.976	3.021	4 1/2	6	5.423	28.274	23.095	2 1/4
2 3/8	2.086	4.430	3.419	4 1/2					

## BOLT HEADS AND NUTS

AMERICAN BRIDGE COMPANY STANDARD

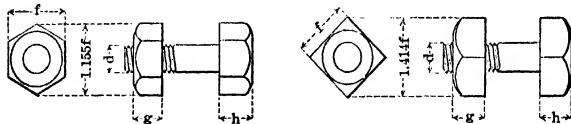







Rough Nut		Finished Nut		Rough Head		Finished Head	
f	d	f	d	f	h	f	h
1.5d + 1/4"	d	1.5d + 1/4"	d - 1/4"	1.5d + 1/4"	0.5 f	1.5d + 1/4"	0.5 f - 1/4"

For Screw Threads, Bolt Heads and Nuts, the American Bridge Company has adopted the Franklin Institute Standard, commonly known as United States Standard.

# BOLTS

## BOLT HEADS AND NUTS, DIMENSIONS IN INCHES

AMERICAN BRIDGE COMPANY STANDARD

Diameter of Bolt, Inches	HEAD						Diameter of Bolt, Inches	NUT					
	Hexagonal		Hex. or Square		Square			Hexagonal		Hex. or Square		Square	
													
	Diameter		Height		Diameter			Diameter		Height		Diameter	
	Long	Short			Long	Short		Long	Short		Long	Short	
$\frac{1}{4}$	$\frac{5}{8}$	$\frac{1}{2}$	$\frac{1}{4}$		$\frac{1}{2}$	$\frac{1}{2}$	$\frac{1}{4}$	$\frac{5}{8}$	$\frac{1}{2}$	$\frac{1}{4}$	$\frac{1}{2}$	$\frac{1}{2}$	
$\frac{3}{8}$	$1\frac{1}{4}$	$\frac{7}{8}$	$\frac{3}{8}$		$\frac{1}{2}$	$\frac{1}{2}$	$\frac{3}{8}$	$\frac{5}{8}$	$\frac{1}{2}$	$\frac{1}{4}$	$\frac{1}{2}$	$\frac{1}{2}$	
$\frac{1}{2}$	$1\frac{3}{4}$	$1\frac{1}{4}$	$\frac{1}{2}$		$\frac{1}{2}$	$\frac{1}{2}$	$\frac{1}{2}$	$1\frac{1}{4}$	$1\frac{1}{4}$	$\frac{3}{8}$	$1\frac{1}{4}$	$1\frac{1}{4}$	
$\frac{5}{8}$	$1\frac{3}{4}$	$1\frac{1}{4}$	$\frac{5}{8}$		$\frac{1}{2}$	$\frac{1}{2}$	$\frac{5}{8}$	$1\frac{1}{4}$	$1\frac{1}{4}$	$\frac{3}{8}$	$1\frac{1}{4}$	$1\frac{1}{4}$	
$\frac{3}{4}$	$1\frac{3}{4}$	$1\frac{1}{4}$	$\frac{3}{4}$		$\frac{1}{2}$	$\frac{1}{2}$	$\frac{3}{4}$	$1\frac{1}{4}$	$1\frac{1}{4}$	$\frac{3}{8}$	$1\frac{1}{4}$	$1\frac{1}{4}$	
$1$	$1\frac{3}{4}$	$1\frac{1}{4}$	$1$		$\frac{1}{2}$	$\frac{1}{2}$	$1$	$1\frac{1}{4}$	$1\frac{1}{4}$	$\frac{3}{8}$	$1\frac{1}{4}$	$1\frac{1}{4}$	
$1\frac{1}{8}$	$2\frac{1}{8}$	$1\frac{7}{8}$	$1\frac{1}{8}$		$\frac{1}{2}$	$\frac{1}{2}$	$1\frac{1}{8}$	$2\frac{1}{8}$	$1\frac{7}{8}$	$\frac{3}{8}$	$2\frac{1}{8}$	$1\frac{7}{8}$	
$1\frac{1}{4}$	$2\frac{1}{8}$	$1\frac{7}{8}$	$1\frac{1}{4}$		$\frac{1}{2}$	$\frac{1}{2}$	$1\frac{1}{4}$	$2\frac{1}{8}$	$1\frac{7}{8}$	$\frac{3}{8}$	$2\frac{1}{8}$	$1\frac{7}{8}$	
$1\frac{3}{8}$	$2\frac{1}{8}$	$1\frac{7}{8}$	$1\frac{3}{8}$		$\frac{1}{2}$	$\frac{1}{2}$	$1\frac{3}{8}$	$2\frac{1}{8}$	$1\frac{7}{8}$	$\frac{3}{8}$	$2\frac{1}{8}$	$1\frac{7}{8}$	
$1\frac{1}{2}$	$2\frac{1}{8}$	$1\frac{7}{8}$	$1\frac{1}{2}$		$\frac{1}{2}$	$\frac{1}{2}$	$1\frac{1}{2}$	$2\frac{1}{8}$	$1\frac{7}{8}$	$\frac{3}{8}$	$2\frac{1}{8}$	$1\frac{7}{8}$	
$1\frac{5}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$1\frac{5}{8}$		$\frac{1}{2}$	$\frac{1}{2}$	$1\frac{5}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$\frac{3}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	
$1\frac{3}{4}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$1\frac{3}{4}$		$\frac{1}{2}$	$\frac{1}{2}$	$1\frac{3}{4}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$\frac{3}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	
$2$	$3\frac{1}{8}$	$2\frac{3}{4}$	$2$		$\frac{1}{2}$	$\frac{1}{2}$	$2$	$3\frac{1}{8}$	$2\frac{3}{4}$	$\frac{3}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	
$2\frac{1}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$2\frac{1}{8}$		$\frac{1}{2}$	$\frac{1}{2}$	$2\frac{1}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$\frac{3}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	
$2\frac{1}{4}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$2\frac{1}{4}$		$\frac{1}{2}$	$\frac{1}{2}$	$2\frac{1}{4}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$\frac{3}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	
$2\frac{3}{4}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$2\frac{3}{4}$		$\frac{1}{2}$	$\frac{1}{2}$	$2\frac{3}{4}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$\frac{3}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	
$3$	$3\frac{1}{8}$	$2\frac{3}{4}$	$3$		$\frac{1}{2}$	$\frac{1}{2}$	$3$	$3\frac{1}{8}$	$2\frac{3}{4}$	$\frac{3}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	
$3\frac{1}{4}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$3\frac{1}{4}$		$\frac{1}{2}$	$\frac{1}{2}$	$3\frac{1}{4}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$\frac{3}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	
$3\frac{1}{2}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$3\frac{1}{2}$		$\frac{1}{2}$	$\frac{1}{2}$	$3\frac{1}{2}$	$3\frac{1}{8}$	$2\frac{3}{4}$	$\frac{3}{8}$	$3\frac{1}{8}$	$2\frac{3}{4}$	

## BOLT THREADS, LENGTH IN INCHES

AMERICAN BRIDGE COMPANY STANDARD

Length, Inches	Diameter, Inches								
	$\frac{1}{4}$	$\frac{3}{8}$	$\frac{1}{2}$	$\frac{5}{8}$	$\frac{3}{4}$	$1$	$1\frac{1}{8}$	$1\frac{1}{2}$	$2$
1 to $1\frac{1}{2}$	$\frac{3}{4}$	$\frac{3}{4}$	1	$1\frac{1}{4}$					
$1\frac{1}{2}$ to 2	$\frac{3}{4}$	$\frac{3}{4}$	1	$1\frac{1}{4}$	$1\frac{1}{2}$	$1\frac{1}{2}$			
$2\frac{1}{2}$ to $2\frac{3}{4}$	$\frac{3}{4}$	$\frac{3}{4}$	1	$1\frac{1}{4}$	$1\frac{1}{2}$	$1\frac{1}{4}$	$1\frac{3}{4}$		
$2\frac{3}{8}$ to 3	$\frac{3}{4}$	$\frac{3}{4}$	1	$1\frac{1}{4}$	$1\frac{1}{2}$	$1\frac{1}{4}$	$1\frac{3}{4}$	$2\frac{1}{4}$	
$3\frac{1}{8}$ to 4	$\frac{3}{4}$	$\frac{3}{4}$	$1\frac{1}{4}$	$1\frac{1}{4}$	$1\frac{1}{2}$	$1\frac{1}{4}$	$1\frac{3}{4}$	$2\frac{1}{4}$	$2\frac{3}{4}$
$4\frac{1}{8}$ to 8	1	1	$1\frac{1}{4}$	$1\frac{1}{4}$	$1\frac{1}{2}$	$1\frac{1}{4}$	$2\frac{1}{4}$	$2\frac{1}{4}$	$2\frac{3}{4}$
$8\frac{1}{8}$ to 12	1	1	$1\frac{1}{2}$	$1\frac{3}{4}$	2	$2\frac{1}{4}$	$2\frac{1}{2}$	3	3
$12\frac{1}{8}$ to 20	1	1	$1\frac{1}{2}$	2	2	$2\frac{1}{4}$	$2\frac{1}{2}$	3	3

Bolts not listed are threaded about 3 times the diameter; in no case standard bolts threaded closer to the head than  $\frac{1}{4}$  inch.

# CARNEGIE STEEL COMPANY

## BOLTS WITH SQUARE HEADS AND NUTS

AMERICAN BRIDGE COMPANY STANDARD

### WEIGHT IN POUNDS PER 100 BOLTS

Length Under Head, Inches	Diameter of Bolt, Inches								
	1	1 1/16	3/8	7/16	1/2	5/8	3/4	7/8	1
1	4	7	11	15	22	37	56		
1 1/4	4	7	11	16	23	39	59		
1 1/2	5	8	12	17	24	41	62		
1 3/4	5	8	13	18	26	43	64		
2	5	9	14	19	27	45	67	101	144
2 1/4	6	9	15	20	28	47	71	104	150
2 1/2	6	10	15	21	30	49	74	109	155
2 3/4	6	10	16	22	31	51	77	113	161
3	7	11	17	24	33	54	80	117	167
3 1/4	7	12	18	25	35	58	86	126	178
4	8	13	20	28	38	62	92	134	189
4 1/4	9	14	21	30	41	66	98	142	198
5	10	15	23	32	43	71	104	151	209
5 1/4	10	16	25	34	46	75	111	159	220
6	11	17	26	36	49	79	117	168	232
6 1/4			28	38	52	84	123	176	243
7			29	40	55	88	129	185	254
7 1/4			31	42	57	92	136	193	265
8			32	45	60	97	142	202	276
9			34	49	65	105	154	218	298
10				53	71	114	167	235	320
12				61	82	131	192	269	364
14					93	148	217	303	409
Per Inch Additional	1.4	2.2	3.1	4.3	5.6	8.7	12.5	17.0	22.3

## SQUARE NUTS AND BOLT HEADS

AMERICAN BRIDGE COMPANY STANDARD

### WEIGHTS IN POUNDS FOR ONE HEAD AND ONE NUT

Diameter of Bolt, Inches	1 1/4	1 1/2	1 3/4	2	2 1/2	3
Square Head and Nut....	2.05	3.51	5.48	8.08	15.5	26.2
Weight of Shank per Inch	.3477	.5007	.6815	.8900	1.391	2.003

# BOLTS

## BOLTS WITH HEXAGON HEADS AND NUTS

AMERICAN BRIDGE COMPANY STANDARD

WEIGHT IN POUNDS PER 100 BOLTS

Length Under Head, Inches	Diameter of Bolt, Inches					Length Under Head, Inches	Diameter of Bolt, Inches				
	1/2	5/8	3/4	7/8	1		1/2	5/8	3/4	7/8	1
1	19	33	52			8	58	92	137	194	264
1 1/4	20	34	54			8 1/2	60	96	143	202	274
1 1/2	22	36	57			9	63	100	149	210	285
1 3/4	23	38	60			9 1/2	66	105	156	219	296
2	24	40	63	93	132	10	68	109	162	227	307
2 1/4	26	43	66	97	137	10 1/2	71	114	168	236	318
2 1/2	27	45	69	101	143	11	74	118	174	244	329
2 3/4	29	47	72	105	148	11 1/2	77	122	181	253	341
3	30	49	75	109	151	12	80	127	187	261	352
3 1/4	31	51	78	114	160	12 1/2	82	131	193	270	363
3 1/2	33	54	82	118	165	13	85	135	199	278	374
3 3/4	34	56	85	122	171	13 1/2	88	139	206	287	385
4	35	58	88	126	176	14	91	144	212	295	396
4 1/4	37	60	90	130	180	14 1/2	93	148	218	304	407
4 1/2	38	62	91	134	186	15	96	152	225	312	418
4 3/4	39	64	97	138	191	15 1/2	99	157	231	321	430
5	41	66	100	143	197	16	102	161	237	329	441
5 1/4	42	68	103	147	202	16 1/2	105	165	243	338	452
5 1/2	44	71	106	151	208	17	107	170	250	346	463
5 3/4	45	73	109	156	213	17 1/2	110	174	256	355	474
6	46	75	112	160	219	18	113	177	262	364	485
6 1/4	48	77	115	164	225	18 1/2	116	183	268	372	496
6 1/2	49	79	119	168	230	19	119	187	275	381	507
6 3/4	51	81	122	173	236	19 1/2	121	191	281	389	519
7	52	84	125	177	241	20	124	196	287	398	530
7 1/4	53	86	128	181	247						
7 1/2	55	88	131	185	252						
7 3/4	56	90	134	190	258						
Per Inch Additional	5.6	8.7	12.5	17.0	22.3	Per Inch Additional	5.6	8.7	12.5	17.0	22.3

## HEXAGON NUTS AND BOLT HEADS

AMERICAN BRIDGE COMPANY STANDARD


WEIGHTS IN POUNDS FOR ONE HEAD AND ONE NUT

Diameter of Bolt, Inches	1 1/4	1 1/2	1 3/4	2	2 1/2	3
Hexagon Head and Nut	1.73	2.95	4.61	6.79	13.0	22.0
Weight of Shank per Inch	.3477	.5007	.6815	.8900	1.391	2.003

# CARNEGIE STEEL COMPANY

## UPSET SCREW ENDS FOR SQUARE BARS

AMERICAN BRIDGE COMPANY STANDARD



Pitch and Shape of Thread A. B. Co. Standard


BAR			UPSET					
Side of Square d, Inches	Area, Sq. Inches	Weight per Foot, Lbs.	Diameter b, Inches	Length a, Inches	Additional Length for Upset +10%, Inches	Diameter at Root of Thread c, Inches	Area	
							At Root of Thread, Sq. Inches	Excess Over Area of Bar, %
* $\frac{3}{8}$	0.563	1.91	$1\frac{1}{8}$	4	4	0.939	0.693	23.2
* $\frac{1}{2}$	0.766	2.60	$1\frac{1}{4}$	4	$3\frac{1}{2}$	1.064	0.890	16.2
1	1.000	3.40*	$1\frac{1}{2}$	4	4	1.283	1.294	29.4
$1\frac{1}{8}$	1.266	4.30	$1\frac{5}{8}$	4	$3\frac{1}{2}$	1.389	1.515	19.7
$1\frac{1}{4}$	1.563	5.31	$1\frac{3}{4}$	$4\frac{1}{2}$	$4\frac{1}{2}$	1.615	2.049	31.1
$1\frac{3}{8}$	1.891	6.43	2	$4\frac{1}{2}$	4	1.711	2.300	21.7
$1\frac{1}{2}$	2.250	7.65	$2\frac{1}{4}$	5	5	1.961	3.021	34.3
$1\frac{5}{8}$	2.641	8.98	$2\frac{3}{8}$	5	$4\frac{1}{2}$	2.086	3.419	29.5
$1\frac{3}{4}$	3.063	10.41	$2\frac{1}{2}$	$5\frac{1}{2}$	$4\frac{1}{2}$	2.175	3.716	21.3
$1\frac{7}{8}$	3.516	11.95	$2\frac{3}{4}$	$5\frac{1}{2}$	5	2.425	4.619	31.4
2	4.000	13.60	$2\frac{7}{8}$	6	5	2.550	5.108	27.7
$2\frac{1}{8}$	4.516	15.35	3	6	$4\frac{1}{2}$	2.629	5.428	20.2
$2\frac{1}{4}$	5.063	17.21	$3\frac{1}{4}$	$6\frac{1}{2}$	$5\frac{1}{2}$	2.879	6.509	28.6
$2\frac{3}{8}$	5.641	19.18	$3\frac{3}{8}$	7	$6\frac{1}{2}$	3.100	7.549	33.8
$2\frac{1}{2}$	6.250	21.25	$3\frac{1}{2}$	7	7	3.317	8.641	38.3
$2\frac{5}{8}$	6.891	23.43	$3\frac{3}{4}$	7	$5\frac{1}{2}$	3.317	8.641	25.4
$2\frac{3}{4}$	7.563	25.71	4	$7\frac{1}{2}$	$6\frac{1}{2}$	3.567	9.903	32.1
$2\frac{7}{8}$	8.266	28.10	$4\frac{1}{4}$	8	$7\frac{1}{2}$	3.798	11.330	37.1
3	9.000	30.60	$4\frac{3}{4}$	8	6	3.798	11.330	25.9
$3\frac{1}{8}$	9.766	33.20	$4\frac{1}{2}$	$8\frac{1}{2}$	7	4.028	12.741	30.5
$3\frac{1}{4}$	10.563	35.91	$4\frac{3}{4}$	$8\frac{1}{2}$	$7\frac{1}{2}$	4.255	14.221	34.6

Upsets marked \* are special.

# UPSET SCREW ENDS

## UPSET SCREW ENDS FOR ROUND BARS

AMERICAN BRIDGE COMPANY STANDARD



Pitch and Shape of Thread A. B. Co. Standard

BAR			UPSET					
Diameter d, Inches	Area, Sq. Inches	Weight per Foot, lbs.	Diameter b, Inches	Length a, Inches	Additional Length for Upset + 10%, Inches	Diameter at Root of Thread c, Inches	Area	
							At Root of Thread, Sq. Inches	Excess Over Area of Bar, %
* 3/8	0.442	1.50	1	4	4	0.838	0.551	24.7
* 7/8	0.601	2.04	1 1/4	4	5	1.064	0.890	48.0
1	0.785	2.67	1 3/8	4	4	1.158	1.054	34.2
1 1/8	0.994	3.38	1 1/2	4	4	1.283	1.294	30.2
1 1/4	1.227	4.17	1 5/8	4	4	1.389	1.515	23.5
1 3/8	1.485	5.05	1 3/4	4	4	1.490	1.744	17.5
1 1/2	1.767	6.01	2	4 1/2	4 1/2	1.711	2.300	30.2
1 5/8	2.074	7.05	2 1/8	4 1/2	4	1.836	2.649	27.7
1 3/4	2.405	8.18	2 1/4	5	4	1.961	3.021	25.6
1 7/8	2.761	9.39	2 3/8	5	4	2.086	3.419	23.8
2	3.142	10.68	2 1/2	5 1/2	4	2.175	3.716	18.3
2 1/8	3.547	12.06	2 5/8	5 1/2	3 1/2	2.300	4.150	17.2
2 1/4	3.976	13.52	2 7/8	6	4 1/2	2.550	5.108	28.4
2 3/8	4.430	15.06	3	6	4 1/2	2.629	5.428	22.5
2 1/2	4.909	16.69	3 1/4	6 1/2	5 1/2	2.879	6.509	32.6
2 5/8	5.412	18.40	3 1/2	6 1/2	4 1/2	2.879	6.509	20.3
2 3/4	5.940	20.19	3 3/4	7	5 1/2	3.100	7.549	27.1
2 7/8	6.492	22.07	3 1/2	7	6	3.317	8.641	33.1
3	7.069	24.03	3 3/4	7	5	3.317	8.641	22.2
3 1/8	7.670	26.08	4	7 1/2	6	3.567	9.993	30.3
3 1/4	8.296	28.21	4	7 1/2	5	3.567	9.993	20.5
3 3/8	8.946	30.42	4 1/4	8	5 1/2	3.798	11.330	26.6
3 1/2	9.621	32.71	4 1/4	8	5	3.798	11.330	17.8
3 3/4	10.321	35.09	4 1/2	8 1/2	5 1/2	4.028	12.741	23.4
3 7/8	11.045	37.55	4 3/4	8 1/2	6	4.255	14.221	28.8
3 7/8	11.793	40.10	4 3/4	8 1/2	5 1/2	4.255	14.221	20.6

Upsets marked \* are special.

# CARNEGIE STEEL COMPANY

## EYE BARS

AMERICAN BRIDGE COMPANY STANDARD

### ORDINARY EYE BAR



### ADJUSTABLE EYE BAR



Minimum length of short end from center of pin to end of screw, 6'-6", preferably 7'-0".  
Thread on short end to be left hand.  
Pitch and Shape of Thread A. B. Co. Standard.

BAR				HEAD				BAR				SCREW END				Additional Material, b, Ft. and in.	
Width In.	Thickness		Dia. d, In.	Maximum Pin		Additional Material, a, Ft. and in.		Width In.	Min. thickness In.	Dia. u, In.	Excess Upset over Bar %	Length m, In.	For ordering Bar	For figuring Wt.	For ordering Bar	For figuring Wt.	
	Max. In.	Min. In.		Dia. In.	Excess Head over Bar, c, %	For ordering Bar	For figuring Weight										Dia. In.
2	1	1/2	4 1/2	1 3/4		1-0	0-7	2	* 3/8	1 1/2	39.6	4	1-0	8			
			5 1/2	2 3/4	37.5	1-4	0-11			1 3/4	36.6	4 1/2	1-0	7 1/2			
2 1/2	1	5/8	6 1/2	3 3/4		1-9	1-4	2 1/2	* 1/2	2	31.4	4 1/2	0-11	7 1/2			
			7	4 1/2	40.0	1-3	0-10			2 1/4	41.2	5	1-0	8			
			8 1/2	5 1/4		1-7	1-2			3	38.1	5 1/2	1-0	8			
			9 1/2	6 1/4		2-0	1-7			3 1/4	36.7	5 1/2	1-0	7 1/2			
3	1 1/2	5/8	7 1/2	3 3/4		1-6	1-1	3	* 3/4	2 3/4	34.3	5	1-0	7 1/2			
			8 1/2	4 1/2	41.7	1-11	1-5			3 1/2	41.6	5 1/2	1-1	8 1/2			
			9 1/2	5 1/4		2-4	1-10			4	23.9	5 1/2	1-1	8 1/2			
			10	6 1/4		1-11	1-6			4 1/4	23.9	5 1/2	1-1	8 1/2			
4	1 3/4	1	11	5 1/2	37.5	2-3	1-10	4	* 1	3 1/4	32.0	6	0-11	7 1/2			
			12 1/2	6 1/2		2-8	2-2			4 1/2	35.7	6 1/2	1-1	8 1/2			
			13 1/2	7 1/4		2-1	1-8			5	44.6	6 1/2	1-2	9 1/2			
5	2	1 1/4	14 1/2	8 1/4	35.0	2-8	2-2	5	* 1 1/8	4 1/4	36.2	6	1-0	8			
			15 1/2	9 1/4		3-3	2-9			5 1/4	21.1	6 1/2	0-11	7			
			16 1/2	10 1/4		2-4	1-10			6	30.2	6 1/2	1-0	8			
6	2	1 1/2	17 1/2	9 1/2	37.5	2-6	2-1	6	* 1 1/4	5 1/4	34.2	7	1-1	8 1/2			
			18 1/2	10 1/2		3-2	2-8			6 1/4	38.3	7	1-2	9			
			19 1/2	11 1/4		2-7	2-2			7 1/4	25.8	7	1-0	7 1/2			
7	2	1 3/4	20 1/2	11 1/2	35.7	2-11	2-6	7	* 1 3/8	6 1/4	28.0	7 1/2	1-0	8			
			21 1/2	12 1/2		3-4	2-11			7 1/4	33.2	7 1/2	1-1	8 1/2			
			22 1/2	13 1/4		2-8	2-3			8 1/4	37.3	8	1-2	9 1/2			
8	2	2	23 1/2	13 1/2	37.5	3-0	2-6	8	* 1 1/2	8 1/4	26.9	7 1/2	1-0	8			
			24 1/2	14 1/2		3-4	2-11			9 1/4	29.5	8	1-1	8 1/2			
			25 1/2	15 1/4		2-11	2-6			10 1/4	32.4	8 1/2	1-2	9			
9	2	2 1/4	26 1/2	15 1/2	38.9	3-7	3-1	9	* 1 5/8	10 1/4	35.4	8 1/2	1-2	9 1/2			
			27 1/2	16 1/2		3-5	2-10			11 1/4	25.9	8	1-0	8			
			28 1/2	17 1/2		3-9	3-3			12 1/4	27.4	8 1/2	1-1	8 1/2			
10	2	2 1/2	29 1/2	17 1/2	35.0	4-1	3-7	10	* 2	12 1/4	29.3	8 1/2	1-1	8 1/2			
			30 1/2	18 1/2		3-8	3-3			13 1/4	31.4	9	1-2	9			
			31 1/2	19 1/2		4-2	3-8			14 1/4	35.2	9 1/2	1-3	10			
12	2	3	32 1/2	19 1/2	37.5	4-8	4-1	12	* 2 1/8	14 1/4	25.9	8	1-1	8 1/2			
			33 1/2	20 1/2		4-3	3-9			15 1/4	27.4	8 1/2	1-1	8 1/2			
			34 1/2	21 1/2		5-5	4-8			16 1/4	32.4	8 1/2	1-1	8 1/2			
14	2	3 1/4	35 1/2	21 1/2	35.0	5-5	4-8	14	* 2 3/8	15 1/4	29.3	8 1/2	1-1	8 1/2			
			36 1/2	22 1/2		5-4	4-7			16 1/4	31.4	9	1-2	9			
			37 1/2	23 1/2		6-1	5-5			17 1/4	35.2	9 1/2	1-3	10			
16	2	3 3/4	38 1/2	23 1/2	34.4	5-5	4-10	16	* 2 3/4	16 1/4	25.9	8	1-1	8 1/2			
			39 1/2	24 1/2		6-1	5-5			17 1/4	27.4	8 1/2	1-1	8 1/2			


Bars marked \* should only be used when absolutely unavoidable.  
Deduct pin hole when figuring weight.

Bars marked \* should only be used when absolutely unavoidable.  
Deduct pin hole when figuring weight.

# LOOP RODS

## LOOP RODS

AMERICAN BRIDGE COMPANY STANDARD

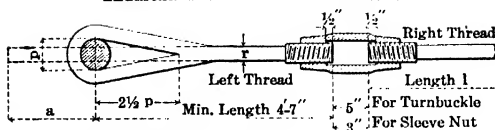

Pitch and Shape of Thread A. B. Co. Standard

ADDITIONAL LENGTH "A" IN FEET AND INCHES FOR ONE LOOP

$$A=4.17p+5.89r$$

Diam. of Pin, p	Diameter or Side "r" of Rod in Inches										
	5/16	7/16	1	1 1/16	1 1/4	1 3/8	1 1/2	1 5/8	1 3/4	1 7/8	2
1 1/8	0- 9 1/2	0-10	0-11	0-11 1/2							
1 1/4	0-10	0-10 1/2	0-11 1/2	1- 0	1- 1						
1 1/2	0-11	0-11 1/2	1- 0 1/2	1- 1	1- 2	1- 2 1/2					
1 3/4	1- 0	1- 0 1/2	1- 1 1/2	1- 2	1- 3	1- 3 1/2	1- 4 1/2	1- 5	1- 6		
2	1- 1	1- 1 1/2	1- 2 1/2	1- 3	1- 4	1- 4 1/2	1- 5 1/2	1- 6	1- 7	1- 7 1/2	1- 8 1/2
2 1/4	1- 2	1- 3	1- 3 1/2	1- 4 1/2	1- 5	1- 5 1/2	1- 6 1/2	1- 7	1- 8	1- 8 1/2	1- 9 1/2
2 1/2	1- 3	1- 4	1- 4 1/2	1- 5 1/2	1- 6	1- 7	1- 7 1/2	1- 8	1- 9	1- 9 1/2	1-10 1/2
2 3/4	1- 4	1- 5	1- 5 1/2	1- 6 1/2	1- 7	1- 8	1- 8 1/2	1- 9 1/2	1-10	1-11	1-11 1/2
3	1- 5	1- 6	1- 6 1/2	1- 7 1/2	1- 8	1- 9	1- 9 1/2	1-10 1/2	1-11	2- 0	2- 0 1/2
*3 1/8	1- 6	1- 7	1- 7 1/2	1- 8 1/2	1- 9	1-10	1-10 1/2	1-11 1/2	2- 0	2- 1	2- 1 1/2
3 1/4	1- 7 1/2	1- 8	1- 8 1/2	1- 9 1/2	1-10	1-11	1-11 1/2	2- 0 1/2	2- 1	2- 2	2- 2 1/2
*3 3/8	1- 8 1/2	1- 9	1-10	1-10 1/2	1-11	2- 0	2- 0 1/2	2- 1 1/2	2- 2	2- 3	2- 3 1/2
4	1- 9 1/2	1-10	1-11	1-11 1/2	2- 0 1/2	2- 1	2- 2	2- 2 1/2	2- 3	2- 4	2- 4 1/2
*4 1/8		1-11	2- 0	2- 0 1/2	2- 1 1/2	2- 2	2- 3	2- 3 1/2	2- 4 1/2	2- 5	2- 6
4 1/4		2- 0	2- 1	2- 1 1/2	2- 2 1/2	2- 3	2- 4	2- 4 1/2	2- 5 1/2	2- 6	2- 7
*4 3/8		2- 1	2- 2	2- 2 1/2	2- 3 1/2	2- 4	2- 5	2- 5 1/2	2- 6 1/2	2- 7	2- 8
5		2- 2 1/2	2- 3	2- 3 1/2	2- 4 1/2	2- 5	2- 6	2- 6 1/2	2- 7 1/2	2- 8	2- 9
*5 1/8			2- 4	2- 5	2- 5 1/2	2- 6	2- 7	2- 7 1/2	2- 8 1/2	2- 9	2-10
5 1/4			2- 5	2- 6	2- 6 1/2	2- 7 1/2	2- 8	2- 9	2- 9 1/2	2-10	2-11
*5 3/8			2- 6	2- 7	2- 7 1/2	2- 8 1/2	2- 9	2-10	2-10 1/2	2-11 1/2	3- 0
6			2- 7	2- 8	2- 8 1/2	2- 9 1/2	2-10	2-11	2-11 1/2	3- 0 1/2	3- 1
*6 1/8				2- 9	2- 9 1/2	2-10 1/2	2-11	3- 0	3- 0 1/2	3- 1 1/2	3- 2
6 1/4				2-10	2-10 1/2	2-11 1/2	3- 0	3- 1	3- 1 1/2	3- 2 1/2	3- 3
*6 3/8				2-11	3- 0	3- 0 1/2	3- 1	3- 2	3- 2 1/2	3- 3 1/2	3- 4
7				3- 0	3- 1	3- 1 1/2	3- 2 1/2	3- 3	3- 3 1/2	3- 4 1/2	3- 5

Pins marked \* are special. Maximum shipping length of "1"=35 feet.




# CARNEGIE STEEL COMPANY

## CLEVISES

AMERICAN BRIDGE COMPANY STANDARD

All dimensions in inches

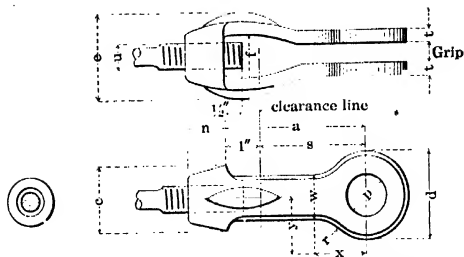

Grip—thickness of plate +  $\frac{1}{4}$ " but must not exceed dimension f

Clev Number	Head								Nut				Fork			Weight, Pounds	
	d	w	t	Max. p	Min. p	r	x	y	n	e	Max. u	Min. u	e	f	a		s
3	3	1 1/2	1/2	1 1/2	1	2 1/4	2 1/4	3	1 1/2	2 1/4	1 1/8	1	3 1/8	1 1/4	5	4	4
4	4	2	1/2	2	1 1/4	3	3	4	1 3/4	2 3/4	1 5/8	1 1/8	3 3/8	1 3/4	6	5	8
5	5	2 1/2	3/4	2 1/2	1 1/2	3 3/4	3 3/4	5	2 1/4	3 3/4	2 1/8	1 1/2	4 1/8	2 1/4	7	6	16
6	6	3	3/4	3	2	4 1/4	4 1/4	6	2 3/4	4 3/4	2 5/8	2	5 3/8	2 3/4	8	7	26
7	7	3 1/2	7/8	3 1/2	2 1/2	5 1/4	5 1/4	7	3	5	3	2 1/2	6 3/8	3 1/4	9	8	36

## CLEVIS NUMBERS FOR VARIOUS RODS AND PINS

Rods			Pins										
Round	Square	Upset	1	1 1/4	1 1/2	1 3/4	2	2 1/4	2 1/2	2 3/4	3	3 1/4	3 1/2
3/4		1	3	3	3								
	3/4	1 1/4	3	3	3	4	4						
7/8	3/8	1 1/2		4	4	4	4						
1		1 3/4		4	4	4	4						
1 1/8	1	1 1/2		4	4	4	4	5	5				
1 1/4	1 1/8	1 1/4		4	4	4	4	5	5				
1 1/2		1 3/4			5	5	5	5	5				
1 3/8		1 1/2			5	5	5	5	5				
	1 1/4	1 1/8				5	5	5	5				
1 1/2	1 3/8	2			5	5	5	5	5	6	6		
1 3/4		2 1/4			5	5	5	5	5	6	6		
1 3/8		2 1/2				5	5	5	5	6	6		
1 3/4	1 1/2	2 1/4					6	6	6	6	6	7	7
1 3/8		2 3/8					6	6	6	6	6	7	7
2	1 3/4	2 1/2					6	6	6	6	6	7	7
2 1/8		2 3/4					6	6	6	6	6	7	7
	1 3/8	2 3/4						7	7	7	7	7	7
2 1/4	2	2 3/8						7	7	7	7	7	7
2 3/8	2 1/8	3						7	7	7	7	7	7


# TURNBUCKLES AND SLEEVE NUTS

## TURNBUCKLES AND SLEEVE NUTS


AMERICAN BRIDGE COMPANY STANDARD

All Dimensions in Inches

### TURNBUCKLES



### SLEEVE NUTS



a=6"; a=9" for turnbuckles marked \*.  
Pitch and shape of thread, A. B. Co. Standard.

Pitch and shape of thread, A. B. Co. Standard


Diam. of Screw u	Standard Dimensions						Weight, Pounds	Diam. of Screw u	Standard Dimensions						Weight, Pounds
	d	l	e	t	g	b			d	l	a	b	e	t	
3/8	1/8	7 1/2	1/8	1/8	1/2	1 1/8	1								
1/2	3/8	7 1/2	1/8	1/8	1/2	1 1/8	1								
3/4	1/2	7 1/2	1/8	1/8	1/2	1 1/8	1 1/2								
1	3/4	7 1/2	1/8	1/8	1/2	1 1/8	1 1/2								
1 1/8	1	8 3/4	1 1/8	1 1/8	3/4	2	2								
1 1/4	1 1/8	8 3/4	1 1/8	1 1/8	3/4	2 1/4	3	7/8	1 1/2	7	1 1/8	1 1/8	1 1/8	3/4	3
1 1/2	1 1/4	9	1 1/8	1 1/8	1 1/4	2 3/8	4	1	1 1/2	7	1 1/8	1 1/8	1 1/8	3/4	3
1 3/4	1 1/2	9 3/8	1 1/8	1 1/8	1 1/4	2 3/8	5	1 1/8	1 3/4	7 1/2	2	2 1/8	1 1/8	1 1/8	4
2	1 3/4	9 3/4	1 1/8	1 1/8	1 1/2	2 3/4	6	1 1/4	1 3/4	7 1/2	2	2 1/8	1 1/8	1 1/8	5
2 1/8	2	10 1/8	1 1/8	1 1/8	1 3/4	3 1/8	7	1 3/8	2	8	2 3/8	2 1/4	1 1/8	1 1/8	6
2 1/4	2 1/8	10 1/8	1 1/8	1 1/8	1 3/4	3 1/8	8	1 1/2	2	8	2 3/8	2 1/4	1 1/8	1 1/8	8
2 1/2	2 1/4	10 1/8	1 1/8	1 1/8	1 3/4	3 1/8	10	1 1/8	2 1/4	8 1/2	2 3/4	3 1/8	1 1/8	1 1/8	9
2 3/4	2 1/2	10 1/8	1 1/8	1 1/8	1 3/4	3 1/8	11	1 1/4	2 1/4	8 1/2	2 3/4	3 1/8	1 1/8	1 1/8	10
3	2 3/4	11 1/4	2 1/8	1 1/8	2	3 3/4	12	1 3/8	2 3/4	9	3 1/8	3 1/8	2 1/8	1 1/8	11
3 1/8	3	12	2 3/8	1 1/8	2 1/4	4 1/4	14	2	2 1/2	9	3 1/8	3 1/8	2 1/8	1 1/8	14
3 1/4	3 1/8	12 3/8	2 1/8	1 1/8	2 1/4	4 1/4	17	2 1/8	2 3/4	9 1/2	3 1/8	4 1/8	2 3/8	1 1/8	15
3 1/2	3 1/4	12 3/4	2 1/8	1 1/8	2 1/4	4 1/4	20	2 1/4	2 3/4	9 1/2	3 1/8	4 1/8	2 3/8	1 1/8	18
3 3/4	3 1/2	13 1/8	2 3/4	1 1/8	2 3/4	4 3/4	22	2 3/8	3	10	3 7/8	4 1/2	2 3/8	1 1/8	23
4	3 3/4	13 1/8	2 3/4	1 1/8	2 3/4	4 3/4	25	2 1/2	3	10	3 7/8	4 1/2	2 3/8	1 1/8	27
4 1/8	4	14 1/4	3 1/4	1 1/8	3 1/4	5 1/4	33	2 3/4	3 1/4	10 1/2	4 1/4	4 1/2	2 3/8	1 1/8	28
4 1/4	4 1/8	14 1/4	3 1/4	1 1/8	3 1/4	5 1/4	36	2 7/8	3 1/2	11	4 5/8	5 1/8	3 1/8	1 1/8	35
4 1/2	4 1/4	15 1/8	3 3/8	1 1/8	3 1/2	5 3/8	40	3	3 1/2	11	4 5/8	5 1/8	3 1/8	1 1/8	40
4 3/4	4 1/2	15 3/4	3 3/8	1 1/8	3 1/2	5 3/8	50	3 1/4	3 3/4	11 1/2	5	5 1/8	3 3/8	1 1/8	47
5	4 3/4	16 1/4	4 1/4	1 1/8	4	6 1/4	65	3 1/2	4	12	5 3/8	6 1/4	3 3/8	1 1/8	55
5 1/8	5	17 1/4	4 1/4	1 1/8	5	6 3/4	95	3 3/4	4 1/4	12 1/2	5 3/8	6 1/4	3 3/8	1 1/8	65
5 1/4	5 1/8	18	4 3/8	1 1/8	5	6 3/4	108	4	4 1/2	13	6 1/8	7 1/8	4 3/8	1 1/8	75
5 1/2	5 1/4	21 1/4	4 3/8	1 1/8	5 3/8	9 1/4	140	4 1/4	4 3/4	13 1/2	6 1/8	7 1/8	4 3/8	1 1/8	
5 3/4	5 1/2	22 1/4	5 1/8	1 1/8	6 1/8	10 1/4	195	4 1/2	5	14	6 3/8	7 1/8	4 3/8	1 1/8	
6	5 3/4	23 1/4	5 3/8	2	6 1/2	11 1/4	205								
6 1/8	6	24	6	2 1/4	6 1/2	11 3/4	250								

# CARNEGIE STEEL COMPANY

## RECESSED PIN NUTS

AMERICAN BRIDGE COMPANY STANDARD

All Dimensions in Inches

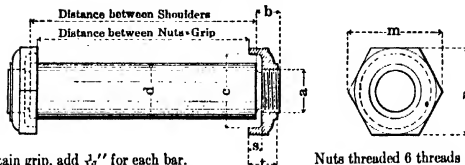

To obtain grip, add  $\frac{1}{8}$ " for each bar.

Nuts threaded 6 threads per inch.

To obtain distance between shoulders, add amount given in table to grip.


Diameter of Pin, d	Pin				Nut						
	Thread		Add to Grip	Thickness	Diameter			Depth	Diameter rough hole	Weight, Pounds	Pattern No.
	a	b			n	m	c				
2, $2\frac{1}{4}$	$1\frac{1}{2}$	1	$\frac{1}{4}$	$\frac{7}{8}$	$2\frac{1}{8}$	$3\frac{3}{8}$	$2\frac{5}{8}$	$\frac{1}{4}$	$1\frac{1}{8}$	1.1	PN 21
3, $3\frac{1}{4}$	2	$1\frac{1}{8}$	$\frac{1}{4}$	1	$3\frac{1}{8}$	$4\frac{1}{8}$	$3\frac{1}{8}$	$\frac{1}{4}$	$1\frac{1}{8}$	1.7	PN 22
$3\frac{1}{2}$ , $4\frac{1}{2}$	$2\frac{1}{4}$	$1\frac{1}{4}$	$\frac{1}{4}$	$1\frac{1}{8}$	$4\frac{1}{8}$	$5\frac{1}{8}$	$3\frac{1}{8}$	$\frac{1}{4}$	$2\frac{1}{8}$	2.5	PN 23
$4\frac{3}{4}$ , $5\frac{1}{4}$	3	$1\frac{3}{8}$	$\frac{1}{4}$	$1\frac{1}{4}$	$5\frac{1}{8}$	$6\frac{1}{8}$	$4\frac{1}{8}$	$\frac{1}{4}$	$2\frac{1}{4}$	3.7	PN 24
$5\frac{1}{2}$ , $6\frac{1}{2}$	$3\frac{1}{2}$	$1\frac{1}{2}$	$\frac{1}{4}$	$1\frac{3}{8}$	$6\frac{1}{8}$	$7\frac{1}{8}$	$5\frac{1}{8}$	$\frac{1}{4}$	$2\frac{3}{8}$	4.6	PN 25
$6\frac{3}{4}$ , $7\frac{1}{4}$	4	$1\frac{5}{8}$	$\frac{1}{4}$	$1\frac{1}{2}$	$7\frac{1}{8}$	$8\frac{1}{8}$	$6\frac{1}{8}$	$\frac{1}{4}$	$3\frac{1}{8}$	6.2	PN 26
$7\frac{1}{2}$ , $8\frac{1}{2}$	$4\frac{1}{2}$	$1\frac{3}{4}$	$\frac{1}{4}$	$1\frac{3}{8}$	$8\frac{1}{8}$	$9\frac{1}{8}$	$7\frac{1}{8}$	$\frac{1}{4}$	$3\frac{1}{4}$	7.8	PN 27
$8\frac{3}{4}$ , $9\frac{1}{4}$	5	$1\frac{7}{8}$	$\frac{1}{4}$	$1\frac{1}{2}$	$9\frac{1}{8}$	$10\frac{1}{8}$	$8\frac{1}{8}$	$\frac{1}{4}$	$4\frac{1}{8}$	9.9	PN 28
$9\frac{1}{2}$ , $10\frac{1}{2}$	$5\frac{1}{2}$	$2$	$\frac{1}{4}$	$1\frac{3}{4}$	$10\frac{1}{8}$	$11\frac{1}{8}$	$9\frac{1}{8}$	$\frac{1}{4}$	$5\frac{1}{8}$	11.8	PN 29
$10\frac{3}{4}$ , $11\frac{1}{4}$	$5\frac{3}{4}$	$2\frac{1}{8}$	$\frac{1}{4}$	$1\frac{7}{8}$	$11\frac{1}{8}$	$12\frac{1}{8}$	$10\frac{1}{8}$	$\frac{1}{4}$	$5\frac{3}{8}$	14.3	PN 30
$11\frac{1}{2}$ , $12\frac{1}{2}$	6	$2\frac{1}{4}$	$\frac{1}{4}$	$2$	$12\frac{1}{8}$	$13\frac{1}{8}$	$11\frac{1}{8}$	$\frac{1}{4}$	$6\frac{1}{8}$	18.6	PN 31
$12\frac{3}{4}$ , $13\frac{1}{4}$	$6\frac{1}{4}$	$2\frac{3}{8}$	$\frac{1}{4}$	$2\frac{1}{8}$	$13\frac{1}{8}$	$14\frac{1}{8}$	$12\frac{1}{8}$	$\frac{1}{4}$	$7\frac{1}{8}$	23.8	PN 32
$13\frac{1}{2}$ , $14\frac{1}{2}$	$6\frac{1}{2}$	$2\frac{1}{2}$	$\frac{1}{4}$	$2\frac{1}{4}$	$14\frac{1}{8}$	$15\frac{1}{8}$	$13\frac{1}{8}$	$\frac{1}{4}$	$8\frac{1}{8}$	31.1	PN 33

Pins marked \* are special.

## COTTER PINS

AMERICAN BRIDGE COMPANY STANDARD

All Dimensions in Inches




HORIZONTAL OR VERTICAL PIN FINISHED					HORIZONTAL PIN ROUGH OR FINISHED				
Pin	Head	g	Cotter		Pin	g1	Cotter		
p	h		c	d	p1		c	d	
$1\frac{1}{4}$	$1\frac{1}{2}$	Net Grip + $\frac{1}{2}$ "	2	$\frac{1}{4}$	$1\frac{1}{4}$	Net Grip + $\frac{1}{2}$ "	2	$\frac{1}{4}$	
$1\frac{1}{2}$	$1\frac{3}{4}$		$2\frac{1}{2}$	$\frac{1}{4}$	$1\frac{1}{2}$		$2\frac{1}{2}$	$\frac{1}{4}$	
$1\frac{3}{4}$	2		$2\frac{3}{4}$	$\frac{1}{4}$	$1\frac{3}{4}$		$2\frac{3}{4}$	$\frac{1}{4}$	
2	$2\frac{1}{4}$		3	$\frac{1}{4}$	2		3	$\frac{1}{4}$	
$2\frac{1}{4}$	$2\frac{3}{4}$		$3\frac{1}{4}$	$\frac{1}{4}$	$2\frac{1}{4}$		$3\frac{1}{4}$	$\frac{1}{4}$	
$2\frac{1}{2}$	$2\frac{7}{8}$		$3\frac{1}{2}$	$\frac{1}{4}$	$2\frac{1}{2}$		$3\frac{1}{2}$	$\frac{1}{4}$	
$2\frac{3}{4}$	3		4	$\frac{1}{4}$	$2\frac{3}{4}$		4	$\frac{1}{4}$	
3	$3\frac{1}{4}$		5	$\frac{1}{4}$	3		5	$\frac{1}{4}$	
$3\frac{1}{4}$	$3\frac{3}{4}$		5	$\frac{1}{4}$	$3\frac{1}{4}$		5	$\frac{1}{4}$	
$3\frac{1}{2}$	4		6	$\frac{1}{4}$	$3\frac{1}{2}$		6	$\frac{1}{4}$	
$3\frac{3}{4}$	$4\frac{1}{4}$		6	$\frac{1}{4}$	$3\frac{3}{4}$		6	$\frac{1}{4}$	

# RIVETS


## STRUCTURAL RIVETS

AMERICAN BRIDGE COMPANY STANDARD

Dimensions in Inches

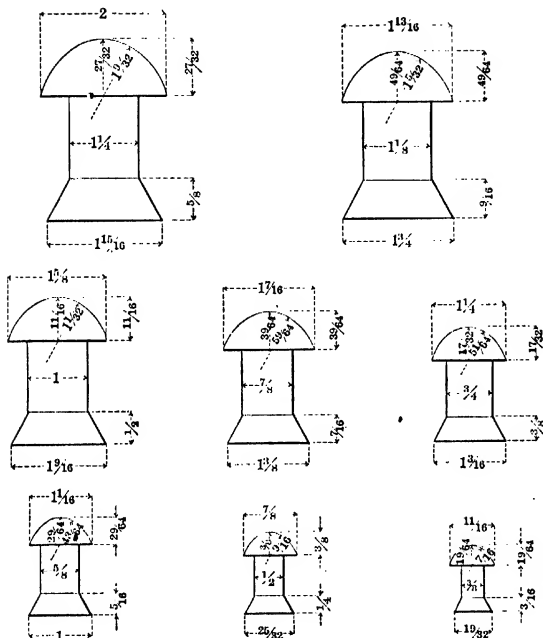

### GENERAL FORMULAS FOR PROPORTIONS OF RIVETS, IN INCHES



Full driven head, diameter,  $a=1.5 d + \frac{1}{8}''$

" " " depth,  $b=0.425 a$

" " " radius,  $c=b$

" " " radius,  $e=1.5 b$

Countersunk head, depth,  $f=0.5 d$

" " " diameter,  $g=1.577 d$

# CARNEGIE STEEL COMPANY

## STRUCTURAL RIVETS

AMERICAN BRIDGE COMPANY STANDARD

### LENGTHS OF FIELD RIVETS FOR VARIOUS GRIPS

Dimensions in Inches



Grip a	Diameter					Grip b	Diameter				
	1/2	5/8	3/4	7/8	1		1/2	5/8	3/4	7/8	1
1	1 1/2	1 3/4	1 7/8	2	2 1/8	1 1/2	1 1/8	1 1/4	1 1/2	1 3/4	1 7/8
1 1/8	1 5/8	1 7/8	2	2 1/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
1 1/4	1 3/4	2	2 1/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
1 1/2	1 7/8	2 1/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
1 3/4	2	2 1/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
2	2 1/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
2 1/8	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
2 1/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
2 1/2	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
2 3/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
3	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
3 1/8	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
3 1/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
3 1/2	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
3 3/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
4 1/8	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
4 1/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
4 1/2	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
4 3/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
5	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
5 1/8	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
5 1/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
5 1/2	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
5 3/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
6	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
6 1/8	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
6 1/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
6 1/2	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
6 3/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
7	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
7 1/8	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
7 1/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
7 1/2	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8
7 3/4	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 1/2	1 1/2	1 5/8	1 7/8	1 7/8	1 7/8
8	2 3/8	2 3/8	2 3/8	2 3/8	2 3/8	1 3/8	1 3/8	1 5/8	1 7/8	1 7/8	1 7/8

# RIVETS

## STRUCTURAL RIVETS

AMERICAN BRIDGE COMPANY STANDARD

WEIGHT IN POUNDS PER 100 RIVETS WITH BUTTON HEADS

Length Under Head, Inches	Diameter of Rivet, Inches								Length Under Head, Inches	Diameter of Rivet, Inches							
	3/8	1/2	5/8	3/4	7/8	1	1 1/8	1 1/4		3/8	1/2	5/8	3/4	7/8	1	1 1/8	1 1/4
5									5	18	33	53	78	109	146	190	252
1 1/4	6	12							1 1/4	18	34	54	80	111	149	193	256
3/8	7	13							3/8	19	34	55	82	113	152	197	260
1/2	7	13	23	35	50	68	91	130	1/2	19	35	56	83	115	155	200	265
5/8	7	14	24	36	52	71	95	134	5/8	20	36	57	85	118	157	204	269
3/4	8	15	25	37	54	74	98	139	3/4	20	37	60	88	122	163	211	278
7/8	8	15	26	39	56	77	102	143	7/8	21	38	61	89	124	166	214	282
2	9	16	27	41	58	80	105	148	6	21	38	62	91	126	169	218	287
1 1/8	9	17	28	43	60	82	109	152	1 1/8	22	39	63	93	128	171	222	291
1 1/4	9	18	29	44	62	85	112	156	1 1/4	22	40	64	94	130	174	225	295
3/8	10	18	30	46	64	88	116	161	3/8	22	40	65	96	132	177	229	300
1/2	10	19	31	47	67	91	119	165	1/2	23	41	66	97	135	180	232	304
5/8	11	20	32	49	69	93	123	169	5/8	23	42	67	99	137	182	236	308
3/4	11	20	34	50	71	96	126	174	3/4	24	43	68	100	139	185	239	313
7/8	11	21	35	52	73	99	130	178	7/8	24	43	69	102	141	188	243	317
3	12	22	36	54	75	102	133	182	7	24	44	70	104	143	191	246	321
1 1/8	12	22	37	55	77	105	137	187	1 1/8	25	45	71	105	145	194	250	326
1 1/4	13	23	38	57	79	107	141	191	1 1/4	25	45	73	107	147	196	253	330
3/8	13	24	39	58	81	110	144	195	3/8	26	46	74	108	149	199	257	334
1/2	13	24	40	60	84	113	148	200	1/2	26	47	75	110	152	202	260	339
5/8	14	25	41	61	86	116	151	204	5/8	26	47	76	111	154	205	264	343
3/4	14	26	42	63	88	118	155	208	3/4	27	48	77	113	156	207	267	347
7/8	15	27	43	64	90	121	158	213	7/8	27	49	78	114	158	210	271	352
4	15	27	44	66	92	124	162	217	8	27	50	79	116	160	213	274	356
1 1/8	15	28	45	68	94	127	165	221	1 1/8	28	50	80	118	162	216	278	360
1 1/4	16	29	47	69	96	130	169	226	1 1/4	28	51	81	119	164	219	281	365
3/8	16	29	48	71	98	132	172	230	3/8	29	52	82	121	166	221	285	369
1/2	16	30	49	72	101	135	176	234	1/2	29	52	83	122	169	224	288	373
5/8	17	31	50	74	103	138	179	239	5/8	29	53	84	124	171	227	292	378
3/4	17	31	51	75	105	141	183	243	3/4	30	54	86	125	173	230	295	382
7/8	18	32	52	77	107	143	186	247	7/8	30	54	87	127	175	232	299	386

Button Heads	Diameter of Rivets, Inches							
	3/8	1/2	5/8	3/4	7/8	1	1 1/8	1 1/4
100 Heads as made on rivets, Pounds...	2.4	5.0	9.7	16.0	24.0	35.0	49.0	78.0
100 Heads as driven in work, Pounds...	1.9	4.0	7.5	12.5	18.5	27.0	37.5	51.0

CARNEGIE STEEL COMPANY

AMERICAN BRIDGE COMPANY

## SPECIFICATIONS

FOR

## STEEL STRUCTURES

DESIGN, DETAILS OF CONSTRUCTION AND WORKMANSHIP

ADOPTED 1912

### DESIGN

1. **Loads.** The steel frame of all structures shall be designed so as to safely support the dead and live loads. The dead load shall consist of the weight of all permanent construction and fixtures, such as walls, floors, roofs, interior partitions, and fixed or permanent appliances. The live load shall consist of movable loads on floors, loads due to machinery or other appliances, and the exterior loads due to snow on the roof and to wind.

2. For structures carrying traveling machinery, such as cranes, conveyors, etc., 25 per cent shall be added to the stresses resulting from such live load, to provide for the effect of impact and vibrations.

3. The wind pressure shall be assumed acting horizontally in any direction as follows:—

First: For finished structures—A pressure of 20 pounds per square foot on the sides and ends of buildings and on the vertical projection of roof surfaces, or

Second: In process of construction—A pressure of 30 pounds per square foot on vertical surfaces and the vertical projection of inclined surfaces of all exposed metal or other frame work.

## CONSTRUCTION SPECIFICATIONS

4. **Unit Stresses.** All parts of structures shall be proportioned so that the sum of the dead and live loads, together with the impact, if any, shall not cause the stresses to exceed the following amounts in pounds per square inch:

Tension, net section, rolled steel.....	16000
Direct compression, rolled steel and steel castings.....	16000
Bending, on extreme fibers of rolled shapes, built sections, girders, and steel castings.....	16000
Bending on extreme fibers of pins.....	24000
Shear on shop rivets and pins.....	12000
Shear on bolts and field rivets.....	10000
Shear—average—on webs of plate girders and rolled beams, gross section.....	10000
Bearing pressure on shop rivets and pins.....	24000
Bearing on bolts and field rivets.....	20000
Pressure per linear inch on expansion rollers shall not exceed 600 times the diameter of rollers in inches.	
Axial compression of gross sections of columns, for	
ratio of $l/r$ up to 120.....	$19000 - 100 l/r$
with a maximum of.....	13000
where $l$ =effective length of member in inches, $r$ =corresponding radius of gyration of section in inches.	

For ratios of  $l/r$  up to 120, and for greater ratios up to 200, use the amounts given in the following table. For intermediate ratios, use proportional amounts.

Ratio	Amount	Ratio	Amount
60	13000	130	6500
70	12000	140	6000
80	11000	150	5500
90	10000	160	5000
100	9000	170	4500
110	8000	180	4000
120	7000	190	3500

5. For bracing and combined stresses due to wind and other loading, the permissible working stresses may be increased 25 per cent—provided the section thus found is not less than that required by the dead and live loads alone.



## CARNEGIE STEEL COMPANY

### PROPORTION OF PARTS

6. **General.** The effective or unsupported length of main compression members shall not exceed 120 times, and for secondary members 200 times, the least radius of gyration.

7. In proportioning columns, provision must be made for eccentric loading.

8. In proportioning tension members, net section must be used. Rivet holes deducted must be taken  $\frac{1}{8}$  inch larger than the nominal size of rivets.

9. Members subject to the action of both axial and bending stresses shall be proportioned so that the greatest fiber stress will not exceed the allowed limits in that member.

10. Members subject to alternate stresses of tension and compression shall be proportioned for the stress giving the largest section, but their connections shall be proportioned for the sum of the stresses.

11. **Girders.** Rolled beams and channels, and built-up members used as beams and girders shall be proportioned by the moment of inertia of their gross sections.

12. Plate girder webs shall have a thickness not less than  $\frac{1}{160}$  of the unsupported distance between flange angles. The webs shall have stiffeners, generally in pairs, over bearings, at points of concentrated loading, and at other points where the thickness of the web is less than  $\frac{1}{60}$  of the unsupported distance between flange angles, generally not farther apart than the depth of the web plate, with a maximum limit of 6 feet.

13. The lateral unsupported length of beams and girders shall not exceed 40 times the width of the compression flange. When the unsupported length ( $l$ ) exceeds 10 times the width ( $b$ ) of the compression flange, the stress per square inch in the compression flange shall not exceed  $19000 - 300 l/b$ .

### DETAILS OF STEEL CONSTRUCTION

14. **General.** Adjustable members in any part of structures shall preferably be avoided.

15. Sections shall preferably be made symmetrical.

16. No connection, except lattice bars, shall have less than two rivets.

## CONSTRUCTION SPECIFICATIONS

17. Trusses shall preferably be riveted structures. Heavy trusses of long span, where the riveted field connections would become unwieldy, or for other good reasons, may be designed as pin-connected structures.

18. Abutting joint in compression members faced for bearing shall be spliced sufficiently to hold the connecting members accurately in place. All other joints in riveted work, whether in tension or compression, shall be fully spliced.

19. Lateral, longitudinal and transverse bracing in all structures shall preferably be composed of rigid members, and shall be designed to be sufficient to withstand wind and other lateral forces when building is in process of erection as well as after completion.

20. **Girders.** When two or more rolled beams are used to form a girder, they shall be connected by bolts and separators at intervals of not more than 5 feet. All beams having a depth of 12 inches and more shall have at least two bolts to each separator.

21. The flange plates of all girders shall be limited in width, so as not to extend more than 6 inches beyond the outer line of rivets connecting them to the angles, or 8 times the thickness of the thinnest plate.

22. Web stiffeners shall be in pairs, and shall have a close bearing against the flange angles. Those over the end bearing or forming the connection between girder and column shall be on fillers. Intermediate stiffeners may be on fillers or crimped over the flange angles.

23. Web plates of girders must be spliced at all points by a plate on each side of the web, capable of transmitting the full stress through splice rivets.

24. **Riveting.** The minimum distance between centers of rivet holes shall be three diameters of the rivet; but the distance shall preferably be not less than 3 inches for  $\frac{7}{8}$ -inch rivets,  $2\frac{1}{2}$  inches for  $\frac{3}{4}$ -inch rivets, 2 inches for  $\frac{5}{8}$ -inch rivets, and  $1\frac{3}{4}$  inches for  $\frac{1}{2}$ -inch rivets. The maximum pitch in the line of the stress for members composed of plates and shapes will be 6 inches for  $\frac{7}{8}$ -inch rivets, 6 inches for  $\frac{3}{4}$ -inch rivets,  $4\frac{1}{2}$  inches for  $\frac{5}{8}$ -inch rivets and 4 inches for  $\frac{1}{2}$ -inch rivets.

25. For angles in built sections with two gage lines, with rivets staggered, the maximum pitch in each line shall be twice as great as given above. Where two or more plates are in contact, rivets not more than 12 inches apart in either direction shall be used to hold the plates together.

# CARNEGIE STEEL COMPANY

26. The minimum distance from the center of any rivet hole to a sheared edge shall be  $1\frac{1}{2}$  inches for  $\frac{3}{8}$ -inch rivets,  $1\frac{1}{4}$  inches for  $\frac{1}{2}$ -inch rivets,  $1\frac{1}{8}$  inches for  $\frac{5}{8}$ -inch rivets, and 1 inch for  $\frac{3}{4}$ -inch rivets; and to a rolled edge,  $1\frac{1}{4}$ ,  $1\frac{1}{8}$ , 1, and  $\frac{7}{8}$  inches, respectively.

27. The maximum distance from any edge shall be eight times the thickness of the plate.

28. The pitch of rivets at the ends of built compression members shall not exceed four diameters of the rivets for a length equal to one and one-half times the maximum width of the member.

29. **Latticing.** The open sides of compression members shall be provided with lattice bars, having tie plates at each end and at intermediate points where the lattice is interrupted. The tie plates shall be as near the ends as practicable. In main members carrying calculated stresses, the end tie plates shall have a length not less than the distance between the lines of rivets connecting them to the flanges, and intermediate ones not less than half this distance. Their thickness shall not be less than  $\frac{1}{60}$  of the same distance.

30. The latticing of compression members shall be proportioned to resist a shearing stress equal to 2 per cent of the direct stress. The minimum thickness of lattice bars shall be for single lattice,  $\frac{1}{40}$ , and for double lattice,  $\frac{1}{60}$  of the distance between the end rivets. Their minimum width shall be as follows:

For 15-inch channels, or  
built sections with  $3\frac{1}{2}$  and 4-inch angles,  $2\frac{1}{2}$  inches ( $\frac{1}{8}$ -inch rivets).

For 12-10-and 9-inch channels, or  
built sections with 3-inch angles . . . . .  $2\frac{1}{4}$  inches ( $\frac{1}{4}$ -inch rivets).

For 8-and 7-inch channels, or  
built sections with  $2\frac{1}{2}$ -inch angles . . . . . 2 inches ( $\frac{5}{8}$ -inch rivets).

For 6-and 5-inch channels, or  
built sections with 2-inch angles . . . . .  $1\frac{3}{4}$  inches ( $\frac{1}{2}$ -inch rivets).

31. The inclination of lattice bars with the axis of the member shall generally be not less than 45 degrees. When the distance between the rivet lines in the flanges is more than 15 inches, if a single rivet bar is used, the lattice shall be double.

32. The pitch of lattice connections, along the flange, divided by the least radius of gyration of the member between connections, shall be less than the corresponding ratio of the member as a whole.

## CONSTRUCTION SPECIFICATIONS

33. **Pins.** Pin holes shall be reinforced by plates where necessary. At least one plate shall be as wide as the projecting flanges will allow; where angles are used, this plate shall be on the same side as the angles. The plates shall contain sufficient rivets to distribute their portion of the pin pressure to the full cross section of the member.

34. Pins shall be long enough to insure a full bearing of all parts connected upon the turned-down body of the pin. Members packed on pins shall be held against lateral movement.

## WORKMANSHIP

35. **General.** The workmanship shall be equal to the best practice in modern structural works. Shearing shall be done accurately, and all portions of the work exposed to view shall be neatly finished.

36. **Punching.** The diameter of the punch shall not be more than  $\frac{1}{16}$  inch, nor that of the die more than  $\frac{1}{8}$  inch, larger than the diameter of the rivet. Punching shall be done accurately, but an occasional slight inaccuracy in the matching of holes may be corrected with reamer. Drifting to enlarge unfair holes will not be allowed.

37. **Riveting.** The size of rivets shall be as called for on the plans. Rivets shall be driven by pressure tools wherever possible. Pneumatic hammers shall be used in preference to hand driving. Rivets shall look neat and finished, with heads of approved shape, full and of equal size. They shall be centered on the shank and shall grip the assembled pieces firmly.

38. **Assembling.** Riveted members shall have all parts well pinned up and firmly drawn together with bolts before riveting is commenced. Contact surfaces shall be painted. Abutting joints shall be cut or dressed true and straight and fitted closely together. In compression joints depending on contact bearing, the surfaces shall be truly faced, so as to have even bearing after they are riveted up complete and when perfectly aligned. The several pieces forming one built member shall be straight and shall fit closely together, and finished members shall be free from twists, bends or open joints.

## CARNEGIE STEEL COMPANY

39. **Eye Bars.** Eye bars shall be straight and true to size, and shall be free from twists, folds in the neck or head, or any other defect. Heads shall be made by upsetting, rolling or forging. Welding will not be allowed. Before boring, each eye bar shall be perfectly annealed and carefully straightened. Pin holes shall be in the center line of bars and in the center of heads. Bars of the same length shall be bored so accurately that, when placed together, pins  $\frac{1}{32}$  inch smaller in diameter than the pin holes can be passed through the holes at both ends of the bars at the same time.

40. **Pins.** Pins and rollers shall be turned accurately to gages, and shall be straight, smooth and entirely free from flaws. Pin holes shall be bored true to gages, smooth and straight, at right angles to the axis of the member and parallel to each other, unless otherwise called for. Wherever possible, the boring shall be done after the member is riveted up. The distance from center to center of pin holes shall be correct within  $\frac{1}{32}$  inch, and the diameter of the hole not more than  $\frac{1}{50}$  inch larger than that of the pin for pins up to 5 inches diameter, and  $\frac{1}{32}$  inch for larger pins.

41. **Bed Plates.** Expansion bed plates shall be planed true and smooth. The cut of the planing tool shall correspond with the direction of expansion.

42. **Annealing.** Steel, except in minor details, which has been partially heated, shall be properly annealed. Welds in steel will not be allowed. All steel castings shall be annealed.

43. **Painting.** Steel work, before leaving the shop, shall be thoroughly cleaned and given one good coating of such paint as may be called for, well worked into all joints and open spaces.

44. In riveted work, the surfaces coming in contact shall be painted before being riveted together.

45. Machine-finished bearing surfaces coming in contact with similar surfaces should be coated with white lead and tallow before shipment.

46. **Inspection.** The manufacturer shall furnish all facilities for inspecting and testing the weight, quality of material and workmanship. He shall furnish a suitable testing machine for testing the specimens, as well as prepare the pieces for the machine free of charge.

47. He shall give the inspector for the purchaser free access to all parts of the works where the material under inspection is manufactured.

## ELEMENTS OF SECTIONS

### ELEMENTS OF SECTIONS

#### DEFINITIONS

In the computations of structural designing, certain mathematical expressions are used to designate the values of structural shapes in the various conditions under which they are subjected to stress. In the pages which immediately follow, these values, usually called properties, are given in United States measurements for shapes common in structural designs, and are defined as follows:—

**A—Area of Section.** expressed in square inches.

**r—Radius of Gyration.** The distance in inches from the center of moments of a section to the point or line at which its area is considered concentrated. The radius of gyration of a section referred to any axis is always the square root of the moment of inertia of the section referred to that axis divided by the area.

**I—Moment of Inertia.** The summation, expressed in inches to the fourth power, of the products of the elementary areas of a section by the squares of their distances from its center of gravity or other axis assumed for purposes of computation.

**S—Section Modulus.** The moment of inertia divided by the distance ( $n$ ) from the axis of moments to the extreme fiber. In an unsymmetrical section there are two section moduli for each axis of moments, the least of which determines the safe unit stress.

**Neutral Axis.** Axis of moments through center of area.

**$x$  and  $y$ .** The distance or distances in an unsymmetrical section from the back or working line of the section to the center of gravity of the section.


The section modulus is used to determine the stress in the extreme fiber of a shape subject to bending by dividing the bending moment by the section modulus, both expressed in like units of measurement. It is also used vice versa in the selection from a table of shapes of the proper section required to support a load by dividing the bending stress by the allowable fiber stress, both in like units of weight.

The radius of gyration is used to ascertain the safe load any section or shape will sustain when used in compression as a strut or column. The unbraced length of the section divided by the radius of gyration is denominated the ratio of slenderness.

The elements of steel sections are based upon the theoretical dimensions given in the pages which precede. No account has been taken of fillets or rounded corners, neither have any approximations entered into any of the calculations.


# CARNEGIE STEEL COMPANY

**SQUARE**  
Axis of moments through center




$$\begin{aligned} A &= d^2 \\ x &= \frac{d}{2} \\ I_{1-1} &= \frac{d^4}{12} \\ S_{1-1} &= \frac{d^3}{6} \\ r_{1-1} &= \frac{d}{\sqrt{12}} = 0.288675d \end{aligned}$$

**SQUARE**  
Axis of moments on base




$$\begin{aligned} A &= d^2 \\ x &= d \\ I_{1-1} &= \frac{d^4}{3} \\ S_{1-1} &= \frac{d^3}{3} \\ r_{1-1} &= \frac{d}{\sqrt{3}} = 0.577350d \end{aligned}$$

**SQUARE**  
Axis of moments on diagonal




$$\begin{aligned} A &= d^2 \\ x &= \frac{d}{\sqrt{2}} = 0.707107d \\ I_{1-1} &= \frac{d^4}{12} \\ S_{1-1} &= \frac{d^3}{6\sqrt{2}} = 0.117851d^3 \\ r_{1-1} &= \frac{d}{\sqrt{12}} = 0.288675d \end{aligned}$$

**HOLLOW SQUARE**  
Axis of moments through center



$$\begin{aligned} A &= d^2 - d_1^2 \\ x &= \frac{d}{2} \\ I_{1-1} &= \frac{d^4 - d_1^4}{12} \\ S_{1-1} &= \frac{d^3 - d_1^3}{6d} \\ r_{1-1} &= \sqrt{\frac{d^2 + d_1^2}{12}} \end{aligned}$$


**HOLLOW SQUARE**  
Axis of moments on diagonal



$$\begin{aligned} A &= d^2 - d_1^2 \\ x &= \frac{d}{\sqrt{2}} \\ I_{1-1} &= \frac{d^4 - d_1^4}{12} \\ S_{1-1} &= \frac{d^3 - d_1^3}{6\sqrt{2}d} = 0.117851 \frac{d^3 - d_1^3}{d} \\ r_{1-1} &= \sqrt{\frac{d^2 + d_1^2}{12}} \end{aligned}$$


# ELEMENTS OF SECTIONS

RECTANGLE  
Axis of moments through center




$$\begin{aligned} A &= bd \\ x &= \frac{d}{2} \\ I_{1-1} &= \frac{bd^3}{12} \\ S_{1-1} &= \frac{bd^2}{6} \\ r_{1-1} &= \frac{d}{\sqrt{12}} = 0.288675d \end{aligned}$$

RECTANGLE  
Axis of moments on base




$$\begin{aligned} A &= bd \\ x &= d \\ I_{1-1} &= \frac{bd^3}{3} \\ S_{1-1} &= \frac{bd^2}{3} \\ r_{1-1} &= \frac{d}{\sqrt{3}} = 0.577350d \end{aligned}$$

RECTANGLE  
Axis of moments on diagonal




$$\begin{aligned} A &= bd \\ x &= \frac{bd}{\sqrt{b^2+d^2}} \\ I_{1-1} &= \frac{b^3 d^3}{6 (b^2+d^2)} \\ S_{1-1} &= \frac{b^2 d^2}{6 \sqrt{b^2+d^2}} \\ r_{1-1} &= \frac{bd}{\sqrt{6 (b^2+d^2)}} \end{aligned}$$

RECTANGLE  
Axis of moments any line through center of gravity



$$\begin{aligned} A &= bd \\ x &= \frac{b \sin \alpha + d \cos \alpha}{2} \\ I_{1-1} &= \frac{bd (b^2 \sin^2 \alpha + d^2 \cos^2 \alpha)}{12} \\ S_{1-1} &= \frac{bd (b^2 \sin^2 \alpha + d^2 \cos^2 \alpha)}{6 (b \sin \alpha + d \cos \alpha)} \\ r_{1-1} &= \sqrt{\frac{b^2 \sin^2 \alpha + d^2 \cos^2 \alpha}{12}} \end{aligned}$$

HOLLOW RECTANGLE  
Axis of moments through center




$$\begin{aligned} A &= bd - b_1 d_1 \\ x &= \frac{d}{2} \\ I_{1-1} &= \frac{bd^3 - b_1 d_1^3}{12} \\ S_{1-1} &= \frac{bd^2 - b_1 d_1^2}{6d} \\ r_{1-1} &= \sqrt{\frac{bd^3 - b_1 d_1^3}{12 (bd - b_1 d_1)}} \end{aligned}$$



# CARNEGIE STEEL COMPANY

**TRIANGLE**  
Axis of moments through  
center of gravity



$$A = \frac{bd}{2}$$

$$x = \frac{2d}{3}$$


$$x_1 = \frac{d}{3}$$

$$I_{1-1} = \frac{bd^3}{36}$$

$$S_{1-1} = \frac{bd^2}{24}$$

$$r_{1-1} = \frac{d}{\sqrt{18}} = 0.235702d$$

**TRIANGLE**  
Axis of moments on base



$$A = \frac{bd}{2}$$


$$x = d$$

$$I_{1-1} = \frac{bd^3}{12}$$

$$S_{1-1} = \frac{bd^2}{12}$$

$$r_{1-1} = \frac{d}{\sqrt{6}} = 0.408248d$$

**TRAPEZOID**  
Axis of moments through  
center of gravity



$$A = \frac{d(b + b_1)}{2}$$

$$x = \frac{d(b_1 + 2b)}{3(b + b_1)}$$


$$x_1 = \frac{d(b + 2b_1)}{3(b + b_1)}$$

$$I_{1-1} = \frac{d^3(b^2 + 4bb_1 + b_1^2)}{36(b + b_1)}$$

$$S_{1-1} = \frac{d^2(b^2 + 4bb_1 + b_1^2)}{12(b + b_1)}$$

$$r_{1-1} = \frac{d}{6(b + b_1)} \sqrt{2(b^2 + 4bb_1 + b_1^2)}$$

**TRAPEZOID**  
Axis of moments on base



$$A = \frac{d(b + b_1)}{2}$$


$$x = d$$

$$I_{1-1} = \frac{d^3(b + 3b_1)}{12}$$

$$S_{1-1} = \frac{d^2(b + 3b_1)}{12}$$

$$r_{1-1} = \frac{d}{\sqrt{6}} \sqrt{\frac{b + 3b_1}{b + b_1}}$$

**REGULAR POLYGON**  
Axis of moments through  
center



$n$  = Number of Sides

$$A = \frac{1}{2} na^2 \cot \phi = \frac{1}{2} n R^2 \sin 2\phi = n R_1^2 \tan \phi$$

$$x = R = \frac{a}{2 \sin \phi} \quad x_1 = R_1 = \frac{a}{2 \tan \phi}$$






$$I_{1-1} = \frac{A(6R^2 - a^2)}{24} = I_{2-2} = \frac{A(12R_1^2 + a^2)}{48}$$

$$S_{1-1} = \frac{A(6R^2 - a^2)}{24R} \quad S_{2-2} = \frac{A(12R_1^2 + a^2)}{48R_1}$$


$$r_{1-1} = \sqrt{\frac{6R^2 - a^2}{24}} = r_{2-2} = \sqrt{\frac{12R_1^2 + a^2}{48}}$$

$$a = 2 \sqrt{R^2 - R_1^2}$$

# ELEMENTS OF SECTIONS

<p><b>CIRCLE</b> Axis of moments through center</p> 	$A = \frac{\pi d^2}{4} = 0.785398 d^2$ $x = \frac{d}{2}$ $I_{1-1} = \frac{\pi d^4}{64} = 0.049087 d^4$ $S_{1-1} = \frac{\pi d^3}{32} = 0.098175 d^3$ $r_{1-1} = \frac{d}{4}$
<p><b>HOLLOW CIRCLE</b> Axis of moments through center</p> 	$A = \frac{\pi (d^2 - d_1^2)}{4} = 0.785398 (d^2 - d_1^2)$ $x = \frac{d}{2}$ $I_{1-1} = \frac{\pi (d^4 - d_1^4)}{64} = 0.049087 (d^4 - d_1^4)$ $S_{1-1} = \frac{\pi (d^3 - d_1^3)}{32d} = 0.098175 \frac{(d^3 - d_1^3)}{d}$ $r_{1-1} = \frac{\sqrt{d^2 + d_1^2}}{4}$
<p><b>HALF CIRCLE</b> Axis of moments through center of gravity</p> 	$A = \frac{\pi d^2}{8} = 0.392699 d^2$ $x = \frac{d(3\pi - 4)}{6\pi} = 0.287793d, \quad x_1 = \frac{2d}{3\pi} = 0.212207d$ $I_{1-1} = \frac{d^4(9\pi^2 - 64)}{1152\pi} = 0.006860 d^4$ $S_{1-1} = \frac{d^3(9\pi^2 - 64)}{192(3\pi - 4)} = 0.023836 d^3$ $r_{1-1} = d \sqrt{\frac{9\pi^2 - 64}{12\pi}} = 0.132168 d$
<p><b>HOLLOW HALF CIRCLE</b> Axis of moments through center of gravity</p> 	$A = \frac{\pi (d^2 - d_1^2)}{8} = 0.392699 (d^2 - d_1^2)$ $x = \frac{2(d^2 - d_1^2)}{3\pi(d^2 - d_1^2)} x_1 = \frac{3\pi d(d^2 - d_1^2) - 4(d^3 - d_1^3)}{6\pi(d^2 - d_1^2)}$ $I_{1-1} = \frac{9\pi^2(d^4 - d_1^4)(d^2 - d_1^2) - 64(d^5 - d_1^5)}{1152\pi(d^2 - d_1^2)^2}$ $S_{1-1} = \frac{I}{x} \text{ if } x > x_1 \quad S_{1-1} = \frac{I}{x_1} \text{ if } x_1 > x$ $r_{1-1} = \frac{1}{12\pi} \sqrt{\frac{9\pi^2(d^4 - d_1^4)(d^2 - d_1^2) - 64(d^5 - d_1^5)}{(d^2 - d_1^2)^2}}$
<p><b>ELLIPSE</b> Axis of moments through center</p> 	$A = \frac{\pi d d_1}{4} = 0.785398 d d_1$ $x = \frac{d}{2}$ $I_{1-1} = \frac{\pi d^3 d_1}{64} = 0.049087 d^3 d_1$ $S_{1-1} = \frac{\pi d^2 d_1}{32} = 0.098175 d^2 d_1$ $r_{1-1} = \frac{d}{4}$

# CARNEGIE STEEL COMPANY

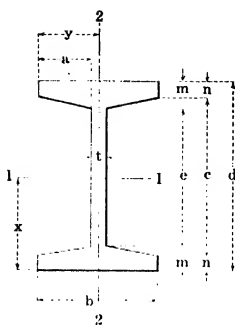

## BEAM


$$A = dt + 2a(m+n)$$

$$x = \frac{d}{2}$$

$$y = \frac{b}{2}$$

$$I_{1-1} = \frac{bd^3 - \frac{a}{4(m+n)}(c^4 - e^4)}{12}$$

$$I_{2-2} = \frac{2nb^3 + ct^3 + \frac{m}{4a}n(b^4 - t^4)}{12}$$

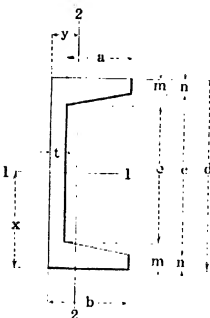

## CHANNEL


$$A = dt + a(m+n)$$

$$x = \frac{d}{2}$$

$$y = \frac{b^2n + \frac{ct^2}{2} + \frac{a(m+n)}{3}(b + 2t)}{A}$$

$$I_{1-1} = \frac{bd^3 - \frac{a}{8(m+n)}(c^4 - e^4)}{12}$$

$$I_{2-2} = \frac{2nb^3 + ct^3 + \frac{m}{2a}n(b^4 - t^4)}{3} - Ay^2$$

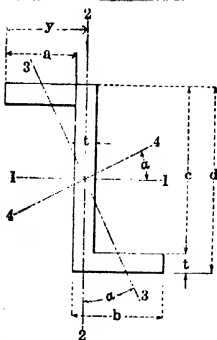

## ZEE

$$A = t(d + 2a)$$

$$x = \frac{d}{2}$$

$$y = \frac{2b-t}{2}$$

$$\tan 2\alpha = \frac{(dt - t^2)(b^2 - bt)}{I_{1-1} - I_{2-2}}$$

$$I_{1-1} = \frac{bd^3 - a(d - 2t)^3}{12}$$


$$I_{2-2} = \frac{d(b + a)^3 - 2a^3c - 6ab^2c}{12}$$

$$I_{3-3} = \frac{I_{2-2} \cos^2 \alpha - I_{1-1} \sin^2 \alpha}{\cos 2\alpha}$$

$$I_{4-4} = \frac{I_{1-1} \cos^2 \alpha - I_{2-2} \sin^2 \alpha}{\cos 2\alpha}$$


# ELEMENTS OF SECTIONS

## EQUAL ANGLE

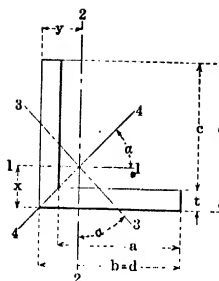


$$\begin{aligned} A &= t(b+c) \\ x &= \frac{b^2+ct}{2(b+c)} \\ y &= x \\ \alpha &= 45^\circ \\ I_{1-1} &= \frac{t(b-x)^3 + bx^3 - a(x-t)^3}{3} \\ I_{2-2} &= I_{1-1} \\ I_{3-3} &= \frac{rt^3 + c^3t + 3ct(b-4x+2t)^2 + t^4 + 6t^2(2x-t)^2}{12} \\ I_{4-4} &= \frac{c^3 + c^3t + 3ct(b^2+t^4)}{12} \end{aligned}$$

## UNEQUAL ANGLE

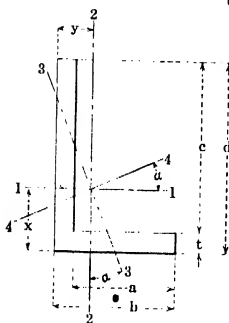

$$\begin{aligned} A &= t(b+c) \\ x &= \frac{t(b+2c) + c^2}{2(b+c)} \\ y &= \frac{t(2a+d) + a^2}{2(a+d)} \\ \tan 2\alpha &= \frac{t[(2y-t)d(d-2x) + a(2x-t)(b+t-2y)]}{2(I_{1-1} - I_{2-2})} \\ I_{1-1} &= \frac{t(d-x)^3 + bx^3 - a(x-t)^3}{3} \\ I_{2-2} &= \frac{t(b-y)^3 + dy^3 - c(y-t)^3}{3} \\ I_{3-3} &= \frac{I_{2-2} \cos^2 \alpha - I_{1-1} \sin^2 \alpha}{\cos 2\alpha} \\ I_{4-4} &= \frac{I_{1-1} \cos^2 \alpha - I_{2-2} \sin^2 \alpha}{\cos 2\alpha} \end{aligned}$$

## TEE

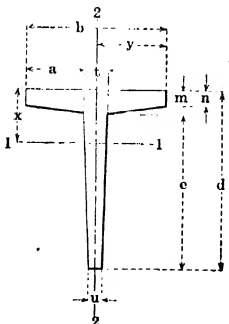

$$\begin{aligned} A &= \frac{c(t+u)}{2} + mt + a(m+n) \\ x &= \frac{6an^2 + 2a(m-n)(m+2n) + 3t[2-c(t-u)(3d-t)}{6A} \\ y &= \frac{b}{2} \\ I_{1-1} &= \frac{c^3(3a+t) + 4bmn - 2a(m-n)^3 - A(x-m)^2}{12} \\ I_{2-2} &= \frac{nb^3 + (m-n)t^3 + cu^3}{12} \\ &\quad + \frac{a(m-n)[2a^2 + (2a+3t)^2]}{36} \\ &\quad + \frac{c(t-u)[(t-u)^2 + 2(t+2u)^2]}{144} \end{aligned}$$

# CARNEGIE STEEL COMPANY

## COMPOUND SECTIONS


### MOMENTS OF INERTIA, SECTION MODULI, AND RADII OF GYRATION

The moment of inertia of a compound section about its neutral axis is equal to the sum of the moment of inertia,  $I$ , of the component parts about axes through their own centers of gravity, plus the areas  $A$ , of the component parts multiplied by the squares of the distances  $d$ , of their own centers of gravity from the neutral axis of the compound section, or

$$\text{Moment of Inertia } I^1 = I + Ad^2$$

$$\text{Section Modulus } S^1 = \frac{I^1}{n}$$

$$\text{Radius of Gyration } r^1 = \sqrt{\frac{I^1}{A^1}}$$

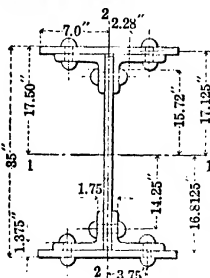

**EXAMPLE 1.** Required the moments of inertia and the section moduli about axes 1-1 and 2-2 of a compound section to be used as a girder, composed of

- 1 Web Plate 33"x $\frac{1}{2}$ "
- 4 Flange Angles 6"x4"x $\frac{5}{8}$ "
- 2 Flange Plates 14"x $\frac{3}{4}$ "

basing the properties on the gross area of the section.

Determine the distances, of the center lines of gravity of plates and angles, from the neutral axes of the compound section, from the dimensions given, then for


<b>AXIS 1-1</b>	$I_{1-1}$ of 4-6"x4"x $\frac{5}{8}$ " Angles	= 4 x 7.52	= 30.08 Inches <sup>4</sup>
	$Ad^2$ of 4-6"x4"x $\frac{5}{8}$ "	= 4 x 5.86x15.72 <sup>2</sup>	= 5792.46 "
	$I_{1-1}$ of 1-33"x $\frac{1}{2}$ " Plate	= 1 x $\frac{0.50 \times 33^3}{12}$	= 1497.38 "
	$I_{1-1}$ of 2-14"x $\frac{3}{4}$ "	= 2 x $\frac{14 \times 0.75^3}{12}$	= 0.98 "
	$Ad^2$ of 2-14"x $\frac{3}{4}$ "	= 2 x 10.50 x 17.125 <sup>2</sup>	= 6158.58 "
Moment of Inertia, gross section			13479.48 Inches <sup>4</sup>
Section Modulus, " "			$\frac{13479.48}{17.50}$ = 770.26 Inches <sup>3</sup>
<b>AXIS 2-2</b>	$I_{2-2}$ of 4-6"x4"x $\frac{5}{8}$ " Angles	= 4 x 21.07	= 84.28 Inches <sup>4</sup>
	$Ad^2$ of 4-6"x4"x $\frac{5}{8}$ "	= 4 x 5.86x2.28 <sup>2</sup>	= 121.85 "
	$I_{2-2}$ of 1-33"x $\frac{1}{2}$ " Plate	= 1 x $\frac{33 \times 0.50^3}{12}$	= 0.34 "
	$I_{2-2}$ of 2-14"x $\frac{3}{4}$ "	= 2 x $\frac{0.75 \times 14^3}{12}$	= 343.00 "
	Moment of Inertia, gross section		549.47 Inches <sup>4</sup>
Section Modulus, " "			$\frac{549.47}{7}$ = 78.50 Inches <sup>3</sup>

If it is desired to calculate the properties of the net section, viz., to deduct the area of the rivet holes, proceed as follows, assuming that  $\frac{3}{8}$ " holes for  $\frac{3}{4}$ " rivets are to be deducted and that not more than one rivet will be driven in any one leg of the angles in the same plane of the section.

<b>AXIS 1-1</b>	$I_{1-1}$ of gross section		13479.48 Inches <sup>4</sup>
	Deduct $I_{1-1}$ of 4-0.875"x1.375" Rectangles	= 4 x $\frac{0.875 \times 1.375^3}{12}$	= 0.76 "
	$Ad^2$ of 4-0.875"x1.375"	= 4 x 1.203x16.8125 <sup>2</sup>	= 1360.16 "
	$I_{1-1}$ of 2-0.875"x1.75"	= 2 x $\frac{1.75 \times 0.875^3}{12}$	= 0.20 "
	$Ad^2$ of 2-0.875"x1.75"	= 2x1.531x14.25 <sup>2</sup>	= 621.77 "
Moment of Inertia, net section			11496.69 Inches <sup>4</sup>
Section Modulus, " "			$\frac{11496.69}{17.50}$ = 656.95 Inches <sup>3</sup>
<b>AXIS 2-2</b>	$I_{2-2}$ of gross section		549.47 Inches <sup>4</sup>
	Deduct $I_{2-2}$ of 4-0.875"x1.375" Rectangles	= 4 x $\frac{1.375 \times 0.875^3}{12}$	= 0.31 "
	$Ad^2$ of 4-0.875"x1.375"	= 4 x 1.203x3.75 <sup>2</sup>	= 67.67 "
	$I_{2-2}$ of 2-0.875"x1.75"	= 2 x $\frac{0.875 \times 1.75^3}{12}$	= 0.78 "
	Moment of Inertia, net section		480.71 Inches <sup>4</sup>
Section Modulus, " "			$\frac{480.71}{7}$ = 68.67 Inches <sup>3</sup>

# ELEMENTS OF SECTIONS

## COMPOUND SECTIONS—Concluded



EXAMPLE 2. Required the moments of inertia and radii of gyration about axes 1-1 and 2-2 of a column section composed as follows:—


- 2 Channels 12" x 30 pounds per foot,
- 2 Flange Plates 14" x  $\frac{3}{4}$ "

properties to be based on the gross section, no deduction being made for holes.

Determine the distances,  $d$ , of center lines of gravity for the various sections from the neutral axes 1-1 and 2-2, in accordance with the dimensions given, then for

$$\begin{aligned} \text{AXIS 1-1 } I_{1-1} \text{ of 2-12" Channels 30 lbs.} &= 2 \times \frac{161.65}{12} = 323.30 \text{ Inches}^4 \\ I_{1-1} \text{ of 2-14" x } \frac{3}{4}" \text{ Plates} &= 2 \times \frac{14 \times 0.75^3}{12} = 0.98 \text{ " } \\ Ad^2 \text{ of 2-14" x } \frac{3}{4}" \text{ " } &= 2 \times 10.5 \times 6.375^2 = 853.45 \text{ " } \\ \text{Moment of Inertia, gross section} &= 1177.73 \text{ Inches}^4 \\ \text{Radius of Gyration, " } &= \sqrt{\frac{1177.73}{38.64}} = 5.52 \text{ Inches} \end{aligned}$$

$$\begin{aligned} \text{AXIS 2-2 } I_{2-2} \text{ of 2-12" Channels 30 lbs.} &= 2 \times 5.22 = 10.44 \text{ Inches}^4 \\ Ad^2 \text{ of 2-12" Channels 30 lbs.} &= 2 \times 8.82 \times 4.164^2 = 305.86 \text{ " } \\ I_{2-2} \text{ of 2-14" x } \frac{3}{4}" \text{ Plates} &= 2 \times \frac{0.75 \times 14^3}{12} = 343.0 \text{ " } \\ \text{Moment of Inertia, gross section} &= 659.30 \text{ Inches}^4 \\ \text{Radius of Gyration, " } &= \sqrt{\frac{659.30}{38.64}} = 4.13 \text{ Inches} \end{aligned}$$



EXAMPLE 3. Required the radii of gyration about axes 1-1 and 2-2 of a strut section composed as follows:—

- 4-6" x 4" x  $\frac{3}{8}$ " Angles laced by  $\frac{3}{8}$ " bars,

properties to be based on the gross section of angles, no deductions being made for rivet holes nor any allowance for lattice bars.

Determine the distances,  $d$ , of center lines of gravity of angles from neutral axes 1-1 and 2-2 in accordance with the dimensions given, then for

$$\begin{aligned} \text{AXIS 1-1 } I_{1-1} \text{ of 4-6" x 4" x } \frac{3}{8}" \text{ Angles} &= 4 \times 4.90 = 19.60 \text{ Inches}^4 \\ Ad^2 \text{ of 4-6" x 4" x } \frac{3}{8}" \text{ " } &= 4 \times 3.61 \times 5.06^2 = 369.72 \text{ " } \\ \text{Moment of Inertia, gross section} &= 389.32 \text{ Inches}^4 \\ \text{Radius of Gyration, " } &= \sqrt{\frac{389.32}{14.44}} = 5.19 \text{ Inches} \end{aligned}$$

AXIS 2-2 From tables of radii of gyration for 2 angles placed back to back, page 196,  $r_{2-2}$  of 4-6" x 4" x  $\frac{3}{8}$ " angles = 2.87 Inches.


Where sections are assembled without any web or flange plates, as, for example, latticed channel columns or latticed angle struts, the radius of gyration,  $r_1$  can be readily obtained, without considering the moment of inertia, from the radius of gyration,  $r$  of one section about the neutral axis, and the distance,  $d$ , between the center of gravity of the section and the neutral axis parallel to the axis of section.

$$r_1 = \sqrt{\frac{I + Ad^2}{A}}, \text{ where } \frac{I}{A} = r^2, \text{ and } r_1 = \sqrt{r^2 + d^2}$$

Thus, in the above example,

$$r_{1-1} = \sqrt{5.06^2 + 1.17^2} = 5.19 \text{ Inches}$$


**CARNEGIE STEEL COMPANY**  
**ELEMENTS OF STRUCTURAL BEAMS**



Section Index	Depth of Beam	Weight per Foot	Area of Section	Width of Flange	Thickness of Web	Axis 1-1			Axis 2-2		
						I	r	S	I	r	S
						In. <sup>4</sup>	In. <sup>3</sup>	In. <sup>3</sup>	In. <sup>4</sup>	In. <sup>3</sup>	In. <sup>3</sup>
B 61	27	90.0	26.33	9.000	0.524	2958.3	10.60	219.1	75.3	1.69	16.7
		115.0	33.98	8.000	0.750	2955.5	9.33	246.3	83.2	1.57	20.8
B 24	24	110.0	32.48	7.938	0.688	2883.5	9.12	240.3	81.0	1.58	20.4
		105.0	30.98	7.875	0.625	2811.5	9.53	234.3	78.9	1.60	20.0
B 1	24	100.0	29.41	7.254	0.754	2379.6	9.00	198.3	48.6	1.28	13.4
		95.0	27.91	7.193	0.693	2309.0	9.09	192.4	47.1	1.30	13.1
		90.0	26.47	7.131	0.631	2238.4	9.20	186.5	45.7	1.31	12.8
		85.0	25.00	7.070	0.570	2167.8	9.31	180.7	44.4	1.33	12.6
		80.0	23.32	7.000	0.500	2087.2	9.46	173.9	42.9	1.36	12.3
B 62	24	74.0	21.70	9.000	0.476	1950.1	9.48	162.5	61.2	1.68	13.6
B 63	21	60.5	17.68	8.250	0.428	1235.5	8.36	117.7	43.5	1.57	10.6
		100.0	29.41	7.284	0.884	1655.6	7.50	165.6	52.7	1.34	14.5
B 2	20	95.0	27.91	7.210	0.810	1606.6	7.58	160.7	50.8	1.35	14.1
		90.0	26.47	7.137	0.737	1557.6	7.67	155.8	49.0	1.36	13.7
		85.0	25.00	7.063	0.663	1508.5	7.77	150.9	47.3	1.37	13.4
		80.0	23.73	7.000	0.600	1466.3	7.86	146.6	45.8	1.39	13.1
B 3	20	75.0	22.06	6.399	0.649	1268.8	7.58	126.9	30.3	1.17	9.5
		70.0	20.59	6.325	0.575	1219.8	7.70	122.0	29.0	1.19	9.2
		65.0	19.08	6.250	0.500	1169.5	7.83	117.0	27.9	1.21	8.9
B 81	18	90.0	26.47	7.245	0.807	1260.4	6.90	110.0	52.0	1.40	14.4
		85.0	25.00	7.163	0.725	1220.7	6.99	105.6	50.0	1.42	14.0
		80.0	23.53	7.082	0.644	1181.0	7.09	101.2	48.1	1.43	13.6
B 80	18	75.0	22.05	7.000	0.562	1141.3	7.19	126.8	46.2	1.45	13.2
		70.0	20.59	6.259	0.719	921.2	6.69	102.4	24.6	1.09	7.9
		65.0	19.12	6.177	0.637	881.5	6.79	97.9	23.5	1.11	7.6
		60.0	17.65	6.095	0.555	841.8	6.91	93.5	22.4	1.13	7.3
B 64	18	55.0	15.93	6.000	0.460	795.6	7.07	88.4	21.2	1.15	7.1
		48.0	14.08	7.500	0.380	737.1	7.23	81.9	30.0	1.46	8.0
B 5	15	75.0	22.06	6.292	0.882	691.2	5.60	92.2	30.7	1.18	9.8
		70.0	20.59	6.194	0.784	663.7	5.68	88.5	29.0	1.19	9.4
		65.0	19.12	6.096	0.686	636.1	5.77	84.8	27.4	1.20	9.0
		60.0	17.67	6.000	0.590	609.0	5.87	81.2	26.0	1.21	8.7
B 7	15	55.0	16.18	5.746	0.656	511.0	5.62	68.4	17.1	1.02	5.9
		50.0	14.71	5.648	0.558	483.4	5.73	64.5	16.0	1.04	5.7
		45.0	13.24	5.550	0.460	455.9	5.87	60.8	15.1	1.07	5.4
		42.0	12.48	5.500	0.410	441.8	5.95	58.9	14.6	1.08	5.3
B 65	15	37.5	10.91	6.750	0.332	405.5	6.10	54.1	19.9	1.35	5.9

# ELEMENTS OF SECTIONS

## ELEMENTS OF STRUCTURAL BEAMS—Concluded




Section Index	Depth of Beam	Weight per Foot	Area of Section	Width of Flange	Thickness of Web	Axis 1-1			Axis 2-2		
						I	r	S	I	r	S
						In. <sup>4</sup>	In.	In. <sup>3</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>
B 8	12	55.0	16.18	5.611	0.821	321.0	4.45	53.5	17.5	1.04	6.2
		50.0	14.71	5.489	0.699	303.4	4.54	50.6	16.1	1.05	5.9
		45.0	13.24	5.366	0.576	285.7	4.65	47.6	14.9	1.06	5.6
		40.0	11.84	5.250	0.460	269.0	4.77	44.8	13.8	1.08	5.3
B 9	12	35.0	10.29	5.086	0.436	228.3	4.71	38.0	10.1	0.99	4.0
		31.5	9.26	5.000	0.350	215.8	4.83	36.0	9.5	1.01	3.8
B 66	12	28.0	8.15	6.000	0.284	199.4	4.95	33.2	12.6	1.24	4.2
B 11	10	40.0	11.76	5.099	0.749	158.7	3.67	31.7	9.5	0.90	3.7
		35.0	10.29	4.952	0.602	146.4	3.77	29.3	8.5	0.91	3.4
		30.0	8.82	4.805	0.455	134.2	3.90	26.8	7.7	0.93	3.2
		25.0	7.37	4.660	0.310	122.1	4.07	24.1	6.9	0.97	3.0
B 67	10	22.25	6.54	5.500	0.252	113.6	4.17	22.7	9.0	1.17	3.3
B 13	9	35.0	10.29	4.772	0.732	111.8	3.29	24.8	7.3	0.84	3.1
		30.0	8.82	4.609	0.569	101.9	3.40	22.6	6.4	0.85	2.8
		25.0	7.35	4.446	0.406	91.9	3.54	20.4	5.7	0.88	2.5
		21.0	6.31	4.330	0.290	84.9	3.67	18.9	5.2	0.90	2.4
B 15	8	25.5	7.50	4.271	0.541	68.4	3.02	17.1	4.8	0.80	2.2
		23.0	6.76	4.179	0.449	64.5	3.09	16.1	4.4	0.81	2.1
		20.5	6.03	4.087	0.357	60.6	3.17	15.2	4.1	0.82	2.0
B 68	8	18.0	5.33	4.000	0.270	56.9	3.27	14.2	3.8	0.84	1.9
		17.5	5.12	5.000	0.220	58.4	3.38	14.6	6.2	1.10	2.5
B 17	7	20.0	5.88	3.868	0.458	42.2	2.68	12.1	3.2	0.74	1.7
		17.5	5.15	3.763	0.353	39.2	2.76	11.2	2.9	0.76	1.6
		15.0	4.42	3.660	0.250	36.2	2.86	10.4	2.7	0.78	1.5
B 19	6	17.25	5.07	3.575	0.475	26.2	2.27	8.7	2.4	0.68	1.3
		14.75	4.34	3.452	0.352	21.0	2.35	8.0	2.1	0.69	1.2
		12.25	3.61	3.330	0.230	21.8	2.46	7.3	1.9	0.72	1.1
B 21	5	14.75	4.31	3.294	0.504	15.2	1.87	6.1	1.7	0.63	1.0
		12.25	3.60	3.147	0.357	13.6	1.94	5.5	1.5	0.63	0.92
		9.75	2.87	3.000	0.210	12.1	2.05	4.8	1.2	0.65	0.82
B 23	4	10.5	3.09	2.880	0.410	7.1	1.52	3.6	1.0	0.57	0.70
		9.5	2.79	2.807	0.337	6.8	1.55	3.4	0.93	0.58	0.66
		8.5	2.50	2.733	0.263	6.4	1.59	3.2	0.85	0.58	0.62
		7.5	2.21	2.660	0.190	6.0	1.64	3.0	0.77	0.59	0.58
B 77	3	7.5	2.21	2.521	0.361	2.9	1.15	1.9	0.60	0.52	0.48
		6.5	1.91	2.423	0.263	2.7	1.19	1.8	0.53	0.52	0.44
		5.5	1.63	2.330	0.170	2.5	1.23	1.7	0.46	0.53	0.40



# CARNEGIE STEEL COMPANY

## ELEMENTS OF STRUCTURAL CHANNELS



Section Index	Depth of Channel	Weight per Foot	Area of Section	Width of Flange	Thickness of Web	Axis 1-1			Axis 2-2			x
						I	r	S	I	r	S	
						In. <sup>4</sup>	In.	In. <sup>3</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	
C 1	15	55.0	16.18	3.818	0.818	430.2	5.16	57.4	12.2	0.87	1.1	0.82
		50.0	14.71	3.720	0.720	402.7	5.23	53.7	11.2	0.87	1.1	0.80
		45.0	13.24	3.622	0.622	375.1	5.32	50.0	10.3	0.88	1.1	0.79
		40.0	11.76	3.524	0.524	347.5	5.43	46.3	9.4	0.89	1.1	0.78
		35.0	10.29	3.426	0.426	319.9	5.58	42.7	8.5	0.91	1.1	0.79
C 2	12	33.0	9.90	3.400	0.400	312.6	5.62	41.7	8.2	0.91	1.1	0.79
		40.0	11.76	3.418	0.758	196.9	4.09	32.8	6.6	0.75	2.5	0.72
		35.0	10.29	3.296	0.636	179.3	4.17	29.9	5.9	0.76	2.3	0.69
		30.0	8.82	3.173	0.513	161.7	4.28	26.9	5.2	0.77	2.1	0.68
		25.0	7.35	3.050	0.390	144.0	4.43	24.0	4.5	0.79	1.9	0.68
C 3	10	20.5	6.03	2.940	0.280	128.1	4.61	21.4	3.9	0.81	1.7	0.70
		35.0	10.29	3.183	0.823	115.5	3.35	23.1	4.7	0.67	1.9	0.70
		30.0	8.82	3.036	0.676	103.2	3.42	20.7	4.0	0.67	1.7	0.65
		25.0	7.35	2.889	0.529	91.0	3.52	18.2	3.4	0.68	1.5	0.62
		20.0	5.88	2.742	0.382	78.7	3.66	15.7	2.9	0.70	1.3	0.61
C 4	9	15.0	4.46	2.600	0.240	66.9	3.87	13.4	2.3	0.72	1.2	0.64
		25.0	7.35	2.815	0.615	70.7	3.10	15.7	3.0	0.61	1.4	0.62
		20.0	5.88	2.652	0.452	60.8	3.21	13.5	2.5	0.65	1.2	0.59
		15.0	4.41	2.488	0.288	50.9	3.40	11.3	2.0	0.67	1.0	0.59
		13.25	3.89	2.430	0.230	47.3	3.49	10.5	1.8	0.67	0.97	0.61
C 5	8	21.25	6.25	2.622	0.582	47.8	2.77	11.9	2.3	0.60	1.1	0.59
		18.75	5.51	2.530	0.490	43.8	2.82	11.0	2.0	0.60	1.0	0.57
		16.25	4.78	2.439	0.399	39.9	2.89	10.0	1.8	0.61	0.95	0.56
		13.75	4.04	2.347	0.307	36.0	2.98	9.0	1.6	0.62	0.87	0.56
		11.25	3.35	2.260	0.220	32.3	3.11	8.1	1.3	0.63	0.79	0.58
C 6	7	19.75	5.81	2.513	0.633	33.2	2.39	9.5	1.9	0.56	0.96	0.58
		17.25	5.07	2.408	0.528	30.2	2.44	8.6	1.6	0.57	0.87	0.56
		14.75	4.34	2.303	0.423	27.2	2.50	7.8	1.4	0.57	0.79	0.54
		12.25	3.60	2.198	0.318	24.2	2.59	6.9	1.2	0.58	0.71	0.53
		9.75	2.85	2.090	0.210	21.1	2.72	6.0	0.98	0.59	0.63	0.55
C 7	6	15.5	4.56	2.283	0.563	19.5	2.07	6.5	1.3	0.53	0.74	0.55
		13.0	3.82	2.160	0.440	17.3	2.13	5.8	1.1	0.53	0.65	0.52
		10.5	3.09	2.038	0.318	15.1	2.21	5.0	0.88	0.53	0.57	0.50
		8.0	2.38	1.920	0.200	13.0	2.34	4.3	0.70	0.54	0.50	0.52
		11.5	3.38	2.037	0.477	10.4	1.75	4.2	0.82	0.49	0.54	0.51
C 8	5	9.0	2.65	1.890	0.330	8.9	1.83	3.6	0.64	0.49	0.45	0.48
		6.5	1.95	1.750	0.190	7.4	1.95	3.0	0.48	0.50	0.38	0.49
		7.25	2.13	1.725	0.325	4.6	1.46	2.3	0.44	0.46	0.35	0.46
		6.25	1.84	1.652	0.252	4.2	1.51	2.1	0.38	0.45	0.32	0.46
		5.25	1.55	1.580	0.180	3.8	1.56	1.9	0.32	0.45	0.29	0.46
C 9	4	6.0	1.76	1.602	0.302	2.1	1.08	1.4	0.31	0.42	0.27	0.46
		5.0	1.47	1.504	0.264	1.8	1.12	1.2	0.25	0.42	0.24	0.44
		4.0	1.19	1.410	0.170	1.6	1.17	1.1	0.20	0.41	0.21	0.44

## ELEMENTS OF SECTIONS


## ELEMENTS OF SHIP BUILDING CHANNELS



Section Index	Depth of Channel	Weight per Foot	Area of Section	Width of Flange				Axis 1-1			Axis 2-2			
				In.	In.	In.	In.	l	r	s	l	r	s	x
In.	Lbs.	In. <sup>2</sup>	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.	In.
C 20	13	55.0	16.17	4.520	0.904	331.5	4.55	51.5	18.1	1.06	5.2	1.00		
		50.0	14.71	4.116	0.791	313.8	4.62	48.3	16.7	1.07	4.9	0.98		
		45.0	13.24	4.303	0.678	293.1	4.71	45.1	15.3	1.08	4.6	0.97		
		40.0	11.76	4.190	0.565	272.3	4.81	41.9	13.9	1.09	4.3	0.97		
		37.0	10.88	4.122	0.497	259.9	4.89	40.0	13.1	1.10	4.2	0.98		
		35.0	10.29	4.077	0.452	251.6	4.95	38.7	12.5	1.10	4.1	0.99		
C 170	12	32.0	9.30	4.000	0.375	237.6	5.06	36.6	11.6	1.12	3.9	1.01		
		50.0	14.70	4.140	0.810	268.6	4.27	44.8	17.8	1.10	5.8	1.06		
		48.4	14.22	4.100	0.800	262.8	4.30	43.8	17.3	1.10	5.7	1.05		
		46.3	13.62	4.050	0.750	255.6	4.33	42.6	16.6	1.11	5.5	1.05		
		44.3	13.02	4.000	0.700	248.4	4.37	41.4	16.0	1.11	5.4	1.05		
		40.0	11.76	3.895	0.595	233.3	4.45	38.9	14.6	1.11	5.1	1.05		
C 171	12	35.0	10.30	3.773	0.473	215.8	4.58	36.0	13.0	1.12	4.8	1.07		
		40.8	12.00	3.700	0.700	217.9	4.26	36.3	11.3	0.97	4.0	0.89		
		37.2	10.92	3.610	0.610	205.0	4.33	34.2	10.4	0.98	3.8	0.89		
		32.7	9.60	3.500	0.500	180.1	4.44	31.5	9.4	0.99	3.6	0.89		
		30.2	8.88	3.440	0.440	180.5	4.51	30.1	8.8	0.99	3.5	0.90		
		40.0	11.77	4.091	0.741	157.1	3.65	31.4	15.4	1.14	5.2	1.11		
C 160	10	36.9	10.86	4.000	0.650	149.5	3.71	29.9	14.3	1.15	4.9	1.11		
		34.4	10.11	3.925	0.575	143.2	3.76	28.6	13.4	1.15	4.8	1.11		
		31.8	9.36	3.850	0.500	137.0	3.83	27.1	12.4	1.15	4.6	1.13		
		30.0	8.83	3.797	0.447	132.6	3.88	26.5	11.7	1.15	4.4	1.14		
		33.2	9.75	3.675	0.675	121.0	3.57	24.8	9.1	0.97	3.3	0.89		
		30.6	9.00	3.600	0.600	117.7	3.62	23.5	8.5	0.97	3.1	0.88		
C 150	10	28.9	8.50	3.550	0.550	113.0	3.66	22.7	8.2	0.98	3.1	0.88		
		27.2	8.00	3.500	0.500	109.5	3.70	21.9	7.8	0.99	3.0	0.89		
		26.4	7.75	3.475	0.475	107.3	3.72	21.5	7.6	0.99	2.9	0.89		
		28.5	8.38	3.575	0.575	108.0	3.59	21.6	7.7	0.96	2.8	0.84		
		26.0	7.63	3.500	0.500	101.7	3.65	20.3	7.1	0.97	2.7	0.84		
		24.3	7.13	3.450	0.450	97.5	3.70	19.5	6.8	0.97	2.6	0.85		
C 150b	10	22.6	6.63	3.400	0.400	93.1	3.75	18.7	6.4	0.98	2.5	0.86		
		21.7	6.38	3.375	0.375	91.3	3.78	18.3	6.2	0.99	2.5	0.87		
		35.5	10.43	4.025	0.675	117.0	3.35	26.0	14.1	1.16	4.9	1.16		
		34.7	10.21	4.000	0.650	115.5	3.36	25.7	13.8	1.16	4.9	1.16		
		31.7	9.31	3.900	0.550	109.5	3.43	24.3	12.6	1.16	4.6	1.17		
		28.6	8.41	3.800	0.450	103.4	3.51	23.0	11.4	1.16	4.4	1.19		
C 140	9	27.2	8.00	3.625	0.625	68.9	2.94	17.2	8.4	1.02	3.2	0.98		
		26.5	7.80	3.600	0.600	67.8	2.95	17.0	8.2	1.03	3.1	0.98		
		25.2	7.40	3.550	0.550	65.7	2.98	16.4	7.8	1.03	3.0	0.98		
		23.8	7.00	3.500	0.500	63.6	3.01	15.9	7.4	1.03	3.0	0.99		
		21.5	6.32	3.415	0.415	60.0	3.08	15.0	6.9	1.05	2.9	0.99		
		21.0	6.16	3.000	0.460	54.1	2.96	13.5	4.3	0.83	1.9	0.79		
C 131	8	17.6	5.16	2.875	0.344	48.8	3.07	12.2	2.8	0.74	1.3	0.80		

# CARNEGIE STEEL COMPANY

## ELEMENTS OF SHIP BUILDING CHANNELS—Concluded



Section Index	Depth of Channel	Weight per Foot	Area of Section	Width of Flange	Thickness of Web	Axis 1-1			Axis 2-2			x
						I	r	S	I	r	S	
						In. <sup>4</sup>	In.	In. <sup>3</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	
C 120	7	21.5	7.20	3.600	0.600	48.9	2.61	14.0	7.9	1.05	3.1	1.04
		23.3	6.85	3.500	0.550	47.5	2.63	13.6	7.5	1.05	3.0	1.04
		22.1	6.60	3.500	0.500	46.0	2.66	13.2	7.1	1.05	2.9	1.05
		20.9	6.15	3.450	0.450	44.6	2.69	12.7	6.7	1.05	2.8	1.05
		19.7	5.80	3.400	0.400	43.2	2.73	12.3	6.3	1.05	2.7	1.07
C 121	7	21.9	6.43	3.575	0.575	42.6	2.57	12.2	6.5	1.01	2.5	0.94
		18.6	5.46	3.438	0.438	38.7	2.66	11.0	5.7	1.02	2.3	0.96
		16.5	4.85	3.350	0.350	36.2	2.73	10.3	5.1	1.03	2.2	0.99
		15.6	4.59	3.313	0.313	35.1	2.77	10.0	4.8	1.03	2.1	1.01
		21.5	6.33	3.685	0.535	33.3	2.29	11.1	7.8	1.11	3.1	1.16
C 110	6	19.0	5.58	3.560	0.410	31.1	2.36	10.4	6.8	1.10	2.9	1.18
C 109	6	15.0	4.46	3.500	0.350	25.0	2.37	8.3	5.2	1.08	2.1	1.08
C 107	6	18.1	5.33	3.063	0.563	25.4	2.18	8.5	3.5	0.82	1.6	0.80
		13.0	3.83	2.813	0.313	20.9	2.34	7.0	2.6	0.82	1.3	0.81
C 108	6	17.0	4.97	2.781	0.531	23.5	2.18	7.8	2.8	0.77	1.3	0.73
		12.5	3.66	2.563	0.313	19.6	2.31	6.5	2.1	0.75	1.1	0.74
C 106	5 3/4	17.0	4.99	3.500	0.375	25.8	2.28	9.0	5.8	1.08	2.5	1.15
C 200	4	13.6	4.00	2.500	0.500	8.8	1.49	4.4	2.2	0.74	1.4	0.87
C 220	4	10.1	2.95	2.087	0.394	6.6	1.40	3.3	1.12	0.62	0.79	0.67
C 190	3	7.1	2.05	1.984	0.250	2.8	1.17	1.9	0.75	0.60	0.60	0.72

## ELEMENTS OF H BEAMS



Section Index	Depth of Beam	Weight per Foot	Area of Section	Width of Flange	Thickness of Web	Axis 1-1			Axis 2-2		
						I	r	S	I	r	S
						In. <sup>4</sup>	In.	In. <sup>3</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>
H 4	8	34.0	10.00	8.0	.375	115.4	3.40	28.9	35.1	1.87	8.8
H 3	6	23.8	7.00	6.0	.313	45.1	2.54	15.0	14.7	1.45	4.9
H 2	5	18.7	5.50	5.0	.313	23.8	2.08	9.5	7.9	1.20	3.1
H 1	4	13.6	4.00	4.0	.313	10.7	1.63	5.3	3.6	0.95	1.8


# BULB SECTIONS

## ELEMENTS OF BULB BEAMS



Section Index	Depth	Flange Width	Web Thickness	Wt. per Foot	Area	Axis 1-1				Axis 2-2			
						I	r	S	x	I	r	S	y
						In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In. <sup>4</sup>	In.	In. <sup>3</sup>
B 100	10	5.500	0.625	36.6	10.62	140.4	3.64	25.3	4.45	7.6	0.84	2.8	2.75
		5.250	0.375	28.1	8.12	118.6	3.82	20.7	4.28	6.3	0.88	2.4	2.63
B 101	9	5.125	0.563	30.1	8.83	95.8	3.29	10.4	4.06	5.4	0.78	2.1	2.56
		4.938	0.375	24.3	7.15	84.0	3.43	16.6	3.95	4.6	0.80	1.9	2.47
B 102	8	5.156	0.469	24.2	7.11	62.8	2.97	14.1	3.54	4.5	0.79	1.7	2.58
		5.000	0.313	20.0	5.86	55.6	3.08	12.2	3.43	3.9	0.82	1.6	2.50
B 103	7	5.094	0.531	23.3	6.85	45.5	2.57	11.7	3.11	4.3	0.79	1.7	2.55
		4.875	0.313	18.1	5.32	38.8	2.70	9.7	2.98	3.6	0.82	1.5	2.44
B 105	6	4.524	0.430	17.2	5.00	24.4	2.20	7.2	2.61	2.7	0.73	1.2	2.26
		4.375	0.281	14.0	4.11	21.6	2.28	6.1	2.46	2.2	0.72	1.0	2.19

## ELEMENTS OF MISCELLANEOUS BULB ANGLES




Section Index	Size	Web Thickness	Wt. per Foot	Area	Axis 1-1				Axis 2-2			
					I	r	S	x	I	r	S	y
		In.	Lbs.	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.
B 130a	10 x 3 1/2	0.625	32.0	9.44	116.0	3.51	21.6	4.62	6.2	0.82	2.3	0.77
B 130	10 x 3 1/2	0.484	26.6	7.80	104.2	3.66	19.9	4.55	5.0	0.80	1.8	0.72
B 132	8 x 3 1/2	0.406	19.3	5.66	48.8	2.95	11.7	3.83	3.7	0.81	1.3	0.71
B 141	7 x 3	0.500	20.0	5.81	36.6	2.51	10.0	3.34	2.9	0.71	1.3	0.70
B 133	7 x 3	0.438	18.3	5.37	34.9	2.56	9.6	3.36	2.6	0.69	1.1	0.68
B 140	7 x 3	0.314	16.1	4.71	32.2	2.61	8.7	3.30	2.7	0.76	1.2	0.72
B 134	6 x 3	0.500	17.3	5.06	23.9	2.16	7.6	2.84	2.5	0.70	1.1	0.71
B 142	6 x 3	0.406	15.0	4.38	21.1	2.19	6.7	2.84	2.3	0.72	1.0	0.69
B 135	6 x 3	0.375	13.8	4.04	20.1	2.21	6.6	2.96	1.9	0.69	0.82	0.65
B 136	6 x 3	0.313	12.4	3.62	18.6	2.28	5.7	2.71	1.8	0.70	0.75	0.64
B 137	5 x 2 1/2	0.313	10.0	2.94	10.2	1.86	4.1	2.49	0.95	0.57	0.49	0.57
B 143	5 x 2 1/2	0.240	8.3	2.44	8.6	1.89	3.4	2.41	0.91	0.61	0.47	0.55
B 144	4 x 2 1/2	0.220	6.7	1.95	5.6	1.69	2.4	2.12	0.60	0.56	0.34	0.50
B 145	3 x 2	0.190	3.60	1.08	1.3	1.09	0.74	1.24	0.31	0.54	0.20	0.45
B 146	3 x 1 1/2	0.160	3.25	0.97	1.2	1.13	0.72	1.31	0.21	0.47	0.16	0.41
B 147	2 1/2 x 1 1/2	0.150	2.66	0.84	0.74	0.94	0.55	1.17	0.12	0.38	0.11	0.36
B 125	5 x 4 1/2	0.438	19.3	5.66	20.8	1.91	7.9	2.39	7.9	1.18	2.4	1.23
B 124	5 x 3 1/2	0.375	13.2	3.82	13.5	1.88	4.9	2.22	3.3	0.92	1.2	0.86
B 122	4 x 3 1/2	0.500	14.3	4.21	8.7	1.44	3.7	1.65	3.0	0.96	1.5	0.90
B 123	4 x 3 1/2	0.375	11.9	3.48	7.9	1.50	3.5	1.77	3.1	0.94	1.2	0.94

CARNEGIE STEEL COMPANY

ELEMENTS OF SHIP BUILDING BULB ANGLES

British Standard Sections




Section Index	Size	Web Thickness	Wt. per Foot	Area	Axis 1-1				Axis 2-2			
					I		r		I		r	
					In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In. <sup>4</sup>	In. <sup>3</sup>	In.
Inches	In.	Lbs.	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In. <sup>3</sup>	In.	In. <sup>3</sup>	In.	In.
B 205	9 1/2 x 3 1/2	0.625	29.7	8.75	95.7	3.31	18.4	4.30	5.6	0.80	2.0	0.74
		0.600	28.8	8.47	93.0	3.32	17.9	4.30	5.3	0.79	1.9	0.73
		0.575	27.8	8.19	90.4	3.32	17.4	4.30	5.1	0.79	1.9	0.72
		0.550	26.9	7.91	87.8	3.33	16.9	4.29	4.9	0.79	1.8	0.71
B 206	9 1/2 x 3 1/2	0.525	25.7	7.50	85.1	3.36	16.5	4.36	4.8	0.80	1.7	0.70
		0.500	24.7	7.28	82.4	3.37	16.0	4.36	4.6	0.79	1.6	0.69
		0.475	23.8	7.00	79.8	3.38	15.6	4.36	4.4	0.79	1.6	0.69
		0.450	22.8	6.72	77.1	3.39	15.1	4.36	4.2	0.79	1.5	0.68
B 201	9 x 3 1/2	0.675	30.4	8.95	86.3	3.11	17.2	4.00	5.8	0.81	2.1	0.76
		0.650	29.5	8.68	84.1	3.11	16.8	3.99	5.6	0.80	2.0	0.75
		0.625	28.6	8.41	81.8	3.12	16.4	3.98	5.4	0.80	2.0	0.74
		0.600	27.7	8.14	79.6	3.12	16.0	3.98	5.1	0.80	1.9	0.73
B 202	9 x 3 1/2	0.575	26.6	7.82	77.6	3.15	15.6	4.03	5.1	0.81	1.8	0.73
		0.550	25.7	7.55	75.3	3.16	15.2	4.03	4.9	0.80	1.8	0.72
		0.525	24.8	7.29	73.1	3.17	14.8	4.03	4.7	0.80	1.7	0.71
		0.500	23.9	7.02	70.8	3.17	14.3	4.02	4.5	0.80	1.6	0.70
B 203	9 x 3 1/2	0.475	22.7	6.68	68.4	3.20	13.9	4.10	4.3	0.81	1.5	0.70
		0.450	21.8	6.41	66.1	3.21	13.5	4.10	4.1	0.80	1.5	0.69
		0.425	20.9	6.14	63.8	3.22	13.1	4.10	3.9	0.80	1.4	0.68
		0.400	20.0	5.87	61.6	3.24	12.7	4.10	3.8	0.80	1.4	0.67
B 208	8 1/2 x 3 1/2	0.575	25.3	7.43	65.5	2.97	13.8	3.74	5.0	0.82	1.8	0.74
		0.550	24.4	7.18	63.6	2.98	13.4	3.74	4.8	0.82	1.8	0.73
		0.525	23.5	6.92	61.7	2.98	13.0	3.73	4.6	0.82	1.7	0.72
		0.500	22.7	6.67	59.7	2.99	12.6	3.73	4.4	0.82	1.6	0.71
D 209	8 1/2 x 3 1/2	0.475	21.6	6.34	57.7	3.02	12.3	3.80	4.3	0.82	1.5	0.71
		0.450	20.7	6.08	55.8	3.03	11.9	3.80	4.1	0.82	1.5	0.70
		0.425	19.8	5.83	53.8	3.04	11.5	3.80	3.9	0.82	1.4	0.69
		0.400	18.9	5.57	51.9	3.05	11.1	3.80	3.7	0.81	1.3	0.68
B 211	8 1/2 x 3	0.575	24.3	7.14	62.0	2.95	13.4	3.90	3.2	0.67	1.3	0.64
		0.550	23.4	6.89	60.1	2.96	13.1	3.89	3.1	0.67	1.3	0.63
		0.525	22.6	6.64	58.3	2.96	12.7	3.89	2.9	0.66	1.2	0.62
		0.500	21.7	6.39	56.4	2.97	12.3	3.89	2.8	0.66	1.2	0.61
B 212	8 1/2 x 3	0.475	20.7	6.09	54.6	2.99	12.0	3.95	2.7	0.67	1.1	0.61
		0.450	19.8	5.84	52.7	3.00	11.6	3.96	2.6	0.67	1.1	0.60
		0.425	19.0	5.59	50.8	3.02	11.2	3.96	2.5	0.67	1.0	0.59
		0.400	18.1	5.34	48.9	3.03	10.8	3.96	2.3	0.66	0.99	0.58

# BULB SECTIONS


## ELEMENTS OF SHIP BUILDING BULB ANGLES

British Standard Sections



Section Index	Size	Web Thickness	Wt. per Foot	Area	Axis 1-1				Axis 2-2			
					l	r	S	x	l	r	S	y
	Inches	In.	Lbs.	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>4</sup>	In.	In. <sup>4</sup>	In.	In. <sup>4</sup>	In.
B 217 8 x 3		0.575	23.1	6.78	52.1	2.78	12.0	3.64	3.2	0.69	1.3	0.65
		0.550	22.2	6.54	50.8	2.79	11.6	3.64	3.1	0.68	1.3	0.64
		0.525	21.4	6.31	49.2	2.79	11.3	3.63	2.9	0.68	1.2	0.63
		0.500	20.6	6.07	47.7	2.80	10.9	3.63	2.8	0.68	1.2	0.62
B 218 8 x 3		0.475	19.6	5.78	46.1	2.82	10.6	3.70	2.7	0.69	1.1	0.62
		0.450	18.8	5.54	44.5	2.83	10.3	3.70	2.6	0.68	1.1	0.61
		0.425	18.0	5.30	42.9	2.84	10.0	3.70	2.4	0.68	1.0	0.60
		0.400	17.2	5.06	41.3	2.85	9.6	3.70	2.3	0.68	0.97	0.59
B 221 7 1/2 x 3 1/2		0.475	19.4	5.70	40.6	2.67	9.6	3.29	4.2	0.85	1.5	0.73
		0.450	18.6	5.47	39.2	2.68	9.3	3.29	4.0	0.85	1.4	0.73
		0.425	17.8	5.24	37.8	2.69	9.0	3.29	3.8	0.85	1.4	0.72
		0.400	17.0	5.01	36.4	2.70	8.7	3.29	3.6	0.85	1.3	0.71
B 223 7 1/2 x 3		0.525	20.3	5.98	41.0	2.62	9.9	3.36	2.9	0.69	1.2	0.64
		0.500	19.6	5.75	39.7	2.63	9.6	3.36	2.7	0.69	1.2	0.63
		0.475	18.8	5.53	38.4	2.63	9.3	3.35	2.6	0.69	1.1	0.62
		0.450	18.0	5.31	37.1	2.64	9.0	3.35	2.5	0.68	1.1	0.61
B 224 7 1/2 x 3		0.425	17.1	5.02	35.7	2.67	8.8	3.42	2.4	0.69	1.0	0.61
		0.400	16.3	4.80	34.4	2.68	8.5	3.42	2.3	0.69	0.96	0.60
		0.375	15.6	4.57	33.1	2.69	8.2	3.42	2.2	0.69	0.92	0.60
		0.350	14.8	4.35	31.7	2.70	7.9	3.42	2.0	0.68	0.87	0.59
B 233 6 1/2 x 3 1/2		0.425	15.7	4.63	24.9	2.32	6.6	2.73	3.7	0.89	1.3	0.76
		0.400	15.0	4.42	23.9	2.33	6.3	2.72	3.5	0.89	1.3	0.75
		0.375	14.3	4.21	23.0	2.34	6.1	2.72	3.3	0.89	1.2	0.74
		0.350	13.6	4.01	22.1	2.35	5.9	2.71	3.1	0.89	1.2	0.73
B 236 6 1/2 x 3		0.425	15.0	4.40	23.5	2.31	6.4	2.87	2.3	0.73	0.97	0.64
		0.400	14.3	4.20	22.6	2.32	6.2	2.87	2.2	0.73	0.93	0.63
		0.375	13.6	4.00	21.7	2.33	6.0	2.87	2.1	0.72	0.88	0.62
		0.350	12.9	3.80	20.8	2.34	5.7	2.86	2.0	0.72	0.84	0.61
B 244 5 1/2 x 3		0.500	15.1	4.45	16.5	1.92	5.1	2.31	2.6	0.76	1.1	0.71
		0.475	14.5	4.28	15.9	1.93	4.9	2.30	2.5	0.76	1.1	0.70
		0.450	13.9	4.10	15.3	1.93	4.8	2.30	2.4	0.76	1.0	0.69
		0.425	13.4	3.93	14.7	1.94	4.6	2.29	2.3	0.76	0.98	0.68
B 245 5 1/2 x 3		0.400	12.5	3.68	14.2	1.96	4.5	2.35	2.1	0.76	0.90	0.67
		0.375	11.9	3.51	13.6	1.97	4.3	2.35	2.0	0.76	0.86	0.66
		0.350	11.3	3.33	13.0	1.98	4.1	2.35	1.9	0.76	0.81	0.65
		0.325	10.7	3.16	12.5	1.99	4.0	2.34	1.8	0.75	0.77	0.64


**CARNEGIE STEEL COMPANY**  
**ELEMENTS OF EQUAL ANGLES**



Section Index	Size		Weight per Foot	Area of Section	Axis 1-1 and Axis 2-2				Axis 3-3
	Inches	Pounds			1	r	S	x	r min.
					In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.
A 113	8 x 8 x 1 1/4	56.9	16.73	98.0	2.42	17.5	2.41	1.55	
A 112	8 x 8 x 1 1/8	54.0	15.87	93.5	2.43	16.7	2.39	1.56	
A 111	8 x 8 x 1	51.0	15.00	89.0	2.44	15.8	2.37	1.56	
A 110	8 x 8 x 7/8	48.1	14.12	84.3	2.44	14.9	2.34	1.56	
A 109	8 x 8 x 3/4	45.0	13.23	79.6	2.45	14.0	2.32	1.56	
A 108	8 x 8 x 1/2	42.0	12.34	74.7	2.46	13.1	2.30	1.57	
A 107	8 x 8 x 1/4	38.9	11.44	69.7	2.47	12.2	2.28	1.57	
A 106	8 x 8 x 1/8	35.8	10.53	64.6	2.48	11.2	2.25	1.58	
A 105	8 x 8 x 1/16	32.7	9.61	59.4	2.49	10.3	2.23	1.58	
A 104	8 x 8 x 1/32	29.6	8.68	54.1	2.50	9.3	2.21	1.58	
A 103	8 x 8 x 1/64	26.4	7.75	48.6	2.51	8.4	2.19	1.58	
A 86	6 x 6 x 1	37.4	11.00	35.5	1.80	8.6	1.86	1.16	
A 87	6 x 6 x 3/4	35.3	10.37	33.7	1.80	8.1	1.84	1.16	
A 1	6 x 6 x 3/8	33.1	9.73	31.9	1.81	7.6	1.82	1.17	
A 2	6 x 6 x 1/4	31.0	9.09	30.1	1.82	7.2	1.80	1.17	
A 3	6 x 6 x 3/16	28.7	8.44	28.2	1.83	6.7	1.78	1.17	
A 4	6 x 6 x 1/8	26.5	7.78	26.2	1.83	6.2	1.75	1.17	
A 5	6 x 6 x 1/16	24.2	7.11	24.2	1.84	5.7	1.73	1.17	
A 6	6 x 6 x 1/32	21.9	6.43	22.1	1.85	5.1	1.71	1.18	
A 7	6 x 6 x 1/64	19.6	5.75	19.9	1.86	4.6	1.68	1.18	
A 8	6 x 6 x 1/128	17.2	5.06	17.7	1.87	4.1	1.66	1.19	
A 88	6 x 6 x 1/256	14.9	4.36	15.4	1.88	3.5	1.64	1.19	
A 91	5 x 5 x 1	30.6	9.00	19.6	1.48	5.8	1.61	0.96	
A 95	5 x 5 x 3/4	28.9	8.50	18.7	1.48	5.5	1.59	0.96	
A 9	5 x 5 x 3/8	27.2	7.98	17.8	1.49	5.2	1.57	0.96	
A 10	5 x 5 x 1/4	25.4	7.47	16.8	1.50	4.9	1.55	0.97	
A 11	5 x 5 x 3/16	23.6	6.94	15.7	1.50	4.5	1.52	0.97	
A 12	5 x 5 x 1/8	21.8	6.40	14.7	1.51	4.2	1.50	0.97	
A 13	5 x 5 x 1/16	20.0	5.86	13.6	1.52	3.9	1.48	0.97	
A 14	5 x 5 x 1/32	18.1	5.31	12.4	1.53	3.5	1.46	0.98	
A 15	5 x 5 x 1/64	16.2	4.75	11.3	1.54	3.2	1.43	0.98	
A 16	5 x 5 x 1/128	14.3	4.18	10.0	1.55	2.8	1.41	0.98	
A 17	5 x 5 x 1/256	12.3	3.61	8.7	1.56	2.4	1.39	0.99	
A 18	4 x 4 x 1	19.9	5.84	8.1	1.18	3.0	1.29	0.77	
A 19	4 x 4 x 3/4	18.5	5.44	7.7	1.19	2.8	1.27	0.77	
A 20	4 x 4 x 3/8	17.1	5.03	7.2	1.19	2.6	1.25	0.77	
A 21	4 x 4 x 1/4	15.7	4.61	6.7	1.20	2.4	1.23	0.77	
A 22	4 x 4 x 3/16	14.3	4.18	6.1	1.21	2.2	1.21	0.78	
A 23	4 x 4 x 1/8	12.8	3.75	5.6	1.22	2.0	1.18	0.78	
A 24	4 x 4 x 1/16	11.3	3.31	5.0	1.23	1.8	1.16	0.78	
A 25	4 x 4 x 1/32	9.8	2.86	4.4	1.23	1.5	1.14	0.79	
A 90	4 x 4 x 1/64	8.2	2.40	3.7	1.24	1.3	1.12	0.79	
A 284	4 x 4 x 1/128	6.6	1.94	3.0	1.25	1.0	1.09	0.79	

## ELEMENTS OF SECTIONS

## ELEMENTS OF EQUAL ANGLES—Concluded




Section Index	Size	Weight per Foot	Area of Section	Axis 1-1 and Axis 2-2				Axis 3-3	
				I	r	S	x	r min.	
	Inches	Pounds	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In.	
A 26	3 1/2 x 3 1/2 x 1/8	17.1	5.03	5.3	1.02	2.3	1.17	0.67	
A 27	3 1/2 x 3 1/2 x 3/16	16.0	4.69	5.0	1.03	2.1	1.15	0.67	
A 28	3 1/2 x 3 1/2 x 1/4	14.8	4.34	4.7	1.04	2.0	1.12	0.67	
A 29	3 1/2 x 3 1/2 x 3/8	13.6	3.98	4.3	1.04	1.8	1.10	0.68	
A 30	3 1/2 x 3 1/2 x 1/2	12.4	3.62	4.0	1.05	1.6	1.08	0.68	
A 31	3 1/2 x 3 1/2 x 3/4	11.1	3.25	3.6	1.06	1.5	1.06	0.68	
A 32	3 1/2 x 3 1/2 x 1/2	9.8	2.87	3.3	1.07	1.3	1.04	0.68	
A 33	3 1/2 x 3 1/2 x 3/8	8.5	2.48	2.9	1.07	1.2	1.01	0.69	
A 99	3 1/2 x 3 1/2 x 1/4	7.2	2.09	2.5	1.08	0.98	0.99	0.69	
A 285	3 1/2 x 3 1/2 x 3/16	5.8	1.69	2.0	1.09	0.79	0.97	0.69	
A 34	3 x 3 x 5/16	11.5	3.36	2.6	0.88	1.3	0.98	0.57	
A 35	3 x 3 x 3/8	10.4	3.06	2.4	0.89	1.2	0.95	0.58	
A 36	3 x 3 x 1/2	9.4	2.75	2.2	0.90	1.1	0.93	0.58	
A 37	3 x 3 x 3/4	8.3	2.43	2.0	0.91	0.95	0.91	0.58	
A 38	3 x 3 x 1/2	7.2	2.11	1.8	0.91	0.83	0.89	0.58	
A 39	3 x 3 x 3/4	6.1	1.78	1.5	0.92	0.71	0.87	0.59	
A 40	3 x 3 x 1/2	4.9	1.44	1.2	0.93	0.58	0.84	0.59	
A 46	2 1/2 x 2 1/2 x 1/2	7.7	2.25	1.2	0.74	0.73	0.81	0.47	
A 47	2 1/2 x 2 1/2 x 3/8	6.8	2.00	1.1	0.75	0.65	0.78	0.48	
A 48	2 1/2 x 2 1/2 x 1/4	5.9	1.73	0.98	0.75	0.57	0.76	0.48	
A 49	2 1/2 x 2 1/2 x 3/8	5.0	1.47	0.85	0.76	0.48	0.74	0.49	
A 50	2 1/2 x 2 1/2 x 1/4	4.1	1.19	0.70	0.77	0.39	0.72	0.49	
A 100	2 1/2 x 2 1/2 x 3/8	3.07	0.90	0.55	0.78	0.30	0.69	0.49	
A 504	2 1/2 x 2 1/2 x 1/8	2.08	0.61	0.38	0.79	0.20	0.67	0.50	
A 56	2 x 2 x 3/8	5.3	1.56	0.54	0.59	0.40	0.66	0.39	
A 57	2 x 2 x 1/2	4.7	1.36	0.48	0.59	0.35	0.64	0.39	
A 58	2 x 2 x 3/4	3.92	1.15	0.42	0.60	0.30	0.61	0.39	
A 59	2 x 2 x 1/2	3.19	0.94	0.35	0.61	0.25	0.59	0.39	
A 60	2 x 2 x 3/8	2.44	0.71	0.28	0.62	0.19	0.57	0.40	
A 506	2 x 2 x 1/8	1.65	0.48	0.19	0.63	0.13	0.55	0.40	
A 61	1 3/4 x 1 3/4 x 1/8	4.6	1.34	0.35	0.51	0.30	0.59	0.33	
A 62	1 3/4 x 1 3/4 x 3/16	3.99	1.17	0.31	0.51	0.26	0.57	0.34	
A 63	1 3/4 x 1 3/4 x 1/4	3.39	1.00	0.27	0.52	0.23	0.55	0.34	
A 64	1 3/4 x 1 3/4 x 3/8	2.77	0.84	0.23	0.53	0.19	0.53	0.34	
A 65	1 3/4 x 1 3/4 x 1/2	2.12	0.62	0.18	0.54	0.14	0.51	0.35	
A 507	1 3/4 x 1 3/4 x 3/8	1.44	0.42	0.13	0.55	0.10	0.48	0.35	
A 66	1 1/2 x 1 1/2 x 3/8	3.35	0.98	0.19	0.44	0.19	0.51	0.29	
A 67	1 1/2 x 1 1/2 x 1/2	2.86	0.84	0.16	0.44	0.16	0.49	0.29	
A 68	1 1/2 x 1 1/2 x 3/4	2.34	0.69	0.14	0.45	0.13	0.47	0.29	
A 69	1 1/2 x 1 1/2 x 1/2	1.80	0.53	0.11	0.46	0.10	0.44	0.29	
A 102	1 1/2 x 1 1/2 x 3/8	1.23	0.36	0.08	0.46	0.07	0.42	0.30	
A 70	1 1/4 x 1 1/4 x 3/8	2.33	0.68	0.09	0.36	0.11	0.42	0.24	
A 71	1 1/4 x 1 1/4 x 1/2	1.92	0.56	0.08	0.37	0.09	0.40	0.24	
A 72	1 1/4 x 1 1/4 x 3/4	1.48	0.43	0.06	0.38	0.07	0.38	0.24	
A 73	1 1/4 x 1 1/4 x 1/2	1.01	0.30	0.04	0.38	0.05	0.35	0.25	
A 78	1 x 1 x 1/4	1.49	0.44	0.04	0.29	0.06	0.34	0.19	
A 79	1 x 1 x 1/8	1.16	0.34	0.03	0.30	0.04	0.32	0.19	
A 80	1 x 1 x 3/16	0.80	0.23	0.02	0.31	0.03	0.30	0.19	



# CARNEGIE STEEL COMPANY

## ELEMENTS OF UNEQUAL ANGLES



Section Index	Size	Weight per Foot	Area of Section	Axis 1-1				Axis 2-2				Axis 3-3	
				I		S		I		S			
				In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.		
	Inches	Lbs.	In. <sup>2</sup>										
A 138	8 x 6 x 1	44.2	13.00	80.8	2.49	15.1	2.65	38.8	1.73	8.9	1.65	1.28	
A 137	8 x 6 x 1	41.7	12.25	76.6	2.50	14.3	2.63	36.8	1.73	8.4	1.63	1.28	
A 136	8 x 6 x 1	39.1	11.48	72.3	2.51	13.4	2.61	34.9	1.74	7.9	1.61	1.28	
A 135	8 x 6 x 1	36.5	10.72	67.9	2.52	12.5	2.59	32.8	1.75	7.4	1.59	1.29	
A 134	8 x 6 x 1	33.8	9.94	63.4	2.53	11.7	2.56	30.7	1.76	6.9	1.56	1.29	
A 133	8 x 6 x 1	31.2	9.15	58.8	2.54	10.8	2.54	28.6	1.77	6.4	1.54	1.29	
A 132	8 x 6 x 1	28.5	8.36	54.1	2.54	9.9	2.52	26.3	1.77	5.9	1.52	1.30	
A 131	8 x 6 x 1	25.7	7.56	49.3	2.55	8.9	2.50	24.0	1.78	5.3	1.50	1.30	
A 130	8 x 6 x 1	23.0	6.75	44.3	2.56	8.0	2.47	21.7	1.79	4.8	1.47	1.30	
A 139	8 x 6 x 1	20.2	5.93	39.2	2.57	7.1	2.45	19.3	1.80	4.2	1.45	1.30	
A 320	8 x 3 1/2 x 1	35.7	10.50	66.2	2.51	13.7	3.17	7.8	0.86	3.0	0.92	0.73	
A 321	8 x 3 1/2 x 1	33.7	9.90	62.9	2.52	12.9	3.14	7.4	0.87	2.9	0.89	0.73	
A 322	8 x 3 1/2 x 1	31.7	9.30	59.4	2.53	12.2	3.12	7.1	0.87	2.7	0.87	0.73	
A 323	8 x 3 1/2 x 1	29.6	8.68	55.9	2.54	11.4	3.10	6.7	0.88	2.5	0.85	0.73	
A 324	8 x 3 1/2 x 1	27.5	8.06	52.3	2.55	10.6	3.07	6.3	0.88	2.3	0.82	0.73	
A 325	8 x 3 1/2 x 1	25.3	7.43	48.5	2.56	9.8	3.05	5.9	0.89	2.2	0.80	0.73	
A 326	8 x 3 1/2 x 1	23.2	6.80	44.7	2.57	9.0	3.03	5.4	0.90	2.0	0.78	0.74	
A 327	8 x 3 1/2 x 1	21.0	6.15	40.8	2.57	8.2	3.00	5.0	0.90	1.8	0.75	0.74	
A 328	8 x 3 1/2 x 1	18.7	5.50	36.7	2.58	7.3	2.98	4.5	0.91	1.6	0.73	0.74	
A 329	8 x 3 1/2 x 1	16.5	4.84	32.5	2.59	6.4	2.95	4.1	0.92	1.5	0.70	0.74	
A 150	7 x 3 1/2 x 1	32.3	9.50	45.4	2.19	10.6	2.71	7.5	0.89	3.0	0.96	0.74	
A 151	7 x 3 1/2 x 1	30.5	8.97	43.1	2.19	10.0	2.69	7.2	0.89	2.8	0.94	0.74	
A 152	7 x 3 1/2 x 1	28.7	8.42	40.8	2.20	9.4	2.66	6.8	0.90	2.6	0.91	0.74	
A 153	7 x 3 1/2 x 1	26.8	7.87	38.4	2.21	8.8	2.64	6.5	0.91	2.5	0.89	0.74	
A 154	7 x 3 1/2 x 1	24.9	7.31	36.0	2.22	8.2	2.62	6.1	0.91	2.3	0.87	0.74	
A 155	7 x 3 1/2 x 1	23.0	6.75	33.5	2.23	7.6	2.60	5.7	0.92	2.1	0.85	0.74	
A 156	7 x 3 1/2 x 1	21.0	6.17	30.9	2.24	7.0	2.57	5.3	0.93	2.0	0.82	0.75	
A 157	7 x 3 1/2 x 1	19.1	5.59	28.2	2.25	6.3	2.55	4.9	0.93	1.8	0.80	0.75	
A 158	7 x 3 1/2 x 1	17.0	5.00	25.4	2.25	5.7	2.53	4.4	0.94	1.6	0.78	0.75	
A 159	7 x 3 1/2 x 1	15.0	4.40	22.6	2.26	5.0	2.50	4.0	0.95	1.4	0.75	0.76	
A 310	7 x 3 1/2 x 1	13.0	3.80	19.6	2.27	4.3	2.48	3.5	0.96	1.3	0.73	0.76	
A 89	6 x 4 x 1	30.6	9.00	30.8	1.85	8.0	2.17	10.8	1.09	3.8	1.17	0.85	
A 91	6 x 4 x 1	28.9	8.50	29.3	1.86	7.6	2.14	10.3	1.10	3.6	1.14	0.85	
A 100	6 x 4 x 1	27.2	7.98	27.7	1.86	7.2	2.12	9.8	1.11	3.4	1.12	0.86	
A 161	6 x 4 x 1	25.4	7.47	26.1	1.87	6.7	2.10	9.2	1.11	3.2	1.10	0.86	
A 162	6 x 4 x 1	23.6	6.94	24.5	1.88	6.2	2.08	8.7	1.12	3.0	1.08	0.86	
A 163	6 x 4 x 1	21.8	6.40	22.8	1.89	5.8	2.06	8.1	1.13	2.8	1.06	0.86	
A 164	6 x 4 x 1	20.0	5.86	21.1	1.90	5.3	2.03	7.5	1.13	2.5	1.03	0.86	
A 165	6 x 4 x 1	18.1	5.31	19.3	1.90	4.8	2.01	6.9	1.14	2.3	1.01	0.87	
A 166	6 x 4 x 1	16.2	4.75	17.4	1.91	4.3	1.99	6.3	1.15	2.1	0.99	0.87	
A 167	6 x 4 x 1	14.3	4.18	15.5	1.92	3.8	1.96	5.6	1.16	1.8	0.96	0.87	
A 168	6 x 4 x 1	12.3	3.61	13.5	1.93	3.3	1.94	4.9	1.17	1.6	0.94	0.88	

# ELEMENTS OF SECTIONS


## ELEMENTS OF UNEQUAL ANGLES—Continued



Section Index	Size	Weight per Foot	Area of Section	Axis 1-1				Axis 2-2				Axis 3-3	
				I				I				y	
				In. <sup>4</sup>	In. <sup>3</sup>	In. <sup>2</sup>	In.	In. <sup>4</sup>	In. <sup>3</sup>	In. <sup>2</sup>	In.	In.	mm.
	Inches	Lbs.	In. <sup>2</sup>										
A 92	6 x 3 1/2 x 1 1/8	28.9	8.50	29.2	1.85	7.8	2.26	7.2	0.92	2.9	1.01	0.74	
A 93	6 x 3 1/2 x 1 1/8	27.3	8.03	27.8	1.86	7.4	2.24	6.9	0.93	2.7	0.99	0.74	
A 169	6 x 3 1/2 x 1 1/8	25.7	7.55	26.4	1.87	7.0	2.22	6.6	0.93	2.6	0.97	0.75	
A 170	6 x 3 1/2 x 1 1/8	24.0	7.06	24.9	1.88	6.6	2.20	6.2	0.94	2.4	0.95	0.75	
A 171	6 x 3 1/2 x 1 1/8	22.4	6.56	23.3	1.89	6.1	2.18	5.8	0.94	2.3	0.93	0.75	
A 172	6 x 3 1/2 x 1 1/8	20.6	6.06	21.7	1.89	5.6	2.15	5.5	0.95	2.1	0.90	0.75	
A 173	6 x 3 1/2 x 1 1/8	18.9	5.55	20.1	1.90	5.2	2.13	5.1	0.96	1.9	0.88	0.75	
A 174	6 x 3 1/2 x 1 1/8	17.1	5.03	18.4	1.91	4.7	2.11	4.7	0.96	1.8	0.86	0.75	
A 175	6 x 3 1/2 x 1 1/8	15.3	4.50	16.6	1.92	4.2	2.08	4.3	0.97	1.6	0.83	0.76	
A 176	6 x 3 1/2 x 1 1/8	13.5	3.97	14.8	1.93	3.7	2.06	3.8	0.98	1.4	0.81	0.76	
A 177	6 x 3 1/2 x 1 1/8	11.7	3.42	12.9	1.94	3.3	2.04	3.3	0.99	1.2	0.79	0.77	
A 301	6 x 3 1/2 x 1 1/8	9.8	2.87	10.9	1.95	2.7	2.01	2.9	1.00	1.0	0.76	0.77	
A 178	5 x 4 x 7/8	24.2	7.11	16.4	1.52	5.0	1.71	9.2	1.14	3.3	1.21	0.84	
A 179	5 x 4 x 7/8	22.7	6.65	15.5	1.53	4.7	1.68	8.7	1.15	3.1	1.18	0.84	
A 180	5 x 4 x 7/8	21.1	6.19	14.6	1.54	4.4	1.66	8.2	1.15	2.9	1.16	0.84	
A 181	5 x 4 x 7/8	19.5	5.72	13.6	1.54	4.1	1.64	7.7	1.16	2.7	1.14	0.84	
A 182	5 x 4 x 7/8	17.8	5.23	12.6	1.55	3.7	1.62	7.1	1.17	2.5	1.12	0.84	
A 183	5 x 4 x 7/8	16.2	4.75	11.6	1.56	3.4	1.60	6.6	1.18	2.3	1.10	0.85	
A 184	5 x 4 x 7/8	14.5	4.25	10.5	1.57	3.1	1.57	6.0	1.18	2.0	1.07	0.85	
A 185	5 x 4 x 7/8	12.8	3.75	9.3	1.58	2.7	1.55	5.3	1.19	1.8	1.05	0.85	
A 186	5 x 4 x 7/8	11.0	3.23	8.1	1.59	2.3	1.53	4.7	1.20	1.6	1.03	0.86	
A 187	5 x 3 1/2 x 7/8	22.7	6.67	15.7	1.53	4.9	1.79	6.2	0.96	2.5	1.04	0.75	
A 188	5 x 3 1/2 x 7/8	21.3	6.25	14.8	1.54	4.6	1.77	5.9	0.97	2.4	1.02	0.75	
A 189	5 x 3 1/2 x 7/8	19.8	5.81	13.9	1.55	4.3	1.75	5.6	0.98	2.2	1.00	0.75	
A 190	5 x 3 1/2 x 7/8	18.3	5.37	13.0	1.56	4.0	1.72	5.2	0.98	2.1	0.97	0.75	
A 191	5 x 3 1/2 x 7/8	16.8	4.92	12.0	1.56	3.7	1.70	4.8	0.99	1.9	0.95	0.75	
A 192	5 x 3 1/2 x 7/8	15.2	4.47	11.0	1.57	3.3	1.68	4.4	1.00	1.7	0.93	0.75	
A 193	5 x 3 1/2 x 7/8	13.6	4.00	10.0	1.58	3.0	1.66	4.0	1.01	1.6	0.91	0.75	
A 194	5 x 3 1/2 x 7/8	12.0	3.53	8.9	1.59	2.6	1.63	3.6	1.01	1.4	0.88	0.76	
A 195	5 x 3 1/2 x 7/8	10.4	3.05	7.8	1.60	2.3	1.61	3.2	1.02	1.2	0.86	0.76	
A 96	5 x 3 1/2 x 7/8	8.7	2.56	6.6	1.61	1.9	1.59	2.7	1.03	1.0	0.84	0.76	
A 196	5 x 3 x 3/4	19.9	5.84	14.0	1.55	4.5	1.86	3.7	0.80	1.7	0.86	0.64	
A 197	5 x 3 x 3/4	18.5	5.44	13.2	1.55	4.2	1.84	3.5	0.80	1.6	0.84	0.64	
A 198	5 x 3 x 3/4	17.1	5.03	12.3	1.56	3.9	1.82	3.3	0.81	1.5	0.82	0.64	
A 199	5 x 3 x 3/4	15.7	4.61	11.4	1.57	3.5	1.80	3.1	0.81	1.4	0.80	0.64	
A 200	5 x 3 x 3/4	14.3	4.18	10.4	1.58	3.2	1.77	2.8	0.82	1.3	0.77	0.65	
A 201	5 x 3 x 3/4	12.8	3.75	9.5	1.59	2.9	1.75	2.6	0.83	1.1	0.75	0.65	
A 202	5 x 3 x 3/4	11.3	3.31	8.4	1.60	2.6	1.73	2.3	0.84	1.0	0.73	0.65	
A 203	5 x 3 x 3/4	9.8	2.86	7.4	1.61	2.2	1.70	2.0	0.84	0.89	0.70	0.65	
A 280	5 x 3 x 3/4	8.2	2.40	6.3	1.61	1.9	1.68	1.8	0.85	0.75	0.68	0.66	

CARNEGIE STEEL COMPANY


ELEMENTS OF UNEQUAL ANGLES—Continued



Section Index	Size	Weight per Foot	Area of Section	Axis 1-1				Axis 2-2				Axis 3-3
				I	r	S	x	I	r	S	y	
	Inches	Lbs.	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	
A 204	4½ x 3 x 1½	18.5	5.43	10.3	1.38	3.6	1.65	3.6	0.81	1.7	0.90	0.64
A 205	4½ x 3 x 1½	17.3	5.04	9.7	1.32	2.5	1.63	3.4	0.82	1.6	0.88	0.64
A 206	4½ x 3 x 1½	16.0	4.68	9.1	1.39	3.1	1.60	3.2	0.83	1.5	0.85	0.64
A 207	4½ x 3 x 1½	14.7	4.30	8.4	1.40	2.9	1.58	3.0	0.83	1.4	0.83	0.64
A 208	4½ x 3 x 1½	13.3	3.90	7.8	1.41	2.6	1.56	2.8	0.85	1.3	0.81	0.64
A 209	4½ x 3 x 1½	11.9	3.50	7.0	1.42	2.4	1.54	2.5	0.85	1.1	0.79	0.65
A 210	4½ x 3 x 1½	10.6	3.09	6.3	1.43	2.1	1.51	2.3	0.85	1.0	0.76	0.65
A 211	4½ x 3 x 1½	9.1	2.67	5.5	1.44	1.8	1.49	2.0	0.86	0.88	0.74	0.66
A 97	4½ x 3 x 1½	7.7	2.25	4.7	1.44	1.5	1.47	1.7	0.87	0.75	0.72	0.66
A 212	4 x 3½ x 1½	18.5	5.43	7.8	1.19	2.9	1.36	5.5	1.01	2.3	1.11	0.72
A 213	4 x 3½ x 1½	17.3	5.06	7.3	1.20	2.8	1.34	5.2	1.01	2.1	1.09	0.72
A 214	4 x 3½ x 1½	16.0	4.68	6.9	1.21	2.6	1.32	4.9	1.02	2.0	1.07	0.72
A 215	4 x 3½ x 1½	14.7	4.30	6.4	1.22	2.4	1.29	4.5	1.03	1.8	1.04	0.72
A 216	4 x 3½ x 1½	13.3	3.90	5.9	1.23	2.1	1.27	4.2	1.03	1.7	1.02	0.72
A 217	4 x 3½ x 1½	11.9	3.50	5.3	1.23	1.9	1.25	3.8	1.04	1.5	1.00	0.72
A 218	4 x 3½ x 1½	10.6	3.09	4.8	1.24	1.7	1.23	3.4	1.05	1.3	0.98	0.72
A 219	4 x 3½ x 1½	9.1	2.67	4.2	1.25	1.5	1.21	3.0	1.06	1.2	0.96	0.73
A 98	4 x 3½ x 1½	7.7	2.25	3.6	1.26	1.3	1.18	2.6	1.07	1.0	0.93	0.73
A 220	4 x 3 x 1½	17.1	5.03	7.3	1.21	2.9	1.44	3.5	0.83	1.7	0.94	0.64
A 221	4 x 3 x 1½	16.0	4.69	6.9	1.22	2.7	1.42	3.3	0.84	1.6	0.92	0.64
A 222	4 x 3 x 1½	14.8	4.34	6.5	1.22	2.5	1.39	3.1	0.84	1.5	0.89	0.64
A 223	4 x 3 x 1½	13.6	3.98	6.0	1.23	2.3	1.37	2.9	0.85	1.4	0.87	0.64
A 224	4 x 3 x 1½	12.4	3.62	5.6	1.24	2.1	1.35	2.7	0.86	1.2	0.85	0.64
A 225	4 x 3 x 1½	11.1	3.25	5.0	1.25	1.9	1.33	2.4	0.86	1.1	0.83	0.64
A 226	4 x 3 x 1½	9.8	2.87	4.5	1.25	1.7	1.30	2.2	0.87	1.0	0.80	0.64
A 227	4 x 3 x 1½	8.5	2.48	4.0	1.26	1.5	1.28	1.9	0.88	0.87	0.78	0.64
A 228	4 x 3 x 1½	7.2	2.09	3.4	1.27	1.2	1.26	1.7	0.89	0.74	0.76	0.65
A 283	4 x 3 x 1½	5.8	1.69	2.8	1.28	1.0	1.24	1.4	0.89	0.60	0.74	0.65
A 229	3½ x 3 x 1½	15.8	4.62	5.0	1.04	2.2	1.23	3.3	0.85	1.7	0.98	0.62
A 230	3½ x 3 x 1½	14.7	4.31	4.7	1.04	2.1	1.21	3.1	0.85	1.5	0.96	0.62
A 231	3½ x 3 x 1½	13.6	4.00	4.4	1.05	1.9	1.19	3.0	0.86	1.4	0.94	0.62
A 232	3½ x 3 x 1½	12.5	3.67	4.1	1.06	1.8	1.17	2.8	0.87	1.3	0.92	0.62
A 233	3½ x 3 x 1½	11.4	3.34	3.8	1.07	1.6	1.15	2.5	0.87	1.2	0.90	0.62
A 234	3½ x 3 x 1½	10.2	3.00	3.5	1.07	1.5	1.13	2.3	0.88	1.1	0.88	0.62
A 235	3½ x 3 x 1½	9.1	2.65	3.1	1.08	1.3	1.10	2.1	0.89	0.98	0.85	0.62
A 236	3½ x 3 x 1½	7.9	2.30	2.7	1.09	1.1	1.08	1.8	0.90	0.85	0.83	0.62
A 237	3½ x 3 x 1½	6.6	1.93	2.3	1.10	0.96	1.06	1.6	0.90	0.72	0.81	0.63
A 286	3½ x 3 x 1½	5.4	1.56	1.9	1.11	0.78	1.04	1.3	0.91	0.58	0.79	0.63
A 238	3½ x 2½ x 1½	12.5	3.65	4.1	1.06	1.9	1.27	1.7	0.69	0.99	0.77	0.53
A 239	3½ x 2½ x 1½	11.5	3.36	3.8	1.07	1.7	1.25	1.6	0.69	0.92	0.75	0.53
A 240	3½ x 2½ x 1½	10.4	3.06	3.6	1.08	1.6	1.23	1.5	0.70	0.84	0.73	0.53
A 241	3½ x 2½ x 1½	9.4	2.75	3.2	1.09	1.4	1.20	1.4	0.70	0.76	0.70	0.53
A 242	3½ x 2½ x 1½	8.3	2.43	2.9	1.09	1.3	1.18	1.2	0.71	0.68	0.68	0.54
A 243	3½ x 2½ x 1½	7.2	2.11	2.6	1.10	1.1	1.16	1.1	0.72	0.59	0.66	0.54
A 244	3½ x 2½ x 1½	6.1	1.78	2.2	1.11	0.93	1.14	0.94	0.73	0.50	0.64	0.54
A 245	3½ x 2½ x 1½	4.9	1.44	1.8	1.12	0.75	1.11	0.78	0.74	0.41	0.61	0.54

## ELEMENTS OF SECTIONS


## ELEMENTS OF UNEQUAL ANGLES—Concluded



Section Index	Size	Weight per Foot	Area of Section	Axis 1-1				Axis 2-2				Axis 3-3	
				I		S		I		S		y	
				In.	In. <sup>2</sup>	In.	In. <sup>3</sup>	In.	In. <sup>2</sup>	In.	In. <sup>3</sup>	In.	In.
A 252	3 x 2 1/2 x 3/8	9.5	2.78	2.3	0.91	1.2	1.02	1.4	0.72	0.82	0.77	0.52	
A 253	3 x 2 1/2 x 3/8	8.5	2.50	2.1	0.91	1.0	1.00	1.3	0.72	0.74	0.75	0.52	
A 254	3 x 2 1/2 x 3/8	7.6	2.21	1.9	0.92	0.93	0.98	1.2	0.73	0.66	0.73	0.52	
A 255	3 x 2 1/2 x 3/8	6.6	1.92	1.7	0.93	0.81	0.96	1.0	0.74	0.58	0.71	0.52	
A 256	3 x 2 1/2 x 3/8	5.6	1.62	1.4	0.94	0.69	0.93	0.90	0.74	0.49	0.68	0.53	
A 257	3 x 2 1/2 x 3/8	4.5	1.31	1.2	0.95	0.56	0.91	0.74	0.75	0.40	0.66	0.53	
A 258	3 x 2 x 1/2	7.7	2.25	1.9	0.92	1.0	1.08	0.67	0.55	0.47	0.58	0.43	
A 259	3 x 2 x 1/2	6.8	2.00	1.7	0.93	0.89	1.06	0.61	0.55	0.42	0.56	0.43	
A 260	3 x 2 x 1/2	5.9	1.73	1.5	0.94	0.78	1.04	0.54	0.56	0.37	0.54	0.43	
A 261	3 x 2 x 1/2	5.0	1.47	1.3	0.95	0.66	1.02	0.47	0.57	0.32	0.52	0.43	
A 262	3 x 2 x 1/4	4.1	1.19	1.1	0.95	0.54	0.99	0.39	0.57	0.25	0.49	0.43	
A 264	2 1/2 x 2 x 1/2	6.8	2.00	1.1	0.75	0.70	0.88	0.64	0.56	0.46	0.63	0.42	
A 265	2 1/2 x 2 x 1/2	6.1	1.78	1.0	0.76	0.62	0.85	0.58	0.57	0.41	0.60	0.42	
A 266	2 1/2 x 2 x 1/2	5.3	1.55	0.91	0.77	0.55	0.83	0.51	0.58	0.36	0.58	0.42	
A 267	2 1/2 x 2 x 1/2	4.5	1.31	0.79	0.78	0.47	0.81	0.45	0.58	0.31	0.56	0.42	
A 268	2 1/2 x 2 x 1/4	3.62	1.06	0.65	0.78	0.38	0.79	0.37	0.59	0.25	0.51	0.42	
A 269	2 1/2 x 2 x 1/8	2.75	0.81	0.51	0.79	0.29	0.76	0.29	0.60	0.20	0.51	0.43	
A 523	2 1/2 x 2 x 1/8	1.86	0.55	0.35	0.80	0.20	0.74	0.20	0.61	0.13	0.49	0.43	
A 610	2 1/2 x 1 1/2 x 3/8	3.92	1.15	0.71	0.79	0.44	0.90	0.19	0.41	0.17	0.40	0.32	
A 611	2 1/2 x 1 1/2 x 3/8	3.19	0.94	0.59	0.79	0.36	0.88	0.16	0.41	0.14	0.38	0.32	
A 612	2 1/2 x 1 1/2 x 3/8	2.44	0.72	0.46	0.80	0.28	0.85	0.13	0.42	0.11	0.35	0.33	
A 270	2 1/4 x 1 1/2 x 1/2	5.6	1.63	0.75	0.68	0.54	0.86	0.26	0.40	0.26	0.48	0.32	
A 271	2 1/4 x 1 1/2 x 1/2	5.0	1.45	0.68	0.69	0.48	0.83	0.21	0.41	0.23	0.46	0.32	
A 272	2 1/4 x 1 1/2 x 5/8	4.4	1.27	0.61	0.69	0.42	0.81	0.21	0.41	0.20	0.44	0.32	
A 273	2 1/4 x 1 1/2 x 5/8	3.66	1.07	0.53	0.70	0.36	0.79	0.19	0.42	0.17	0.42	0.32	
A 274	2 1/4 x 1 1/2 x 5/8	2.98	0.88	0.44	0.71	0.30	0.77	0.16	0.42	0.14	0.39	0.32	
A 275	2 1/4 x 1 1/2 x 5/8	2.28	0.67	0.34	0.72	0.23	0.75	0.12	0.43	0.11	0.37	0.33	
A 631	2 x 1 1/2 x 3/8	3.09	1.17	0.43	0.61	0.34	0.71	0.21	0.42	0.20	0.46	0.32	
A 614	2 x 1 1/2 x 3/8	3.39	1.00	0.38	0.62	0.29	0.69	0.18	0.42	0.17	0.41	0.32	
A 615	2 x 1 1/2 x 3/8	2.77	0.81	0.32	0.62	0.24	0.66	0.15	0.43	0.14	0.41	0.32	
A 616	2 x 1 1/2 x 3/8	2.12	0.62	0.25	0.63	0.18	0.64	0.12	0.44	0.11	0.39	0.32	
A 525	2 x 1 1/2 x 3/8	1.44	0.42	0.17	0.64	0.13	0.62	0.09	0.45	0.08	0.37	0.33	
A 646	2 x 1 1/4 x 1/4	2.55	0.75	0.30	0.63	0.23	0.71	0.09	0.34	0.10	0.33	0.27	
A 645	2 x 1 1/4 x 1/8	1.96	0.57	0.23	0.64	0.18	0.69	0.07	0.35	0.08	0.31	0.27	
A 618	1 3/4 x 1 1/4 x 1/4	2.34	0.69	0.20	0.54	0.18	0.60	0.09	0.35	0.10	0.35	0.27	
A 619	1 3/4 x 1 1/4 x 1/8	1.80	0.53	0.16	0.55	0.14	0.58	0.07	0.36	0.08	0.33	0.27	
A 620	1 3/4 x 1 1/4 x 1/8	1.23	0.36	0.11	0.56	0.09	0.56	0.05	0.37	0.05	0.31	0.27	
A 670	1 1/2 x 1 1/4 x 1/8	2.59	0.76	0.16	0.45	0.16	0.52	0.10	0.35	0.11	0.40	0.26	
A 623	1 1/2 x 1 1/4 x 1/8	2.13	0.63	0.13	0.46	0.13	0.50	0.08	0.36	0.09	0.38	0.26	
A 624	1 1/2 x 1 1/4 x 1/8	1.64	0.48	0.10	0.46	0.10	0.48	0.07	0.37	0.07	0.35	0.26	

# CARNEGIE STEEL COMPANY


## ELEMENTS OF EQUAL TEES



Section Index	Size				Weight per Foot	Area of Section	Axis 1-1				Axis 2-2			
	Flange	Stem	Minimum Thickness				I	r	S	x	I	r	S	
			Flange	Stem										
	In.	In.	In.	In.	lbs.	In. <sup>2</sup>	In. <sup>1</sup>	In.	In. <sup>3</sup>	In.	In. <sup>1</sup>	In.	In. <sup>3</sup>	
T 40	6½	6½	0.40	0.45	19.8	5.80	23.5	2.01	5.0	1.76	10.1	1.32	3.1	
T 1	4	4	½	½	13.5	3.97	5.7	1.20	2.0	1.18	2.8	0.84	1.4	
T 2	4	4	¾	¾	10.5	3.09	4.5	1.21	1.6	1.13	2.1	0.83	1.1	
T 3	3½	3½	½	½	11.7	3.44	3.7	1.04	1.5	1.05	1.9	0.74	1.1	
T 4	3½	3½	¾	¾	9.2	2.68	3.0	1.05	1.2	1.01	1.4	0.73	0.81	
T 6	3	3	½	½	9.9	2.91	2.3	0.88	1.1	0.93	1.2	0.64	0.80	
T 7	3	3	⅝	⅝	8.9	2.59	2.1	0.89	0.98	0.91	1.0	0.63	0.70	
T 8	3	3	¾	¾	7.8	2.27	1.8	0.90	0.86	0.88	0.90	0.63	0.60	
T 9	3	3	⅞	⅞	6.7	1.95	1.6	0.90	0.74	0.86	0.75	0.62	0.50	
T 10	2½	2½	¾	¾	6.4	1.87	1.0	0.74	0.59	0.76	0.52	0.53	0.42	
T 11	2½	2½	⅞	⅞	5.5	1.60	0.88	0.74	0.50	0.74	0.44	0.52	0.35	
T 12	2¼	2¼	⅞	⅞	4.9	1.43	0.65	0.67	0.41	0.68	0.33	0.48	0.29	
T 13	2¼	2¼	¾	¾	4.1	1.19	0.52	0.66	0.32	0.65	0.25	0.46	0.22	
T 14	2	2	⅞	⅞	4.3	1.26	0.44	0.59	0.31	0.61	0.23	0.43	0.23	
T 15	2	2	¾	¾	3.56	1.05	0.37	0.59	0.26	0.59	0.18	0.42	0.18	
T 16	1¾	1¾	¾	¾	3.09	0.91	0.23	0.51	0.19	0.54	0.12	0.37	0.14	
T 17	1¾	1¾	⅞	⅞	2.47	0.73	0.15	0.45	0.14	0.47	0.08	0.32	0.10	
T 18	1½	1½	⅞	⅞	1.94	0.57	0.11	0.45	0.11	0.44	0.06	0.32	0.08	
T 19	1¾	1¾	¾	¾	2.02	0.59	0.08	0.37	0.10	0.40	0.05	0.28	0.07	
T 20	1¾	1¾	⅞	⅞	1.59	0.47	0.06	0.37	0.07	0.38	0.03	0.27	0.05	
T 21	1	1	⅞	⅞	1.25	0.37	0.03	0.29	0.05	0.32	0.02	0.22	0.04	
T 22	1	1	¾	¾	0.89	0.26	0.02	0.30	0.03	0.29	0.01	0.21	0.02	

## ELEMENTS OF SECTIONS


## ELEMENTS OF UNEQUAL TEES



Section Index	Size				Weight per Foot	Area of Section	Axis 1-1			Axis 2-2			
	Flange		Stem				l	r	S	x	l	r	S
	Minimum Thickness		Minimum Thickness										
	Flange	Stem	Flange	Stem									
	In.	In.	In.	In.	Lbs.	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In. <sup>4</sup>	In.	In. <sup>3</sup>
T 50	5	3	$\frac{1}{2}$	$\frac{1}{2}$	13.4	3.93	2.4	0.78	1.1	0.73	5.4	1.17	2.2
T 51	5	$2\frac{1}{2}$	$\frac{3}{8}$	$\frac{1}{2}$	10.9	3.18	1.5	0.68	0.78	0.63	4.1	1.14	1.6
T 52	$4\frac{1}{2}$	$3\frac{1}{2}$	$\frac{1}{2}$	$\frac{1}{2}$	15.7	4.60	5.1	1.05	2.1	1.11	3.7	0.90	1.7
T 53	$4\frac{1}{2}$	3	$\frac{3}{8}$	$\frac{3}{8}$	9.8	2.88	2.1	0.84	0.91	0.74	3.0	1.02	1.3
T 54	$4\frac{1}{2}$	3	$\frac{3}{8}$	$\frac{3}{8}$	8.4	2.46	1.8	0.85	0.78	0.71	2.5	1.01	1.1
T 55	$4\frac{1}{2}$	$2\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	9.2	2.68	1.2	0.67	0.63	0.59	3.0	1.05	1.3
T 56	$4\frac{1}{2}$	$2\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	7.8	2.29	1.0	0.68	0.54	0.57	2.5	1.05	1.1
T 57	4	5	$\frac{1}{2}$	$\frac{1}{2}$	15.3	4.50	10.8	1.55	3.1	1.56	2.8	0.79	1.4
T 58	4	5	$\frac{3}{8}$	$\frac{3}{8}$	11.9	3.19	8.5	1.56	2.4	1.51	2.1	0.78	1.1
T 59	4	$4\frac{1}{2}$	$\frac{1}{2}$	$\frac{1}{2}$	14.4	4.23	7.9	1.37	2.5	1.37	2.8	0.81	1.4
T 60	4	$4\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	11.2	3.29	6.3	1.39	2.0	1.31	2.1	0.80	1.1
T 61	4	3	$\frac{3}{8}$	$\frac{3}{8}$	9.2	2.68	2.0	0.86	0.90	0.78	2.1	0.89	1.1
T 62	4	3	$\frac{3}{8}$	$\frac{3}{8}$	7.8	2.29	1.7	0.87	0.77	0.75	1.8	0.88	0.88
T 63	4	$2\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	8.5	2.48	1.2	0.69	0.62	0.62	2.1	0.92	1.0
T 64	4	$2\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	7.2	2.12	1.0	0.69	0.53	0.60	1.8	0.91	0.88
T 65	4	2	$\frac{3}{8}$	$\frac{3}{8}$	7.8	2.27	0.60	0.52	0.40	0.48	2.1	0.96	1.1
T 66	$3\frac{1}{2}$	4	$\frac{1}{2}$	$\frac{1}{2}$	6.7	1.95	0.53	0.52	0.34	0.46	1.8	0.95	0.88
T 67	$3\frac{1}{2}$	4	$\frac{3}{8}$	$\frac{3}{8}$	12.6	3.70	5.5	1.21	2.0	1.24	1.9	0.72	1.1
T 68	$3\frac{1}{2}$	4	$\frac{3}{8}$	$\frac{3}{8}$	9.8	2.88	4.3	1.23	1.5	1.19	1.4	0.70	0.81
T 69	$3\frac{1}{2}$	3	$\frac{1}{2}$	$\frac{1}{2}$	10.8	3.17	2.1	0.87	1.1	0.88	1.9	0.77	1.1
T 70	$3\frac{1}{2}$	3	$\frac{3}{8}$	$\frac{3}{8}$	8.5	2.48	1.9	0.88	0.89	0.83	1.4	0.75	0.81
T 71	$3\frac{1}{2}$	3	$\frac{3}{8}$	$\frac{3}{8}$	7.5	2.20	1.8	0.91	0.85	0.85	1.2	0.74	0.68
T 72	3	4	$\frac{1}{2}$	$\frac{1}{2}$	11.7	3.44	5.2	1.23	1.9	1.32	1.2	0.59	0.81
T 73	3	4	$\frac{3}{8}$	$\frac{3}{8}$	10.5	3.06	4.7	1.23	1.7	1.29	1.1	0.59	0.70
T 74	3	4	$\frac{3}{8}$	$\frac{3}{8}$	9.2	2.68	4.1	1.24	1.5	1.27	0.90	0.58	0.60
T 75	3	$3\frac{1}{2}$	$\frac{1}{2}$	$\frac{1}{2}$	10.8	3.17	3.5	1.06	1.5	1.12	1.2	0.62	0.80
T 76	3	$3\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	9.7	2.83	3.2	1.06	1.3	1.10	1.0	0.60	0.69
T 77	3	$3\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	8.5	2.48	2.8	1.07	1.2	1.07	0.93	0.61	0.62
T 78	3	$2\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	7.1	2.07	1.1	0.72	0.60	0.71	0.89	0.66	0.50
T 79	3	$2\frac{1}{2}$	$\frac{3}{8}$	$\frac{3}{8}$	6.1	1.77	0.94	0.73	0.52	0.68	0.75	0.65	0.50
T 82	$2\frac{1}{2}$	3	$\frac{3}{8}$	$\frac{3}{8}$	7.1	2.07	1.7	0.91	0.84	0.95	0.53	0.51	0.42
T 83	$2\frac{1}{2}$	3	$\frac{3}{8}$	$\frac{3}{8}$	6.1	1.77	1.5	0.92	0.72	0.92	0.44	0.50	0.35
T 86	$2\frac{1}{2}$	$1\frac{1}{4}$	$\frac{3}{8}$	$\frac{3}{8}$	2.87	0.84	0.08	0.31	0.09	0.32	0.29	0.58	0.23
T 87	2	$1\frac{1}{2}$	$\frac{3}{4}$	$\frac{3}{4}$	3.09	0.91	0.16	0.42	0.15	0.42	0.18	0.45	0.18
T 519	$1\frac{1}{2}$	2	$\frac{3}{8}$	$\frac{3}{8}$	2.45	0.72	0.27	0.61	0.19	0.63	0.06	0.92	0.08
T 605	$1\frac{1}{2}$	$1\frac{1}{4}$	$\frac{3}{8}$	$\frac{3}{8}$	1.25	0.37	0.05	0.37	0.05	0.33	0.04	0.32	0.05
T 603	$1\frac{1}{4}$	$\frac{5}{8}$	No. 9	$\frac{1}{8}$	0.88	0.26	0.01	0.16	0.01	0.16	0.02	0.31	0.04

# CARNEGIE STEEL COMPANY


## ELEMENTS OF ZEES



Section Index	Size			Weight per Foot	Area of Section	Axis 1-1			Axis 2-2			Axis 3-3
	Depth	Flange	Thick-ness			I	r	S	I	r	S	
	In.	In.	In.	lbs.	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.
Z 3	6 $\frac{1}{8}$	3 $\frac{5}{8}$	$\frac{7}{8}$	34.6	10.17	50.2	2.22	16.4	19.2	1.37	6.0	0.83
	6 $\frac{1}{8}$	3 $\frac{5}{8}$	$\frac{1}{4}$	32.0	9.40	46.1	2.22	15.2	17.3	1.36	5.5	0.82
	6	3 $\frac{1}{2}$	$\frac{3}{4}$	29.4	8.63	42.1	2.21	14.0	15.4	1.34	4.9	0.81
Z 2	6 $\frac{1}{8}$	3 $\frac{5}{8}$	$\frac{1}{2}$	28.1	8.25	43.2	2.20	14.1	16.3	1.41	5.0	0.84
	6 $\frac{1}{8}$	3 $\frac{5}{8}$	$\frac{5}{16}$	25.4	7.46	38.9	2.28	12.8	14.4	1.39	4.4	0.82
	6	3 $\frac{1}{2}$	$\frac{3}{8}$	22.8	6.68	34.6	2.28	11.5	12.6	1.37	3.9	0.81
Z 1	6 $\frac{1}{8}$	3 $\frac{5}{8}$	$\frac{1}{2}$	21.1	6.19	34.4	2.36	11.2	12.9	1.44	3.8	0.84
	6 $\frac{1}{8}$	3 $\frac{5}{8}$	$\frac{5}{16}$	18.4	5.39	29.8	2.35	9.8	11.0	1.43	3.3	0.83
	6	3 $\frac{1}{2}$	$\frac{3}{8}$	15.7	4.59	25.3	2.35	8.4	9.1	1.41	2.8	0.83
Z 0	5 $\frac{1}{8}$	3 $\frac{3}{8}$	$\frac{1}{4}$	28.4	8.33	28.7	1.86	11.2	14.4	1.31	4.8	0.76
	5 $\frac{1}{8}$	3 $\frac{3}{8}$	$\frac{3}{16}$	26.0	7.61	26.2	1.85	10.3	12.8	1.30	4.4	0.74
	5	3 $\frac{1}{4}$	$\frac{1}{2}$	23.7	6.96	23.7	1.84	9.5	11.4	1.28	3.9	0.73
Z 5	5 $\frac{1}{8}$	3 $\frac{3}{8}$	$\frac{5}{8}$	22.6	6.64	24.5	1.92	9.6	12.1	1.35	3.9	0.76
	5 $\frac{1}{8}$	3 $\frac{3}{8}$	$\frac{3}{4}$	20.2	5.94	21.8	1.91	8.6	10.5	1.33	3.5	0.75
	5	3 $\frac{1}{4}$	$\frac{3}{2}$	17.9	5.25	19.2	1.91	7.7	9.1	1.31	3.0	0.74
Z 4	5 $\frac{1}{8}$	3 $\frac{3}{8}$	$\frac{7}{8}$	16.4	4.81	19.1	1.99	7.4	9.2	1.38	2.9	0.77
	5 $\frac{1}{8}$	3 $\frac{3}{8}$	$\frac{3}{4}$	14.0	4.10	16.2	1.99	6.4	7.7	1.37	2.5	0.76
	5	3 $\frac{1}{4}$	$\frac{5}{8}$	11.6	3.40	13.4	1.98	5.3	6.2	1.35	2.0	0.75
Z 9	4 $\frac{1}{8}$	3 $\frac{1}{8}$	$\frac{3}{4}$	23.0	6.75	15.0	1.49	7.3	11.2	1.29	4.0	0.68
	4 $\frac{1}{8}$	3 $\frac{1}{8}$	$\frac{1}{2}$	20.9	6.14	13.5	1.48	6.7	10.0	1.27	3.6	0.67
	4	3 $\frac{1}{8}$	$\frac{5}{8}$	18.9	5.55	12.1	1.48	6.1	8.7	1.25	3.2	0.66
Z 8	4 $\frac{1}{8}$	3 $\frac{1}{8}$	$\frac{5}{8}$	18.0	5.27	12.7	1.55	6.2	9.3	1.33	3.2	0.68
	4 $\frac{1}{8}$	3 $\frac{1}{8}$	$\frac{3}{4}$	15.9	4.66	11.2	1.55	5.5	8.0	1.31	2.8	0.67
	4	3 $\frac{1}{8}$	$\frac{1}{2}$	13.8	4.05	9.7	1.55	4.8	6.7	1.29	2.4	0.66
Z 7	4 $\frac{1}{8}$	3 $\frac{1}{8}$	$\frac{3}{8}$	12.5	3.66	9.6	1.62	4.7	6.8	1.36	2.3	0.69
	4 $\frac{1}{8}$	3 $\frac{1}{8}$	$\frac{1}{4}$	10.3	3.03	7.9	1.62	3.9	5.5	1.34	1.8	0.68
	4	3 $\frac{1}{8}$	$\frac{3}{4}$	8.2	2.41	6.3	1.62	3.1	4.2	1.33	1.4	0.67
Z 12	3 $\frac{1}{8}$	2 $\frac{3}{8}$	$\frac{5}{8}$	14.3	4.18	5.3	1.12	3.4	5.7	1.17	2.3	0.54
	3	2 $\frac{1}{8}$	$\frac{3}{2}$	12.6	3.69	4.6	1.12	3.1	4.9	1.15	2.0	0.53
Z 11	3 $\frac{1}{8}$	2 $\frac{3}{8}$	$\frac{7}{8}$	11.5	3.36	4.6	1.17	3.0	4.8	1.19	1.9	0.55
	3	2 $\frac{1}{8}$	$\frac{1}{4}$	9.8	2.86	3.9	1.16	2.6	3.9	1.17	1.6	0.54
Z 10	3 $\frac{1}{8}$	2 $\frac{3}{8}$	$\frac{3}{4}$	8.5	2.48	3.6	1.21	2.4	3.6	1.21	1.4	0.56
	3	2 $\frac{1}{8}$	$\frac{1}{2}$	6.7	1.97	2.9	1.21	1.9	2.8	1.19	1.1	0.55

# ELEMENTS OF SECTIONS


## ELEMENTS OF CROSS TIES



Section Index	Depth of Section	Wt. per Foot	Area of Section	Width of Flange		Thick-ness of Web	Axis 1-1				Axis 2-2			
				Top	Bottom		I	r	S	x	I	r	S	
	In.	Lbs.	In. <sup>2</sup>	In.	In.	In.	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.
M 28	6.50	27.8	8.09	5.0	10.0	.313	57.5	2.67	14.3	2.49	30.8	1.95	6.2	
M 29	5.50	23.5	7.01	5.0	8.0	.375	35.4	2.25	11.3	2.38	16.8	1.55	4.2	
M 21	5.50	20.0	5.71	4.5	8.0	.250	30.9	2.33	9.7	2.33	14.9	1.62	3.7	
M 25	4.25	14.5	4.10	4.0	6.0	.250	13.0	1.78	5.5	1.88	6.1	1.22	2.0	
M 24	3.00	9.5	2.80	3.0	5.0	.203	4.3	1.24	2.5	1.27	3.1	1.05	1.2	



Section Index	Depth of Section	Wt. per Foot	Area of Section	Width of Section		Thickness	Axis 1-1			Axis 2-2			
				Top	Bottom		l	r	S	x	l	r	S
In.	Lbs.	In. <sup>2</sup>	In.	In.	In.	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.	In. <sup>4</sup>	In.	In. <sup>4</sup>	
M 27	2.25	9.0	2.62	5.5	7.0	.250	1.28	0.70	0.79	1.62	16.8	2.53	4.8
M 20	2.00	6.0	1.72	4.5	6.0	.188	0.71	0.64	0.51	1.41	8.4	2.22	2.8
M 18	1.50	4.0	1.21	3.4	5.0	.156	0.31	0.50	0.31	1.00	3.6	1.73	1.5




Section Index	Depth of Section	Wt. per Foot	Area of Section	Width of Section	Thickness	Axis 1-1				Axis 2-2			
						I		S	x	I		S	x
						In.	In.			In.	In.		
M 26	1 1/4	3.20	0.97	4 1/2	1/8	0.059	0.25	0.110	0.54	2.44	1.58	0.99	
M 19	3/4	2.50	0.74	4	3/16	0.024	0.18	0.057	0.43	1.15	1.25	0.58	




# CARNEGIE STEEL COMPANY

## ELEMENTS OF TROUGH PLATES

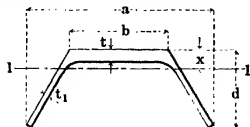


Section Index	Dimensions					Weight per Foot	Area of Section	Axis 1-1			
	a	b	d	t	t <sub>1</sub>			I	r	S	x
	In.	In.	In.	In.	In.	Lbs.	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.
M 14	9 1/2	5	3 3/4	3/8	3/8	23.2	6.82	5.5	0.90	2.2	1.21
M 13	9 1/2	5	3 3/4	3/8	3/8	21.4	6.30	5.0	0.90	2.0	1.19
M 12	9 1/2	5	3 3/4	3/8	3/8	19.7	5.79	4.6	0.90	1.8	1.16
M 11	9 1/2	5	3 3/4	3/8	3/8	18.0	5.28	4.1	0.91	1.6	1.12
M 10	9 1/2	5	3 3/4	3/8	3/8	16.3	4.78	3.7	0.91	1.4	1.08

## ELEMENTS OF CORRUGATED PLATES



Section Index	Dimensions					Weight per Foot	Area of Section	Axis 1-1			
	a	b	d	t	r			I	r	S	x
	In.	In.	In.	In.	In.	Lbs.	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>	In.
M 35	12 1/8	7 3/8	2 3/8	1/8	3 7/8	23.7	6.97	6.8	0.99	4.5	1.34
M 34	12 1/8	7 3/8	2 3/8	1/8	3 7/8	20.8	6.10	5.8	0.98	3.9	1.32
M 33	12 1/8	7 3/8	2 3/8	1/8	3 7/8	17.8	5.22	4.8	0.96	3.3	1.31
M 32	8 3/4	5 1/2	1 5/8	3/8	3 3/8	12.0	3.53	1.3	0.62	1.4	0.74
M 31	8 3/4	5 1/2	1 1/8	3/8	3 3/8	10.1	2.90	0.95	0.57	1.1	0.72
M 30	8 3/4	5 1/2	1 1/2	3/8	3 3/8	8.1	2.38	0.64	0.52	0.80	0.70


## ELEMENTS OF U. S. STEEL SHEET PILING SECTIONS



Section Index	Dimensions					Weight per Foot	Area of Section	Axis 1-1		
	a	b	c	d	t			I	r	S
	In.	In.	In.	In.	In.	Lbs.	In. <sup>2</sup>	In. <sup>4</sup>	In.	In. <sup>3</sup>
M 105	13 1/4	12 1/2	4 1/8	2 5/8	1/2	43	12.72	9.20	0.85	4.53
M 104	13 1/4	12 1/2	3 1/8	2 1/2	3/4	38	11.20	8.35	0.87	4.30
M 103	9 3/4	9	2 3/8	1 3/4	3/4	16	4.71	1.45	0.56	1.13

# ELEMENTS OF SECTIONS

## ELEMENTS OF RAIL AND SPLICE BARS

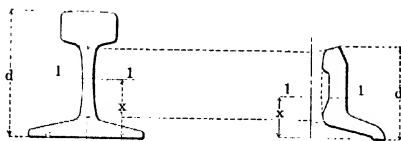


Section Index	Weight per Yard	Depth of Section	Area of Section	Axis 1-1			Section Index	Weight per Foot	Depth of Section	Area of Section	Axis 1-1		
				I	S	x					I	S	x
	Lbs.	In.	In. <sup>2</sup>	In. <sup>4</sup>	In. <sup>3</sup>	In.		Lbs.	In.	In. <sup>2</sup>	In. <sup>4</sup>	In. <sup>3</sup>	In.
A. S. C. E. RAILS							A. S. C. E. SPLICE BARS						
10040	100	5 <sup>3</sup> / <sub>4</sub>	9.84	43.97	14.55	2.73	810040	15.80	4 <sup>7</sup> / <sub>8</sub>	4.65	13.43	5.82	1.91
9040	90	5 <sup>3</sup> / <sub>8</sub>	8.83	34.39	12.19	2.55	80040	13.50	3 <sup>7</sup> / <sub>8</sub>	3.97	10.30	4.79	1.81
8540	85	5 <sup>1</sup> / <sub>8</sub>	8.33	30.07	11.08	2.47	8540	12.40	3 <sup>1</sup> / <sub>2</sub>	3.65	8.43	4.02	1.71
8040	80	5	7.86	26.38	10.07	2.38	8040	11.50	3 <sup>1</sup> / <sub>2</sub>	3.38	7.36	3.75	1.68
7540	75	4 <sup>1</sup> / <sub>2</sub>	7.33	22.86	9.10	2.30	87540	10.70	3 <sup>1</sup> / <sub>2</sub>	3.15	6.02	3.28	1.65
7040	70	4 <sup>1</sup> / <sub>8</sub>	6.81	19.70	8.19	2.22	87040	10.00	3 <sup>1</sup> / <sub>2</sub>	2.95	5.82	3.15	1.61
6540	65	4 <sup>1</sup> / <sub>8</sub>	6.33	16.90	7.37	2.14	86540	9.20	3 <sup>1</sup> / <sub>2</sub>	2.71	4.87	2.73	1.56
6040	60	4 <sup>1</sup> / <sub>4</sub>	5.93	14.56	6.62	2.05	86040	8.40	3 <sup>1</sup> / <sub>2</sub>	2.47	4.04	2.38	1.51
5540	55	4 <sup>1</sup> / <sub>4</sub>	5.38	12.03	5.75	1.97	85540	7.50	3 <sup>1</sup> / <sub>2</sub>	2.21	3.41	2.07	1.41
5040	50	3 <sup>3</sup> / <sub>8</sub>	4.87	9.94	4.98	1.88	85040	6.62	2 <sup>1</sup> / <sub>2</sub>	1.95	2.72	1.74	1.37
A. R. A. RAILS—TYPE A							A. R. A. SPLICE BARS—TYPE A						
10020	100	6	9.84	48.94	15.04	2.75	810020	19.04	4 <sup>1</sup> / <sub>2</sub>	5.60	21.30	7.88	2.02
9020	90	5 <sup>7</sup> / <sub>8</sub>	8.82	38.70	12.56	2.54	80020	16.64	4 <sup>1</sup> / <sub>2</sub>	4.90	16.10	6.30	1.91
8020	80	5 <sup>1</sup> / <sub>8</sub>	7.86	28.80	10.24	2.31	80020	13.43	3 <sup>1</sup> / <sub>2</sub>	3.95	10.13	4.57	1.72
7020	70	4 <sup>1</sup> / <sub>2</sub>	6.82	21.05	8.21	2.20	87020	11.64	3 <sup>1</sup> / <sub>2</sub>	3.43	7.42	3.63	1.48
6020	60	4 <sup>1</sup> / <sub>2</sub>	5.86	15.41	6.50	2.13	86020	10.63	3 <sup>1</sup> / <sub>2</sub>	3.13	6.22	3.16	1.52
A. R. A. RAILS—TYPE B							A. R. A. SPLICE BARS—TYPE B						
10030	100	5 <sup>1</sup> / <sub>2</sub>	9.85	41.30	13.70	2.63	810030	16.92	4 <sup>7</sup> / <sub>8</sub>	4.98	14.31	6.30	1.83
9030	90	4 <sup>1</sup> / <sub>2</sub>	8.87	32.30	11.45	2.44	89030	14.42	3 <sup>7</sup> / <sub>8</sub>	4.24	10.16	4.71	1.67
8030	80	4 <sup>1</sup> / <sub>8</sub>	7.91	25.10	9.38	2.27	88030	12.65	3 <sup>3</sup> / <sub>8</sub>	3.72	7.70	3.79	1.59
LIGHT RAILS							LIGHT RAIL SPLICE BARS						
4540	45	3 <sup>1</sup> / <sub>2</sub>	4.40	8.13	4.25	1.78	84540	5.80	2 <sup>3</sup> / <sub>8</sub>	1.70			1.29
4040	40	3 <sup>1</sup> / <sub>2</sub>	3.94	6.57	3.62	1.68	84040	5.00	2 <sup>3</sup> / <sub>8</sub>	1.47			1.27
3540	35	3 <sup>1</sup> / <sub>8</sub>	3.44	5.17	3.02	1.60	83540	4.58	2 <sup>1</sup> / <sub>2</sub>	1.35			1.19
3040	30	3 <sup>1</sup> / <sub>8</sub>	3.00	4.06	2.53	1.52	83040	3.97	2 <sup>1</sup> / <sub>2</sub>	1.17			1.10
2540	25	2 <sup>3</sup> / <sub>8</sub>	2.39	2.50	1.77	1.33	82540	2.20	1 <sup>1</sup> / <sub>2</sub>	0.65			0.90
2040	20	2 <sup>3</sup> / <sub>8</sub>	2.00	1.94	1.43	1.27	82040	1.87	1 <sup>1</sup> / <sub>2</sub>	0.55			0.86
1640	16	2 <sup>1</sup> / <sub>8</sub>	1.55	1.24	1.01	1.15	81640	1.70	1 <sup>1</sup> / <sub>2</sub>	0.50			0.79
1440	14	1 <sup>3</sup> / <sub>8</sub>	1.34	0.76	0.73	1.02	81440	1.36	1 <sup>1</sup> / <sub>2</sub>	0.40			0.65
1240	12	1 <sup>3</sup> / <sub>8</sub>	0.96	0.66	0.63	0.96	81240	1.36	1 <sup>1</sup> / <sub>2</sub>	0.40			0.65
1040	10	1 <sup>1</sup> / <sub>8</sub>	0.96	0.40	0.46	0.87	81040	0.985	1 <sup>1</sup> / <sub>2</sub>	0.29			0.56
840	8	1 <sup>1</sup> / <sub>8</sub>	0.77	0.20	0.32	0.75	840	0.747	1 <sup>1</sup> / <sub>8</sub>	0.22			0.49

# CARNEGIE STEEL COMPANY

## MOMENTS OF INERTIA OF RECTANGLES

IN WIDTHS FROM  $\frac{1}{4}$  TO  $\frac{5}{8}$  INCH AND 1 INCH

Neutral Axis Through Center Normal to Depth



This and the following table may be used in computing the Moments of Inertia of Plate Girders, Columns and other compound sections in which plates are used; see pages 168 and 169.


Depth, Inches	Width, Inches							
	$\frac{1}{4}$	$\frac{1}{2}$	$\frac{3}{8}$	$\frac{1}{2}$	$\frac{1}{2}$	$\frac{3}{4}$	$\frac{5}{8}$	1
1	.021	.026	.031	.037	.042	.047	.052	.083
2	.167	.208	.250	.292	.333	.375	.417	.667
3	.563	.703	.844	.984	1.125	1.266	1.406	2.250
4	1.333	1.667	2.000	2.333	2.667	3.000	3.333	5.333
5	2.604	3.255	3.906	4.557	5.208	5.859	6.510	10.417
6	4.500	5.625	6.750	7.875	9.000	10.125	11.250	18.000
7	7.146	8.932	10.719	12.505	14.292	16.078	17.865	28.583
8	10.667	13.333	16.000	18.667	21.333	24.000	26.667	42.667
9	15.188	18.984	22.781	26.578	30.375	34.172	37.969	60.750
10	20.833	26.042	31.250	36.458	41.667	46.875	52.083	83.333
11	27.729	34.662	41.594	48.526	55.458	62.391	69.323	110.917
12	36.000	45.000	51.000	63.000	72.000	81.000	90.000	144.000
13	45.771	57.214	68.656	80.099	91.542	102.984	114.427	183.083
14	57.167	71.458	85.750	100.042	114.333	128.625	142.917	228.667
15	70.313	87.891	105.469	123.047	140.625	158.203	175.781	281.250
16	85.333	106.667	128.000	149.333	170.667	192.000	213.333	341.333
17	102.354	127.943	153.531	179.120	204.708	230.297	255.885	409.417
18	121.500	151.875	182.250	212.625	243.000	273.375	303.750	486.000
19	142.896	178.620	214.344	250.068	285.792	321.516	357.240	571.583
20	166.667	208.333	250.000	291.667	333.333	375.000	416.667	666.667
21	192.938	241.172	289.406	337.041	385.875	434.109	482.344	771.750
22	221.833	277.292	332.750	388.208	443.667	499.125	551.583	887.333
23	253.479	316.849	380.219	443.589	506.958	570.328	633.698	1013.917
24	288.000	360.000	432.000	504.000	576.000	648.000	720.000	1152.000
25	325.521	406.901	488.281	569.662	651.042	732.422	813.802	1302.083
26	366.167	457.708	549.250	640.792	732.333	823.875	915.417	1464.667
27	410.063	512.578	615.094	717.609	820.125	922.641	1025.156	1640.250
28	457.333	571.667	686.000	800.333	914.667	1029.000	1143.333	1829.333
29	508.104	635.130	762.156	889.182	1016.208	1143.234	1270.260	2032.417
30	562.500	703.125	843.750	984.375	1125.000	1265.625	1406.250	2250.000
32	682.667	853.444	1024.000	1194.667	1365.333	1536.000	1706.667	2730.667
34	818.833	1023.542	1228.250	1432.958	1637.667	1842.375	2047.083	3275.333
36	972.000	1215.000	1458.000	1701.000	1944.000	2187.000	2430.000	3888.000
38	1143.167	1428.958	1714.750	2000.542	2286.333	2572.125	2857.917	4572.667
40	1333.333	1666.667	2000.000	2333.333	2666.667	3000.000	3333.333	5333.333
42	1543.500	1929.375	2315.250	2701.125	3087.000	3472.875	3858.750	6174.000
44	1774.667	2218.333	2662.000	3105.667	3549.333	3993.000	4436.667	7098.667
46	2027.833	2534.792	3041.750	3548.708	4055.667	4562.625	5069.583	8111.333
48	2304.000	2880.000	3456.000	4032.000	4608.000	5184.000	5760.000	9216.000
50	2604.167	3255.208	3906.250	4557.292	5208.333	5859.375	6510.417	10416.667
52	2929.333	3661.667	4394.000	5126.333	5858.667	6591.000	7323.333	11717.333
54	3280.500	4100.625	4920.750	5740.875	6561.000	7381.125	8201.250	13222.000
56	3658.667	4573.333	5488.000	6402.667	7317.333	8232.000	9146.667	14934.667
58	4064.833	5081.042	6097.250	7113.458	8129.667	9145.875	10162.083	16259.333
60	4500.000	5625.000	6750.000	7875.000	9000.000	10125.000	11250.000	18000.000

# ELEMENTS OF SECTIONS

## MOMENTS OF INERTIA OF RECTANGLES

### IN WIDTHS OF 1 INCH

Neutral Axis Through Center Normal to Depth




To obtain the Moment of Inertia of any rectangle, multiply the tabular value for its depth by its width in inches. For deeper rectangles of tabular thickness, multiply the tabular values for half their depth by 8; or for one-third their depth by 27, etc.

Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>	Depth, Inches	$I_{1-1}$ Inches <sup>4</sup>
0	.000	6	18.000	12	144.000	18	486.000	24	1152.000	30	2250.000										
.000		6	19.149	12	148.547	18	496.195	24	1170.094	30	2278.243										
.001		6	20.345	12	153.189	18	506.533	24	1188.376	30	2306.721										
.004		6	21.590	12	157.926	18	517.012	24	1206.848	30	2335.434										
.010		6	22.885	12	162.760	18	527.635	24	1225.510	30	2364.385										
.020		6	24.231	12	167.692	18	538.403	24	1244.364	30	2393.575										
.035		6	25.629	12	172.723	18	549.317	24	1263.410	30	2423.004										
.056		6	27.079	12	177.853	18	560.376	24	1282.650	30	2452.674										
.083		6	28.583	12	183.083	18	571.583	24	1302.083	30	2482.583										
.110		6	30.142	12	188.416	18	582.939	24	1321.713	30	2512.737										
.163		6	31.757	12	193.850	18	594.444	24	1341.538	30	2543.132										
.217		6	33.428	12	199.389	18	606.099	24	1361.561	30	2573.771										
.281		6	35.156	12	205.031	18	617.906	24	1381.781	30	2604.656										
.358		6	36.944	12	210.779	18	629.866	24	1402.202	30	2635.787										
.447		6	38.790	12	216.634	18	641.978	24	1422.821	30	2667.165										
.549		6	40.698	12	222.596	18	654.245	24	1443.644	30	2698.792										
.667		6	42.667	12	228.667	18	666.667	24	1464.667	30	2730.667										
.800		6	44.698	12	234.847	18	679.245	24	1485.893	30	2762.792										
.949		6	46.793	12	241.137	18	691.840	24	1507.324	30	2795.168										
1.116		6	48.952	12	247.538	18	704.874	24	1528.961	30	2827.797										
1.302		6	51.177	12	254.052	18	717.927	24	1550.802	30	2860.672										
1.507		6	53.468	12	260.679	18	731.141	24	1572.851	30	2893.811										
1.733		6	55.827	12	267.421	18	744.514	24	1595.108	30	2927.202										
1.980		6	58.254	12	274.277	18	758.051	24	1617.575	30	2960.849										
2.250		6	60.750	12	281.250	18	771.750	24	1640.250	30	2994.750										
2.543		6	63.317	12	288.340	18	785.613	24	1663.136	30	3028.911										
2.861		6	65.954	12	295.548	18	799.652	24	1686.236	30	3063.329										
3.204		6	68.665	12	302.875	18	813.836	24	1709.547	30	3098.000										
3.573		6	71.448	12	310.323	18	828.198	24	1733.073	30	3132.948										
3.970		6	74.305	12	317.891	18	842.727	24	1756.814	30	3168.150										
4.395		6	77.238	12	325.582	18	857.426	24	1780.770	30	3203.614										
4.849		6	80.247	12	333.396	18	872.294	24	1804.943	30	3239.341										
5.333		6	83.333	12	341.333	18	887.333	24	1829.333	30	3275.333										
5.849		6	86.498	12	349.936	18	902.545	24	1853.943	30	3311.592										
6.397		6	89.741	12	357.585	18	917.928	24	1878.773	30	3348.117										
6.978		6	93.064	12	365.900	18	933.486	24	1903.823	30	3384.909										
7.594		6	96.469	12	374.344	18	949.219	24	1929.094	30	3421.969										
8.244		6	99.955	12	382.916	18	965.127	24	1954.588	30	3459.300										
8.931		6	103.525	12	391.618	18	981.212	24	1980.305	30	3496.900										
9.655		6	107.178	12	400.152	18	997.475	24	2006.249	30	3534.772										
10.417		6	110.917	12	409.417	18	1013.917	24	2032.417	30	3572.917										
11.218		6	114.741	12	418.515	18	1030.538	24	2058.811	30	3611.334										
12.059		6	118.652	12	427.746	18	1047.340	24	2085.434	30	3650.027										
12.941		6	122.652	12	437.113	18	1064.323	24	2112.285	30	3688.994										
13.865		6	126.740	12	446.615	18	1081.490	24	2139.365	30	3728.240										
14.832		6	130.918	12	456.253	18	1098.839	24	2166.676	30	3767.763										
15.843		6	135.186	12	466.030	18	1116.374	24	2194.218	30	3807.561										
16.898		6	139.547	12	475.945	18	1134.094	24	2221.992	30	3847.641										
18.000		6	144.000	12	486.000	18	1152.000	24	2250.000	30	3888.000										

# CARNEGIE STEEL COMPANY

## HOLLOW ROUND SECTIONS

### AREAS AND RADII OF GYRATION



$$\text{Area} = \frac{\pi(D^2 - d^2)}{4} = 0.7854 (D^2 - d^2) \text{ sq. in.}$$

$$\text{Radius of gyration} = \frac{\sqrt{D^2 + d^2}}{4} \text{ in.}$$

Dia. Inches	Element	Thickness in Inches																	
		1/16	1/8	3/16	1/4	5/16	3/8	7/16	1/2	9/16	5/8	3/4	7/8	1	1 1/16	1 1/8	1 1/4	1 3/8	1 1/2
2	A	1.37	1.66																
	r	0.63	0.61																
3	A	2.16	2.64																
	r	0.98	0.96																
4	A	2.95	3.62	4.27	5.50														
	r	1.33	1.31	1.29	1.25														
5	A	3.73	4.60	5.45	7.07	8.59	10.01												
	r	1.88	1.69	1.64	1.60	1.56	1.50												
6	A	4.52	5.58	6.63	8.64	10.55	12.37	14.09	15.71										
	r	2.03	2.01	1.99	1.95	1.91	1.88	1.84	1.80										
7	A	5.30	6.57	7.80	10.21	12.52	14.73	16.84	18.85	20.76	22.58								
	r	2.59	2.37	2.35	2.30	2.27	2.23	2.19	2.15	2.12	2.08								
8	A	6.09	7.55	8.75	11.78	14.45	17.78	19.57	21.95	24.36	26.51	28.42	30.65						
	r	2.74	2.72	2.70	2.66	2.62	2.58	2.54	2.50	2.46	2.43	2.39	2.36						
9	A	6.87	8.53	10.16	13.35	16.44	19.44	22.39	25.13	27.83	30.43	32.94	35.34	37.65	39.86				
	r	3.09	3.07	3.05	3.01	2.97	2.93	2.89	2.85	2.81	2.78	2.74	2.70	2.67	2.64				
10	A	7.66	9.51	11.34	14.92	18.41	21.79	25.08	28.27	31.37	34.36	37.26	40.06	42.76	45.36	47.86	50.27		
	r	3.45	3.43	3.41	3.36	3.32	3.28	3.24	3.20	3.16	3.13	3.09	3.05	3.02	2.98	2.95	2.92		
11	A	8.44	10.49	12.52	16.49	20.37	24.15	27.83	31.42	34.90	38.29	41.58	44.77	47.86	50.85	53.75	56.55		
	r	3.80	3.78	3.76	3.72	3.67	3.63	3.59	3.55	3.51	3.48	3.44	3.40	3.36	3.33	3.29	3.26		
12	A	9.23	11.47	13.70	18.06	22.33	26.51	30.58	34.56	38.44	41.22	45.90	49.48	52.97	56.35	59.64	62.83		
	r	4.16	4.13	4.11	4.07	4.03	3.99	3.95	3.91	3.87	3.83	3.79	3.75	3.71	3.68	3.64	3.61		
13	A	10.01	12.46	14.87	19.63	24.30	28.86	33.33	37.70	41.97	46.14	50.22	54.19	58.07	61.85	65.53	69.12		
	r	4.51	4.49	4.47	4.42	4.38	4.34	4.30	4.26	4.22	4.18	4.14	4.10	4.06	4.03	3.99	3.95		
14	A	10.80	13.41	16.06	21.21	26.26	31.22	36.08	40.84	45.50	50.07	54.54	58.91	63.18	67.35	71.42	75.40		
	r	4.86	4.84	4.82	4.78	4.73	4.69	4.65	4.61	4.57	4.53	4.49	4.45	4.41	4.38	4.34	4.30		
15	A	11.58	14.42	17.23	22.75	28.23	33.55	38.82	43.98	49.04	54.00	58.86	63.62	68.28	72.85	77.31	81.68		
	r	5.22	5.19	5.17	5.13	5.09	5.05	5.00	4.96	4.92	4.88	4.84	4.80	4.76	4.73	4.69	4.65		
16	A	12.37	15.40	18.41	24.35	30.19	35.93	41.58	47.12	52.55	57.92	63.18	68.33	73.39	78.34	83.20	87.97		
	r	5.57	5.55	5.53	5.48	5.44	5.40	5.36	5.32	5.27	5.23	5.19	5.15	5.11	5.08	5.04	5.00		
17	A	13.16	16.38	19.59	25.92	32.15	38.29	44.33	50.27	56.11	61.85	67.50	73.04	78.49	83.84	89.09	94.25		
	r	5.92	5.90	5.88	5.84	5.79	5.75	5.71	5.67	5.63	5.59	5.55	5.51	5.47	5.43	5.39	5.35		
18	A	13.94	17.36	20.76	27.49	34.12	40.64	47.07	53.41	59.64	65.78	71.82	77.75	83.60	89.34	94.98	100.53		
	r	6.28	6.25	6.23	6.19	6.15	6.10	6.06	6.02	5.98	5.94	5.90	5.86	5.82	5.78	5.74	5.70		
19	A	14.73	18.35	21.94	29.06	36.08	43.00	49.82	56.55	63.18	69.70	76.13	82.47	88.70	94.84	100.87	106.82		
	r	6.63	6.61	6.58	6.54	6.50	6.46	6.42	6.37	6.33	6.29	6.25	6.21	6.17	6.13	6.09	6.05		
20	A	15.51	19.33	23.12	30.63	38.04	45.36	52.57	59.69	66.71	73.63	80.45	87.18	93.81	100.33	106.77	113.10		
	r	6.98	6.96	6.94	6.90	6.85	6.81	6.77	6.73	6.69	6.64	6.60	6.56	6.52	6.48	6.44	6.40		

# ELEMENTS OF SECTIONS

## HOLLOW SQUARE SECTIONS

### AREAS AND RADII OF GYRATION





$$\text{Area} = D^2 - d^2 \text{ sq. in.}$$

$$\text{Radius of gyration} = \sqrt{\frac{D^2 + d^2}{12}} \text{ in.}$$

Side D, Inches	Elements	Thickness, t, Inches																
		1/4	5/16	3/8	1/2	5/8	3/4	7/8	1	1 1/8	1 1/4	1 5/8	1 3/4	1 7/8	2	2 1/4	2 1/2	2 3/4
2	A	1.75	2.11															
	r	.72	.70															
3	A	2.75	3.36															
	r	1.13	1.10															
4	A	3.75	4.61	5.44	7.00													
	r	1.53	1.51	1.49	1.44													
5	A	4.75	5.86	6.94	9.00	10.94	12.75											
	r	1.94	1.92	1.89	1.85	1.80	1.76											
6	A	5.75	7.11	8.44	11.00	13.44	15.75	17.94	20.00									
	r	2.35	2.33	2.30	2.25	2.21	2.17	2.12	2.08									
7	A	6.75	8.36	9.94	13.00	15.94	18.75	21.44	24.00	26.44	28.75							
	r	2.76	2.73	2.71	2.66	2.62	2.57	2.53	2.48	2.44	2.40							
8	A	7.75	9.61	11.44	15.00	18.44	21.75	24.94	28.00	30.94	33.75	36.44	39.00					
	r	3.17	3.14	3.12	3.07	3.02	2.98	2.93	2.89	2.84	2.80	2.76	2.72					
9	A	8.75	10.86	12.94	17.00	20.94	24.75	28.44	32.00	35.44	38.75	41.94	45.00	47.94	50.75			
	r	3.57	3.55	3.53	3.48	3.43	3.38	3.34	3.29	3.25	3.20	3.16	3.12	3.08	3.05			
10	A	9.75	12.11	14.44	19.00	23.44	27.75	31.94	36.00	39.94	43.75	47.44	51.00	54.44	57.75	60.94	64.00	
	r	3.98	3.96	3.93	3.88	3.84	3.79	3.74	3.70	3.65	3.61	3.57	3.52	3.48	3.44	3.40	3.37	
11	A	10.75	13.36	15.94	21.00	25.94	30.75	35.44	40.00	44.44	48.75	52.94	57.00	60.94	64.75	68.44	72.00	
	r	4.39	4.37	4.34	4.29	4.24	4.20	4.15	4.10	4.06	4.01	3.97	3.93	3.88	3.84	3.80	3.76	
12	A	11.75	14.61	17.44	23.00	28.44	33.75	38.94	44.00	48.94	53.75	58.44	63.00	67.44	71.75	75.94	80.00	
	r	4.80	4.77	4.75	4.70	4.65	4.60	4.56	4.51	4.46	4.42	4.37	4.33	4.29	4.25	4.20	4.16	
13	A	12.75	15.86	18.94	25.00	30.94	36.75	42.44	48.00	53.44	58.75	63.94	69.00	73.94	78.75	83.44	88.00	
	r	5.21	5.18	5.16	5.11	5.06	5.01	4.96	4.92	4.87	4.82	4.78	4.74	4.69	4.65	4.61	4.56	
14	A	13.75	17.11	20.44	27.00	33.44	39.75	45.94	52.00	57.94	63.75	69.44	75.00	80.44	85.75	90.94	96.00	
	r	5.61	5.59	5.56	5.51	5.47	5.42	5.37	5.32	5.28	5.23	5.18	5.14	5.10	5.05	5.01	4.97	
15	A	14.75	18.36	21.94	29.00	35.94	42.75	49.44	56.00	62.44	68.75	74.94	81.00	86.94	92.75	98.44	104.00	
	r	6.02	6.00	5.97	5.92	5.87	5.83	5.78	5.73	5.68	5.64	5.59	5.55	5.50	5.46	5.41	5.37	
16	A	15.75	19.61	23.44	31.00	38.44	45.75	52.94	60.00	66.94	73.75	80.44	87.00	93.44	99.75	105.94	112.00	
	r	6.43	6.41	6.38	6.33	6.28	6.23	6.19	6.14	6.09	6.04	6.00	5.95	5.91	5.86	5.82	5.77	
17	A	16.75	20.86	24.94	33.00	40.94	48.75	56.44	64.00	71.44	78.75	85.94	93.00	99.94	106.75	113.44	120.00	
	r	6.84	6.81	6.79	6.74	6.69	6.64	6.59	6.54	6.50	6.45	6.40	6.36	6.31	6.27	6.23	6.18	
18	A	17.75	22.11	26.44	35.00	43.44	51.75	59.94	68.00	75.94	83.75	91.44	99.00	106.44	113.75	120.94	128.00	
	r	7.25	7.22	7.20	7.15	7.10	7.05	7.00	6.95	6.90	6.86	6.81	6.76	6.72	6.67	6.63	6.58	
19	A	18.75	23.36	27.94	37.00	45.94	54.75	63.44	72.00	80.44	88.75	96.94	105.00	112.94	120.75	128.44	136.00	
	r	7.66	7.63	7.61	7.56	7.51	7.46	7.41	7.36	7.31	7.26	7.22	7.17	7.12	7.08	7.03	6.99	
20	A	19.75	24.61	29.44	39.00	48.44	57.75	66.94	76.00	84.94	93.75	102.44	111.00	119.44	127.75	135.94	144.00	
	r	8.06	8.04	8.01	7.96	7.91	7.87	7.82	7.77	7.72	7.67	7.62	7.58	7.53	7.49	7.44	7.39	

# CARNEGIE STEEL COMPANY

## RADI OF GYRATION FOR TWO EQUAL ANGLES



Single Angle	Weight, Pounds per Foot	Two Angles Area, Inches <sup>2</sup>	Radii of Gyration, Inches					
			Axis 1-1	In Contact	1/4" Apart	3/8" Apart	1/2" Apart	3/4" Apart
8 x 8 x 1 1/8	56.9	33.46	2.42	3.42	3.51	3.55	3.60	3.69
8 x 8 x 1 1/4	42.0	24.68	2.46	3.37	3.46	3.50	3.55	3.64
8 x 8 x 1 1/2	26.4	15.50	2.51	3.33	3.41	3.45	3.50	3.59
6 x 6 x 1	37.4	22.00	1.80	2.59	2.68	2.72	2.77	2.87
6 x 6 x 1 1/8	26.5	15.56	1.83	2.54	2.63	2.67	2.71	2.81
6 x 6 x 1 1/4	14.9	8.72	1.88	2.49	2.58	2.62	2.66	2.75
5 x 5 x 1	30.6	18.00	1.48	2.19	2.28	2.33	2.38	2.47
5 x 5 x 1 1/8	21.8	12.80	1.51	2.13	2.22	2.26	2.31	2.40
5 x 5 x 1 1/4	12.3	7.22	1.56	2.09	2.17	2.21	2.26	2.35
4 x 4 x 1 1/8	19.9	11.68	1.18	1.75	1.85	1.89	1.94	2.04
4 x 4 x 1 1/4	6.6	3.88	1.25	1.66	1.75	1.79	1.84	1.93
3 1/2 x 3 1/2 x 1 1/8	17.1	10.06	1.02	1.55	1.65	1.70	1.75	1.85
3 1/2 x 3 1/2 x 1 1/4	5.8	3.38	1.09	1.46	1.55	1.59	1.64	1.73
3 x 3 x 5/8	11.5	6.72	0.88	1.32	1.41	1.46	1.51	1.61
3 x 3 x 3/4	4.9	2.88	0.93	1.25	1.34	1.38	1.43	1.53
2 1/2 x 2 1/2 x 1 1/8	7.7	4.50	0.74	1.09	1.19	1.24	1.29	1.39
2 1/2 x 2 1/2 x 1 1/4	4.1	2.38	0.77	1.05	1.14	1.19	1.24	1.34
2 x 2 x 5/8	5.3	3.12	0.59	0.88	0.98	1.03	1.08	1.19
2 x 2 x 3/4	3.19	1.88	0.61	0.85	0.94	0.99	1.04	1.14

This table and the two following are employed in computing the safe resistance to compressive stress of two angles, back to back, used as a strut or as the compression chord of a roof truss, etc., as follows:

Obtain from the compression formula in use the allowed stress per square inch corresponding to the ratio of slenderness of the section, and multiply that value by the area. The result will be the allowable compressive stress.

Example 1. Section given. Required the safe load in compression as per formula  $f = 19000 - 100 l/r$  on a strut composed of two angles  $4'' \times 4'' \times 1/4''$ , back to back, with an unsupported length of 9 feet.

Area of Section,  $A = 3.88$  square inches; Least Radius,  $r = 1.25$ .

Ratio of Slenderness,  $l/r = 9 \times 12 : 1.25 = 86.4$ .

Allowed Unit Stress,  $f = 19000 - 100 \times 86.4 = 10360$  pounds per square inch.

Safe Load,  $Af = 3.88 \times 10360 = 40200$  pounds.

Example 2. Stress given. Required a section for a member in compression  $12' 3''$  long, made of two angles separated by  $1/2$  inch gusset plates, to resist a total stress of 35000 pounds; ratio of slenderness not to exceed 120.

Assume 2 angles,  $5'' \times 3'' \times 5/16''$ , long legs, back to back.

Area of Section,  $A = 4.80$  square inches; Least Radius,  $r = 1.26$  inches.

Ratio of Slenderness,  $l/r = 12.25 \times 12 : 1.26 = 116.7$ .

Allowed Unit Stress,  $f = 19000 - 100 \times 116.7 = 7330$  pounds per square inch.



Safe Stress,  $Af = 4.80 \times 7330 = 35200$  pounds.

In the first case the least radius is that about axis 1-1; in the second case about axis 2-2; in all cases the least radius determines the ratio of slenderness and therewith the allowed safe compressive stress. In all cases also the two angles are to be secured together by stay rivets so spaced as to insure that the section acts as a unit. The ratio of slenderness of any single angle between rivets must always be less than that of the strut or compression chord.

# ELEMENTS OF SECTIONS

## RADI OF GYRATION FOR TWO UNEQUAL ANGLES

Long Legs Vertical





Single Angle		Two Angles	Radii of Gyration, Inches						
Size, Inches	Weight, Pounds per Foot		Axis 1-1		Axis 2-2				
		Area, Inches <sup>2</sup>		In Contact	1/4" Apart	3/8" Apart	1/2" Apart	3/4" Apart	1" Apart
8 x 6 x 1/2	44.2	26.00	2.49	2.39	2.48	2.52	2.57	2.66	
8 x 6 x 3/4	33.8	19.88	2.53	2.35	2.44	2.48	2.52	2.61	
8 x 6 x 1	20.2	11.86	2.57	2.31	2.39	2.43	2.48	2.56	
8 x 3 1/2 x 1	35.7	21.00	2.51	1.26	1.35	1.40	1.45	1.55	
8 x 3 1/2 x 3/4	27.5	16.12	2.55	1.20	1.29	1.34	1.39	1.49	
8 x 3 1/2 x 1/2	16.5	9.68	2.59	1.15	1.23	1.28	1.32	1.41	
7 x 3 1/2 x 1	32.3	19.00	2.19	1.31	1.40	1.45	1.50	1.60	
7 x 3 1/2 x 3/4	23.0	13.50	2.23	1.25	1.34	1.39	1.44	1.53	
7 x 3 1/2 x 1/2	13.0	7.60	2.27	1.20	1.28	1.33	1.37	1.46	
6 x 4 x 1	30.6	18.00	1.85	1.60	1.69	1.74	1.79	1.89	
6 x 4 x 3/4	21.8	12.80	1.89	1.55	1.63	1.68	1.73	1.82	
6 x 4 x 1/2	12.3	7.22	1.93	1.50	1.58	1.62	1.67	1.76	
6 x 3 1/2 x 1	28.9	17.00	1.85	1.37	1.47	1.51	1.56	1.66	
6 x 3 1/2 x 3/4	20.6	12.12	1.89	1.31	1.41	1.45	1.49	1.60	
6 x 3 1/2 x 1/2	9.8	5.74	1.95	1.25	1.33	1.37	1.42	1.50	
5 x 4 x 1	24.2	14.22	1.52	1.66	1.76	1.80	1.85	1.95	
5 x 4 x 3/4	17.0	6.46	1.59	1.58	1.66	1.70	1.75	1.85	
5 x 3 1/2 x 1	22.7	13.34	1.53	1.42	1.51	1.56	1.61	1.71	
5 x 3 1/2 x 3/4	8.7	5.12	1.61	1.33	1.41	1.45	1.50	1.59	
5 x 3 x 1 1/4	19.9	11.68	1.55	1.18	1.27	1.32	1.37	1.47	
5 x 3 x 1 1/2	8.2	4.80	1.61	1.09	1.17	1.22	1.26	1.35	
4 1/2 x 3 x 1 1/4	18.5	10.86	1.38	1.21	1.31	1.36	1.41	1.51	
4 1/2 x 3 x 1 1/2	7.7	4.50	1.44	1.13	1.22	1.26	1.30	1.40	
4 x 3 1/2 x 1 1/4	18.5	10.86	1.19	1.50	1.59	1.64	1.69	1.79	
4 x 3 1/2 x 1 1/2	7.7	4.50	1.26	1.42	1.51	1.55	1.60	1.69	
4 x 3 x 1 1/4	17.1	10.06	1.21	1.25	1.35	1.40	1.45	1.55	
4 x 3 x 1 1/2	5.8	3.38	1.28	1.16	1.24	1.28	1.33	1.43	
3 1/2 x 3 x 1 1/4	15.8	9.24	1.04	1.30	1.40	1.45	1.50	1.60	
3 1/2 x 3 x 1 1/2	5.4	3.12	1.11	1.20	1.29	1.34	1.38	1.48	
3 1/2 x 2 1/2 x 1 1/4	12.5	7.30	1.06	1.03	1.13	1.18	1.23	1.33	
3 1/2 x 2 1/2 x 1 1/2	4.9	2.88	1.12	0.95	1.04	1.09	1.13	1.23	
3 x 2 1/2 x 1 1/4	9.5	5.56	0.91	1.05	1.15	1.20	1.25	1.35	
3 x 2 1/2 x 1 1/2	4.5	2.64	0.95	1.00	1.09	1.13	1.18	1.28	
3 x 2 x 1 1/4	7.7	4.50	0.92	0.80	0.89	0.94	1.00	1.10	
3 x 2 x 1 1/2	4.1	2.38	0.95	0.74	0.84	0.88	0.93	1.03	
2 1/2 x 2 x 1 1/4	6.8	4.00	0.75	0.84	0.94	0.99	1.04	1.15	
2 1/2 x 2 x 1 1/2	3.62	2.12	0.78	0.80	0.89	0.93	0.98	1.08	



# CARNEGIE STEEL COMPANY

## RADI OF GYRATION FOR TWO UNEQUAL ANGLES

### Short Legs Vertical



Single Angle		Two Angles		Radii of Gyration, Inches					
Size, Inches	Weight, Pounds per Foot	Area, Inches <sup>2</sup>	Axis 1-1	In Contact	Axis 2-2	$\frac{1}{4}''$ Apart	$\frac{3}{8}''$ Apart	$\frac{1}{2}''$ Apart	$\frac{3}{4}''$ Apart
8 x 6 x $\frac{1}{2}$	44.2	26.00	1.73	3.64	3.73	3.78	3.83	3.92	
8 x 6 x $\frac{3}{4}$	33.8	19.88	1.76	3.60	3.69	3.73	3.78	3.87	
8 x 6 x 1	20.2	11.86	1.80	3.55	3.64	3.68	3.73	3.82	
8 x 3 $\frac{1}{2}$ x 1	35.7	21.00	0.86	4.04	4.14	4.19	4.24	4.34	
8 x 3 $\frac{1}{2}$ x $\frac{3}{4}$	27.5	16.12	0.88	3.99	4.09	4.13	4.18	4.28	
8 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	16.5	9.68	0.92	3.93	4.02	4.07	4.12	4.22	
7 x 3 $\frac{1}{2}$ x 1	32.3	19.00	0.89	3.48	3.58	3.63	3.68	3.78	
7 x 3 $\frac{1}{2}$ x $\frac{3}{4}$	23.0	13.50	0.92	3.42	3.52	3.57	3.62	3.72	
7 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	13.0	7.60	0.96	3.36	3.46	3.50	3.55	3.65	
6 x 4 x 1	30.6	18.00	1.09	2.85	2.95	2.99	3.04	3.14	
6 x 4 x $\frac{3}{4}$	21.8	12.80	1.13	2.79	2.89	2.93	2.98	3.08	
6 x 4 x $\frac{1}{2}$	12.3	7.22	1.17	2.74	2.83	2.87	2.92	3.02	
6 x 3 $\frac{1}{2}$ x 1	28.9	17.00	0.92	2.92	3.02	3.07	3.12	3.22	
6 x 3 $\frac{1}{2}$ x $\frac{3}{4}$	20.6	12.12	0.95	2.87	2.96	3.01	3.06	3.16	
6 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	9.8	5.74	1.00	2.81	2.90	2.95	3.00	3.09	
5 x 4 x $\frac{3}{4}$	24.2	14.22	1.14	2.29	2.38	2.43	2.48	2.58	
5 x 4 x $\frac{1}{2}$	11.0	6.46	1.20	2.20	2.29	2.34	2.38	2.48	
5 x 3 $\frac{1}{2}$ x $\frac{3}{4}$	22.7	13.34	0.96	2.36	2.45	2.50	2.55	2.65	
5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	8.7	5.12	1.03	2.26	2.35	2.39	2.44	2.54	
5 x 3 x $\frac{3}{4}$	19.9	11.68	0.80	2.42	2.52	2.57	2.62	2.72	
5 x 3 x $\frac{1}{2}$	8.2	4.80	0.85	2.33	2.42	2.47	2.52	2.61	
4 $\frac{1}{2}$ x 3 x $\frac{3}{4}$	18.5	10.86	0.81	2.15	2.25	2.30	2.35	2.45	
4 $\frac{1}{2}$ x 3 x $\frac{1}{2}$	7.7	4.50	0.87	2.06	2.15	2.20	2.25	2.34	
4 x 3 $\frac{1}{2}$ x $\frac{3}{4}$	18.5	10.86	1.01	1.81	1.91	1.96	2.01	2.11	
4 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	7.7	4.50	1.07	1.73	1.81	1.86	1.91	2.00	
4 x 3 x $\frac{3}{4}$	17.1	10.06	0.83	1.88	1.98	2.03	2.08	2.18	
4 x 3 x $\frac{1}{2}$	5.8	3.38	0.89	1.78	1.87	1.92	1.96	2.06	
3 $\frac{1}{2}$ x 3 x $\frac{3}{4}$	15.8	9.24	0.85	1.61	1.71	1.76	1.81	1.91	
3 $\frac{1}{2}$ x 3 x $\frac{1}{2}$	5.4	3.12	0.91	1.52	1.61	1.65	1.70	1.80	
3 $\frac{1}{2}$ x 2 $\frac{1}{2}$ x $\frac{3}{4}$	12.5	7.30	0.69	1.66	1.75	1.80	1.86	1.96	
3 $\frac{1}{2}$ x 2 $\frac{1}{2}$ x $\frac{1}{2}$	4.9	2.88	0.74	1.58	1.67	1.71	1.76	1.86	
3 x 2 $\frac{1}{2}$ x $\frac{3}{4}$	9.5	5.56	0.72	1.37	1.46	1.51	1.56	1.66	
3 x 2 $\frac{1}{2}$ x $\frac{1}{2}$	4.5	2.64	0.75	1.31	1.40	1.45	1.50	1.59	
3 x 2 x $\frac{3}{4}$	7.7	4.50	0.55	1.42	1.52	1.57	1.62	1.72	
3 x 2 x $\frac{1}{2}$	4.1	2.38	0.57	1.38	1.47	1.52	1.57	1.67	
2 $\frac{1}{2}$ x 2 x $\frac{3}{4}$	6.8	4.00	0.56	1.15	1.25	1.30	1.35	1.46	
2 $\frac{1}{2}$ x 2 x $\frac{1}{2}$	3.62	2.12	0.59	1.11	1.20	1.25	1.30	1.40	

## FLEXURE FORMULAS

### STRESSES IN BEAMS

In the application of the principles of structural mechanics to determine what sections should be used safely to sustain superimposed loads under specified conditions of loading, it is necessary to ascertain, first, the effects produced on the structure by the loads under those conditions; second, to decide what unit strength the material, the use of which is contemplated, has to resist the stresses produced within the structure by the loading; and, third, to select a section whose section modulus is equivalent to the ratio found to exist between the stresses tending to cause deformation within the structure and the unit strength of the material to resist them.

**Reactions.** In the simple case of a beam supported at both ends, each support reacts with an upward pressure called the reaction of the support. The sum of these two reactions is equal to the total load on the beam.

**Shear.** The loads and the reactions of the supports are vertical forces tending to shear or cut the beam across and the stresses they produce within the beam are, therefore, called shearing stresses. The shear at each support is equal to the reaction of the support; the shear at any point between the supports is equal to the reaction of a support less the total load between that support and the point; or, if the reaction acting upward is considered as positive and the loads, acting downwards, as negative, the shear at any point is the algebraic sum of the vertical forces acting on the beam between that point and either support.

If such a simple beam supported at both ends carries a load uniformly distributed over its entire length, the reaction and the shear at each support is equal to one-half the total load on the beam, but the shear decreases uniformly to zero at the center of the span; if the load is concentrated at the center of the span, the reaction and the shear at each support are also equal to one-half the total load, but the shear is uniform throughout the entire length of the beam.

**Bending Moment.** The loads on the beam and the reactions of the supports constitute external forces which produce bending stress in the beam. The summation of the moments of the external forces about any point is called the bending moment and varies from point to point. It attains a maximum value at a point where the shear is either zero or changes from positive to negative or vice versa. If the loads are concentrated at several points, the maximum bending moment always occurs at the point of application of

## CARNEGIE STEEL COMPANY

one of the loads so located that the sum of all the loads on the beam between one support up to and including that load is equal to or greater than the reaction of the support.

**Vertical Deflection.** Bending stress within a beam produces flexure, and the deflection, or the amount of its departure from a straight line, is the measure of the deformation which the beam has undergone in its resistance to bending stress. So long as the stress is within the safe limits allowed for the material, the deflection is negligible so far as concerns the beam itself; it may, however, be of sufficient magnitude to cause the disruption of other materials in contact with or supported by the beam but of less strength, such as plaster. In such cases the limit of allowable deflection may determine or at least influence the choice of a section.

**Lateral Deflection.** The stresses within a beam under transverse loading are compressive on one side of the neutral axis and tensile on the other. The tensile stresses tend to hold the beam in a straight line between the supports, while the compressive stresses tend to deflect it in a lateral direction, just as the bending stresses as a whole tend to deflect it in a vertical plane. On long spans unsupported against sidewise deflection, this consideration may influence the choice of sections.

**Method of Computation.** A complete investigation of the strength of beams under transverse loading must take into account all the elements, the bending moment, the vertical deflection, the lateral deflection and the shearing stress; though under the usual loading conditions the first alone determines the size and weight of section.

In the calculation of bending stresses, the loads are usually expressed in pounds, the span length and the distance between the loads in feet; the resulting bending moments are in terms of foot pounds, which necessitates conversion to inch pounds before the section can be selected from the tables. The section modulus of the required section is obtained by dividing the maximum bending moment in inch pounds by the allowed fiber stress in pounds per square inch. In such calculations it is assumed that the neutral axis of the section is normal to the line of action of the load. When this is not the case, correction must be made for the eccentricity of the loading.


In the pages which immediately follow are given general formulas for the bending moments and vertical deflections of beams under the usual conditions of loading, and also diagrams illustrative of those conditions. The general method for the computation of the maximum bending moment of a beam supported at its ends and loaded at various points is as follows:—

## FLEXURE FORMULAS

First. Find the reaction at the left (right) support by multiplying each load by its distance from the right (left) support and dividing the sum of these products by the length of the span.

Second. Starting from the left (right) end of the beam, add the successive loads until a point is reached where the sum of the loads equals or exceeds the reaction of the left (right) support; the point of maximum bending moment is located at this point.

Third. Multiply the reaction at the left (right) support by its distance from the point of maximum bending moment and subtract the sum of the products of all loads to the left (right) of this point by the corresponding distance from this point; the difference between these moments is then the maximum bending moment.

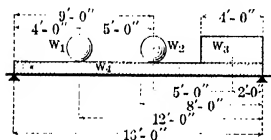

Example: Required the size of a steel beam to support the following quiescent loads over a clear span of 16 feet between supports, at a maximum fiber stress not to exceed 16000 pounds per square inch.

$W_1 = 16000$  pounds, 4 feet from left support.

$W_2 = 18000$  " " " " " "

$W_3 = 2000$  " " per foot, uniform up to 4 feet from right support.

$W_4 = 60$  " " " " assumed weight of beam uniformly distributed over entire span.

$$\text{Left Reaction, } \frac{16000 \times 12 + (60 \times 16)8 + 18000 \times 7 + (2000 \times 4) \times 2}{16} = 21355 \text{ lbs.}$$

$$\text{Right Reaction, } \frac{16000 \times 4 + (60 \times 16)8 + 18000 \times 9 + (2000 \times 4) \times 14}{16} = 21605 \text{ lbs.}$$

$$\text{Sum of reactions} = \text{sum of loads} = W_1 + W_2 + W_3 + W_4 = 212960 \text{ lbs.}$$

$$\text{Points of maximum moment } (60 \times 4) + 16000 = 16240 < 21355$$

$$(60 \times 9) + 16000 + 18000 = 34510 > 21355$$

therefore the point of maximum bending moment is at point of load  $W_2$ .

$$\text{Maximum bending moment, } 21355 \times 9 - 16000 \times 5 - (60 \times 9) \times 4.5 = 109765 \text{ ft. lbs.}$$

$$\text{or, } 21605 \times 7 - (2000 \times 4) \times 5 - (60 \times 7) \times 3.5 = 109765 \text{ ft. lbs.}$$

$$\text{Required section modulus} = \frac{109765 \times 12}{16000} = \frac{1317180}{16000} = 82.4$$

As the section modulus of the 15 inch 65 pound or the 18 inch 55 pound beam is greater than this, either of these sections may be used. If it is decided that the 18 inch 46 pound supplementary beam is strong enough for the purpose, the actual fiber stress on that section would be  $\frac{1317180}{81.5} = 16162$  pounds per square inch. If the allowed fiber stress were 12500 pounds per square inch, the required section modulus would be  $\frac{109765 \times 12}{12500} = \frac{1317180}{12500} = 105.38$  and the permissible minimum sections would be 20 inch 65 pound, 21 inch 57.5 pound beams, etc.

# CARNEGIE STEEL COMPANY

## NOTATION USED IN FORMULAS

- A** ==Area of section, in square inches.  
**n** ==Distance from center line of gravity to extreme fiber, in inches.  
**I** ==Moment of inertia about center line of gravity, in inches<sup>4</sup>.  
**M<sub>s</sub>**==Static moment, in inches<sup>3</sup>.  
**S** ==Section modulus= $I/n$ , in inches<sup>3</sup>.  
**r** ==Radius of gyration= $\sqrt{I/A}$ , in inches.  
**f** ==Bending stress in extreme fiber, in pounds per square inch.  
**f<sub>b</sub>** ==Resistance of web, in pounds per square inch.  
**E** ==Modulus of elasticity, in pounds per square inch.  
**L** ==Length of section, in feet.  
**l** ==Length of section, in inches.  
**d** ==Depth of section, in inches.  
**b** ==Width of section, in inches.  
**t** ==Thickness of section, in inches.  
**W, W<sub>1</sub>, W<sub>2</sub>**==Superimposed loads supported by beam, in pounds.  
**w** ==Superimposed load, in pounds per unit length or area.  
**W max** ==Maximum safe load at point given, in pounds.  
**R, R<sub>1</sub>** ==Reactions at points of support, in pounds.  
**V** ==Vertical shear, in pounds.  
**M, M<sub>1</sub>, M<sub>2</sub>**==Bending moments at points given, in inch pounds.  
**M max** ==Maximum bending moment, in inch pounds.  
**M<sub>r</sub>** ==Maximum resisting moment, in inch pounds= $f I/n = f S$ .  
**D, D<sub>1</sub>** ==Deflections at points given, in inches.  
**D max** ==Maximum deflection at point given, in inches.

## FLEXURE FORMULAS

### COMPARISON OF VARIOUS LOADING CONDITIONS

The formulas and diagrams on pages 202 to 205 give the various stresses in sections used as beams, resulting from usual conditions of loading.

Taking as a unit of comparison a uniformly distributed safe load on beams of equal length and section, supported at the extreme ends, the following table gives the relative maximum safe loads or bending moments and deflections.


As a check on the accuracy of a computation, the safe load obtained from the formula for any condition of loading may be multiplied by the reciprocal given in the table corresponding to such loading condition; the result should be the maximum allowable uniform load as taken from beam safe load tables.

Conditions of Loading	Case No.	Maximum Safe Load		Maximum Deflection
		Relative	Reciprocal	Relative
BEAM SUPPORTED AT ENDS				
Load uniformly distributed over span	IX	1	1	1
Load concentrated at center of span	V	$\frac{1}{2}$	2	.80
Two equal loads symmetrically concentrated	VII	$1/4a$	$4a/1$	
Load increasing uniformly to one end	X	.9743	1.0264	.976
Load increasing uniformly to center	XII	$\frac{3}{4}$	$1\frac{1}{3}$	.96
Load decreasing uniformly to center	XI	$\frac{3}{2}$	$\frac{2}{3}$	1.08
BEAM FIXED AT ONE END, CANTILEVER				
Load uniformly distributed over span	II	$\frac{1}{2}$	4	2.40
Load concentrated at end	I	$\frac{1}{8}$	8	3.20
Load increasing uniformly to fixed end	III	$\frac{3}{8}$	$2\frac{2}{3}$	1.92
BEAM CONTINUOUS OVER TWO SUPPORTS EQUIDISTANT FROM ENDS				
Load uniformly distributed over span	XVI			
1. If distance $a > 0.2071 l$		$l^2/4a^2$	$4a^2/l^2$	
2. If distance $a < 0.2071 l$		$\frac{1}{4a}$	$\frac{4a}{1}$	
3. If distance $a = 0.2071 l$		5.8285	.1716	
Two equal loads concentrated at ends	XV	$1/4a$	$4a/1$	

# CARNEGIE STEEL COMPANY


## BEAMS UNDER VARIOUS LOADING CONDITIONS BENDING MOMENTS AND DEFLECTIONS

### I. CANTILEVER BEAM—Concentrated load at free end




$$\begin{aligned} R_1 (\text{max. shear}) &= W \\ M, \text{ distance } x &= Wx \\ M \text{ max. at } R_1 &= \frac{Wl}{1} \\ W \text{ max.} &= \frac{fS}{1} \\ D \text{ max.} &= \frac{Wl^3}{3EI} \end{aligned}$$

### II. CANTILEVER BEAM—Uniformly distributed load




$$\begin{aligned} R_1 (\text{max. shear}) &= W \\ M, \text{ distance } x &= \frac{Wx^2}{2l} \\ M \text{ max. at } R_1 &= \frac{Wl}{2} \\ W \text{ max.} &= \frac{2fS}{1} \\ D \text{ max.} &= \frac{Wl^3}{8EI} \end{aligned}$$

### III. CANTILEVER BEAM—Load increasing uniformly to fixed end



$$\begin{aligned} R_1 (\text{max. shear}) &= W \\ M, \text{ distance } x &= \frac{W}{3} \cdot \frac{x^3}{l^2} \\ M \text{ max. at } R_1 &= \frac{Wl}{3} \\ W \text{ max.} &= \frac{3fS}{1} \\ D \text{ max.} &= \frac{Wl^3}{15EI} \end{aligned}$$

### IV. BEAM SUPPORTED AT ENDS—Concentrated load near one end




$$\begin{aligned} R (\text{max. shear if } b > a) &= \frac{Wb}{l} \\ R_1 (\text{max. shear if } a > b) &= \frac{Wa}{l} \\ M, \text{ distance } x &= \frac{Wbx}{l} \\ M \text{ max., at point of load} &= \frac{Wab}{l} \\ W \text{ max.} &= \frac{fS}{ab} \\ D \text{ max.} &= \frac{Wab(a+2b)\sqrt{3a(a+2b)}}{27EI} \end{aligned}$$

## FLEXURE FORMULAS

### BEAMS UNDER VARIOUS LOADING CONDITIONS


#### BENDING MOMENTS AND DEFLECTIONS

##### V. BEAM SUPPORTED AT ENDS—Concentrated load at center




$$\begin{aligned} M_{\max} R (\max. \text{ shear}) &= R_1 = \frac{W}{2} \\ M, \text{ distance } x &= \frac{Wx}{2} \\ M_{\max.}, \text{ at point of load} &= \frac{Wl}{4} \\ W_{\max.} &= \frac{4fS}{l} \\ D_{\max.} &= \frac{Wl^3}{48EI} \end{aligned}$$

##### VI. BEAM SUPPORTED AT ENDS—Two unsymmetrical concentrated loads




$$\begin{aligned} R (\max. \text{ shear if } a < b) &= \frac{W}{2l}(l-a+b) \\ R_1 &= \frac{W}{2l}(l+a-b) \\ M, \text{ distance } a &= Ra = \frac{Wa}{2l}(l-a+b) \\ M_1 \max., \text{ distance } b (b > a) &= R_1 b = \frac{Wb}{2l}(l+a-b) \\ M_2, \text{ distance } x &= Rx = \frac{W}{2}(x-a) \\ W_{\max.} (b > a) &= \frac{2fS}{b(l+a-b)} \end{aligned}$$

##### VII. BEAM SUPPORTED AT ENDS—Two symmetrical concentrated loads



$$\begin{aligned} M_{\max} R (\max. \text{ shear}) &= R_1 = \frac{W}{2} \\ M, \text{ distance } x &= \frac{Wx}{2} \\ M_{\max.} \text{ at and between loads} &= \frac{Wa}{2} \\ W_{\max.} &= \frac{2fS}{a} \\ D_{\max.} &= \frac{Wa}{12EI} (3l^2 - 4a^2) \end{aligned}$$

##### VIII. BEAM SUPPORTED AT ENDS—Three concentrated loads



$$\begin{aligned} R &= \frac{Wb + W_1b_1 + W_2b_2}{l} \\ R_1 &= \frac{Wa + W_1a_1 + W_2a_2}{l} \\ M \text{ at } W &= Ra \\ M_{\max.} \text{ if } W &= \text{or } > R \\ M \text{ at } W_1 &= Ra_1 - W(a_1 - a) \\ M_{\max.} \text{ if } W_1 + W &= R \text{ or } > R \\ M_{\max.} \text{ if } W_1 + W_2 &= R_1 \text{ or } > R_1 \\ M \text{ at } W_2 &= Ra_2 - W(a_2 - a) - W_1(a_2 - a_1) \\ M_{\max.} \text{ if } W_2 &= R_1 \text{ or } > R_1 \end{aligned}$$




# CARNEGIE STEEL COMPANY

## BEAMS UNDER VARIOUS LOADING CONDITIONS


### BENDING MOMENTS AND DEFLECTIONS

#### IX. BEAM SUPPORTED AT ENDS—Uniformly distributed load




$$\begin{aligned} R(\text{max. shear}) &= R_1 = \frac{W}{2} \\ M, \text{ distance } x &= \frac{Wx}{2} \left(1 - \frac{x}{l}\right) \\ M \text{ max. at center} &= \frac{Wl}{8} \\ W \text{ max.} &= \frac{8fs}{l} \\ D \text{ max.} &= \frac{5Wl^3}{384EI} \end{aligned}$$

#### X BEAM SUPPORTED AT ENDS—Load increasing uniformly to one end




$$\begin{aligned} R &= \frac{W}{3} \\ R_1(\text{max. shear}) &= \frac{2W}{3} \\ M, \text{ distance } x &= \frac{Wx}{3} \left(1 - \frac{x^2}{l^2}\right) \\ M \text{ max., distance } \frac{l\sqrt{3}}{3} &= \frac{2Wl}{9\sqrt{3}} \\ W \text{ max.} &= \frac{27fs}{2l\sqrt{3}} \\ D \text{ max.} &= \frac{.013044 Wl^3}{EI} \end{aligned}$$

#### XI. BEAM SUPPORTED AT ENDS—Load decreasing uniformly to center



$$\begin{aligned} R(\text{max. shear}) &= R_1 = \frac{W}{2} \\ M, \text{ distance } x &= Wx \left(\frac{1}{2} - \frac{x}{l} + \frac{2x^2}{3l^2}\right) \\ M \text{ max., distance } \frac{l}{2} &= \frac{Wl}{12} \\ W \text{ max.} &= \frac{12fs}{l} \\ D \text{ max.} &= \frac{3Wl^3}{320EI} \end{aligned}$$

#### XII. BEAM SUPPORTED AT ENDS—Load increasing uniformly to center




$$\begin{aligned} R(\text{max. shear}) &= R_1 = \frac{W}{2} \\ M, \text{ distance } x &= Wx \left(\frac{1}{2} - \frac{2x^2}{3l^2}\right) \\ M \text{ max., distance } \frac{l}{2} &= \frac{Wl}{6} \\ W \text{ max.} &= \frac{6fs}{l} \\ D \text{ max.} &= \frac{Wl^3}{60EI} \end{aligned}$$

## FLEXURE FORMULAS

### BEAMS UNDER VARIOUS LOADING CONDITIONS


#### BENDING MOMENTS AND DEFLECTIONS—Concluded

#### XIII. BEAM SUPPORTED AT ENDS—Uniform load partially distributed




$$\begin{aligned}
 R \text{ (max. shear if } a < c) &= \frac{W(2c + b)}{2l} \\
 R_1 &= \frac{W(2a + b)}{2l} \\
 M_1 \text{ (dist. } x = a \text{ or } < a, &= Rx \\
 M_1 \text{ (dist. } x > a, &= Rx - \frac{W(x - a)^2}{2b} \\
 M_2 \text{ (dist. } x > (a + b), &= Rx - \frac{W(2x - 2a - b)}{2} \\
 M \text{ max., dist. } a + \frac{Rb}{W}, &= \frac{W(2c + b)[4al + b(2c + b)]}{8l^2} \\
 W \text{ max.} &= \frac{8l^2 f_s}{(2c + b)[4al + b(2c + b)]}
 \end{aligned}$$

#### XIV. BEAM SUPPORTED AT ENDS—Uniform load partially discontinuous




$$\begin{aligned}
 R \text{ (max. shear if } W_1 > W_2) &= \frac{W(2l - a) + W_1 c}{2l} \\
 R_1 &= \frac{W_1(2l - c) + W a}{2l} \\
 M_1 \text{ distance } x < a, &= Rx - \frac{Wx^2}{2a} \\
 M_1 \text{ distance } x > a, &= Rx - \frac{W(2x - a)}{2} \\
 M \text{ max., dist. } x &= \frac{2Wal - Wa^2 + W_1 ca}{2Wl} \quad \& \quad W a < W_1 c \\
 &= \frac{R_1^2 a}{2W} \\
 W \text{ max.} &= \frac{R_1^2 a}{2l f_s}
 \end{aligned}$$

#### XV. BEAM CONTINUOUS OVER TWO SUPPORTS—Two exterior symmetrical loads



$$\begin{aligned}
 R \text{ (max. shear)} &= R_1 = \frac{W}{2} \\
 M_1 \text{ distance } x &= \frac{Wx}{2} \\
 M \text{ max., from } R \text{ to } R_1 &= \frac{Wa}{2} \\
 W \text{ max.} &= \frac{2f_s l}{a} \\
 D, \text{ distance } a &= \frac{Wa(3al - 4a^2)}{l^2 EI} \\
 D_1, \text{ distance } \frac{1}{2}l - a &= \frac{Wa(l - 2a)^2}{16EI}
 \end{aligned}$$

#### XVI. BEAM CONTINUOUS OVER TWO SUPPORTS—Uniformly distributed load



$$\begin{aligned}
 R &= R_1 = \frac{W}{2} \\
 M_1 \text{ (dist. } x &= \frac{W(x^2 - lx + al)}{2l} \quad \text{or, if } x = \frac{l}{2} \sqrt{\frac{l(1-4a)}{4}} \\
 M_1 \text{ at Rand } R_1 &= \frac{Wa^2}{2l} \quad \text{max. if } a > l(\sqrt{\frac{1}{4}} - \frac{1}{2}) \\
 M_2 \text{ at center} &= \frac{W(l - 4a)}{8} \quad \text{max. if } a < l(\sqrt{\frac{1}{4}} - \frac{1}{2}) \\
 W_1 \text{ max.} &= \frac{2lf_s}{a^2} \quad \text{max. if } a > l(\sqrt{\frac{1}{4}} - \frac{1}{2}) \\
 W_2 \text{ max.} &= \frac{8f_s}{1 - 4a} \quad \text{max. if } a < l(\sqrt{\frac{1}{4}} - \frac{1}{2})
 \end{aligned}$$

## CARNEGIE STEEL COMPANY

### SAFE LOADS FOR SECTIONS USED AS BEAMS

#### EXPLANATION OF TABLES

The tables of safe loads for structural and supplementary beams, I-beams, cross tie sections and channels, used as beams under conditions of transverse loading, give the uniformly distributed safe loads in thousands of pounds for spans customary in bridge and building construction based upon an extreme fiber stress of 6,000 pounds per square inch. The tables of safe loads for angles, tees and zees give the values at the same fiber stress on spans of one foot from which the safe load for any span length may be obtained by direct division and also the values for those spans at which the allowed safe load will produce a deflection of  $\frac{1}{360}$  of the span length. The loads in all cases include the weight of the section, which should be deducted in order to arrive at the net load which the section will support.

In addition to these usual tables of safe loads, there follow, on the same basis, tables of the allowable uniform load in pounds per foot on beams and channels for various span lengths, which may be used in proportioning the floor systems of buildings. The choice between various weights and depths of sections for any given span or any uniform load per running foot may be made on inspection.

It is assumed in all cases that the loads are applied normal to the axis I-I as shown in the tables of elements of sections, and that the beam deflects vertically in the plane of bending only. If the conditions of loading involve the introduction of forces outside this plane of loading, the allowable safe loads must be determined from the general theory of flexure in accordance with the mode of application of the load and its character. This applies particularly to unsymmetrical sections, such as zee bars and angles, which should be used only under those conditions of loading where the section can deflect vertically only, being rigidly secured against lateral deflection or twisting throughout the entire span. In all such cases of eccentric loading, the actual safe loads would be considerably lower than the tabulated safe loads which have been based upon the most favorable conditions of loading.

**Vertical Deflection of Beams.** In the case of beams intended to carry plastered ceilings, experience indicates that the vertical deflection to avoid cracking the plaster should be limited to not more than  $\frac{1}{360}$  of the span length. This span limit for steel beams is approximately in feet twice the depth in inches and is indicated in the tables by the lower zigzag line. Beams intended for such purposes

# BEAM SAFE LOADS

should not be used for greater spans unless the allowable tabular safe load exceeds the actual load to be supported. As the dead load of the floor is supported by the beams before the plaster is applied, only the deflection due to the live load really needs to be considered.

The coefficients given below may be used to obtain the deflection, in inches, of sections subjected to transverse stresses due to uniformly distributed loads at various fiber stresses and are based upon the following formulas, using the notation given on page 200,

$$\text{Deflection, } D = \frac{Wl^3}{76.8EI}, \text{ when } W = \frac{Sfl}{n} \text{ or } D = \frac{Sfl^3}{76.8En} = \frac{15fl^3}{E} \times \frac{1}{n}$$

$$\text{For symmetrical sections, } n = \frac{d}{2}, D = \frac{30fl^3}{E} \times \frac{1}{d} = \frac{\text{Coefficient}}{\text{depth in inches}}$$

## COEFFICIENTS OF DEFLECTION UNIFORMLY DISTRIBUTED LOADS

Span, Feet	Fiber Stress, Pounds per Square Inch			Span, Feet	Fiber Stress, Pounds per Square Inch		
	16000	14000	12500		16000	14000	12500
1	0.017	0.014	0.013	26	11.189	9.790	8.741
2	0.066	0.058	0.052	27	12.066	10.558	9.427
3	0.149	0.130	0.116	28	12.977	11.354	10.138
4	0.265	0.232	0.207	29	13.920	12.180	10.875
5	0.414	0.362	0.323	30	14.897	13.034	11.638
6	0.596	0.521	0.466	31	15.906	13.918	12.427
7	0.811	0.710	0.634	32	16.949	14.830	13.241
8	1.059	0.927	0.828	33	18.025	15.772	14.082
9	1.341	1.173	1.047	34	19.134	16.742	14.948
10	1.655	1.448	1.293	35	20.276	17.741	15.841
11	2.003	1.752	1.565	36	21.451	18.770	16.759
12	2.383	2.086	1.862	37	22.659	19.827	17.703
13	2.797	2.448	2.185	38	23.901	20.913	18.672
14	3.244	2.839	2.534	39	25.175	22.028	19.668
15	3.724	3.259	2.909	40	26.483	23.172	20.690
16	4.237	3.708	3.310	41	27.823	24.346	21.737
17	4.783	4.186	3.737	42	29.197	25.548	22.810
18	5.363	4.692	4.190	43	30.604	26.779	23.909
19	5.975	5.228	4.668	44	32.044	28.039	25.034
20	6.621	5.793	5.172	45	33.517	29.328	26.185
21	7.299	6.387	5.703	46	35.023	30.646	27.362
22	8.011	7.010	6.259	47	36.562	31.992	28.565
23	8.756	7.661	6.841	48	38.135	33.368	29.793
24	9.534	8.342	7.448	49	39.741	34.773	31.047
25	10.345	9.052	8.082	50	41.379	36.207	32.328

To find the deflection in inches of a section symmetrical about the neutral axis, such as beams, channels, zees, etc., divide the coefficient in the table corresponding to given span and fiber stress by the depth of the section in inches.

## CARNEGIE STEEL COMPANY

To find the deflection in inches of a section not symmetrical about the neutral axis, such as angles, tees, etc., divide the coefficient corresponding to given span and fiber stress by twice the distance of extreme fiber from neutral axis obtained from table of elements of sections, pages 170 to 189, inclusive.

To find the deflection in inches of a section for any other fiber stress than those given, multiply this fiber stress by any of the coefficients in the table for the given span and divide by the fiber stress corresponding to the coefficient used.

**Lateral Deflection of Beams.** The tabular safe loads are based on the assumption that the compression flanges of the various sections are secured against lateral deflection by the use of tie rods or by other means at proper intervals. According to the Construction Specifications, page 156, the lateral unbraced length of beams and girders should not exceed forty times the width of the compression flanges. When the unbraced length exceeds ten times the width, the tabular safe loads should be reduced in accordance with the ratios given in the following table in order to insure that the stresses in the compression flanges should not exceed the allowed safe unit stress:—

Unbraced Length of Span		Allowable Safe Load	Unbraced Length of Span		Allowable Safe Load
5 x flange width		Full tabular load	25 x flange width		71.9% tabular load
10 x " "		" " "	30 x " "		62.5% " "
15 x " "		90.6% tabular load	35 x " "		53.1% " "
20 x " "		81.2% " "	40 x " "		43.8% " "

In addition to this lateral deflection which is induced within the beam by the action of pure bending stresses, lateral deflection may be induced by the thrust of floor arches or other loading acting on an axis perpendicular to the line of principal bending stress. The thrust of these arches should either be neutralized by tie rods, or the safe carrying capacity of the beam should be computed in accordance with the general formulas of flexure to provide for the combined stresses due to the action of both vertical and horizontal forces; that is to say, the safe loads should be figured around both the axes 1-1 and 2-2, and the unit stress computed so as not to exceed 16,000 pounds per square inch.

**Effect of Impact on Stresses.** The formulas upon which the tables of safe loads are based assume all loads to be quiescent or static. The effect of moving loads may be taken care of either by reducing the allowable unit stresses, or else by increasing the theoretical loads. See Construction Specifications, page 154, paragraph 2.

## BEAM SAFE LOADS

When the load is suddenly applied, the resultant stresses are greater than those due to an equal static load. When the load is instantaneously applied, the resultant stresses are double.

When an instantaneously applied load produces impact or percussion, the resultant stresses are dynamic and are measured by the laws governing the energy of bodies in motion. The following empirical formulas may be used to ascertain the approximate fiber stress and deflection due to a load falling on the center of a beam supported at both ends, when no account is taken of the distortion due to the impact or percussion at the point of application of the load:—Let

$W$  =—Weight of load, in pounds.

$W_1$ —Weight of beam, in pounds.

$h$  =—Height of fall, in inches.

$f$  =—Extreme fiber stress due to static load,  $W+W_1$ , in pounds per square inch.

$f_d$  =—Extreme fiber stress due to dynamic load,  $W$ , in pounds per square inch.

$D$  =—Deflection due to static load,  $W+W_1$ , in inches.

$D_d$  =—Deflection due to dynamic load,  $W$ , in inches.

$m = \frac{35 W}{35 W + 17 W_1}$ , Then

$f_d = f \left( 1 + \sqrt{\frac{2mh}{D}} + 1 \right)$  and  $D_d = D + \sqrt{2mhD + D^2}$

**Shearing Stresses.** The safe load tables for beams and channels are computed solely with reference to safe unit stresses due to flexure, and the safe loads uniformly distributed on the spans given will not produce average shearing stresses in the web greater than the 10,000 pounds per square inch allowed by the Construction Specifications. When, however, beams are loaded with heavy loads concentrated near the supports, or when beams of short span are loaded with uniformly distributed loads to their full carrying capacity as regards flexure, the bending moments may be small in comparison with the reactions at the supports, and the beams may fail along the neutral plane as a result of longitudinal shearing stresses, or may buckle as a result of the combined longitudinal and vertical web stresses. On such spans the safe shearing or buckling strength of the web may limit the carrying capacity of the beam rather than the resistance of the flanges to bending stresses.

**Longitudinal Shear.** At any point in any section of a beam, the horizontal and vertical components of the web stress are equal to each other and proportional to the vertical shear; their intensities are


## CARNEGIE STEEL COMPANY

dependent upon the distance of the point from the neutral axis. In order to determine the intensity of the vertical shearing stress at a given point in a vertical section of the beam, therefore, it is sufficient to find the equal intensity of the horizontal shearing stress at the same point in the horizontal plane.

The longitudinal unit shear is zero at the upper and lower flanges of the beam and a maximum at the neutral plane. It is greatest at the supports and zero where there is no vertical shear.

The intensity of the longitudinal shear at any point in any section is the product of the vertical shear,  $V$ , for that section and the statial moment,  $M_s$  of the section included between the horizontal plane of shear through that point and the extreme fibers on the same side of the neutral plane divided by the product of the moment of inertia of the beam around the proper axis and the thickness at the plane of shear; or

$$\text{Longitudinal shear per square inch} = \frac{V M_s}{t I}.$$



**Example**—Required the maximum longitudinal shear per square inch in a 24" 80 lb. beam loaded with two symmetrical loads of 100,000 pounds each, disregarding the weight of the beam.

$$M_s \text{ of Flange Rectangle} = 7 \times .60 \times 11.7 = 49.14$$

$$M_s \text{ of Flange Triangles} = 3.25 \times .542 \times 11.219 = 19.76$$

$$M_s \text{ of Web} = 11.40 \times .50 \times 5.70 = 32.49$$

$$\text{Total Static Moment} = 101.39$$

$$\text{Moment of Inertia of Beam} = 2087.2$$

$$\text{Longitudinal Shear} = \frac{100000 \times 101.39}{2087.2 \times .50}$$

$$= 9715 \text{ pounds per square inch.}$$


Under usual conditions of loading, the vertical shear need not be taken into consideration.

**Buckling Values of Beam Webs.** The vertical shearing stresses or the vertical compressive components of the web stress may under some conditions exceed the safe resistance of the beam to buckling, and there remains the possibility that a web or web plate which is amply secure as against the safe allowed shear of 10,000 pounds per square inch will not be of sufficient strength when considered as a column. In such cases provision must be made for security against buckling either in the way of stiffeners or by increasing the thickness of the web or web plate.

A series of experiments have been carried out on beams of various depths and web thicknesses to arrive at a basis for a simpler method of computation to use in the investigation of the safe buckling

## BEAM SAFE LOADS

resistance of beams with unsupported webs, and from these experiments the following formulas have been deduced:



Safe end reaction  $R = f_b \times t \left( a + \frac{d}{4} \right)$

Safe interior load  $W = 2 f_b \times t \left( a^1 + \frac{d}{4} \right)$

In these formulas  $R$  is the end reaction,  $W$  the concentrated load,  $t$  the web thickness,  $d$  the depth of the beam,  $a^1$  half the distance over which the concentrated load is applied and  $a$  the whole distance over which the end reaction is applied, while  $f_b$  is the safe resistance of the web to buckling in pounds per square inch by the formula  $19000 - 100 d/2r$  ( $d/2 = l$  in column formula).

The first formula is general and applies to any condition of loading. The second formula covers the case of a single load concentrated at the center of a span; it can be extended to cover a system of concentrated loads provided the sum of the distances  $a^1$  is not less than  $a$ .

The tables which immediately follow give for beams and channels with unsupported webs:

1. Allowed web resistance  $f_b$ , in pounds per square inch computed from this compression formula.
2. The distance  $a$ , or the distance over which the end reaction must be distributed when the shearing stress,  $V$ , in the web is the maximum allowable of 10,000 pounds per square inch.
3. The allowable end reaction ( $R$ ) when  $a$  is taken at  $3\frac{1}{2}$ " which is the usual length of beam actually resting on the 4" angles ordinarily used in building construction for beam seats.
4. The allowable shear  $V$ , on the gross area of beam or channel webs at 10,000 pounds per square inch.

In addition to these data which have to do with the maximum loads on beams and channels as computed from the web resistance, these tables also give the maximum bending moments in foot pounds, obtained by the multiplication of the section modulus of each section by the allowed fiber stress of 16,000 pounds and the division of the product by 12 in order to reduce to a foot pound basis. These maximum bending moments may be used on inspection instead of the table of properties to ascertain the proper size section to be used in any particular instance.



## CARNEGIE STEEL COMPANY

### EXAMPLES OF THE USE OF BEAM SAFE LOAD TABLES

**Example 1. Direct Bending.** Required the proper size of a beam laterally braced to support a superimposed or net load of 30,000 pounds uniformly distributed over a clear span of 20 feet.

From the table of safe loads, page 218, it is found that a 15 inch 42 pound beam will support a gross load of 31,400 pounds. The weight of a beam 20 feet long is 810 pounds. The net safe load is, therefore, 31,400 - 810 = 30,590 pounds. A 15 inch 42 pound beam will, therefore, carry the net load specified.

**Example 2. Shear.** Required the maximum load which a 20 inch 85 pound beam can support without exceeding the safe web resistance of the section.

From the table, page 217, the maximum load for this section given in small figures above the upper zigzag line is found to be 265,200 pounds.

**Example 3. Vertical Deflection.** Required the proper size and the deflection of a channel supporting a net load of 10,000 pounds concentrated in the middle of a 14-foot span, assuming that the channel is braced against lateral deflection.

The specified load is equivalent on the given span to a uniformly distributed load of  $2 \times 10,000 = 20,000$  pounds.

In the table, page 226, it is found that a 12 inch 30 pound channel will support a gross load of 20,500 pounds or a net load of 20,500 - 14 x 30 = 20,080 pounds. The net safe load concentrated at the middle of the span will be one-half this or 10,040 pounds.

The deflection produced by a uniformly distributed load of 20,500 pounds is found from the coefficient given in the same table and page 207 to be  $\frac{3.24}{12} = 0.270''$ . The deflection for the specified load concentrated in the middle of the span is approximately  $\frac{0.270 \times \frac{1}{2}}{5} = 0.216''$ . See page 201.

**Example 4. Vertical Deflection.** Required the deflection of a riveted girder 37 inches deep for a span of 35 feet and a fiber stress of 14,000 pounds per square inch.

Required deflection, see table, page 207,  $= \frac{17.741}{37} = 0.479''$ .

**Example 5. Vertical Deflection.** Required the deflection of an angle 6 x 4 x 7/16" about an axis parallel to the short leg for a span of 14 feet and a fiber stress of 16,000 pounds.

Required deflection, see table, pages 207 and 208, is  $\frac{3.244}{2 \times (6 - 1.06)} = 0.401''$ .

**Example 6. Vertical Deflection.** Required the deflection of a 10 inch beam for a span of 18 feet with a fiber stress of 11,000 pounds.

Required deflection, see table, pages 207 and 208,  $= \frac{11,000 \times 5.363}{16,000 \times 10} = 0.369''$ .

**Example 7. Lateral Deflection.** Required the safe load on a 12 inch 31½ pound beam for a span of 16 feet without any lateral support or bracing.

Tabular load, page 219, = 24,000 pounds.

Ratio  $\frac{\text{Length of span}}{\text{Flange width}} = \frac{16 \times 12}{5} = 38.4$

Reduced safe load, page 208,  $24,000 \times 0.468 = 11,232$  pounds.

# BEAM SAFE LOADS

## BEAMS

### MAXIMUM BENDING MOMENTS AND WEB RESISTANCE

M <sub>max</sub>	d	t	V	f <sub>b</sub>	a	R	
Maximum Bending Moment	Depth of Beam	Weight per Foot	Thickness of Web	Allowable Web Shear	Allowable Buckling Resistance	Min. End Bearing	End Reaction a = 30 1/2"
Foot Pounds	Inches	Pounds	Inches	Pounds	Pounds per Sq. In.	Inches	Pounds
292130	27	90.0	.524	141480	10080	20.0	54140
328390		115.0	.750	180000	13460	11.8	95880
320390		110.0	.688	165120	12960	12.5	84690
312390		105.0	.625	150000	12350	13.4	73320
264400		100.0	.751	180060	13190	11.8	96620
256560	24	95.0	.693	166320	13000	12.5	85610
248710		90.0	.631	151440	12410	13.3	74110
240870		85.0	.570	136800	11710	14.5	63410
231920		80.0	.500	120000	10690	16.5	50780
216670		74.0	.476	114210	10260	17.4	46100
156930	21	60.5	.428	89880	10500	11.8	39320
220750		100.0	.884	176800	15080	8.3	113320
214210		95.0	.810	162000	14720	8.6	101370
207680		90.0	.737	147400	14300	9.0	89590
201140	20	85.0	.663	132600	13780	9.5	77630
195510		80.0	.600	120000	13230	10.1	67460
169170		75.0	.649	129800	13660	9.6	75380
162610		70.0	.575	115000	12980	10.4	63420
155930		65.0	.500	100000	12080	11.6	51320
186720		90.0	.807	145260	15110	7.1	97730
180810		85.0	.725	130500	14700	7.7	85260
174960		80.0	.644	115920	14160	8.2	72940
169080		75.0	.562	101160	13450	8.9	60480
136480	18	70.0	.719	129120	14670	7.8	84350
130590		65.0	.637	114660	14110	8.3	71890
124710		60.0	.555	99900	13380	9.0	59420
117860		55.0	.460	82800	12220	10.2	44980
109200		48.0	.380	68400	10800	12.2	32830
122800		75.0	.882	132300	16050	5.6	102660
117980		70.0	.784	117600	15690	5.8	89160
113080		65.0	.686	102900	15210	6.1	75650
108270		60.0	.590	88500	14600	6.5	62440
90850	15	55.0	.656	98400	15040	6.2	71530
85940		50.0	.558	83700	14340	6.7	58020
81040		45.0	.460	69000	13350	7.5	44520
78530		42.0	.410	61500	12670	8.1	37660
72130		37.5	.332	49800	11180	9.7	26910

# CARNEGIE STEEL COMPANY

## BEAMS

### MAXIMUM BENDING MOMENTS AND WEB RESISTANCES

M <sub>max</sub>	d	t	V	f <sub>b</sub>	a	R	
Maximum Bending Moment	Depth of Beam	Weight per Foot	Thickness of Web	Allowable Web Shear	Allowable Buckling Resistance	Min. End Reaction	
Foot Pounds	Inches	Pounds	Inches	Pounds	Pounds per Sq. In.	Inches Pounds	
71330	12	55.0	.821	98520	16470	4.3	87890
67410		50.0	.699	83880	16030	4.5	72830
63490		45.0	.576	69120	15390	4.8	57620
59770		40.0	.460	55200	14480	5.3	43300
50730		35.0	.336	52320	14230	5.4	40330
47960		31.5	.350	42000	13060	6.2	29710
44270	10	28.0	.281	31080	11680	7.3	21560
42320		40.0	.749	74900	16690	3.5	75010
39050		35.0	.602	60200	16120	3.7	58220
35780		30.0	.455	45500	15190	4.1	41470
32560		25.0	.310	31000	13410	5.0	24940
30270		22.25	.252	25200	12130	5.7	18310
33120	9	35.0	.732	65880	16870	3.1	71010
30180		30.0	.569	51210	16260	3.3	53200
27240		25.0	.406	36540	15160	3.7	35390
25160		21.0	.290	26100	13620	4.4	22710
22810	8	25.5	.541	43280	16440	2.9	48920
21500		23.0	.449	35920	15910	3.0	39290
20190		20.5	.357	28560	15120	3.3	26690
18960		18.0	.270	21600	13870	3.8	20600
19470	7	17.5	.220	17600	12700	4.5	15370
16070		20.0	.458	32060	16350	2.5	39310
14930		17.5	.353	21710	15570	2.7	28850
13800		15.0	.250	17500	14150	3.2	18580
11640	6	17.25	.475	28500	16810	2.1	39930
10660		14.75	.352	21120	16050	2.2	28250
9680		12.25	.230	13800	14480	2.6	16650
10260	5	17.0	.380	19000	16720	1.7	30180
8080		14.75	.504	25200	17280	1.6	41370
7260		12.25	.357	17850	16580	1.8	28120
6450		9.75	.210	10500	14870	2.1	14830
4760	4	10.5	.410	16400	17310	1.3	31940
4500		9.5	.337	13480	16940	1.4	25690
4240		8.5	.263	10520	16360	1.4	19360
3980		7.5	.190	7600	15360	1.6	13130
2590	3	7.5	.361	10830	17560	1.0	26940
2390		6.5	.263	7890	17020	1.0	19020
2210		5.5	.170	5100	15950	1.1	11530

# BEAM SAFE LOADS

## CHANNELS

### MAXIMUM BENDING MOMENTS AND WEB RESISTANCES

Mmax	d		t	V	f <sub>b</sub>	a	R
Maximum Bending Moment	Depth of Channel	Weight per Foot	Thickness of Web	Allowable Web Shear	Allowable Buckling Resistance	Min. End Bearing	End Reaction a=3 1/2"
Foot Pounds	Inches	Pounds	Inches	Pounds	Pounds per Sq. In.	Inches	Pounds
76190	15	55.0	.818	122700	15820	5.7	93830
71590		50.0	.720	108000	15390	6.0	80350
66680		45.0	.622	93300	14820	6.4	66840
61780		40.0	.524	78600	14040	6.9	53350
56880		35.0	.426	63900	12900	7.9	39850
55570		33.0	.400	60000	12510	8.2	36270
61360	13	50.0	.791	102830	16150	4.8	86250
60110		45.0	.678	88140	15680	5.0	71760
55870		40.0	.565	73450	15020	5.4	57260
53320		37.0	.497	64610	14470	5.7	48540
51620		35.0	.452	58700	14020	6.0	42770
48740		32.0	.375	48750	13000	6.8	32900
43760	12	40.0	.758	90060	16260	4.4	80090
39840		35.0	.636	76320	15730	4.6	65040
35920		30.0	.513	61560	14950	5.0	49850
32000		25.0	.390	46800	13670	5.8	34660
28470		20.5	.280	33600	11570	7.4	21060
30800	10	35.0	.823	82300	16900	3.4	83430
27530		30.0	.676	67600	16410	3.6	66670
24260		25.0	.529	52900	15750	3.9	49910
20900		20.0	.382	38200	14470	4.4	33160
17840		15.0	.240	24000	11780	6.0	16970
20950	9	25.0	.615	55350	16470	3.2	58220
18010		20.0	.452	40680	15550	3.5	40420
15070		15.0	.288	25920	13590	4.4	22500
14020		13.25	.230	20700	12220	5.1	16170
15920		21.25	.582	46560	16620	2.8	53200
14610	8	18.75	.490	39200	16170	2.9	43580
13310		16.25	.399	31920	15530	3.2	34070
12000		13.75	.307	24560	14490	3.5	24460
10770		11.25	.220	17600	12700	4.3	15370
12640		19.75	.633	44310	17090	2.3	56780
11490	7	17.25	.528	36960	16700	2.4	46300
10350		14.75	.423	29610	16130	2.6	35830
9210		12.25	.318	22260	15190	2.9	25360
8030		9.75	.210	14700	13230	3.5	14580
8680		15.5	.563	33780	17150	2.0	48280
7700	6	13.0	.440	26400	16640	2.1	36610
6720		10.5	.318	19080	15730	2.3	25010
5780		8.0	.200	12000	13810	2.8	13810
5550		11.5	.477	23850	17180	1.7	38920
4730		9.0	.330	16500	16380	1.8	25670
3960	5	6.5	.190	9500	14450	2.2	13040
3050		7.25	.325	13000	16870	1.4	24670
2790		6.25	.252	10080	16250	1.5	18430
2530		5.25	.180	7200	15150	1.6	12270
1840		6.0	.362	10860	17560	1.0	27020
1640	3	5.0	.264	7920	17030	1.0	19110
1450		4.0	.170	5100	15940	1.1	11520

# CARNEGIE STEEL COMPANY

## BEAMS

### MAXIMUM BENDING MOMENTS AND WEB RESISTANCES

M <sub>max</sub>	d	t	V	f <sub>b</sub>	a	R	
Maximum Bending Moment	Depth of Beam	Weight per Foot	Thickness of Web	Allowable Web Shear	Allowable Buckling Resistance	Min. End Reaction	
Foot Pounds	Inches	Pounds	Inches	Pounds	Pounds per Sq. In.	Inches Pounds	
71330	12	55.0	.821	98520	16470	4.3	87890
67410		50.0	.699	83880	16030	4.5	72830
63490		45.0	.576	69120	15390	4.8	57620
59770		40.0	.460	55200	14480	5.3	43300
50730		35.0	.336	52320	14230	5.4	40330
47960		31.5	.350	42000	13060	6.2	29710
44270	10	28.0	.281	31080	11680	7.3	21560
42320		40.0	.749	74900	16690	3.5	75010
39050		35.0	.602	60200	16120	3.7	58220
35780		30.0	.455	45500	15190	4.1	41470
32560		25.0	.310	31000	13410	5.0	24940
30270		22.25	.252	25200	12130	5.7	18310
33120	9	35.0	.732	65880	16870	3.1	71010
30180		30.0	.569	51210	16260	3.3	53200
27240		25.0	.406	36540	15160	3.7	35390
25160		21.0	.290	26100	13620	4.4	22710
22810	8	25.5	.541	43280	16440	2.9	48920
21500		23.0	.449	35920	15910	3.0	39290
20190		20.5	.357	28560	15120	3.3	26690
18960		18.0	.270	21600	13870	3.8	20600
19470	7	17.5	.220	17600	12700	4.5	15370
16070		20.0	.458	32060	16350	2.5	39310
14930		17.5	.353	21710	15570	2.7	28850
13800		15.0	.250	17500	14150	3.2	18580
11640	6	17.25	.475	28500	16810	2.1	39930
10660		14.75	.352	21120	16050	2.2	28250
9680		12.25	.230	13800	14480	2.6	16650
10260	5	17.0	.380	19000	16720	1.7	30180
8080		14.75	.504	25200	17280	1.6	41370
7260		12.25	.357	17850	16580	1.8	28120
6450		9.75	.210	10500	14870	2.1	14830
4760	4	10.5	.410	16400	17310	1.3	31940
4500		9.5	.337	13480	16940	1.4	25690
4240		8.5	.263	10520	16360	1.4	19360
3980		7.5	.190	7600	15360	1.6	13130
2590	3	7.5	.361	10830	17560	1.0	26940
2390		6.5	.263	7890	17020	1.0	19020
2210		5.5	.170	5100	15950	1.1	11530

# BEAM SAFE LOADS

## BEAMS

### ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16,000 Pounds per Square Inch

Depth and Weight of Sections														
Span in Feet	20 Inch								18 Inch					Coefficient of Deflection
	100 lbs.	95 lbs.	90 lbs.	85 lbs.	80 lbs.	75 lbs.	70 lbs.	65 lbs.	90 lbs.	85 lbs.	80 lbs.	75 lbs.		
5	353.6 353.2												0.41	
6	294.3	285.0	276.9	265.2	240.0	225.6	216.8	200.0	249.0	241.1	231.8	202.3	0.60	
7	252.3	244.8	237.7	229.9	223.4	193.3	185.9	178.2	213.4	206.7	200.0	193.2	0.81	
8	220.7	214.2	207.7	201.1	195.5	169.2	162.6	155.9	186.7	180.8	175.0	169.1	1.06	
9	196.2	190.4	184.6	178.8	173.8	150.4	144.6	138.6	166.0	160.7	155.5	150.3	1.34	
10	176.6	171.4	166.1	160.9	156.1	135.3	130.1	124.7	149.4	144.7	140.0	135.5	1.66	
11	160.5	155.8	151.0	146.3	142.2	123.0	118.3	113.4	135.8	131.5	127.2	123.0	2.00	
12	147.2	142.8	138.5	134.1	130.3	112.8	108.4	104.0	124.5	120.6	116.6	112.7	2.38	
13	135.8	131.8	127.8	123.8	120.3	104.1	100.1	96.0	114.9	111.3	107.7	104.1	2.80	
14	126.1	122.4	118.7	114.9	111.7	96.7	92.9	89.1	106.7	103.3	100.0	96.6	3.24	
15	117.7	114.2	110.8	107.3	104.3	90.2	86.7	83.2	99.6	96.4	93.3	90.2	3.72	
16	110.4	107.1	103.8	100.6	97.7	84.6	81.3	78.0	93.4	90.4	87.5	84.5	4.24	
17	103.9	100.8	97.7	94.1	92.0	79.6	76.5	73.4	87.9	85.1	82.3	79.6	4.78	
18	98.1	95.2	92.3	89.4	86.9	76.3	72.3	69.3	83.0	80.4	77.8	75.1	5.36	
19	92.9	90.2	87.4	84.7	82.3	71.2	68.5	65.7	78.6	76.1	73.7	71.2	5.98	
20	88.3	85.7	83.1	80.5	78.2	67.7	65.1	62.4	74.7	72.3	70.0	67.6	6.62	
21	84.1	81.6	79.1	76.6	74.5	64.1	62.0	59.4	71.1	68.9	66.7	64.4	7.30	
22	80.3	77.9	75.5	73.1	71.1	61.5	59.1	56.7	67.9	65.8	63.6	61.5	8.01	
23	76.8	74.5	72.2	70.0	68.0	58.8	56.6	54.2	64.9	62.9	60.9	58.8	8.76	
24	73.6	71.4	69.2	67.0	65.2	56.4	54.2	52.0	62.2	60.3	58.3	56.4	9.53	
25	70.6	68.5	66.5	64.4	62.6	54.1	52.0	49.9	59.8	57.9	56.0	54.1	10.35	
26	67.9	65.9	63.9	61.9	60.2	52.1	50.0	48.0	57.5	55.6	53.8	52.0	11.19	
27	65.4	63.5	61.5	59.6	57.9	50.1	48.2	46.2	55.3	53.6	51.8	50.1	12.07	
28	63.1	61.2	59.3	57.5	55.9	48.3	46.5	44.6	53.3	51.7	50.0	48.3	12.98	
29	60.9	59.1	57.3	55.5	53.9	46.7	44.9	43.0	51.5	49.9	48.3	46.6	13.92	
30	58.9	57.1	55.4	53.6	52.1	45.1	43.4	41.6	49.8	48.2	46.7	45.1	14.90	
31	57.0	55.3	53.6	51.9	50.5	43.7	42.0	40.2	48.2	46.7	45.2	43.6	15.91	
32	55.2	53.6	51.9	50.3	48.9	42.3	40.7	39.0	46.7	45.2	43.7	42.3	16.95	
33	53.5	51.9	50.4	48.8	47.4	41.0	39.4	37.8	45.3	43.8	42.4	41.0	18.03	
34	51.9	50.4	48.9	47.3	46.0	39.8	38.3	36.7	43.9	42.4	41.2	39.8	19.13	
35	50.5	49.0	47.5	46.0	44.7	38.7	37.2	35.6	42.7	41.3	40.0	38.6	20.28	
36	49.1	47.6	46.2	44.7	43.4	37.6	36.1	34.7	41.5	40.2	38.9	37.6	21.45	
37	47.7	46.3	44.9	43.5	42.3	36.6	35.2	33.7	40.4	39.1	37.8	36.6	22.66	
38	46.5	45.1	43.7	42.3	41.2	35.6	34.2	32.8	39.3	38.1	36.8	35.6	23.90	
39	45.3	43.9	42.6	41.3	40.1	34.7	33.4	32.0					25.18	
40	44.1	42.8	41.5	40.2	39.1	33.8	32.5	31.2					26.48	
41													27.82	
42	48.1	46.8	45.6	44.3	43.0	38.1	36.8	35.5	40.4	39.1	37.8	36.6	29.20	

Loads above upper horizontal lines will produce maximum allowable shear in webs.

Loads below lower horizontal lines will produce excessive deflections.

For maximum safe loads, see page 213.

# CARNEGIE STEEL COMPANY

## BEAMS

### ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16,000 Pounds per Square Inch

Span in Feet	Depth and Weight of Sections														Coefficient of Deflection
	18 Inch							15 Inch							
	70 lbs.	65 lbs.	60 lbs.	55 lbs.	48 lbs.	75 lbs.	70 lbs.	65 lbs.	60 lbs.	55 lbs.	50 lbs.	45 lbs.	42 lbs.		
4	258.8	220.8	199.8			204.6	245.8	205.2	205.8	177.0	181.7	167.4	138.0	0.27	
5	218.4	208.9	199.5			196.6	188.8	180.9	173.2	145.4	137.5	129.7		0.41	
6				165.6						196.8					
7	182.0	174.1	166.3	157.1	138.8	163.8	157.3	150.8	144.4	121.1	114.6	108.1	104.7	0.60	
8	156.0	149.2	142.5	134.7	124.8	140.4	134.8	129.2	123.7	103.8	98.2	92.6	89.8	0.81	
9	136.5	130.6	124.7	117.9	109.2	122.9	118.0	113.1	108.3	90.8	85.9	81.0	78.5	1.06	
10	121.3	116.1	110.9	104.8	97.1	109.2	104.9	100.5	96.2	80.8	76.4	72.0	69.8	1.34	
11	109.2	104.5	99.8	94.3	87.4	98.3	94.4	90.5	86.6	72.7	68.8	64.8	62.8	1.66	
12	99.3	95.0	90.7	85.7	79.4	89.4	85.8	82.2	78.7	66.1	62.5	58.9	57.1	2.00	
13	91.0	87.1	83.1	78.6	72.8	81.9	78.7	75.4	72.2	60.6	57.3	54.0	52.4	2.38	
14	84.0	80.4	76.7	72.5	67.2	75.6	72.6	69.6	66.6	55.9	52.9	49.9	48.3	2.80	
15	78.0	74.6	71.3	67.3	62.4	70.2	67.4	64.6	61.9	51.9	49.1	46.3	44.9	3.24	
16	72.8	69.6	66.5	62.9	58.2	65.5	62.9	60.3	57.7	48.5	45.8	43.2	41.9	3.72	
17	68.2	65.3	62.4	58.9	54.6	61.4	59.0	56.5	54.1	45.4	43.0	40.5	39.3	4.24	
18	64.2	61.5	58.7	55.5	51.4	57.8	55.5	53.2	50.9	42.8	40.4	38.1	37.0	4.78	
19	60.7	58.0	55.4	52.4	48.5	54.6	52.4	50.3	48.1	40.4	38.2	36.0	34.9	5.36	
20	57.5	55.0	52.5	49.6	46.0	51.7	49.7	47.6	45.6	38.3	36.2	34.1	33.1	5.98	
21	54.6	52.2	49.9	47.1	43.7	49.2	47.2	45.2	43.3	36.3	34.1	32.1	31.4	6.62	
22	52.0	49.7	47.5	44.9	41.6	46.8	44.9	43.1	41.2	34.6	32.7	30.9	29.9	7.30	
23	49.6	47.5	45.3	42.9	39.7	44.7	42.9	41.1	39.4	33.0	31.3	29.5	28.6	8.01	
24	47.5	45.1	43.4	41.0	38.0	42.7	41.0	39.3	37.7	31.6	29.9	28.2	27.3	8.76	
25	45.5	43.5	41.6	39.3	36.4	41.0	39.3	37.7	36.1	30.3	28.6	27.0	26.2	9.53	
26	43.7	41.8	39.9	37.7	34.9	39.3	37.8	36.2	34.6	29.1	27.5	25.9	25.1	10.35	
27	42.0	40.2	38.4	36.3	33.6	37.8	36.3	34.8	33.3	28.0	26.4	24.9	24.2	11.19	
28	40.4	38.7	37.0	34.9	32.4	36.4	35.0	33.5	32.1	26.9	25.5	24.0	23.3	12.07	
29	39.0	37.3	35.6	33.7	31.2	35.1	33.7	32.3	30.9	26.0	24.6	23.2	22.4	12.98	
30	37.6	36.0	34.4	32.5	30.1	33.9	32.5	31.2	29.9	25.1	23.7	22.4	21.7	13.92	
31	36.4	34.8	33.3	31.4	29.1	32.8	31.5	30.2	28.9	24.2	22.9	21.6	20.9	14.90	
32	35.2	33.7	32.2	30.4	28.2	31.7	30.4	29.2	27.9	23.1	22.2	20.9	20.3	15.91	
33	34.1	32.6	31.2	29.5	27.3	30.7	29.5	28.3	27.1	22.7	21.5	20.3	19.6	16.95	
34	33.1	31.7	30.2	28.6	26.5									18.03	
35	32.1	30.7	29.3	27.7	25.7									19.13	
36	31.2	29.8	28.5	26.9	25.0									20.28	
37	30.3	29.0	27.7	26.2	24.3									21.45	
38	29.5	28.2	27.0	25.5	23.6									22.66	
39	28.7	27.5	26.3	24.8	23.0									23.90	

Loads above upper horizontal lines will produce maximum allowable shear in webs.

Loads below lower horizontal lines will produce excessive deflections.

For maximum safe loads, see page 213.

# BEAM SAFE LOADS

## BEAMS

### ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16,000 Pounds Per Square Inch

Span in Feet	Depth and Weight of Sections													Coefficient of Deflection	
	15In.	12 Inch						10 Inch					25 lbs.		22½ lbs.
	37½ lbs.	55 lbs.	50 lbs.	45 lbs.	40 lbs.	35 lbs.	31½ lbs.	28 lbs.	40 lbs.	35 lbs.	30 lbs.				
3		197.0							149.8	120.4				0.15	
4		130.2	167.8	138.2		104.6			112.8	104.1	91.0			0.27	
5		142.7	134.8	127.0	110.4	101.5	84.0		84.6	78.1	71.0	62.0	50.4	0.41	
		114.1	107.9	101.6	95.6	81.2	76.7		67.7	62.5	57.2	52.1	48.5	0.27	
6	99.6						68.2							0.60	
7	96.1	95.1	89.9	84.7	79.7	67.6	63.9	59.1	56.4	52.1	47.7	43.4	40.4	0.81	
8	82.4	81.5	77.0	72.6	68.3	58.0	54.8	50.6	48.4	44.6	40.9	37.2	34.6	1.06	
9	72.1	71.3	67.4	63.5	59.8	50.7	48.0	44.3	42.3	39.0	35.8	32.6	30.3	1.34	
9	61.1	63.4	59.9	56.4	53.1	45.1	42.6	39.4	37.6	34.7	31.8	28.9	26.9	1.66	
10	57.7	57.1	53.9	50.8	47.8	40.6	38.4	35.5	33.9	31.2	28.6	26.0	24.2	1.66	
11	52.4	51.9	49.0	46.2	43.5	36.9	34.9	32.2	30.8	28.4	26.0	23.7	22.0	2.00	
12	48.1	47.6	44.9	42.3	39.8	33.8	32.0	29.5	28.2	26.0	23.9	21.7	20.2	2.38	
13	44.1	43.9	41.5	39.1	36.8	31.2	29.5	27.3	26.0	24.0	22.0	20.0	18.6	2.80	
14	41.2	40.8	38.5	36.3	34.2	29.0	27.4	25.3	24.2	22.3	20.4	18.6	17.3	3.24	
15	38.4	38.0	36.0	33.9	31.9	27.1	25.6	23.6	22.6	20.8	19.1	17.4	16.2	3.72	
16	36.0	35.7	33.7	31.7	29.9	25.4	24.0	22.2	21.2	19.5	17.9	16.3	15.1	4.24	
17	33.9	33.6	31.7	29.9	28.1	23.9	22.6	20.9	19.9	18.4	16.8	15.3	14.3	4.78	
18	32.0	31.7	30.0	28.2	26.6	22.5	21.3	19.7	18.8	17.4	15.9	14.5	13.5	5.36	
19	30.4	30.1	28.4	26.7	25.2	21.4	20.2	18.7	17.8	16.4	15.1	13.7	12.8	5.98	
20	28.8	28.5	27.0	25.4	23.9	20.3	19.2	17.7	16.9	15.6	14.3	13.0	12.1	6.62	
21	27.5	27.2	25.7	24.2	22.8	19.3	18.3	16.9	16.1	14.9	13.6	12.4	11.5	7.30	
22	26.2	25.9	24.5	23.1	21.7	18.4	17.4	16.1	15.4	14.2	13.0	11.8	11.0	8.01	
23	25.1	24.8	23.4	22.1	20.8	17.6	16.7	15.4						8.76	
24	24.0	23.8	22.5	21.2	19.9	16.9	16.0	14.8						9.53	
25	23.1	22.9	21.6	20.3	19.1	16.2	15.3	14.2						10.35	
26	22.2	21.9	20.7	19.5	18.4	15.6	14.8	13.6						11.19	
27	21.4													12.07	
28	20.6													12.98	
29	19.9													13.92	
30	19.2													14.90	
31	18.6													15.91	
32	18.0													16.95	

Loads above upper horizontal lines will produce maximum allowable shear in webs.

Loads below lower horizontal lines will produce excessive deflections.

For maximum safe loads, see pages 213 and 214.



# CARNEGIE STEEL COMPANY

## BEAMS

### ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16,000 Pounds per Square Inch

Span in Feet	Depth and Weight of Sections												Coefficient of Deflection
	9 Inch				8 Inch				7 Inch				
	35 lbs.	30 lbs.	25 lbs.	21 lbs.	25½ lbs.	23 lbs.	20½ lbs.	18 lbs.	17½ lbs.	20 lbs.	17½ lbs.	15 lbs.	
3	131.8	102.4	73.1		86.6	71.8	57.1			64.1	49.4		0.15
4	88.3	80.5	72.6	62.2	60.8	57.3	53.9	43.2		42.9	39.8	36.0	0.27
5	66.2	60.4	54.5	50.3	45.6	43.0	40.4	37.9	35.2	32.1	29.9	27.6	0.41
6	53.0	48.3	43.6	40.3	36.5	34.4	32.3	30.3	31.1	25.7	23.9	22.1	
7	44.2	40.2	36.3	33.6	30.4	28.7	26.9	25.3	25.9	21.4	19.9	18.4	0.60
8	37.9	34.5	31.1	28.8	26.1	24.6	23.1	21.7	22.2	18.4	17.1	15.8	0.81
9	33.1	30.2	27.2	25.2	22.8	21.5	20.2	19.0	19.5	16.1	14.9	13.8	1.06
10	29.4	26.8	24.2	22.4	20.3	19.1	18.0	16.9	17.3	14.3	13.3	12.3	1.34
11	26.5	24.1	21.8	20.1	18.2	17.2	16.2	15.2	15.6	12.9	11.9	11.0	1.66
12	24.1	22.0	19.8	18.3	16.6	15.6	14.7	13.8	14.2	11.7	10.9	10.0	2.00
13	22.1	20.1	18.2	16.8	15.2	14.3	13.5	12.6	13.0	10.7	10.0	9.2	2.38
14	20.4	18.6	16.8	15.5	14.0	13.2	12.4	11.7	12.0	9.9	9.2	8.5	2.80
15	18.9	17.2	15.6	14.4	13.0	12.3	11.5	10.8	11.1	9.2	8.5	7.9	3.21
16	17.7	16.1	14.5	13.4	12.2	11.5	10.8	10.1	10.4	8.6	8.0	7.4	3.72
17	16.6	15.1	13.6	12.6	11.4	10.8	10.1	9.5	9.7				4.24
18	15.6	14.2	12.8	11.8	10.7	10.1	9.5	9.0	9.2	8.0	7.5	6.9	4.78
19	14.7	13.4	12.1	11.2	10.1	9.6	9.0	8.4	8.6				5.36
20	13.9	12.7	11.5	10.6									5.98
21	13.3	12.1	10.9	10.1									6.62

Span in Feet	Depth and Weight of Sections												Coefficient of Deflection	
	6 Inch			5 Inch			4 Inch			3 Inch				
	17½ lbs.	14½ lbs.	12½ lbs.	14½ lbs.	12½ lbs.	9½ lbs.	10½ lbs.	9½ lbs.	8½ lbs.	7½ lbs.	7½ lbs.	6½ lbs.		5½ lbs.
1	57.0			60.4	35.7		32.8	27.9	21.0		21.7			0.02
2	40.6	42.2	27.6	32.3	29.1	21.0	19.0	18.0	16.9	16.2	10.4	9.6	8.8	0.07
3	31.0	28.4	25.8	21.5	19.4	17.2	12.7	12.0	11.3	10.6	6.9	6.4	5.9	0.15
4	23.3	21.3	19.4	16.2	14.5	12.9	9.5	9.0	8.5	8.0	5.2	4.8	4.4	0.27
5	18.6	17.1	15.5	12.9	11.6	10.3	7.6	7.2	6.8	6.4	4.1	3.8	3.5	0.41
6	15.5	14.2	12.9	10.8	9.7	8.6	6.3	6.0	5.6	5.3	3.5	3.2	2.9	0.60
7	13.3	12.2	11.1	9.2	8.3	7.4	5.4	5.1	4.8	4.5	2.9	2.7	2.5	0.81
8	11.6	10.7	9.7	8.1	7.3	6.4	4.8	4.5	4.2	4.0	2.6	2.4	2.2	1.06
9	10.3	9.5	8.6	7.2	6.5	5.7	4.3	4.0	3.8	3.6				1.34
10	9.3	8.5	7.7	6.5	5.8	5.2	3.8	3.6	3.4	3.2				1.66
11	8.5	7.8	7.0	5.9	5.3	4.7								2.00
12	7.8	7.1	6.5	5.4	4.8	4.3								2.38
13	7.2	6.6	6.0											2.80
14	6.7	6.1	5.5											3.24

Loads above upper horizontal lines will produce maximum allowable shear in webs.

Loads below lower horizontal lines will produce excessive deflections.

For maximum safe loads, see page 211.

# BEAM SAFE LOADS

BEAMS—ALLOWABLE UNIFORM LOAD IN POUNDS PER FOOT

		Span in Feet																							
		10	11	12	13	14	15	16	17	18	19	20	21	22	23	24	25	26	27	28	29	30			
Depth, Inches	Pounds per Foot	90	23340	19290	16210	13810	11910	10370	9120	8080	7200	6470	5840	5290	4820	4410	4050	3730	3450	3200	2980	2800	2590		
		115	26270	21710	18240	15550	13400	11680	10260	9090	8110	7280	6570	5960	5430	4970	4560	4200	3890	3600	3350	3020	2820		
100	25630	21180	17800	15170	13080	11390	10010	8870	7910	7100	6410	5810	5300	4840	4430	4100	3790	3520	3270	2950	2750	2550			
95	24990	20650	17360	14790	12730	11110	9760	8650	7710	6920	6250	5670	5160	4720	4340	4000	3700	3430	3190	2780	2580	2380			
90	24350	20010	16720	14150	12090	10470	9120	8020	7100	6340	5690	5130	4620	4200	3820	3480	3180	2910	2650	2420	2210	2010			
85	23710	19370	16080	13510	11450	9830	8560	7530	6670	5950	5340	4820	4370	3980	3610	3350	3080	2840	2640	2340	2140	1890			
80	23070	18730	15440	12870	10810	9190	7920	6890	6030	5310	4700	4180	3730	3340	3000	2740	2480	2280	2080	1780	1580	1380			
75	22430	18090	14800	12230	10170	8550	7280	6250	5390	4670	4060	3540	3090	2700	2360	2100	1840	1640	1440	1240	1040	840			
70	21790	17450	14160	11590	9530	7910	6640	5610	4750	4030	3420	2900	2450	2060	1720	1460	1260	1060	860	660	460	260			
65	21150	16810	13520	10950	8890	7270	6000	4970	4110	3390	2780	2260	1810	1420	1160	960	760	560	360	160	100	20			
60	20510	16170	12880	10310	8250	6630	5360	4330	3510	2790	2180	1660	1210	820	560	360	160	100	20	10	0	0			
55	19870	15530	12240	9670	7610	5990	4720	3690	2870	2150	1540	1020	570	210	100	20	10	0	0	0	0	0			
50	19230	14890	11600	9030	6970	5350	4080	3050	2230	1510	900	390	130	20	10	0	0	0	0	0	0	0			
45	18590	14250	10960	8390	6330	4710	3440	2410	1590	870	260	100	20	10	0	0	0	0	0	0	0	0			
40	17950	13610	10320	7750	5690	4070	2800	1770	950	200	100	20	10	0	0	0	0	0	0	0	0	0			
35	17310	12970	9680	7110	5050	3430	2160	1130	200	100	20	10	0	0	0	0	0	0	0	0	0	0			
30	16670	12330	8940	6470	4410	2790	1520	500	100	20	10	0	0	0	0	0	0	0	0	0	0	0			
25	16030	11690	8200	5730	3650	2030	800	100	20	10	0	0	0	0	0	0	0	0	0	0	0	0			
20	15390	11050	7460	4990	2910	1310	200	100	20	10	0	0	0	0	0	0	0	0	0	0	0	0			
15	14750	10410	6720	4250	2150	500	100	20	10	0	0	0	0	0	0	0	0	0	0	0	0	0			
10	14110	9770	5480	3590	1000	200	100	20	10	0	0	0	0	0	0	0	0	0	0	0	0	0			
5	13470	9130	4240	2430	200	100	20	10	0	0	0	0	0	0	0	0	0	0	0	0	0	0			
0	12830	8490	3000	1170	100	20	10	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0			

# CARNEGIE STEEL COMPANY

BEAMS—ALLOWABLE UNIFORM LOAD IN POUNDS PER FOOT

Depth, inches	Pounds per foot	Span in Feet																							
		6	7	8	9	10	11	12	13	14	15	16	17	18	19	20	21	22	23	24	25	26			
15	75	27310	200660	153600	121400	98300	81200	68300	58200	50200	43700	38400	34000	30300	27200	24600	22300	20300	18600	17100	15700	14500			
	70	262200	192660	147300	116300	94400	78000	65500	55900	48200	42000	36900	32700	29100	26100	23600	21400	19500	17800	16400	15100	14000			
	65	251300	184660	141400	111700	90500	74800	62800	53200	46200	40200	35300	31300	27900	25100	22600	20500	18700	17100	15700	14500	13400			
	60	240600	176800	133300	106900	86600	71600	60100	51200	44200	38500	33800	30000	26700	24000	21700	19600	17900	16400	15000	13900	12800			
	55	230100	168300	125600	99700	80700	67200	56000	47000	40000	35100	30400	26900	23800	21200	19100	17200	15600	14200	13000	11900	10800			
12	50	191000	140300	107400	84900	68800	56800	47800	40700	35100	30400	26900	23800	21200	19100	17200	15600	14200	13000	11900	10800	10200			
	45	180100	132300	101300	80000	64800	53600	45000	38400	33100	28800	25300	22400	20000	18000	16200	14700	13400	12300	11300	10400	9600			
	42	174500	128200	98200	77600	62800	51900	43800	37200	32100	27900	24500	21700	19400	17400	15700	14300	13000	11900	10900	10100	9300			
	37.5	160200	117700	90100	71300	57700	47700	40100	34100	29400	25600	22500	20000	17800	16000	14400	13100	11900	10900	10000	9200	8500			
	35	158500	116560	89200	70500	57100	47200	39600	33500	29100	25400	22300	19800	17600	15800	14300	12900	11800	10800	9900	9100	8400			
10	55	149500	110100	84300	66800	53900	44600	37300	31900	27300	24000	21100	18700	16600	14900	13300	12200	11100	10200	9400	8600	8000			
	50	141100	103700	79400	62700	50800	42000	35300	30100	25900	22600	19800	17600	15700	14100	12700	11500	10500	9600	8800	8100	7500			
	45	132500	97600	74700	59000	47800	39500	33200	28300	24400	21300	18700	16500	14600	13200	12000	10800	9900	9000	8300	7700	7100			
	40	112700	82800	63400	50100	40800	33500	28200	24000	20700	18000	15800	14000	12500	11200	10200	9300	8400	7700	7000	6500	6000			
	35	106600	78300	60000	47400	38400	31700	26400	22700	19600	17100	15000	13300	11800	10600	9600	8700	7900	7300	6700	6100	5700			
9	28	98500	72400	55400	43800	35500	29300	24600	21000	18100	15800	13900	12300	10900	9800	8900	8000	7300	6700	6100	5700	5200			
	40	94000	69100	52900	41800	33900	28000	23500	20000	17300	15000	13200	11700	10400	9400	8500	7700	7000	Loads within heavy horizontal lines are maximum loads for web shear. Loads below dotted horizontal lines will produce excessive deflection.						
	35	86800	63800	48800	38600	31200	25800	21700	18300	15900	13900	12200	10800	9600	8700	7800	7100	6500							
	30	79500	58400	44700	35300	28600	23700	20000	16900	14600	12700	11200	9900	8800	7900	7200	6600	5900							
	25	72400	53200	40700	32200	26100	21500	18100	15400	13300	11600	10200	9000	8000	7300	6700	6100	5400							
22.25	67300	49500	37900	29900	24200	20000	16800	14300	12400	10800	9500	8400	7500	6700	6100	5500									

Loads within heavy horizontal lines are maximum loads for web shear.  
Loads below dotted horizontal lines will produce excessive deflection.

# BEAM SAFE LOADS

BEAMS—ALLOWABLE UNIFORM LOAD IN POUNDS PER FOOT

Depth, Inches	Pounds per Foot	Span in Feet																					
		2	2½	3	3½	4	4½	5	5½	6	6½	7	8	9	10	11	12	13	14	15	16	17	18
25.5	43280	29200	20280	14900	11410	9010	7300	6030	5070	4320	3720	2850	2250	1830	1510	1270	1080	930	810	710	630	560	
23.	35920	27320	19110	14040	10750	8490	6880	5690	4780	4070	3510	2690	2120	1720	1420	1190	1020	880	760	670	600	530	
20.5	28560	22840	17950	13190	10100	7980	6460	5340	4490	3820	3300	2520	1990	1620	1340	1120	960	820	720	630	560	500	
18.	21600	17280	14400	12340	9480	7490	6070	5010	4210	3590	3100	2370	1870	1520	1250	1050	900	770	670	590	530	470	
17.5	17600	14080	11730	10060	8060	6350	5140	4250	3570	3040	2620	2010	1590	1290	1060	890	760	660	570	500			
20.	32000	20570	14280	10490	8040	6350	5140	4250	3570	3040	2620	2010	1590	1290	1060	890	760	660	570	500			
7	17.5	24710	19100	13270	9750	7400	5900	4780	3950	3320	2830	2440	1870	1470	1190	990	830	710	610	530	470		
15.	17500	11000	11700	9010	6900	5450	4420	3650	3070	2610	2250	1730	1360	1100	910	770	650	560	490	430			
17.25	22280	14900	10350	7600	5820	4600	3720	3080	2590	2200	1900	1450	1150	930	770	650	530	480					
6	14.75	21120	13650	9470	6960	5330	4210	3410	2820	2370	2020	1740	1330	1050	850	700	590	500	440				
12.25	13800	11040	8610	6320	4840	3830	3100	2560	2150	1830	1580	1210	960	780	640	540	460	400					
14.75	16100	10340	7180	5280	4040	3190	2590	2140	1800	1530	1320	1010	800	650	530	450							
12.25	14530	9300	6460	4740	3630	2870	2320	1920	1610	1380	1190	910	720	580	480	400							
9.75	10500	8250	5730	4210	3220	2550	2000	1710	1430	1220	1050	810	640	520	430	360							
10.5	9520	6990	4230	3110	2380	1880	1520	1260	1060	900	780	590	470	380									
9.5	9000	5700	4000	2940	2250	1780	1440	1190	1000	850	730	560	440	360									
8.5	8470	5420	3770	2770	2120	1670	1360	1120	940	800	690	530	420	340									
7.5	7600	5090	3530	2600	1990	1570	1270	1050	880	750	650	500	390	320									
7.5	5180	3310	2300	1690	1290	1020	830	680	580	490	420												
3	4.75	3060	2130	1560	1200	940	770	630	530	450	390												
5.5	4410	2820	1960	1440	1100	870	710	580	490	420	360												

Loads within heavy horizontal lines are maximum loads for web shear.

Loads below dotted horizontal lines will produce excessive deflection.

Loads within heavy horizontal lines are maximum loads for web shear.  
Loads below dotted, horizontal lines will produce excessive deflection.

# CARNEGIE STEEL COMPANY

## MISCELLANEOUS BEAMS

ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16,000 Pounds per Square Inch

### II BEAMS

Span in Feet	Depth and Weight of Sections				Coefficients of Deflection
	8 Inch 34.0 Pounds	6 Inch 23.8 Pounds	5 Inch 18.7 Pounds	4 Inch 13.6 Pounds	
3				26.0	0.15
4		37.6	31.3	19.0	0.27
5		32.1	20.3	14.3	0.41
6	60.0			11.4	
7	51.3	26.7	16.9	9.5	0.60
8	44.0	22.9	14.5	8.1	0.81
9	38.5	20.1	12.7	7.1	1.06
10	34.2	17.8	11.3	6.3	1.34
	30.8	16.0	10.1	5.7	1.66
11	28.0	14.6	9.2		2.00
12	25.6	13.4	8.5		2.38
13	23.7	12.3			2.80
14	22.0	11.5			3.24
15	20.5				3.72
16	19.2				4.24
17	18.1				4.78
18	17.1				5.36

### CROSS TIE SECTIONS

Span in Feet	Depth and Weight of Sections					Coefficients of Deflection
	6.5 Inch 27.8 Pounds	5.5 Inch 23.5 Pounds	5.5 Inch 20.0 Pounds	4.25 Inch 14.5 Pounds	3 Inch 9.5 Pounds	
3		41.8		21.3	12.2	0.15
4	40.6	40.3	27.5	19.6	8.9	0.27
5	38.2	30.2	26.0	14.7	6.7	0.41
	30.6	24.2	20.8	11.8	5.4	
6	25.5	20.2	17.3	9.8	4.5	0.60
7	21.8	17.3	14.8	8.4	3.8	0.81
8	19.1	15.1	13.0	7.3	3.3	1.06
9	17.0	13.4	11.5	6.5	3.0	1.34
10	15.3	12.1	10.4	5.9	2.7	1.66
11	13.9	11.0	9.4	5.3		2.00
12	12.7	10.1	8.7			2.38
13	11.8	9.3	8.0			2.80
14	10.9	8.6	7.4			3.24
15	10.2					3.72
16	9.5					4.24
17	9.0					4.78

Loads above upper horizontal lines will produce maximum allowable shear in webs.  
Loads below lower horizontal lines will produce excessive deflections.

# BEAM SAFE LOADS

## CHANNELS

ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16,000 Pounds per Square Inch

Span in Feet	Depth and Weight of Sections												Coefficient of Deflection
	15 Inch						13 Inch						
	55 lbs.	50 lbs.	45 lbs.	40 lbs.	35 lbs.	33 lbs.	50 lbs.	45 lbs.	40 lbs.	37 lbs.	35 lbs.	32 lbs.	
	245.4	216.0	186.6				206.7	176.3					
3	204.0	190.9	177.8	167.2	127.8	120.0	171.6	160.3	146.9	129.2	117.5	97.5	0.15
4	153.0	143.2	133.4	123.6	113.8	111.1	128.7	120.2	111.7	106.6	103.2	97.5	0.27
5	122.4	114.5	106.7	98.9	91.0	88.9	103.0	96.2	89.1	85.3	82.6	78.0	0.41
6	102.0	95.1	88.9	82.4	75.8	71.1	85.8	80.2	74.5	71.1	68.8	65.0	0.60
7	87.4	81.8	76.2	70.6	65.0	63.5	73.6	68.7	63.8	60.9	59.0	55.7	0.81
8	76.5	71.6	66.7	61.8	56.9	55.6	64.4	60.1	55.9	53.3	51.6	48.7	1.06
9	68.0	63.6	59.3	54.9	50.6	49.4	57.2	53.4	49.7	47.1	45.9	43.3	1.34
10	61.2	57.3	53.3	49.4	45.5	44.5	51.5	48.1	44.7	42.7	41.3	39.0	1.66
11	55.6	52.1	48.5	44.9	41.4	40.1	46.8	43.7	40.6	38.8	37.5	35.4	2.00
12	51.0	47.7	44.5	41.2	37.9	37.0	42.9	40.1	37.2	35.5	34.1	32.5	2.38
13	47.1	44.1	41.0	38.0	35.0	34.2	39.6	37.0	34.4	32.8	31.8	30.0	2.80
14	43.7	40.9	38.1	35.3	32.5	31.8	36.8	34.1	31.9	30.5	29.5	27.9	3.24
15	40.8	38.2	35.6	33.0	30.3	29.6	34.3	32.1	29.8	28.4	27.5	26.0	3.72
16	38.2	35.8	33.3	30.9	28.4	27.8	32.2	30.1	27.9	26.7	25.8	24.4	4.24
17	36.0	33.7	31.4	29.1	26.8	26.1	30.3	28.3	26.3	25.1	24.3	22.9	4.78
18	34.0	31.8	29.6	27.5	25.3	24.7	28.6	26.7	24.8	23.7	22.9	21.7	5.36
19	32.2	30.1	28.1	26.0	23.9	23.1	27.1	25.3	23.5	22.4	21.7	20.5	5.98
20	30.6	28.6	26.7	24.7	22.8	22.3	25.7	24.0	22.3	21.3	20.6	19.5	6.62
21	29.1	27.3	25.4	23.5	21.7	21.2	24.5	22.9	21.3	20.3	19.7	18.6	7.30
22	27.8	26.0	24.3	22.5	20.7	20.2	23.4	21.9	20.3	19.4	18.8	17.7	8.01
23	26.6	24.9	23.2	21.5	19.8	19.3	22.4	20.9	19.4	18.5	18.0	17.0	8.76
24	25.5	23.9	22.2	20.6	19.0	18.5	21.5	20.0	18.6	17.8	17.2	16.2	9.53
25	24.5	22.9	21.3	19.8	18.2	17.8	20.6	19.2	17.9	17.1	16.5	15.6	10.35
26	23.5	22.0	20.5	19.0	17.5	17.1	19.8	18.5	17.2	16.4	15.9	15.0	11.19
27	22.7	21.2	19.8	18.3	16.9	16.5	19.1	17.8	16.6	15.8	15.3	14.4	12.07
28	21.9	20.5	19.1	17.7	16.3	15.9	18.4	17.2	16.0	15.2	14.7	13.9	12.98
29	21.1	19.7	18.4	17.0	15.7	15.3							13.92
30	20.4	19.1	17.8	16.5	15.2	14.8							14.90
31	19.7	18.5	17.2	15.9	14.7	14.3							15.91
32	19.1	17.9	16.7	15.4	14.2	13.9							16.95

Loads above upper horizontal lines will produce maximum allowable shear in webs.

Loads below lower horizontal lines will produce excessive deflections.

For maximum safe loads, see page 215.



# CARNEGIE STEEL COMPANY

## CHANNELS

### ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16,000 Pounds per Square Inch

Depth and Weight of Sections												Coefficient of Deflection
Span in Feet	12 Inch					10 Inch						
	40 lbs.	35 lbs.	30 lbs.	25 lbs.	20½ lbs.	35 lbs.	30 lbs.	25 lbs.	20 lbs.	15 lbs.		
	181.9	162.6	123.1	93.6	67.2	164.6	135.2	106.8	76.4	48.0		
2	175.1	156.4	119.1	88.6	62.9	123.2	110.1	97.0	76.4	48.0	0.07	
3	116.7	106.2	95.8	85.3	67.2	82.1	73.4	64.7	56.0	47.6	0.15	
4	87.5	79.7	71.8	64.0	56.9	61.6	55.1	48.5	42.0	35.7	0.27	
5	70.0	63.7	57.5	51.2	45.5	49.3	44.0	38.8	33.6	28.5	0.41	
6	58.4	53.1	47.9	42.7	38.0	41.1	36.7	32.3	28.0	23.8	0.60	
7	50.0	45.5	41.1	36.6	32.5	35.2	31.5	27.7	24.0	20.4	0.81	
8	43.8	39.8	35.9	32.0	28.5	30.8	27.5	24.3	21.0	17.8	1.06	
9	38.9	35.4	31.9	28.4	25.3	27.4	24.5	21.6	18.7	15.9	1.34	
10	35.0	31.9	28.7	25.6	22.8	24.6	22.0	19.4	16.8	14.3	1.66	
11	31.8	29.0	26.1	23.3	20.7	22.4	20.0	17.6	15.3	13.0	2.00	
12	29.2	26.6	23.9	21.3	19.0	20.5	18.4	16.2	14.0	11.9	2.38	
13	26.9	24.5	22.1	19.7	17.5	19.0	16.9	14.9	12.9	11.0	2.80	
14	25.0	22.8	20.5	18.3	16.3	17.6	15.7	13.9	12.0	10.2	3.24	
15	23.3	21.2	19.2	17.1	15.2	16.4	14.7	12.9	11.2	9.5	3.72	
16	21.9	19.9	18.0	16.0	14.2	15.4	13.8	12.1	10.5	8.9	4.24	
17	20.6	18.7	16.9	15.1	13.4	14.5	13.0	11.4	9.9	8.4	4.78	
18	19.5	17.7	16.0	14.2	12.7	13.7	12.2	10.8	9.3	7.9	5.36	
19	18.4	16.8	15.1	13.5	12.0	13.0	11.6	10.2	8.8	7.5	5.98	
20	17.5	15.9	14.1	12.8	11.1	12.3	11.0	9.7	8.4	7.1	6.62	
21	16.7	15.2	13.7	12.2	10.8	11.7	10.5	9.2	8.0	6.8	7.30	
22	15.9	14.5	13.1	11.6	10.3	11.2	10.0	8.8	7.6	6.5	8.01	
23	15.2	13.9	12.5	11.1	9.9						8.76	
24	14.6	13.3	12.0	10.7	9.5						9.53	
25	14.0	12.8	11.5	10.2	9.1						10.35	
26	13.5	12.3	11.1	9.8	8.8						11.19	

Loads above upper horizontal lines will produce maximum allowable shear in webs.

Loads below lower horizontal lines will produce excessive deflections.

For maximum safe loads, see page 215.

# BEAM SAFE LOADS

## CHANNELS

### ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16,000 Pounds per Square Inch

Depth and Weight of Sections																	Coefficient of Deflection
Span in Feet	9 Inch					8 Inch					7 Inch						
	25 lbs.	20 lbs.	15 lbs.	13½ lbs.	21½ lbs.	18½ lbs.	16½ lbs.	13½ lbs.	11½ lbs.	19½ lbs.	17½ lbs.	14½ lbs.	12½ lbs.	9½ lbs.			
	110.7	81.4			93.1	78.4	63.8	49.1		88.6	73.9	59.2	44.5				
2	83.8	72.0	61.8	41.4	63.7	58.5	53.2	48.0	36.9	50.6	46.0	41.4	36.8	29.4		0.07	
3	55.9	48.0	40.2	37.1	42.5	39.0	35.5	32.0	28.7	33.7	30.7	27.6	24.6	21.1		0.15	
4	41.9	36.0	30.1	28.0	31.8	29.2	26.6	24.0	21.5	25.3	23.0	20.7	18.4	16.1		0.27	
5	33.5	28.8	24.1	22.4	25.5	23.4	21.3	19.2	17.2	20.2	18.4	16.6	14.7	12.9		0.41	
6	27.9	24.0	20.1	18.7	21.2	19.5	17.7	16.0	14.1	16.9	15.3	13.8	12.3	10.7		0.60	
7	23.9	20.6	17.2	16.0	18.2	16.7	15.2	13.7	12.3	14.4	13.1	11.8	10.5	9.2		0.81	
8	20.9	18.0	15.1	14.0	15.9	14.6	13.3	12.0	10.8	12.6	11.5	10.4	9.2	8.0		1.06	
9	18.6	16.0	13.4	12.5	14.2	13.0	11.8	10.7	9.6	11.2	10.2	9.2	8.2	7.1		1.34	
10	16.8	14.4	12.1	11.2	12.7	11.7	10.6	9.6	8.6	10.1	9.2	8.3	7.4	6.4		1.66	
11	15.2	13.1	11.0	10.2	11.6	10.6	9.7	8.7	7.8	9.2	8.4	7.5	6.7	5.8		2.00	
12	14.0	12.0	10.1	9.3	10.6	9.7	8.9	8.0	7.2	8.1	7.7	6.9	6.1	5.1		2.38	
13	12.9	11.1	9.3	8.6	9.8	9.0	8.2	7.4	6.6	7.8	7.1	6.4	5.7	4.9		2.80	
14	12.0	10.3	8.6	8.0	9.1	8.4	7.6	6.9	6.2	7.2	6.6	5.9	5.3	4.6		3.24	
15	11.2	9.6	8.0	7.5	8.5	7.8	7.1	6.4	5.7	6.7	6.1	5.5	4.9	4.3		3.72	
16	10.5	9.0	7.5	7.0	8.0	7.3	6.7	6.0	5.4	6.3	5.7	5.2	4.6	4.0		4.21	
17	9.9	8.5	7.1	6.6	7.5	6.9	6.3	5.6	5.1							4.78	
18	9.3	8.0	6.7	6.2	7.1	6.5	5.9	5.3	4.8							5.36	
19	8.8	7.6	6.3	5.9												5.98	
20	8.4	7.2	6.0	5.6												6.62	

Span in Feet	Depth and Weight of Sections															Coefficient of Deflection					
	6 Inch					5 Inch					4 Inch						3 Inch				
	13½	13	10½	8	11½	9	6½	7½	6½	5½	6	5	4	3½	3		2½				
	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.	lbs.		lbs.				
1	67.6	62.8	58.2	54.0	47.7	44.4	39.0	34.0	24.1	20.2	14.4	14.7	13.1	10.2			0.02				
2	31.7	30.8	26.9	23.1	22.2	18.9	15.8	12.2	12.2	11.1	10.1	7.4	6.6	5.8			0.07				
3	23.2	20.5	17.9	15.1	14.8	12.6	10.5	8.1	7.4	6.7	4.9	4.4	3.9	3.9			0.15				
4	17.1	15.4	13.4	11.6	11.1	9.5	7.9	6.1	5.6	5.1	3.7	3.3	2.9	2.7			0.27				
5	13.9	12.3	10.8	9.2	8.9	7.6	6.3	4.9	4.5	4.1	2.9	2.6	2.3	2.1			0.41				
6	11.6	10.3	9.0	7.7	7.1	6.3	5.3	4.1	3.7	3.4	2.5	2.2	1.9	1.7			0.60				
7	9.9	8.8	7.7	6.6	6.3	5.4	4.5	3.5	3.2	2.9	2.1	1.9	1.7	1.6			0.81				
8	8.7	7.7	6.7	5.8	5.5	4.7	4.0	3.0	2.8	2.5	1.8	1.6	1.5	1.4			1.06				
9	7.7	6.8	6.0	5.1	4.9	4.2	3.5	2.7	2.5	2.2							1.34				
10	6.9	6.2	5.4	4.6	4.4	3.8	3.2	2.4	2.2	2.0							1.66				
11	6.3	5.6	4.9	4.2	4.0	3.4	2.9										2.00				
12	5.8	5.1	4.5	3.9	3.7	3.2	2.6										2.38				
13	5.3	4.7	4.1	3.6													2.80				
14	5.0	4.4	3.8	3.3													3.24				

Loads above upper horizontal lines will produce maximum allowable shear in webs.

Loads below lower horizontal lines will produce excessive deflections.

For maximum safe loads, see page 215.



# CARNEGIE STEEL COMPANY

## CHANNELS—ALLOWABLE UNIFORM LOAD IN POUNDS PER FOOT

Depth, inches	Pounds per foot	Span in Feet																		25	26
		6	7	8	9	10	11	12	13	14	15	16	17	18	19	20	21	22	23		
55	17000	12400	9560	7550	6120	5060	4250	3620	3120	2720	2390	2120	1890	1690	1530	1390	1260	1160	1060	950	910
50	15010	11690	9340	7070	5730	4730	3980	3390	2920	2530	2240	1980	1770	1590	1430	1300	1180	1080	990	920	850
45	14820	10890	8540	6390	5330	4410	3700	3160	2720	2370	2080	1850	1650	1480	1330	1210	1100	1010	930	850	790
40	13730	10080	7720	5900	4940	4080	3380	2820	2320	2000	1730	1530	1370	1230	1110	1020	930	860	790	730	670
35	12540	9290	7110	5260	4350	3590	3160	2660	2220	1870	1570	1400	1260	1140	1030	940	860	790	730	670	610
33	12350	9070	6950	5130	4250	3500	2990	2530	2100	1740	1430	1260	1120	1010	920	840	770	710	650	590	530
30	11300	8050	6360	5150	4260	3580	3050	2630	2290	2010	1780	1590	1430	1290	1170	1060	970	890	820	760	700
25	10310	7310	5940	4810	3970	3340	2830	2430	2140	1880	1660	1480	1320	1190	1070	960	870	800	740	680	620
20	9210	6580	5320	4470	3690	3060	2570	2180	1890	1670	1480	1300	1140	1010	900	810	740	680	620	560	500
18	8710	6180	5040	4240	3490	2880	2410	2040	1760	1550	1370	1200	1040	910	800	720	650	590	530	470	410
16	8170	5730	4640	3870	3140	2550	2100	1740	1480	1280	1110	950	800	690	600	520	450	390	330	270	210
14	7590	5250	4200	3460	2760	2190	1760	1420	1180	1000	840	700	580	480	400	320	250	190	130	70	10
12	7080	4800	3800	3100	2440	1890	1480	1160	940	790	660	540	430	340	260	180	110	50	0	0	0
10	6530	4360	3400	2740	2120	1590	1200	900	710	580	470	370	280	200	120	50	0	0	0	0	0
9	6040	3940	3020	2400	1820	1320	960	740	580	460	350	260	180	100	40	0	0	0	0	0	0
8	5610	3570	2700	2120	1580	1110	810	630	490	380	280	190	110	50	0	0	0	0	0	0	0
7	5230	3240	2420	1880	1390	990	740	570	430	320	220	140	70	10	0	0	0	0	0	0	0
6	4900	2940	2220	1720	1260	880	660	500	370	260	170	90	30	0	0	0	0	0	0	0	0
5	4620	2620	2020	1560	1120	780	580	430	310	210	120	50	10	0	0	0	0	0	0	0	0
4	4380	2340	1780	1340	960	690	500	360	240	140	70	20	10	0	0	0	0	0	0	0	0
3	4160	2100	1580	1160	820	590	420	290	180	90	30	10	0	0	0	0	0	0	0	0	0
2	3960	1920	1440	1040	740	530	380	250	150	70	20	10	0	0	0	0	0	0	0	0	0
1	3780	1760	1300	940	680	490	340	220	130	60	20	10	0	0	0	0	0	0	0	0	0

Leds within heavy horizontal lines  
are maximum loads for web shear.  
Leds below dotted horizontal lines  
will produce excessive deflection.

# BEAM SAFE LOADS

CHANNELS—ALLOWABLE UNIFORM LOAD IN POUNDS PER FOOT

Depth, Inches	Pounds per foot	Span in Feet																					
		2	2½	3	3½	4	4½	5	5½	6	6½	7	8	9	10	11	12	13	14	15	16	17	18
21.25	31840	20380	11150	10400	7960	6290	5090	4210	3540	3010	2500	1990	1570	1270	1050	880	750	650	570	500	440	390	
18.75	29230	18710	12900	9540	7310	5770	4580	3860	3250	2770	2300	1830	1410	1170	970	810	690	600	520	460	410	360	
8	16.25	26610	17030	11830	8890	6850	5260	4160	3370	2860	2370	1900	1500	1240	1040	880	740	630	540	470	420	370	330
13.75	24090	15300	10370	7810	6000	4740	3840	3170	2670	2270	1900	1500	1190	960	790	670	570	490	430	370	330	300	270
11.25	17600	13780	9370	7030	5380	4250	3450	2870	2380	2040	1700	1350	1080	860	710	600	510	440	380	340	300	270	
10.75	22850	16180	11230	8250	6320	4990	4040	3340	2810	2390	2000	1580	1250	1010	840	700	600	520	450	400			
17.25	22990	14710	10220	7510	5750	4540	3680	3040	2550	2180	1800	1410	1140	920	760	640	540	470	410	360			
7	14.75	20700	13230	9200	6760	5180	4040	3310	2740	2300	1900	1500	1200	930	780	680	580	500	420	370	320		
12.25	18410	11780	8180	6010	4600	3610	2930	2430	2050	1740	1400	1150	910	740	610	510	440	380	330	290			
9.75	14700	10280	7140	5250	4020	3170	2570	2120	1740	1520	1310	1060	730	640	530	440	370	320	280	250			
15.5	17360	11110	7720	5670	4340	3430	2780	2300	1950	1640	1320	1040	800	690	570	480	410	350					
13.0	13400	9850	6840	5030	3850	3010	2460	2040	1710	1490	1260	960	700	620	510	430	360	310					
6	10.5	13440	8600	5970	4380	3360	2630	2150	1780	1490	1270	1000	840	690	540	440	370	320	270				
8.0	11550	7390	5130	3770	2890	2280	1850	1530	1280	1090	940	720	570	460	380	320	270	240					
11.5	11100	7100	4930	3620	2770	2190	1780	1470	1230	1050	910	690	550	440	370	310							
5	9.0	9460	6090	4210	3090	2370	1870	1510	1250	1050	900	770	590	470	380	310	260						
6.5	7910	5060	3520	2580	1980	1560	1270	1050	880	750	630	490	390	320	260	220							
7.25	6090	3900	2710	1990	1520	1200	980	810	680	580	500	380	300	240									
4	6.25	5370	3570	2480	1820	1390	1160	890	740	620	530	460	350	280	220								
5.25	5060	3240	2250	1650	1250	1000	810	670	560	480	410	320	250	200									
6.0	3680	2350	1630	1200	920	730	590	490	410	350	300												
3	5.0	3290	2100	1470	1070	820	650	530	430	370	310	270											
4.0	2910	1860	1290	950	730	570	470	380	320	280	240												

Loads within heavy horizontal lines are maximum loads for web shear.

Loads below dotted horizontal lines will produce excessive deflection.

Loads within heavy horizontal lines are maximum loads for web shear.

Loads below dotted horizontal lines will produce excessive deflection.

# CARNEGIE STEEL COMPANY

## EQUAL ANGLES

ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Neutral Axis Parallel to Either Leg

Maximum Bending Stress, 16,000 Pounds per Square Inch

Size, Inches	Thick- ness, Inches	1 Foot Span		Maximum Span 360 x Deflection		Size, Inches	Thick- ness, Inches	1 Foot Span		Maximum Span 360 x Deflection	
		Safe Load	Safe Load	Length, Feet				Safe Load	Safe Load	Length, Feet	
8 x 8	1 5/8	186.99	8.31	22.5		3 1/2 x 3 1/2	1 1/2	24.00	2.55	9.4	
8 x 8	1 1/2	177.81	7.87	22.6		3 1/2 x 3 1/2	1 1/4	22.51	2.37	9.5	
8 x 8	1	168.53	7.43	22.7		3 1/2 x 3 1/2	1 3/8	20.91	2.18	9.6	
8 x 8	7/8	159.15	6.98	22.8		3 1/2 x 3 1/2	1 1/2	19.31	2.00	9.7	
8 x 8	3/4	149.55	6.53	22.9		3 1/2 x 3 1/2	1 1/4	17.60	1.81	9.7	
8 x 8	13/16	139.84	6.08	23.0		3 1/2 x 3 1/2	1 3/8	15.89	1.62	9.8	
8 x 8	5/8	130.03	5.63	23.1		3 1/2 x 3 1/2	1 1/2	14.08	1.42	9.9	
8 x 8	11/16	120.00	5.18	23.2		3 1/2 x 3 1/2	1 1/4	12.27	1.23	10.0	
8 x 8	5/8	109.87	4.73	23.2		3 1/2 x 3 1/2	1 3/8	10.45	1.04	10.1	
8 x 8	1 1/8	99.63	4.28	23.3		3 x 3	1 1/4	8.43	0.83	10.2	
8 x 8	1 1/2	89.28	3.82	23.4		3 x 3	1 3/8	13.87	1.69	8.2	
						3 x 3	1 1/2	12.69	1.53	8.3	
						3 x 3	1 3/4	11.41	1.37	8.3	
6 x 6	1	91.41	5.48	16.7		3 x 3	1 3/8	10.13	1.21	8.4	
6 x 6	7/8	86.51	5.16	16.8		3 x 3	1 1/2	8.85	1.04	8.5	
6 x 6	3/4	81.39	4.84	16.8		3 x 3	1 3/4	7.57	0.88	8.6	
6 x 6	11/16	76.27	4.51	16.9		3 x 3	1 1/4	6.19	0.71	8.7	
6 x 6	5/8	71.04	4.18	17.0		2 1/2 x 2 1/2	1 1/2	7.79	1.15	6.8	
6 x 6	11/16	65.81	3.85	17.1		2 1/2 x 2 1/2	1 3/8	6.93	1.01	6.9	
6 x 6	5/8	60.37	3.51	17.2		2 1/2 x 2 1/2	1 1/2	6.08	0.87	7.0	
6 x 6	1 1/8	54.83	3.17	17.3		2 1/2 x 2 1/2	1 3/4	5.12	0.72	7.1	
6 x 6	1 1/2	49.17	2.83	17.4		2 1/2 x 2 1/2	1 1/4	4.16	0.58	7.2	
6 x 6	1 3/8	43.41	2.48	17.5		2 1/2 x 2 1/2	1 3/8	3.20	0.41	7.3	
6 x 6	3/8	37.65	2.14	17.6		2 1/2 x 2 1/2	1 1/2	2.13	0.29	7.4	
						2 x 2	1 1/4	4.27	0.79	5.4	
						2 x 2	1 3/8	3.73	0.68	5.5	
5 x 5	1	61.87	4.55	13.6		2 x 2	1 1/2	3.20	0.57	5.6	
5 x 5	7/8	58.56	4.28	13.7		2 x 2	1 3/4	2.67	0.46	5.7	
5 x 5	3/4	55.15	4.00	13.8		2 x 2	1 1/4	2.03	0.35	5.8	
5 x 5	11/16	51.73	3.73	13.9		2 x 2	1 3/8	1.39	0.24	5.8	
5 x 5	5/8	48.32	3.45	14.0							
5 x 5	11/16	44.80	3.18	14.1		1 1/2 x 1 1/2	1 1/4	3.20	0.68	4.7	
5 x 5	3/4	41.17	2.90	14.2		1 1/2 x 1 1/2	1 3/8	2.77	0.60	4.7	
5 x 5	5/8	37.44	2.62	14.3		1 1/2 x 1 1/2	1 1/2	2.45	0.51	4.8	
5 x 5	1 1/8	33.60	2.34	14.4		1 1/2 x 1 1/2	1 3/4	2.03	0.41	4.9	
5 x 5	1 1/2	29.76	2.06	14.5		1 1/2 x 1 1/2	1 1/4	1.49	0.30	5.0	
5 x 5	1 3/8	25.81	1.78	14.5		1 1/2 x 1 1/2	1 3/8	1.07	0.21	5.1	
						1 1/2 x 1 1/2	1 1/2	2.03	0.51	4.0	
						1 1/2 x 1 1/2	1 3/4	1.71	0.42	4.1	
4 x 4	1 1/4	32.11	2.95	10.9		1 1/2 x 1 1/2	1 1/4	1.39	0.33	4.2	
4 x 4	3/4	29.97	2.73	11.0		1 1/2 x 1 1/2	1 3/8	1.07	0.25	4.3	
4 x 4	11/16	27.84	2.51	11.1		1 1/2 x 1 1/2	1 1/2	0.77	0.17	4.4	
4 x 4	5/8	25.60	2.29	11.2		1 1/2 x 1 1/2	1 3/4	1.17	0.36	3.3	
4 x 4	1 1/8	23.36	2.07	11.3		1 1/2 x 1 1/2	1 1/4	0.97	0.29	3.4	
4 x 4	1 1/2	21.01	1.85	11.4		1 1/2 x 1 1/2	1 3/8	0.76	0.22	3.5	
4 x 4	1 3/8	18.67	1.63	11.4		1 1/2 x 1 1/2	1 1/2	0.52	0.14	3.6	
4 x 4	3/8	16.21	1.41	11.5		1 x 1	1 1/4	0.60	0.22	2.6	
4 x 4	1 1/4	13.76	1.19	11.6		1 x 1	1 3/8	0.47	0.17	2.7	
4 x 4	1 3/4	11.20	0.96	11.7		1 x 1	1 1/2	0.33	0.12	2.8	

# BEAM SAFE LOADS

## UNEQUAL ANGLES

ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Neutral Axis Parallel to Shorter Leg

Maximum Bending Stress, 16,000 Pounds per Square Inch

Size, Inches	Thick- ness, Inches	1 Foot Span	Maximum Span 360x Deflection		Size, Inches	Thick- ness, Inches	1 Foot Span	Maximum Span 360x Deflection	
		Safe Load	Safe Load	Length, Feet			Safe Load	Safe Load	Length, Feet
8 x 6	1	161.17	7.49	21.5	6 x 3½	1	83.52	5.57	15.0
8 x 6	1½	152.21	7.04	21.6	6 x 3½	1½	79.04	5.24	15.1
8 x 6	2	143.01	6.59	21.7	6 x 3½	2	74.45	4.90	15.2
8 x 6	2½	133.87	6.14	21.8	6 x 3½	2½	69.87	4.57	15.3
8 x 6	3	124.48	5.68	21.9	6 x 3½	3	65.07	4.23	15.4
8 x 6	3½	114.88	5.22	22.0	6 x 3½	3½	60.27	3.89	15.5
8 x 6	4	105.28	4.76	22.1	6 x 3½	4	55.36	3.55	15.6
8 x 6	4½	95.47	4.30	22.2	6 x 3½	4½	50.35	3.21	15.7
8 x 6	5	85.55	3.84	22.3	6 x 3½	5	45.23	2.86	15.8
8 x 6	5½	75.41	3.37	22.4	6 x 3½	5½	40.00	2.52	15.9
8 x 3½	1	146.03	7.53	19.4	6 x 3½	6	34.67	2.17	16.0
8 x 3½	1½	138.03	7.08	19.5	6 x 3½	6½	29.23	1.83	16.0
8 x 3½	2	129.92	6.63	19.6					
8 x 3½	2½	121.60	6.17	19.7	5 x 4	7	53.23	4.00	13.3
8 x 3½	3	113.17	5.72	19.8	5 x 4	7½	50.03	3.73	13.4
8 x 3½	3½	104.58	5.23	19.9	5 x 4	8	46.61	3.46	13.5
8 x 3½	4	95.79	4.78	20.0	5 x 4	8½	43.20	3.19	13.5
8 x 3½	4½	86.93	4.32	20.1	5 x 4	9	39.79	2.92	13.6
8 x 3½	5	77.97	3.86	20.2	5 x 4	9½	36.16	2.64	13.7
8 x 3½	5½	68.80	3.39	20.3	5 x 4	10	32.53	2.36	13.8
7 x 3½	1	112.85	6.52	17.3	5 x 4	10½	28.80	2.07	13.9
7 x 3½	1½	106.67	6.13	17.1	5 x 4	11	24.96	1.78	14.0
7 x 3½	2	100.48	5.75	17.5					
7 x 3½	2½	94.08	5.36	17.6	5 x 3½	7½	52.05	4.01	12.9
7 x 3½	3	87.68	4.97	17.6	5 x 3½	8	48.85	3.76	13.0
7 x 3½	3½	81.07	4.58	17.7	5 x 3½	8½	45.65	3.49	13.1
7 x 3½	4	74.35	4.18	17.8	5 x 3½	9	42.35	3.21	13.2
7 x 3½	4½	67.52	3.77	17.9	5 x 3½	9½	38.93	2.93	13.3
7 x 3½	5	60.59	3.37	18.0	5 x 3½	10	35.41	2.64	13.4
7 x 3½	5½	53.44	2.96	18.1	5 x 3½	10½	31.89	2.36	13.5
7 x 3½	6	46.19	2.54	18.2	5 x 3½	11	28.16	2.07	13.6
					5 x 3½	11½	24.43	1.79	13.7
6 x 4	1	85.55	5.56	15.4	5 x 3½	12	20.69	1.51	13.7
6 x 4	1½	80.96	5.22	15.5					
6 x 4	2	76.27	4.89	15.6	5 x 3	12½	47.47	3.77	12.6
6 x 4	2½	71.47	4.55	15.7	5 x 3	13	44.37	3.49	12.7
6 x 4	3	66.67	4.22	15.8	5 x 3	13½	41.17	3.22	12.8
6 x 4	3½	61.65	3.88	15.9	5 x 3	14	37.87	2.94	12.9
6 x 4	4	56.64	3.54	16.0	5 x 3	14½	34.45	2.65	13.0
6 x 4	4½	51.52	3.20	16.1	5 x 3	15	31.04	2.37	13.1
6 x 4	5	46.19	2.85	16.2	5 x 3	15½	27.52	2.09	13.2
6 x 4	5½	40.85	2.51	16.3	5 x 3	16	23.89	1.80	13.3
6 x 4	6	35.41	2.16	16.4	5 x 3	16½	20.16	1.51	13.4

# CARNEGIE STEEL COMPANY

## UNEQUAL ANGLES

ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Neutral Axis Parallel to Shorter Leg

Maximum Bending Stress, 16,000 Pounds per Square Inch

Size, Inches	Thick- ness, Inches	1 Foot Span	Maximum Span 360x Deflection		Size, Inches	Thick- ness, Inches	1 Foot Span	Maximum Span 360x Deflection	
		Safe Load	Safe Load	Length, Feet			Safe Load	Safe Load	Length, Feet
4½ x 3	1½	38.61	3.36	11.5	3 x 2½	1½	12.27	1.53	8.0
4½ x 3	1½	36.05	3.11	11.6	3 x 2½	1½	11.09	1.37	8.1
4½ x 3	1½	33.49	2.87	11.7	3 x 2½	1½	9.92	1.22	8.1
4½ x 3	1½	30.83	2.62	11.8	3 x 2½	1½	8.64	1.06	8.2
4½ x 3	1½	28.16	2.38	11.8	3 x 2½	1½	7.36	0.89	8.3
4½ x 3	1½	25.28	2.13	11.9	3 x 2½	1½	5.97	0.71	8.4
4½ x 3	1½	22.40	1.87	12.0					
4½ x 3	1½	19.52	1.61	12.1	3 x 2	1½	10.67	1.39	7.7
4½ x 3	1½	16.43	1.35	12.2	3 x 2	1½	9.49	1.22	7.8
					3 x 2	1½	8.32	1.05	7.9
					3 x 2	1½	7.04	0.88	8.0
					3 x 2	1½	5.76	0.71	8.1
4 x 3½	1½	31.15	2.94	10.6					
4 x 3½	1½	29.23	2.73	10.7					
4 x 3½	1½	27.20	2.52	10.8					
4 x 3½	1½	25.07	2.30	10.9	2½ x 2	1½	7.47	1.15	6.5
4 x 3½	1½	22.93	2.08	11.0	2½ x 2	1½	6.72	1.02	6.6
4 x 3½	1½	20.69	1.86	11.1	2½ x 2	1½	5.87	0.88	6.7
4 x 3½	1½	18.35	1.64	11.2	2½ x 2	1½	5.01	0.74	6.8
4 x 3½	1½	16.00	1.41	11.3	2½ x 2	1½	4.05	0.59	6.9
4 x 3½	1½	13.44	1.18	11.4	2½ x 2	1½	3.09	0.44	7.0
					2½ x 2	1½	2.13	0.30	7.1
4 x 3	1½	30.61	2.97	10.3					
4 x 3	1½	28.59	2.75	10.4	2½ x 1½	1½	4.69	0.73	6.4
4 x 3	1½	26.56	2.53	10.5	2½ x 1½	1½	3.84	0.59	6.5
4 x 3	1½	24.53	2.31	10.6	2½ x 1½	1½	2.99	0.45	6.6
4 x 3	1½	22.40	2.09	10.7					
4 x 3	1½	20.16	1.87	10.8	2½ x 1½	1½	5.76	1.02	5.6
4 x 3	1½	17.92	1.64	10.9	2½ x 1½	1½	5.12	0.90	5.7
4 x 3	1½	15.57	1.42	11.0	2½ x 1½	1½	4.48	0.77	5.8
4 x 3	1½	13.12	1.19	11.0	2½ x 1½	1½	3.84	0.65	5.9
4 x 3	1½	10.67	0.96	11.1	2½ x 1½	1½	3.20	0.53	6.0
					2½ x 1½	1½	2.45	0.40	6.0
3½ x 3	1½	23.47	2.57	9.1					
3½ x 3	1½	21.87	2.38	9.2	2 x 1½	1½	3.63	0.70	5.2
3½ x 3	1½	20.37	2.19	9.3	2 x 1½	1½	3.09	0.58	5.3
3½ x 3	1½	18.77	2.00	9.4	2 x 1½	1½	2.56	0.47	5.4
3½ x 3	1½	17.17	1.81	9.5	2 x 1½	1½	1.92	0.35	5.5
3½ x 3	1½	15.47	1.62	9.5	2 x 1½	1½	1.39	0.24	5.6
3½ x 3	1½	13.76	1.43	9.6					
3½ x 3	1½	12.05	1.24	9.7					
3½ x 3	1½	10.24	1.05	9.8	2 x 1½	1½	2.45	0.47	5.2
3½ x 3	1½	8.32	0.84	9.9	2 x 1½	1½	1.92	0.36	5.3
3½ x 2½	1½	19.73	2.19	9.0	1½ x 1½	1½	1.92	0.42	4.6
3½ x 2½	1½	18.24	2.00	9.1	1½ x 1½	1½	1.49	0.32	4.7
3½ x 2½	1½	16.64	1.82	9.1	1½ x 1½	1½	1.00	0.21	4.8
3½ x 2½	1½	15.04	1.63	9.2					
3½ x 2½	1½	13.44	1.44	9.3					
3½ x 2½	1½	11.73	1.24	9.4	1½ x 1½	1½	1.71	0.44	3.9
3½ x 2½	1½	9.92	1.04	9.5	1½ x 1½	1½	1.39	0.35	4.0
3½ x 2½	1½	8.00	0.83	9.6	1½ x 1½	1½	1.07	0.26	4.1

# BEAM SAFE LOADS

## UNEQUAL ANGLES

ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Neutral Axis Parallel to Longer Leg

Maximum Bending Stress, 16,000 Pounds per Square Inch

Size, Inches	Thick- ness, Inches	1 Foot Span			Size, Inches	Thick- ness, Inches	1 Foot Span		
		Safe Load	Safe Load	Length, Feet			Safe Load	Safe Load	Length, Feet
8 x 6	1	95.15	5.44	17.5	6 x 3½	1	30.93	3.09	10.0
8 x 6	1½	89.92	5.11	17.6	6 x 3½	1½	29.23	2.90	10.1
8 x 6	7/8	81.69	4.79	17.7	6 x 3½	7/8	27.63	2.71	10.2
8 x 6	1¼	79.36	4.45	17.8	6 x 3½	1¼	25.92	2.52	10.3
8 x 6	¾	73.92	4.13	17.9	6 x 3½	¾	24.21	2.33	10.4
8 x 6	1½	68.37	3.80	18.0	6 x 3½	1½	22.51	2.14	10.5
8 x 6	7/8	62.72	3.48	18.0	6 x 3½	7/8	20.69	1.95	10.6
8 x 6	1¼	56.96	3.15	18.1	6 x 3½	1¼	18.88	1.76	10.7
8 x 6	¾	51.09	2.81	18.2	6 x 3½	¾	16.96	1.57	10.8
8 x 6	1½	45.12	2.47	18.3	6 x 3½	1½	15.04	1.38	10.9
8 x 3½	1	32.21	3.10	10.4	6 x 3½	1	13.12	1.19	11.0
8 x 3½	1½	30.10	2.90	10.5	6 x 3½	1½	11.00	1.00	11.1
8 x 3½	7/8	28.69	2.71	10.6	5 x 4	7/8	35.31	3.15	11.2
8 x 3½	1¼	26.88	2.52	10.7	5 x 4	1¼	33.17	2.93	11.3
8 x 3½	¾	25.07	2.33	10.8	5 x 4	¾	30.93	2.71	11.4
8 x 3½	1½	23.15	2.13	10.9	5 x 4	1½	28.69	2.50	11.5
8 x 3½	7/8	21.33	1.94	11.0	5 x 4	7/8	26.15	2.28	11.6
8 x 3½	1¼	19.41	1.74	11.1	5 x 4	1¼	24.11	2.16	11.7
8 x 3½	¾	17.49	1.57	11.2	5 x 4	¾	21.76	1.81	11.8
8 x 3½	1½	15.57	1.38	11.3	5 x 4	1½	19.31	1.62	11.9
7 x 3½	1	31.57	3.10	10.2	5 x 4	1	16.75	1.40	12.0
7 x 3½	1½	29.87	2.90	10.3					
7 x 3½	7/8	28.16	2.71	10.4	5 x 3½	7/8	26.88	2.71	9.9
7 x 3½	1¼	26.45	2.52	10.5	5 x 3½	1¼	25.28	2.53	10.0
7 x 3½	¾	24.61	2.33	10.6	5 x 3½	¾	23.68	2.34	10.1
7 x 3½	1½	22.83	2.11	10.7	5 x 3½	1½	21.97	2.15	10.2
7 x 3½	7/8	21.01	1.95	10.8	5 x 3½	7/8	20.27	1.97	10.3
7 x 3½	1¼	19.20	1.76	10.9	5 x 3½	1¼	18.45	1.78	10.4
7 x 3½	¾	17.28	1.57	11.0	5 x 3½	¾	16.64	1.60	10.5
7 x 3½	1½	15.36	1.38	11.1	5 x 3½	1½	14.83	1.41	10.6
7 x 3½	7/8	13.44	1.19	11.2	5 x 3½	7/8	12.91	1.22	10.7
6 x 4	1	40.43	3.55	11.4	5 x 3½	1	10.88	1.02	10.7
6 x 4	1½	38.29	3.33	11.5	5 x 3	1½	18.56	2.16	8.6
6 x 4	7/8	36.16	3.12	11.6	5 x 3	7/8	17.39	2.00	8.7
6 x 4	1¼	33.92	2.90	11.7	5 x 3	1¼	16.11	1.83	8.8
6 x 4	¾	31.68	2.69	11.8	5 x 3	¾	14.83	1.67	8.9
6 x 4	1½	29.44	2.47	11.9	5 x 3	1½	13.55	1.51	9.0
6 x 4	7/8	27.09	2.26	12.0	5 x 3	7/8	12.27	1.35	9.1
6 x 4	1¼	24.64	2.05	12.0	5 x 3	1¼	10.88	1.18	9.2
6 x 4	¾	22.19	1.81	12.1	5 x 3	¾	9.49	1.02	9.3
6 x 4	1½	19.73	1.62	12.2	5 x 3	1½	8.00	0.85	9.4
6 x 4	7/8	17.07	1.39	12.3	5 x 3	7/8			

# CARNEGIE STEEL COMPANY

## UNEQUAL ANGLES

ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Neutral Axis Parallel to Longer Leg

Maximum Bending Stress, 16,000 Pounds per Square Inch

Size, Inches	Thick- ness, Inches	1 Foot Span Maximum Span 360° Deflection			Size, Inches	Thick- ness, Inches	1 Foot Span Maximum Span 360° Deflection		
		Safe Load	Safe Load	Length, Feet			Safe Load	Safe Load	Length, Feet
4½ x 3	½	18.24	2.15	8.5	3 x 2½	½	8.75	1.25	7.0
4½ x 3	¾	17.07	1.99	8.6	3 x 2½	¾	7.89	1.12	7.0
4½ x 3	1	15.89	1.83	8.7	3 x 2½	1	7.04	0.99	7.1
4½ x 3	1¼	14.61	1.67	8.8	3 x 2½	1¼	6.19	0.85	7.2
4½ x 3	1½	13.33	1.51	8.8	3 x 2½	1½	5.23	0.72	7.3
4½ x 3	1¾	12.05	1.35	8.9	3 x 2½	1¾	4.27	0.58	7.4
4½ x 3	2	10.77	1.19	9.0					
4½ x 3	2¼	9.39	1.03	9.1	3 x 2	½	5.01	0.88	5.7
4½ x 3	2½	8.00	0.87	9.2	3 x 2	¾	4.48	0.77	5.8
					3 x 2	1	3.95	0.67	5.9
4 x 3½	½	24.53	2.56	9.6	3 x 2	1¼	3.41	0.57	6.0
4 x 3½	¾	22.03	2.37	9.7	3 x 2	1½	2.77	0.46	6.1
4 x 3½	1	21.33	2.18	9.8					
4 x 3½	1¼	19.63	1.98	9.9	2½ x 2	½	4.91	0.89	5.5
4 x 3½	1½	17.92	1.79	10.0	2½ x 2	¾	4.37	0.78	5.6
4 x 3½	1¾	16.21	1.60	10.1	2½ x 2	1	3.84	0.67	5.7
4 x 3½	2	14.40	1.41	10.2	2½ x 2	1¼	3.31	0.57	5.8
4 x 3½	2¼	12.59	1.22	10.3	2½ x 2	1½	2.67	0.46	5.9
4 x 3½	2½	10.67	1.03	10.4	2½ x 2	1¾	2.13	0.35	6.0
					2½ x 2	2	1.49	0.23	6.1
4 x 3	½	17.92	2.15	8.3					
4 x 3	¾	16.75	1.99	8.4	2½ x 1½	½	1.81	0.41	4.4
4 x 3	1	15.57	1.83	8.5	2½ x 1½	¾	1.49	0.33	4.5
4 x 3	1¼	14.40	1.67	8.6	2½ x 1½	1	1.17	0.25	4.6
4 x 3	1½	13.12	1.51	8.7					
4 x 3	1¾	11.84	1.35	8.8	2½ x 1½	1¼	2.77	0.67	4.1
4 x 3	2	10.56	1.19	8.9	2½ x 1½	1½	2.45	0.58	4.2
4 x 3	2¼	9.28	1.03	8.9	2½ x 1½	1¾	2.13	0.50	4.3
4 x 3	2½	7.89	0.87	9.0	2½ x 1½	2	1.81	0.41	4.4
4 x 3	3	6.40	0.70	9.1	2½ x 1½	2¼	1.49	0.33	4.5
					2½ x 1½	2½	1.17	0.25	4.6
3½ x 3	½	17.60	2.17	8.1					
3½ x 3	¾	16.43	2.01	8.2	2 x 1½	½	2.13	0.51	4.2
3½ x 3	1	15.36	1.85	8.3	2 x 1½	¾	1.81	0.42	4.3
3½ x 3	1¼	14.10	1.69	8.4	2 x 1½	1	1.49	0.34	4.4
3½ x 3	1½	12.91	1.52	8.5	2 x 1½	1¼	1.17	0.26	4.5
3½ x 3	1¾	11.73	1.36	8.6	2 x 1½	1½	0.80	0.17	4.6
3½ x 3	2	10.45	1.20	8.7					
3½ x 3	2¼	9.07	1.04	8.7	2 x 1½	1¾	1.04	0.28	3.7
3½ x 3	2½	7.68	0.87	8.8	2 x 1½	2	0.80	0.21	3.8
3½ x 3	3	6.19	0.70	8.9					
3½ x 2½	½	10.56	1.51	7.0	1½ x 1½	½	1.01	0.28	3.6
3½ x 2½	¾	9.81	1.39	7.1	1½ x 1½	¾	0.80	0.22	3.7
3½ x 2½	1	8.96	1.26	7.1	1½ x 1½	1	0.56	0.15	3.8
3½ x 2½	1¼	8.11	1.13	7.2					
3½ x 2½	1½	7.25	0.99	7.3	1½ x 1½	1¼	1.17	0.34	3.4
3½ x 2½	1¾	6.29	0.85	7.4	1½ x 1½	1½	0.99	0.28	3.5
3½ x 2½	2	5.33	0.71	7.5	1½ x 1½	1¾	0.78	0.22	3.6
3½ x 2½	2¼	4.37	0.58	7.6					

# BEAM SAFE LOADS

## TEES

### ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Neutral Axis Parallel to Flange

Maximum Bending Stress, 16,000 Pounds per Square Inch

#### EQUAL TEES

Size			1 Foot Span			Maximum Span			Size			1 Foot Span			Maximum Span		
Flange, Inches	Stem, Inches	Weight per Foot, Pounds	360° Deflection			Flange, Inches	Stem, Inches	Weight per Foot, Pounds	360° Deflection			Flange, Inches	Stem, Inches	Weight per Foot, Pounds	360° Deflection		
			Safe Load	Safe Load	Length, Feet				Safe Load	Safe Load	Length, Feet				Safe Load	Safe Load	Length, Feet
6 1/2	6 1/2	19.8	52.80	2.77	19.1	2 1/4	2 1/4	4.9	4.37	0.69	6.3	2 1/4	2 1/4	4.1	3.41	0.53	6.4
4	4	13.5	21.55	1.89	11.4	2 1/4	2 1/4	4.3	3.31	0.59	5.6	2	2	3.56	2.77	0.49	5.7
4	4	10.5	16.85	1.45	11.6	2	2	3.09	2.03	0.41	4.9	1 1/2	1 1/2	2.47	1.49	0.36	4.1
3 1/2	3 1/2	11.7	16.32	1.65	9.9	2	2	1.94	1.94	0.27	4.3	1 1/2	1 1/2	2.02	1.01	0.30	3.4
3 1/2	3 1/2	9.2	12.69	1.27	10.0	1 1/2	1 1/2	1.59	0.78	0.22	3.5	1 1/2	1 1/2	1.25	0.49	0.18	2.7
3	3	9.9	11.73	1.41	8.3	1 1/2	1 1/2	0.89	0.35	0.12	2.9	1	1				
3	3	8.9	10.45	1.24	8.4	1 1/2	1 1/2										
3	3	7.8	9.17	1.08	8.5	1 1/2	1 1/2										
3	3	6.7	7.89	0.92	8.6	1 1/2	1 1/2										
2 1/2	2 1/2	6.4	6.29	0.90	7.0	1	1										
2 1/2	2 1/2	5.5	5.33	0.75	7.1	1	1										

#### UNEQUAL TEES

Size			1 Foot Span			Maximum Span			Size			1 Foot Span			Maximum Span		
Flange, Inches	Stem, Inches	Weight per Foot, Pounds	360° Deflection			Flange, Inches	Stem, Inches	Weight per Foot, Pounds	360° Deflection			Flange, Inches	Stem, Inches	Weight per Foot, Pounds	360° Deflection		
			Safe Load	Safe Load	Length, Feet				Safe Load	Safe Load	Length, Feet				Safe Load	Safe Load	Length, Feet
5	3	13.4	11.41	1.25	9.1	3 1/2	3	10.8	12.05	1.42	8.5	3 1/2	3	8.5	9.49	1.09	8.7
5	2 1/2	10.9	8.96	1.20	7.5	3 1/2	3	7.5	9.07	1.04	8.7	3 1/2	3	7.5	9.07	1.04	8.7
4 1/2	3 1/2	15.7	22.72	2.37	9.6	3 1/2	3	11.7	20.69	1.92	10.8	3	4	10.5	18.35	1.68	10.9
4 1/2	3	9.8	9.71	1.07	9.1	3	4	9.2	16.11	1.47	11.0	3	4	9.2	16.11	1.47	11.0
4 1/2	3	8.4	8.32	0.90	9.2	3	4	10.8	15.89	1.66	9.6	3	3 1/2	9.7	14.19	1.46	9.7
4 1/2	2 1/2	9.2	6.72	0.87	7.7	3	4	8.5	12.37	1.26	9.8	3	3 1/2	7.1	6.40	0.89	7.2
4 1/2	2 1/2	7.8	5.70	0.74	7.8	3	3 1/2	6.1	5.55	0.76	7.3	3	2 1/2	6.1	5.55	0.76	7.3
4	5	15.3	33.39	2.40	13.9	3	3 1/2	7.1	8.96	1.08	8.3	3	3	6.1	7.68	0.91	8.4
4	5	11.0	25.92	1.84	14.1	3	3 1/2	2.87	0.93	0.25	3.7	3	2 1/2	2.87	0.93	0.25	3.7
4	4 1/2	14.4	27.09	2.15	12.6	3	2 1/2	3.09	1.60	0.36	4.4	2	1 1/2	3.09	1.60	0.36	4.4
4	4 1/2	11.2	21.12	1.65	12.8	3	2 1/2	2.45	2.03	0.37	5.5	2	1 1/2	2.45	2.03	0.37	5.5
4	3	9.2	9.60	1.08	8.9	2 1/2	3	1.25	0.57	0.15	3.7	1 1/2	1 1/2	1.25	0.57	0.15	3.7
4	3	7.8	8.21	0.90	9.1	2 1/2	3	0.88	0.14	0.07	1.9	1 1/2	1 1/2	0.88	0.14	0.07	1.9
4	2 1/2	8.5	6.61	0.87	7.6	2 1/2	1 1/2										
4	2 1/2	7.2	5.65	0.73	7.7	2	1 1/2										
4	2	7.8	4.27	0.70	6.1	1 1/2	1 1/2										
4	2	6.7	3.63	0.59	6.2	1 1/2	1 1/2										
3 1/2	4	12.6	21.12	1.90	11.1	1 1/2	1 1/2										
3 1/2	4	9.8	16.53	1.46	11.3	1 1/2	1 1/2										



# CARNEGIE STEEL COMPANY

## ZEEES

### ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS



Neutral Axis Parallel to Flanges

Maximum Bending Stress, 16,000 Pounds per Square Inch

Depth, Inches	Size		Weight per Foot, Pounds	1 Foot Span	Maximum Span 360 x Deflection	
	Flanges, Inches	Thickness, Inches		Safe Load	Safe Load	Length, Feet
6½	3½	¾	34.6	174.93	14.18	12.3
6¼	3¼	1¾	32.0	162.35	13.30	12.2
6	3½	¾	29.4	149.76	12.40	12.1
6½	3½	1¼	28.1	150.40	12.19	12.3
6¼	3¼	¾	25.4	136.75	11.20	12.2
6	3½	1¼	22.8	123.20	10.20	12.1
6½	3½	1½	21.1	119.68	9.70	12.3
6¼	3¼	1¼	18.4	104.85	8.50	12.2
6	3½	¾	15.7	90.03	7.45	12.1
5½	3½	1¾	28.4	119.47	11.58	10.3
5¼	3¼	¾	26.0	110.29	10.82	10.2
5	3½	1¼	23.7	101.01	10.03	10.1
5½	3½	¾	22.6	102.08	9.89	10.3
5¼	3¼	1¼	20.2	91.95	9.02	10.2
5	3½	1½	17.9	81.92	8.14	10.1
5½	3½	1¼	16.4	79.36	7.69	10.3
5¼	3¼	¾	14.0	68.16	6.69	10.2
5	3½	1¼	11.6	56.96	5.66	10.1
4½	3¼	¾	23.0	77.44	9.32	8.3
4¼	3½	1¼	20.9	70.93	8.67	8.2
4	3¼	¾	18.9	64.53	8.01	8.1
4½	3¼	1¼	18.0	65.92	7.93	8.3
4¼	3½	1½	15.9	58.67	7.17	8.2
4	3¼	1¼	13.8	51.52	6.40	8.1
4½	3¼	¾	12.5	49.81	6.00	8.3
4¼	3½	1¼	10.3	41.71	5.10	8.2
4	3¼	¾	8.2	33.49	4.16	8.1
3½	2¾	1¼	14.3	36.59	5.93	6.2
3	2¼	1½	12.6	32.64	5.40	6.1
3½	2¾	1¼	11.5	31.79	5.15	6.2
3	2¼	¾	9.8	27.41	4.54	6.1
3½	2¾	1¼	8.5	25.39	4.12	6.2
3	2¼	¾	6.7	20.48	3.39	6.1

# STRUCTURAL DETAILS

## STANDARD GAGES AND DIMENSIONS FOR BEAMS





Nominal dimensions are:—flange width and "e" in eighths, web thickness in sixteenths. Gages for connection angles are determined by  $\frac{1}{2}$  web thickness. Standard gages may be varied if conditions require.

Depth of Beam	Weight per Foot	Flange Width	Web Thickness	$\frac{1}{2}$ Web Thickness	Gage g	Grip p	Distance			Max. Rivet in Flange
							f	o	h	
In.	Lbs.	In.	In.	In.	In.	In.	In.	In.	In.	In.
27	90.0	9	$\frac{1}{2}$	$\frac{1}{4}$	4	$\frac{3}{4}$	$22\frac{1}{2}$	$2\frac{1}{4}$	$\frac{5}{16}$	$\frac{3}{8}$
24	115.0	8	$\frac{3}{4}$	$\frac{3}{8}$	4	$1\frac{1}{8}$	$20\frac{1}{4}$	$1\frac{7}{8}$	$\frac{7}{16}$	$\frac{3}{8}$
	110.0	8	$1\frac{1}{16}$	$\frac{3}{8}$	4	$1\frac{1}{8}$	$20\frac{3}{4}$	$1\frac{7}{8}$	$\frac{7}{16}$	
	105.0	$7\frac{3}{8}$	$\frac{5}{8}$	$\frac{9}{16}$	4	$1\frac{1}{8}$	$20\frac{3}{4}$	$1\frac{7}{8}$	$\frac{7}{8}$	
24	100.0	$7\frac{1}{4}$	$\frac{3}{4}$	$\frac{3}{8}$	4	$\frac{7}{8}$	$20\frac{3}{4}$	$1\frac{5}{8}$	$\frac{7}{16}$	$\frac{3}{8}$
	95.0	$7\frac{1}{8}$	$1\frac{1}{16}$	$\frac{3}{8}$	4	$\frac{7}{8}$	$20\frac{3}{4}$	$1\frac{5}{8}$	$\frac{7}{16}$	
	90.0	$7\frac{1}{8}$	$\frac{5}{8}$	$\frac{5}{16}$	4	$\frac{7}{8}$	$20\frac{3}{4}$	$1\frac{5}{8}$	$\frac{3}{8}$	
	85.0	$7\frac{1}{8}$	$\frac{9}{16}$	$\frac{5}{16}$	4	$\frac{7}{8}$	$20\frac{3}{4}$	$1\frac{5}{8}$	$\frac{3}{8}$	
	80.0	7	$\frac{1}{2}$	$\frac{1}{4}$	4	$\frac{7}{8}$	$20\frac{3}{4}$	$1\frac{5}{8}$	$\frac{5}{16}$	
24	74.0	9	$\frac{1}{2}$	$\frac{1}{4}$	4	$\frac{5}{8}$	20	2	$\frac{5}{16}$	$\frac{3}{8}$
21	60.5	$8\frac{1}{4}$	$\frac{7}{16}$	$\frac{3}{16}$	4	$\frac{9}{16}$	$17\frac{1}{2}$	$1\frac{3}{4}$	$\frac{1}{4}$	$\frac{3}{8}$
20	100.0	$7\frac{1}{4}$	$\frac{7}{8}$	$\frac{7}{16}$	4	1	$16\frac{1}{2}$	$1\frac{3}{4}$	$\frac{1}{2}$	$\frac{3}{8}$
	95.0	$7\frac{1}{4}$	$1\frac{1}{16}$	$\frac{7}{16}$	4	1	$16\frac{1}{2}$	$1\frac{3}{4}$	$\frac{1}{2}$	
	90.0	$7\frac{1}{8}$	$\frac{3}{4}$	$\frac{3}{8}$	4	1	$16\frac{1}{2}$	$1\frac{3}{4}$	$\frac{7}{16}$	
	85.0	$7\frac{1}{8}$	$1\frac{1}{16}$	$\frac{3}{8}$	4	1	$16\frac{1}{2}$	$1\frac{3}{4}$	$\frac{3}{8}$	
	80.0	7	$\frac{5}{8}$	$\frac{5}{16}$	4	1	$16\frac{1}{2}$	$1\frac{3}{4}$	$\frac{3}{8}$	
20	75.0	$6\frac{3}{8}$	$1\frac{1}{16}$	$\frac{5}{16}$	4	$\frac{3}{4}$	17	$1\frac{1}{2}$	$\frac{5}{8}$	$\frac{3}{8}$
	70.0	$6\frac{3}{8}$	$\frac{9}{16}$	$\frac{5}{16}$	4	$\frac{3}{4}$	17	$1\frac{1}{2}$	$\frac{5}{8}$	
	65.0	$6\frac{1}{4}$	$\frac{1}{2}$	$\frac{1}{4}$	4	$\frac{3}{4}$	17	$1\frac{1}{2}$	$\frac{6}{16}$	
18	90.0	$7\frac{1}{4}$	$1\frac{1}{16}$	$\frac{7}{16}$	4	1	$14\frac{1}{2}$	$1\frac{3}{4}$	$\frac{1}{2}$	$\frac{3}{8}$
	85.0	$7\frac{1}{8}$	$\frac{3}{4}$	$\frac{3}{8}$	4	1	$14\frac{1}{2}$	$1\frac{3}{4}$	$\frac{7}{16}$	
	80.0	$7\frac{1}{8}$	$\frac{5}{8}$	$\frac{5}{16}$	4	1	$14\frac{1}{2}$	$1\frac{3}{4}$	$\frac{3}{8}$	
	75.0	7	$\frac{9}{16}$	$\frac{9}{16}$	4	1	$14\frac{1}{2}$	$1\frac{3}{4}$	$\frac{3}{8}$	
	70.0	$6\frac{1}{4}$	$\frac{13}{16}$	$\frac{7}{16}$	4	$\frac{3}{4}$	$15\frac{1}{4}$	$1\frac{3}{8}$	$\frac{7}{16}$	
18	65.0	$6\frac{1}{4}$	$\frac{5}{8}$	$\frac{5}{16}$	$3\frac{3}{4}$	$\frac{3}{4}$	$15\frac{1}{4}$	$1\frac{3}{8}$	$\frac{3}{8}$	$\frac{3}{8}$
	60.0	$6\frac{1}{8}$	$\frac{9}{16}$	$\frac{5}{16}$	$3\frac{3}{4}$	$\frac{3}{4}$	$15\frac{1}{4}$	$1\frac{3}{8}$	$\frac{3}{8}$	
	55.0	6	$\frac{1}{2}$	$\frac{1}{4}$	$3\frac{3}{4}$	$\frac{3}{4}$	$15\frac{1}{4}$	$1\frac{3}{8}$	$\frac{6}{16}$	
	50.0	6	$\frac{1}{2}$	$\frac{1}{4}$	$3\frac{3}{4}$	$\frac{3}{4}$	$15\frac{1}{4}$	$1\frac{3}{8}$	$\frac{6}{16}$	
18	48.0	$7\frac{1}{2}$	$\frac{5}{8}$	$\frac{9}{16}$	$3\frac{3}{4}$	$\frac{1}{2}$	$14\frac{3}{4}$	$1\frac{5}{8}$	$\frac{1}{4}$	$\frac{3}{8}$
15	75.0	$6\frac{3}{8}$	$\frac{7}{8}$	$\frac{7}{16}$	$3\frac{1}{4}$	$\frac{7}{8}$	$11\frac{3}{4}$	$1\frac{5}{8}$	$\frac{1}{2}$	$\frac{3}{8}$
	70.0	$6\frac{1}{4}$	$1\frac{1}{16}$	$\frac{3}{8}$	$3\frac{1}{2}$	$\frac{7}{8}$	$11\frac{3}{4}$	$1\frac{5}{8}$	$\frac{7}{16}$	
	65.0	$6\frac{3}{8}$	$1\frac{1}{16}$	$\frac{3}{8}$	$3\frac{1}{2}$	$\frac{7}{8}$	$11\frac{3}{4}$	$1\frac{5}{8}$	$\frac{7}{16}$	
	60.0	6	$\frac{5}{8}$	$\frac{9}{16}$	$3\frac{1}{2}$	$\frac{7}{8}$	$11\frac{3}{4}$	$1\frac{5}{8}$	$\frac{3}{8}$	
	55.0	$5\frac{3}{4}$	$1\frac{1}{16}$	$\frac{5}{16}$	$3\frac{1}{2}$	$\frac{5}{8}$	$12\frac{1}{2}$	$1\frac{1}{4}$	$\frac{3}{8}$	
15	50.0	$5\frac{3}{4}$	$\frac{9}{16}$	$\frac{5}{16}$	$3\frac{1}{2}$	$\frac{5}{8}$	$12\frac{1}{2}$	$1\frac{1}{4}$	$\frac{3}{8}$	$\frac{3}{8}$
	45.0	$5\frac{3}{8}$	$\frac{1}{2}$	$\frac{1}{4}$	$3\frac{1}{2}$	$\frac{5}{8}$	$12\frac{1}{2}$	$1\frac{1}{4}$	$\frac{6}{16}$	
	42.0	$5\frac{1}{2}$	$\frac{7}{16}$	$\frac{9}{16}$	$3\frac{1}{2}$	$\frac{5}{8}$	$12\frac{1}{2}$	$1\frac{1}{4}$	$\frac{1}{4}$	
	37.5	$6\frac{1}{4}$	$\frac{9}{16}$	$\frac{9}{16}$	$3\frac{1}{2}$	$\frac{7}{16}$	$12\frac{1}{4}$	$1\frac{3}{8}$	$\frac{1}{4}$	

# CARNEGIE STEEL COMPANY

## STANDARD GAGES AND DIMENSIONS FOR BEAMS





Nominal dimensions are:—flange width and "o" in eighths, web thickness in sixteenths. Gages for connection angles are determined by  $\frac{1}{2}$  web thickness. Standard gages may be varied if conditions require.

Depth of Beam	Weight per Foot	Flange Width	Web Thickness	$\frac{1}{2}$ Web Thickness	Gage g	Grip p	Distance			Max. Rivet in Flange
							f	o	h	
In.	Lbs.	in.	In.	In.	In.	In.	in.	In.	In.	In.
12	55.0	5 $\frac{5}{8}$	1 $\frac{13}{16}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	3 $\frac{1}{4}$	9 $\frac{1}{2}$	1 $\frac{3}{8}$	1 $\frac{3}{8}$	3 $\frac{1}{4}$
	50.0	5 $\frac{1}{2}$	1 $\frac{11}{16}$	3 $\frac{1}{8}$	3 $\frac{1}{2}$	3 $\frac{1}{4}$	9 $\frac{1}{4}$	1 $\frac{3}{8}$	1 $\frac{3}{8}$	
	45.0	5 $\frac{3}{8}$	1 $\frac{9}{16}$	3 $\frac{1}{8}$	3	3 $\frac{1}{4}$	9 $\frac{1}{4}$	1 $\frac{3}{8}$	1 $\frac{3}{8}$	
	40.0	5 $\frac{1}{4}$	1 $\frac{1}{2}$	3 $\frac{1}{4}$	3	3 $\frac{1}{4}$	9 $\frac{1}{4}$	1 $\frac{3}{8}$	1 $\frac{3}{8}$	
12	35.0	5 $\frac{1}{8}$	3 $\frac{1}{8}$	3 $\frac{1}{4}$	3	3 $\frac{1}{8}$	9 $\frac{3}{4}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$	3 $\frac{1}{4}$
	31.5	5	3 $\frac{1}{8}$	3 $\frac{1}{4}$	3	3 $\frac{1}{8}$	9 $\frac{3}{4}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$	
12	28.0	6	3 $\frac{1}{8}$	3 $\frac{1}{2}$	3	3 $\frac{1}{8}$	9 $\frac{1}{2}$	1 $\frac{1}{4}$	1 $\frac{1}{4}$	3 $\frac{1}{4}$
10	40.0	5 $\frac{1}{8}$	3 $\frac{1}{4}$	3 $\frac{3}{8}$	2 $\frac{3}{4}$	1 $\frac{1}{2}$	8	1	1	3 $\frac{1}{4}$
	35.0	5	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{3}{4}$	1 $\frac{1}{2}$	8	1	1	
	30.0	4 $\frac{7}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{3}{4}$	1 $\frac{1}{2}$	8	1	1	
	25.0	4 $\frac{5}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{3}{4}$	1 $\frac{1}{2}$	8	1	1	
10	22.25	5 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{3}{4}$	3 $\frac{1}{8}$	7 $\frac{3}{4}$	1 $\frac{1}{8}$	1 $\frac{1}{8}$	3 $\frac{1}{4}$
9	35.0	4 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{3}{8}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	7	1	1	3 $\frac{1}{4}$
	30.0	4 $\frac{5}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	7	1	1	
	25.0	4 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	7	1	1	
	21.0	4 $\frac{3}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{2}$	1 $\frac{1}{2}$	7	1	1	
8	25.5	4 $\frac{1}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{4}$	1 $\frac{1}{2}$	6 $\frac{1}{4}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$	3 $\frac{1}{4}$
	23.0	4 $\frac{1}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{4}$	1 $\frac{1}{2}$	6 $\frac{1}{4}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$	
	20.5	4 $\frac{1}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{4}$	1 $\frac{1}{2}$	6 $\frac{1}{4}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$	
	18.0	4	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{4}$	1 $\frac{1}{2}$	6 $\frac{1}{4}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$	
8	17.5	5	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{4}$	3 $\frac{1}{8}$	6	1	1	3 $\frac{1}{4}$
7	20.0	3 $\frac{7}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{4}$	3 $\frac{1}{8}$	5 $\frac{1}{4}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$	3 $\frac{1}{4}$
	17.5	3 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{4}$	3 $\frac{1}{8}$	5 $\frac{1}{4}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$	
	15.0	3 $\frac{5}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2 $\frac{1}{4}$	3 $\frac{1}{8}$	5 $\frac{1}{4}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$	
6	17.25	3 $\frac{5}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2	3 $\frac{1}{8}$	4 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$
	14.75	3 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2	3 $\frac{1}{8}$	4 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	
	12.25	3 $\frac{3}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	2	3 $\frac{1}{8}$	4 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	
5	14.75	3 $\frac{3}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{3}{4}$	3 $\frac{1}{8}$	3 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$
	12.25	3 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{3}{4}$	3 $\frac{1}{8}$	3 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	
	9.75	3	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{3}{4}$	3 $\frac{1}{8}$	3 $\frac{1}{2}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	
4	10.5	2 $\frac{7}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{1}{2}$	3 $\frac{1}{8}$	2 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$
	9.5	2 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{1}{2}$	3 $\frac{1}{8}$	2 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	
	8.5	2 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{1}{2}$	3 $\frac{1}{8}$	2 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	
	7.5	2 $\frac{3}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{1}{2}$	3 $\frac{1}{8}$	2 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	
3	7.5	2 $\frac{1}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{1}{2}$	3 $\frac{1}{8}$	1 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$
	6.5	2 $\frac{1}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{1}{2}$	3 $\frac{1}{8}$	1 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	
	5.5	2 $\frac{3}{8}$	3 $\frac{1}{4}$	3 $\frac{1}{2}$	1 $\frac{1}{2}$	3 $\frac{1}{8}$	1 $\frac{3}{4}$	3 $\frac{1}{4}$	3 $\frac{1}{4}$	

# STRUCTURAL DETAILS

## STANDARD GAGES AND DIMENSIONS FOR CHANNELS




Nominal dimensions are:—flange width and “o” in eighths, web thickness in sixteenths. Gages for connection angles are determined by  $\frac{1}{2}$  web thickness. Standard gages may be varied if conditions require. Gages for channels in riveted channel columns are given on pages 291 to 301.


Depth of Channel	Weight per Foot	Flange Width	Web Thickness	$\frac{1}{2}$ Web Thickness	Gage g	Grip p	Distance			Max. Rivet in Flange
							f	o	h	
In.	Lbs.	In.	In.	In.	In.	In.	In.	In.	In.	In.
15	55.0	3 $\frac{7}{8}$	1 $\frac{3}{16}$	$\frac{7}{16}$	2 $\frac{1}{2}$	1 $\frac{1}{16}$	12 $\frac{3}{4}$	1 $\frac{3}{8}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$
	50.0	3 $\frac{5}{8}$	1 $\frac{3}{16}$	$\frac{5}{8}$	2 $\frac{1}{2}$	1 $\frac{1}{16}$	12 $\frac{3}{4}$	1 $\frac{3}{8}$	13 $\frac{1}{16}$	
	45.0	3 $\frac{5}{8}$	1 $\frac{3}{8}$	$\frac{5}{16}$	2	$\frac{5}{8}$	12 $\frac{3}{4}$	1 $\frac{3}{8}$	11 $\frac{1}{16}$	
	40.0	3 $\frac{1}{2}$	1 $\frac{1}{2}$	$\frac{1}{4}$	2	$\frac{5}{8}$	12 $\frac{3}{4}$	1 $\frac{3}{8}$	10 $\frac{1}{16}$	
	35.0	3 $\frac{1}{2}$	1 $\frac{1}{4}$	$\frac{1}{4}$	2	$\frac{5}{8}$	12 $\frac{3}{4}$	1 $\frac{3}{8}$	1 $\frac{1}{2}$	
	33.0	3 $\frac{3}{8}$	$\frac{7}{16}$	$\frac{5}{16}$	2	$\frac{5}{8}$	12 $\frac{3}{4}$	1 $\frac{3}{8}$	1 $\frac{1}{2}$	
13	50.0	4 $\frac{3}{8}$	1 $\frac{3}{16}$	$\frac{3}{8}$	3	$\frac{5}{16}$	10 $\frac{1}{4}$	1 $\frac{3}{8}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$
	45.0	4 $\frac{1}{4}$	1 $\frac{1}{16}$	$\frac{5}{16}$	2 $\frac{3}{4}$	$\frac{5}{16}$	10 $\frac{1}{4}$	1 $\frac{3}{8}$	3 $\frac{3}{8}$	
	40.0	4 $\frac{1}{4}$	$\frac{5}{16}$	$\frac{5}{16}$	2 $\frac{3}{4}$	$\frac{5}{16}$	10 $\frac{1}{4}$	1 $\frac{3}{8}$	5 $\frac{1}{8}$	
	37.0	4 $\frac{1}{8}$	1 $\frac{1}{2}$	$\frac{1}{4}$	2 $\frac{1}{2}$	$\frac{5}{16}$	10 $\frac{1}{4}$	1 $\frac{3}{8}$	5 $\frac{1}{8}$	
	35.0	4 $\frac{1}{8}$	$\frac{7}{16}$	$\frac{1}{4}$	2 $\frac{1}{2}$	$\frac{5}{16}$	10 $\frac{1}{4}$	1 $\frac{3}{8}$	5 $\frac{1}{8}$	
	32.0	4	$\frac{3}{8}$	$\frac{5}{16}$	2 $\frac{1}{2}$	$\frac{5}{16}$	10 $\frac{1}{4}$	1 $\frac{3}{8}$	1 $\frac{1}{4}$	
12	40.0	3 $\frac{1}{2}$	$\frac{3}{4}$	$\frac{3}{8}$	2	$\frac{5}{16}$	10	1	18 $\frac{1}{16}$	7 $\frac{1}{8}$
	35.0	3 $\frac{1}{2}$	$\frac{5}{8}$	$\frac{5}{16}$	2	$\frac{5}{16}$	10	1	11 $\frac{1}{16}$	
	30.0	3 $\frac{1}{2}$	1 $\frac{1}{4}$	$\frac{1}{4}$	1 $\frac{3}{4}$	$\frac{5}{16}$	10	1	9 $\frac{1}{16}$	
	25.0	3 $\frac{1}{8}$	$\frac{3}{8}$	$\frac{5}{16}$	1 $\frac{3}{4}$	$\frac{5}{16}$	10	1	7 $\frac{1}{16}$	
	20.5	3	$\frac{5}{16}$	$\frac{3}{8}$	1 $\frac{3}{4}$	$\frac{5}{16}$	10	1	3 $\frac{3}{8}$	
10	35.0	3 $\frac{1}{4}$	18 $\frac{1}{16}$	$\frac{7}{16}$	1 $\frac{3}{4}$	1 $\frac{1}{2}$	8 $\frac{1}{4}$	7 $\frac{1}{8}$	7 $\frac{1}{8}$	3 $\frac{1}{4}$
	30.0	3 $\frac{1}{8}$	11 $\frac{1}{16}$	$\frac{3}{8}$	1 $\frac{3}{4}$	1 $\frac{1}{2}$	8 $\frac{1}{4}$	7 $\frac{1}{8}$	5 $\frac{1}{8}$	
	25.0	2 $\frac{7}{8}$	1 $\frac{1}{2}$	1 $\frac{1}{4}$	1 $\frac{3}{4}$	1 $\frac{1}{2}$	8 $\frac{1}{4}$	7 $\frac{1}{8}$	9 $\frac{1}{16}$	
	20.0	2 $\frac{3}{4}$	$\frac{5}{8}$	$\frac{5}{16}$	1 $\frac{1}{2}$	$\frac{7}{16}$	8 $\frac{1}{4}$	7 $\frac{1}{8}$	7 $\frac{1}{16}$	
	15.0	2 $\frac{3}{8}$	1 $\frac{1}{4}$	$\frac{3}{8}$	1 $\frac{1}{2}$	$\frac{7}{16}$	8 $\frac{1}{4}$	7 $\frac{1}{8}$	9 $\frac{1}{16}$	
9	25.0	2 $\frac{3}{4}$	$\frac{5}{8}$	$\frac{5}{16}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	7 $\frac{1}{4}$	7 $\frac{1}{8}$	11 $\frac{1}{16}$	3 $\frac{1}{4}$
	20.0	2 $\frac{5}{8}$	$\frac{7}{16}$	1 $\frac{1}{4}$	1 $\frac{1}{2}$	1 $\frac{1}{2}$	7 $\frac{1}{4}$	7 $\frac{1}{8}$	1 $\frac{1}{2}$	
	15.0	2 $\frac{1}{2}$	$\frac{5}{16}$	$\frac{5}{16}$	1 $\frac{3}{8}$	$\frac{7}{16}$	7 $\frac{1}{4}$	7 $\frac{1}{8}$	3 $\frac{3}{8}$	
	13.25	2 $\frac{1}{2}$	1 $\frac{1}{4}$	$\frac{3}{8}$	1 $\frac{3}{8}$	$\frac{7}{16}$	7 $\frac{1}{4}$	7 $\frac{1}{8}$	5 $\frac{1}{16}$	
	21.25	2 $\frac{5}{8}$	$\frac{5}{8}$	$\frac{5}{16}$	1 $\frac{1}{2}$	$\frac{7}{16}$	6 $\frac{1}{4}$	7 $\frac{1}{8}$	11 $\frac{1}{16}$	
	18.75	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{4}$	1 $\frac{1}{2}$	$\frac{7}{16}$	6 $\frac{1}{4}$	7 $\frac{1}{8}$	9 $\frac{1}{16}$	
8	16.25	2 $\frac{1}{2}$	$\frac{7}{16}$	$\frac{5}{16}$	1 $\frac{1}{2}$	$\frac{7}{16}$	6 $\frac{1}{4}$	7 $\frac{1}{8}$	1 $\frac{1}{2}$	3 $\frac{1}{4}$
	13.75	2 $\frac{3}{8}$	$\frac{5}{16}$	$\frac{5}{16}$	1 $\frac{3}{8}$	$\frac{3}{8}$	6 $\frac{1}{4}$	7 $\frac{1}{8}$	3 $\frac{3}{8}$	
	11.25	2 $\frac{1}{4}$	1 $\frac{1}{4}$	$\frac{3}{8}$	1 $\frac{3}{8}$	$\frac{3}{8}$	6 $\frac{1}{4}$	7 $\frac{1}{8}$	9 $\frac{1}{16}$	
	19.75	2 $\frac{1}{2}$	$\frac{5}{8}$	$\frac{5}{16}$	1 $\frac{1}{2}$	$\frac{7}{16}$	5 $\frac{1}{2}$	8 $\frac{1}{4}$	11 $\frac{1}{16}$	
	17.25	2 $\frac{1}{2}$	1 $\frac{1}{2}$	1 $\frac{1}{4}$	1 $\frac{1}{2}$	$\frac{7}{16}$	5 $\frac{1}{2}$	8 $\frac{1}{4}$	9 $\frac{1}{16}$	
	14.75	2 $\frac{3}{8}$	$\frac{7}{16}$	1 $\frac{1}{4}$	1 $\frac{1}{4}$	$\frac{7}{16}$	5 $\frac{1}{2}$	8 $\frac{1}{4}$	1 $\frac{1}{2}$	
7	12.25	2 $\frac{1}{4}$	$\frac{5}{16}$	$\frac{5}{16}$	1 $\frac{1}{4}$	$\frac{3}{8}$	5 $\frac{1}{2}$	8 $\frac{1}{4}$	3 $\frac{3}{8}$	3 $\frac{1}{8}$
	9.75	2 $\frac{1}{8}$	$\frac{3}{4}$	$\frac{3}{8}$	1 $\frac{1}{4}$	$\frac{3}{8}$	5 $\frac{1}{2}$	8 $\frac{1}{4}$	9 $\frac{1}{16}$	
	15.5	2 $\frac{1}{4}$	$\frac{5}{16}$	$\frac{5}{16}$	1 $\frac{3}{8}$	$\frac{3}{8}$	4 $\frac{1}{2}$	8 $\frac{1}{4}$	5 $\frac{1}{8}$	
	13.0	2 $\frac{1}{4}$	$\frac{7}{16}$	1 $\frac{1}{4}$	1 $\frac{3}{8}$	$\frac{3}{8}$	4 $\frac{1}{2}$	8 $\frac{1}{4}$	1 $\frac{1}{2}$	
	10.5	2 $\frac{1}{8}$	$\frac{5}{16}$	$\frac{5}{16}$	1 $\frac{1}{8}$	$\frac{3}{8}$	4 $\frac{1}{2}$	8 $\frac{1}{4}$	3 $\frac{3}{8}$	
	8.0	2	$\frac{5}{16}$	$\frac{3}{8}$	1 $\frac{1}{8}$	$\frac{3}{8}$	4 $\frac{1}{2}$	8 $\frac{1}{4}$	1 $\frac{1}{4}$	
5	11.5	2 $\frac{1}{8}$	$\frac{1}{2}$	1 $\frac{1}{4}$	1 $\frac{1}{8}$	$\frac{5}{16}$	3 $\frac{3}{4}$	8 $\frac{1}{4}$	9 $\frac{1}{16}$	3 $\frac{1}{2}$
	9.0	1 $\frac{7}{8}$	$\frac{5}{16}$	$\frac{5}{16}$	1 $\frac{1}{8}$	$\frac{5}{16}$	3 $\frac{3}{4}$	8 $\frac{1}{4}$	3 $\frac{3}{8}$	
	6.5	1 $\frac{3}{4}$	8 $\frac{1}{16}$	$\frac{3}{8}$	1 $\frac{1}{8}$	$\frac{5}{16}$	3 $\frac{3}{4}$	8 $\frac{1}{4}$	1 $\frac{1}{4}$	
	7.25	1 $\frac{3}{8}$	$\frac{5}{16}$	$\frac{5}{16}$	1	$\frac{5}{16}$	2 $\frac{3}{4}$	8 $\frac{1}{4}$	3 $\frac{3}{8}$	
	6.25	1 $\frac{5}{8}$	$\frac{1}{4}$	$\frac{1}{8}$	1	$\frac{5}{16}$	2 $\frac{3}{4}$	8 $\frac{1}{4}$	9 $\frac{1}{16}$	
	5.25	1 $\frac{5}{8}$	$\frac{5}{16}$	$\frac{3}{8}$	1	$\frac{5}{16}$	2 $\frac{3}{4}$	8 $\frac{1}{4}$	1 $\frac{1}{4}$	
4	6.0	1 $\frac{5}{8}$	$\frac{3}{8}$	$\frac{5}{16}$	$\frac{1}{8}$	$\frac{1}{4}$	1 $\frac{3}{4}$	8 $\frac{1}{4}$	7 $\frac{1}{8}$	3 $\frac{1}{4}$
	5.0	1 $\frac{1}{2}$	$\frac{1}{4}$	$\frac{1}{8}$	$\frac{1}{8}$	$\frac{1}{4}$	1 $\frac{3}{4}$	8 $\frac{1}{4}$	9 $\frac{1}{16}$	
	4.0	1 $\frac{1}{2}$	$\frac{5}{16}$	$\frac{1}{8}$	$\frac{1}{8}$	$\frac{1}{4}$	1 $\frac{3}{4}$	8 $\frac{1}{4}$	1 $\frac{1}{4}$	

# CARNEGIE STEEL COMPANY


## BEAM CONNECTIONS




2 L<sup>3</sup> 4" x 4" x 1/2" x 1-8 1/2"  
Weight 46 lbs.




2 L<sup>3</sup> 4" x 4" x 1/2" x 1-5 1/2"  
Weight 39 lbs.




2 L<sup>3</sup> 4" x 4" x 1/2" x 1-2 1/2"  
Weight 33 lbs.




2 L<sup>3</sup> 4" x 4" x 3/4" x 1-11 1/2"  
Weight 23 lbs.




2 L<sup>3</sup> 4" x 4" x 3/4" x 0-8 1/2"  
Weight 17 lbs.



2 L<sup>3</sup> 6" x 4" x 3/4" x 0-5 1/2"  
Weight 13 lbs.



2 L<sup>3</sup> 6" x 4" x 3/4" x 0-3"  
Weight 7 lbs.



2 L<sup>3</sup> 6" x 4" x 3/4" x 0-2"  
Weight 5 lbs.

Rivets and bolts 3/4" diameter.

Weights given are for 3/4-inch shop rivets and angle connections; about 20 per cent should be added for field rivets or bolts.

# STRUCTURAL DETAILS

## BEAM CONNECTIONS—Concluded

### LIMITING VALUES OF BEAM CONNECTIONS

I Beams		Value of Web Connection	Values of Outstanding Legs of Connection Angles					
Depth, Inches	Weight Pounds per Foot		Field Rivets			Field Bolts		
		Shop Rivets in Enclosed Bearing, Pounds	$\frac{3}{4}$ " Rivets or Turned Bolts, Single Shear, Pounds	Minimum Allowable Span in Feet, Uniform Load	t, In.	$\frac{3}{4}$ " Rough Bolts, Single Shear, Pounds	Minimum Allowable Span in Feet, Uniform Load	t, In.
27	90	82530	61900	18.9	$\frac{5}{8}$	49500	23.6	$\frac{5}{8}$
24	80	67500	53000	17.5	$\frac{5}{8}$	42400	21.9	$\frac{5}{8}$
	74	64260	53000	16.4	$\frac{5}{8}$	42400	20.4	$\frac{5}{8}$
21	60½	48150	44200	14.2	$\frac{3}{8}$	35300	17.8	$\frac{5}{8}$
20	65	45000	35300	17.6	$\frac{5}{8}$	28300	22.1	$\frac{5}{8}$
18	55	41400	35300	13.3	$\frac{5}{8}$	28300	16.7	$\frac{5}{8}$
	48	34200	35300	12.8	$\frac{1}{16}$	28300	15.4	$\frac{5}{8}$
15	42	30900	35300	8.9	$\frac{5}{8}$	28300	11.1	$\frac{5}{8}$
	37½	29880	35300	9.7	$\frac{1}{16}$	28300	10.2	$\frac{1}{16}$
12	31½	23600	26500	8.1	$\frac{1}{16}$	21200	9.0	$\frac{5}{8}$
	28	19170	26500	9.2	$\frac{1}{16}$	21200	9.2	$\frac{1}{16}$
10	25	27900	17700	7.4	$\frac{5}{8}$	14100	9.2	$\frac{5}{8}$
	22¼	22680	17700	6.8	$\frac{5}{8}$	14100	8.6	$\frac{5}{8}$
9	21	26100	17700	5.7	$\frac{5}{8}$	14100	7.1	$\frac{5}{8}$
8	18	24300	17700	4.3	$\frac{5}{8}$	14100	5.4	$\frac{5}{8}$
	17½	19800	17700	4.4	$\frac{5}{8}$	14100	5.5	$\frac{5}{8}$
7	15	11300	8800	6.2	$\frac{5}{8}$	7100	7.8	$\frac{5}{8}$
6	12¼	10400	8800	4.4	$\frac{5}{8}$	7100	5.5	$\frac{5}{8}$
5	9¾	9500	8800	2.9	$\frac{5}{8}$	7100	3.6	$\frac{5}{8}$
4	7½	8600	8800	2.2	$\frac{1}{16}$	7100	2.7	$\frac{5}{8}$
3	5½	7700	8800	1.3	$\frac{1}{16}$	7100	1.4	$\frac{5}{8}$

### ALLOWABLE UNIT STRESS IN POUNDS PER SQUARE INCH

Single Shear	Rivets . . . . . Shop	12000	Bearing	Rivets—enclosed . . . . . Shop	30000
	Rivets and Turned Bolts . . . . . Field	10000		Rivets—one side . . . . . Shop	24000
	Rough Bolts . . . . . Field	8000		Rivets and Turned Bolts, Field	20000
				Rough Bolts . . . . . Field	16000

t=Web thickness, in bearing, to develop max. allowable reactions, when beams frame opposite. Connections are figured for bearing and shear (no moment considered).

The above values agree with tests made on beams under ordinary conditions of use.

Where web is enclosed between connection angles (enclosed bearing), values are greater because of the increased efficiency due to friction and grip.

Special connections shall be used when any of the limiting conditions given above are exceeded—such as end reaction from loaded beam being greater than value of connection; shorter span with beam fully loaded; or a less thickness of web when maximum allowable reactions are used.


# CARNEGIE STEEL COMPANY

## BEAM SEPARATORS


AMERICAN BRIDGE COMPANY STANDARD

Depth, Inches	Beams			Separator				5/8" Bolts		
	Weight per Foot, Pounds	Center to Center of Beams, Inches	Out to Out of Flanges, Inches	Dimensions				Length, Inches	Weight, Pounds	Increase in Weight for 1" Add. Length
				w In.	h In.	d In.	t In.			
24	115-110-105	8 3/4	16 3/4	8	20	12	3/8	31	3.6	10 1/2
24	100	8	15 1/4	7 1/4	20	12	3/8	28	3.6	10
	95 and 90	8	15 1/4	7 1/4	20	12	3/8	28	3.6	10
	85	8	15 1/4	7 1/4	20	12	3/8	29	3.6	9 1/2
	80	8	15	7 1/4	20	12	3/8	29	3.6	9 1/2
20	100 and 95	8	15 1/4	7 1/4	16	12	3/8	22	2.9	10
	90	7 1/2	14 3/4	6 3/4	16	12	3/8	22	2.9	9 1/2
	85 and 80	7 1/2	14 3/4	6 3/4	16	12	3/8	22	2.9	9
	75	7 1/2	14	6 3/4	16	12	3/8	22	2.9	9
20	70	7	13 3/4	6 1/2	16	12	3/8	21	2.9	9
	65	7	13 3/4	6 1/2	16	12	3/8	21	2.9	8 1/2
	60	8	15 1/4	7 1/4	14	9	3/8	20	2.5	10
	55	8	15 1/4	7 1/4	14	9	3/8	21	2.5	10
18	85 and 80	8	15 1/4	7 1/4	14	9	3/8	21	2.5	10
	75	8	15	7 1/4	14	9	3/8	21	2.5	10
	70 and 65	7	13 3/4	6 1/4	14	9	3/8	18	2.5	9
	60	7	13 3/4	6 1/4	14	9	3/8	19	2.5	8 1/2
18	55	7	13	6 1/4	14	9	3/8	19	2.5	8 1/2
	75	7	13 3/4	6	11	7 1/2	3/4	12	1.6	9
	70 and 65	7	13 1/4	6 1/4	11	7 1/2	3/4	11	1.6	8
	60	6 1/2	12 3/4	5 3/4	11	7 1/2	3/4	11	1.6	8
15	50 and 45	6 1/2	12 3/4	6	11	7 1/2	3/4	12	1.6	8
	42	6 1/2	12	6	11	7 1/2	3/4	12	1.6	8
	55	6	11 3/4	5 1/4	8 3/4	5	1/2	9	1.3	8
	50	6	11 3/4	5 1/4	8 3/4	5	1/2	9	1.3	8
12	45	6	11 3/4	5 1/4	8 3/4	5	1/2	9	1.3	7 1/2
	40 and 35	6	11 3/4	5 1/4	8 3/4	5	1/2	9	1.3	7 1/2
	31.5	6	11	5 1/2	8 3/4	5	1/2	9	1.3	7 1/2
10	40	5 1/2	10 3/4	4 3/4	7 1/2	5	1/2	6	1.1	7 1/2
	35	5 1/2	10 3/4	4 3/4	7 1/2	5	1/2	6	1.1	7
	30	5 1/2	10 1/2	5	7 1/2	5	1/2	7	1.1	7
	25	5 1/2	10	5	7 1/2	5	1/2	7	1.1	7
9	35	5	10	4 1/4	6 1/2	5	1/2	5	0.9	7
	30	5	9 3/4	4 1/4	6 1/2	5	1/2	5	0.9	6 1/2
	25	5	9 3/4	4 1/4	6 1/2	5	1/2	5	0.9	6 1/2
	21	5	9 3/4	4 1/4	6 1/2	5	1/2	5	0.9	6 1/2
8	25.5	4 3/4	9	4	5 1/2	5	1/2	4	0.8	6
	23	4 3/4	8 3/4	4	5 1/2	5	1/2	4	0.8	6
	20.5 and 18	4 3/4	8 3/4	4	5 1/2	5	1/2	4	0.8	6
	20	4 3/4	8 1/4	4	5	5	1/2	4	0.7	6
7	17.5	4 3/4	8 1/4	4	5	5	1/2	4	0.7	6
	15	4 3/4	8 1/4	4 1/4	5	5	1/2	4	0.7	6
	17.25	4	7 3/4	3 1/2	4 1/2	5	1/2	4	0.6	5 1/2
	14.75	4	7 3/4	3 1/2	4 1/2	5	1/2	4	0.6	5 1/2
6	12.25	4	7 3/4	3 1/2	4 1/2	5	1/2	4	0.6	5 1/2
	12.25	4	7 3/4	3 1/2	4 1/2	5	1/2	4	0.6	5 1/2

Diagrams



3/8" Cored Holes




3/8" Cored Hole

For 5", 4" and 3" beams, use 1" gas pipe 3 1/4", 3" and 2 3/4" long respectively.

## STRUCTURAL DETAILS

### TIE RODS AND ANCHORS

AMERICAN BRIDGE COMPANY STANDARD



#### 1/2 INCH TIE RODS


LENGTHS AND WEIGHTS FOR VARIOUS DISTANCES C. TO C. OF BEAMS

Weights include two Nuts

C. to C. Ft.-In.	Length Ft.-In.	Weight Pounds	C. to C. Ft.-In.	Length Ft.-In.	Weight Pounds	C. to C. Ft.-In.	Length Ft.-In.	Weight Pounds	C. to C. Ft.-In.	Length Ft.-In.	Weight Pounds
1-0	1-3	2.30	1-3	1-6	2.67	1-6	1-9	3.05	1-9	2-0	3.42
2-0	2-3	3.80	2-3	2-6	4.17	2-6	2-9	4.55	2-9	3-0	4.92
3-0	3-3	5.30	3-3	3-6	5.67	3-6	3-9	6.05	3-9	4-0	6.42
4-0	4-3	6.80	4-3	4-6	7.17	4-6	4-9	7.55	4-9	5-0	7.92
5-0	5-3	8.30	5-3	5-6	8.67	5-6	5-9	9.05	5-9	6-0	9.42
6-0	6-3	9.80	6-3	6-6	10.17	6-6	6-9	10.55	6-9	7-0	10.92
7-0	7-3	11.30	7-3	7-6	11.67	7-6	7-9	12.05	7-9	8-0	12.42
8-0	8-3	12.80	8-3	8-6	13.17	8-6	8-9	13.55	8-9	9-0	13.92

### ANCHORS


#### SWEDGE BOLT



Weight includes Nut


Diameter Inches	Length Feet - Inches	Weight Pounds
3/4	0-9	1.3
7/8	1-0	2.3
1	1-0	3.1
1 1/4	1-3	6.1

#### GOVERNMENT ANCHOR




3/4" Rod 1' 9" long. Wt., 3 lbs.

#### BUILT-IN ANCHOR BOLTS



When center to center of anchors is less than width of washer, use washer with two holes.

#### ANGLE ANCHOR



2 Angles 6" x 4" x 7/16" x 0' 2 1/2"  
Weight with 3/4" bolts, 7 lbs.



# CARNEGIE STEEL COMPANY

## BEARING PLATES


The size and thickness of steel bearing plates depend on the end reaction, length of bearing, and unit pressure. The following table gives sizes for beams of usual spans, the allowable safe loads in thousands of pounds and the span of beams giving equivalent end reactions.

### STANDARD BEARING PLATES

Beam		Bearing Plate					Beam		Bearing Plate					Lim. Span of Beam, Ft.	
Depth, In.	Wt. Lbs. per Ft.	Wall Bearing, Inches	Size, In.	Wt. Lbs.	Max. Safe Load	Lim. Span of Beam, Ft.	Depth, In.	Wt. Lbs. per Ft.	Wall Bearing, Inches	Size, In.	Wt. Lbs.	Max. Safe Load	Lim. Span of Beam, Ft.	Lim. Span of Beam, Ft.	
27	83	16	16x16x1	73	40.2	28.4	10	25	8	12x8x3/4	21	13.1	9.9		
24	80	16	16x16x1	73	37.9	24.5	9	21	8	12x8x3/4	17	8.7	11.6		
21	57.50	16	16x16x1	73	35.9	17.4	8	18	8	8x8x3/4	12	16.7	4.5		
20	65	16	16x16x1	73	35.0	17.8	7	15	8	8x8x3/4	12	15.4	3.6		
18	55	16	16x16x1	73	34.1	13.8	6	12.25	6	6x6x1/2	5	12.0	3.2		
15	60	16	16x16x1	73	34.1	12.6	5	9.75	6	6x6x1/2	5	10.7	2.4		
15	42	12	12x12x3/4	55	24.4	12.9	4	7.50	4	4x4x3/4	2	9.0	1.8		
12	31.50	12	12x12x3/4	31	20.6	9.3	3	5.50	4	4x4x3/4	2	7.2	1.3		

Allowable loads given for standard beams will apply also to supplementary and other beams of equal depth and end reactions.

Plates of special sizes may be taken from the table of projection coefficients given below, calculated from the following formula. Let



A=length of bearing plate, in inches.

B=width of bearing plate, in inches.

t=thickness of bearing plate, in inches.

b=flange width of beam, in inches.

R=reaction on bearing plate, in pounds.

w=R÷AxB, allowable unit pressure on masonry.

$$M = \frac{R(B-b)}{8} = \frac{wAB(B-b)}{8} = fS = \frac{fAt^2}{6}; B(B-b) = \frac{4ft^2}{3w}, \text{ or when } f = 16000,$$

$$B(B-b) = \frac{64000 t^2}{3w}, \text{ the same as the formula for rolled steel slabs, page 259.}$$

**RULE:**—Take from table on opposite page the proper size bearing plate for the reaction and unit pressure. Multiply the width of the plate by the width minus the width of the beam flange and select from the table below the thickness corresponding to the value for the given unit pressure.

### PROJECTION COEFFICIENTS

Unit Pressure, Lbs. per Sq. In.	Thickness of Bearing Plates, in Inches															
	%	$\frac{1}{2}$	$\frac{3}{8}$	$\frac{1}{4}$	$\frac{3}{16}$	1	$\frac{1}{2}$	$\frac{1}{4}$	$\frac{1}{8}$	$\frac{1}{16}$	$\frac{1}{32}$	$\frac{1}{64}$	$\frac{1}{128}$	$\frac{1}{256}$	$\frac{1}{512}$	2
75	40.0	71.1	111.1	160	218	284	360	444	538	640	751	871	1000	1138		
100	30.0	53.3	83.3	120	163	213	270	333	403	480	563	653	750	853		
125	24.0	42.7	67.7	96	131	171	216	267	323	384	451	523	600	683		
150	20.0	35.6	55.6	80	109	142	180	222	269	320	376	436	500	569		
175	17.1	30.5	47.6	69	93	122	154	190	230	274	322	373	429	488		
200	15.0	26.7	41.7	60	82	107	135	167	202	240	282	327	375	427		
250	12.0	21.3	33.3	48	65	85	108	133	161	192	225	261	300	341		
300	10.0	17.8	27.8	40	54	71	90	111	134	160	188	218	250	284		
350	8.6	15.2	23.8	34	47	61	77	95	115	137	161	187	214	244		
400	7.5	13.3	20.8	30	41	53	68	83	101	120	141	163	188	213		

# STRUCTURAL DETAILS

## BEARING PLATES

SAFE RESISTANCES IN THOUSANDS OF POUNDS

Wall Bearing, Inches	Bearing Plates		Pressure in Pounds per Square Inch									
	Length, Inches	Width, Inches	75	100	125	150	175	200	250	300	350	400
4	4	4	1.2	1.6	2.0	2.4	2.8	3.2	4.0	4.8	5.6	6.4
4	4	6	1.8	2.4	3.0	3.6	4.2	4.8	6.0	7.2	8.4	9.6
4	4	8	2.4	3.2	4.0	4.8	5.6	6.4	8.0	9.6	11.2	12.8
6	6	6	2.7	3.6	4.5	5.4	6.3	7.2	9.0	10.8	12.6	14.4
6	6	8	3.6	4.8	6.0	7.2	8.4	9.6	12.0	14.4	16.8	19.2
6	6	10	4.5	6.0	7.5	9.0	10.5	12.0	15.0	18.0	21.0	24.0
8	8	8	4.8	6.4	8.0	9.6	11.2	12.8	16.0	19.2	22.4	25.6
8	8	10	6.0	8.0	10.0	12.0	14.0	16.0	20.0	24.0	28.0	32.0
8	8	12	7.2	9.6	12.0	14.4	16.8	19.2	24.0	28.8	33.6	38.4
10	10	10	7.5	10.0	12.5	15.0	17.5	20.0	25.0	30.0	35.0	40.0
10	10	12	9.0	12.0	15.0	18.0	21.0	24.0	30.0	36.0	42.0	48.0
10	10	14	10.5	14.0	17.5	21.0	24.5	28.0	35.0	42.0	49.0	56.0
12	12	12	10.8	14.4	18.0	21.6	25.2	28.8	36.0	43.2	50.4	57.6
12	12	14	12.6	16.8	21.0	25.2	29.4	33.6	42.0	50.4	58.8	67.2
12	12	16	14.4	19.2	24.0	28.8	33.6	38.4	48.0	57.6	67.2	76.8
14	14	14	14.7	19.6	24.5	29.4	34.3	39.2	49.0	58.8	68.6	78.4
14	14	16	16.8	22.4	28.0	33.6	39.2	44.8	56.0	67.2	78.4	89.6
14	14	18	18.9	25.2	31.5	37.8	44.1	50.4	63.0	75.6	88.2	100.8
14	14	20	21.0	28.0	35.0	42.0	49.0	56.0	70.0	84.0	98.0	112.0
16	16	16	19.2	25.6	32.0	38.4	44.8	51.2	64.0	76.8	89.6	102.4
16	16	18	21.6	28.8	36.0	43.2	50.4	57.6	72.0	86.4	100.8	115.2
16	16	20	24.0	32.0	40.0	48.0	56.0	64.0	80.0	96.0	112.0	128.0
16	16	22	26.4	35.2	44.0	52.8	61.6	70.4	88.0	105.6	123.2	140.8
18	18	18	24.3	32.4	40.5	48.6	56.7	64.8	81.0	97.2	113.4	129.6
18	18	20	27.0	36.0	45.0	54.0	63.0	72.0	90.0	108.0	126.0	144.0
18	18	22	29.7	39.6	49.5	59.4	69.3	79.2	99.0	118.8	138.6	158.4
18	18	24	32.4	43.2	54.0	64.8	75.6	86.4	108.0	129.6	151.2	172.8
20	20	20	30.0	40.0	50.0	60.0	70.0	80.0	100.0	120.0	140.0	160.0
20	20	22	33.0	44.0	55.0	66.0	77.0	88.0	110.0	132.0	154.0	176.0
20	20	24	36.0	48.0	60.0	72.0	84.0	96.0	120.0	144.0	168.0	192.0
20	20	26	39.0	52.0	65.0	78.0	91.0	104.0	130.0	156.0	182.0	208.0
22	22	22	36.3	48.4	60.5	72.6	84.7	96.8	121.0	145.2	169.4	193.6
22	22	24	39.6	52.8	66.0	79.2	92.4	105.6	132.0	158.4	184.8	211.2
22	22	26	42.9	57.2	71.5	85.8	100.1	114.4	143.0	171.6	200.2	228.8
22	22	28	46.2	61.6	77.0	92.4	107.8	123.2	154.0	184.8	215.6	246.4
24	24	24	43.2	57.6	72.0	86.4	100.8	115.2	144.0	172.8	201.6	230.4
24	24	26	46.8	62.4	78.0	93.6	109.2	124.8	156.0	187.2	218.4	249.6
24	24	28	50.4	67.2	84.0	100.8	117.6	134.4	168.0	201.6	235.2	268.8
24	24	30	54.0	72.0	90.0	108.0	126.0	144.0	180.0	216.0	252.0	288.0

# CARNEGIE STEEL COMPANY

## DETAILS FOR PUNCHING AND RIVETING

AMERICAN BRIDGE COMPANY STANDARD

### CONVENTIONAL SIGNS FOR RIVETING

Shop Rivets				Field Rivets				Shop Rivets					
Countersunk and chipped				Countersunk and chipped				Countersunk but not chipped		Flattened to $\frac{1}{4}$ " high		Flattened to $\frac{3}{8}$ " high	
Max. height, $\frac{1}{8}$ "				Max. height, $\frac{1}{8}$ "				Max. height, $\frac{1}{8}$ "		Max. height, $\frac{1}{8}$ "		Max. height, $\frac{1}{8}$ "	
Two full heads				Two full heads				Near side		Far side		Both sides	
Near side				Near side				Near side		Far side		Both sides	
Far side				Far side				Far side		Far side		Both sides	
Both sides				Both sides				Both sides		Both sides		Both sides	



### GAGES FOR ANGLES, INCHES

Leg	8	7	6	5	4	3½	3	2½	2	1½	1¼	1⅜	1¼	1	¾
g1	4½	4	3½	3	2½	2	1¾	1½	1¼	1	¾	¾	¾	¾	¾
g2	3	2½	2½	2											
g3	3	3	2½	1¾											
Max. rivet	1½	1	¾	¾	¾	¾	¾	¾	¾	¾	¾	¾	¾	¾	¾

For column details, 6" leg ( $\frac{1}{2}$  inch thick or less) against column shaft,  $g^2 = 1\frac{3}{4}$ ",  $g^1 = 3$ ".  
For diagonal angles, etc., gage in middle, where riveted leg equals or exceeds 3" for  $\frac{3}{4}$ " rivets,  $3\frac{1}{2}$ " for  $\frac{5}{8}$ " rivets.

Use special gages to adapt work to multiple punch, or to secure desirable details.

### CLEARANCE FOR WEB RIVETING

Min. Riv. Holes	For $\frac{5}{8}$ " Rivets
$\frac{7}{8}$ "	$1\frac{1}{8}$ "
$1\frac{1}{8}$ "	$1\frac{1}{4}$ "
$1\frac{1}{4}$ "	$1\frac{3}{8}$ "
$1\frac{1}{2}$ "	$1\frac{1}{2}$ "
$1\frac{3}{4}$ "	$1\frac{3}{4}$ "

### RIVETS IN CRIMPED ANGLES



Distance x should be  $1\frac{1}{2}$ " plus thickness of chord angles, but never less than 2".

### STANDARD RIVET DIES

2"	For $\frac{5}{8}$ " Rivets	
$2\frac{1}{4}$ "	" $\frac{3}{4}$ "	"
$2\frac{1}{2}$ "	" $\frac{7}{8}$ "	"
$2\frac{3}{4}$ "	" 1"	"
3"	" $1\frac{1}{4}$ "	"

### CLEARANCE FOR COVER PLATE RIVETING

Dimensions in Inches


e	d	d	d	d	d	d	d	d	d	d	d	d	d	d	d
$\frac{1}{2}$	1	1½	2	2½	3	3½	4	4½	5	5½	6				
$2\frac{1}{2}$	$2\frac{3}{4}$	$2\frac{3}{4}$	$2\frac{3}{4}$	$2\frac{3}{4}$	$2\frac{3}{4}$	$2\frac{3}{4}$	3	$3\frac{1}{8}$	$3\frac{1}{8}$	$3\frac{1}{8}$	$3\frac{1}{8}$	$3\frac{1}{8}$	$3\frac{1}{8}$	$3\frac{1}{8}$	$3\frac{1}{8}$
0	$\frac{1}{2}$	1	1½	2	2½										
$2\frac{1}{2}$	$2\frac{1}{4}$	$2\frac{1}{4}$	2	1½	0										

# STRUCTURAL DETAILS

## RIVET SPACING

AMERICAN BRIDGE COMPANY STANDARD

### MINIMUM STAGGER FOR RIVETS



Dia. of Rivet, Inches	Minimum stagger, d, inches															
	c, Inches															
5/8	1 1/8	1 1/4	1 1/2	1 3/4	1 7/8	2	2 1/8	2 1/4	2 3/8	2 1/2	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4
3/4	1 1/4	1 1/2	1 3/4	2	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8
7/8	1 1/2	1 3/4	2	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4
1	1 3/4	2	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4	3 3/4
1 1/4	2	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4	3 3/4	3 3/4

### DISTANCE CENTER TO CENTER OF STAGGERED RIVETS

Values of x for varying values of a and b


b, In.	a, Inches															
	5/8	1	1 1/8	1 1/4	1 1/2	1 3/4	1 7/8	2	2 1/8	2 1/4	2 3/8	2 1/2	2 5/8	2 3/4	2 7/8	3
1 1/8	1 1/8	1 1/4	1 1/2	1 3/4	1 7/8	2	2 1/8	2 1/4	2 3/8	2 1/2	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4
1 1/4	1 1/4	1 1/2	1 3/4	2	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8
1 1/2	1 1/2	1 3/4	2	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4
1 3/4	1 3/4	2	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4	3 3/4
2	2	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4	3 3/4	3 3/4
2 1/8	2 1/8	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4	3 3/4	3 3/4
2 1/4	2 1/4	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4	3 3/4	3 3/4	3 3/4
2 3/8	2 3/8	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4	3 3/4	3 3/4	3 3/4
2 1/2	2 1/2	2 3/4	2 5/8	2 3/4	2 7/8	3	3 1/8	3 1/4	3 1/2	3 3/4	3 5/8	3 3/4	3 3/4	3 3/4	3 3/4	3 3/4

Values below and to right of upper zigzag line are large enough for 5/8" rivets  
Values below and to right of lower zigzag line are large enough for 3/4" rivets.

### MINIMUM RIVET SPACING



Dia. of Rivet, Inches	1/4	3/8	1/2	5/8	3/4	7/8	1	1 1/4
x, Minimum, Inches	1	1 1/4	1 3/4	2	2 1/4	2 3/4	3	3 3/4



# CARNEGIE STEEL COMPANY

## REDUCTION OF AREA FOR RIVET HOLES


Area In Square Inches=Diameter of Hole by Thickness of Metal

Thickness of Metal, Inches	Diameter of Hole in Inches											
	1/4	1/2	3/8	5/8	1 1/8	3/4	1 1/4	7/8	1 3/8	1	1 1/2	1 3/4
1/8	.05	.09	.11	.12	.13	.14	.15	.16	.18	.19	.20	.21
1/4	.06	.13	.14	.16	.17	.19	.20	.22	.23	.25	.27	.28
3/8	.08	.16	.18	.20	.21	.23	.25	.27	.29	.31	.33	.35
1/2	.09	.19	.21	.23	.26	.28	.30	.33	.35	.38	.40	.42
5/8	.11	.22	.25	.27	.30	.33	.36	.38	.41	.44	.46	.49
3/4	.13	.25	.28	.31	.34	.38	.41	.44	.47	.50	.53	.56
7/8	.14	.28	.32	.35	.39	.42	.46	.49	.53	.56	.60	.63
1	.16	.31	.35	.39	.43	.47	.51	.55	.59	.63	.66	.70
1 1/8	.17	.34	.39	.43	.47	.52	.56	.60	.64	.69	.73	.77
1 1/4	.19	.38	.42	.47	.52	.56	.61	.66	.70	.75	.80	.84
1 3/8	.20	.41	.46	.51	.56	.61	.66	.71	.76	.81	.86	.91
1 1/2	.22	.44	.49	.55	.60	.66	.71	.77	.82	.88	.93	.98
1 3/4	.23	.47	.53	.59	.64	.70	.76	.82	.88	.94	1.00	1.05
1	.25	.50	.56	.63	.69	.75	.81	.88	.94	1.00	1.06	1.13
1 1/8	.27	.53	.60	.66	.73	.80	.86	.93	1.00	1.06	1.13	1.20
1 1/4	.28	.56	.63	.70	.77	.84	.91	.98	1.05	1.13	1.20	1.27
1 3/8	.30	.59	.67	.74	.82	.89	.96	1.04	1.11	1.19	1.26	1.34
1 1/2	.31	.63	.70	.78	.86	.94	1.02	1.09	1.17	1.25	1.33	1.41
1 3/4	.33	.66	.74	.82	.90	.98	1.07	1.15	1.23	1.31	1.39	1.48
1 7/8	.34	.69	.77	.86	.95	1.03	1.12	1.20	1.29	1.38	1.46	1.55
1 5/8	.36	.72	.81	.90	.99	1.08	1.17	1.26	1.35	1.44	1.53	1.62
1 1/2	.38	.75	.84	.94	1.03	1.13	1.22	1.31	1.41	1.50	1.59	1.69


## STAGGER OF RIVETS TO MAINTAIN NET SECTION

AMERICAN BRIDGE COMPANY STANDARD

1 Hole Out



2 Holes Out



Dimensions in Inches

a	3/4" Rivet	7/8" Rivet	a1	3/4" Rivet	7/8" Rivet
	b	b		b	b
1	1 1/8	1 3/8	5	3 1/8	3 3/8
1 1/2	1 3/8	2	5 1/2	3 3/8	3 3/8
2	2 1/8	2 1/4	6	3 3/8	3 3/8
2 1/2	2 3/8	2 3/8	6 1/2	3 3/8	3 3/8
3	2 3/4	2 3/4	7	3 3/8	3 3/8
3 1/2	2 3/4	2 3/4	7 1/2	3 3/8	3 3/8
4	2 3/4	3	8	3 3/8	3 3/8
4 1/2	2 3/4	3 1/8	8 1/2	4	4 1/8

y=diameter of rivet + 1/8"

$$a-y = \sqrt{a^2 + b^2} - 2y$$

$$b = \sqrt{2ay + y^2}$$

$$a1 - 2y = \sqrt{a^2 + b^2} - 3y$$

$$b = \sqrt{2ay + y^2}$$

a=sum of gauges minus thickness of angle.

3/8" rivets, can be taken at 1/8" less than for 3/4" rivets.

1" rivets, can be taken at 1/8" more than for 3/4" rivets.

## RIVETS AND PINS

### STRESSES IN RIVETS AND PINS

**Rivets.** In transmitting stresses between riveted pieces, it is customary to disregard friction and to proportion rivets to the entire stress to be transmitted. They must be of sufficient size and number to resist shear and to afford such bearing area as not to cause distortion of the metal at the rivet holes. In the case of beams which frame opposite and of single web girders, this latter condition often necessitates a greater thickness of web than required by the shearing stresses. In a plate girder with  $\frac{5}{16}$ " web,  $\frac{3}{4}$ " rivets connecting the web with the flange angles would have a bearing value at 24,000 pounds unit stress of 5,630 pounds per rivet, while their value in double shear at 12,000 pounds unit stress is 10,600 pounds per rivet; and it might be necessary to increase the web thickness to  $\frac{3}{8}$ " or more in order that the pressure of the rivets upon the metal be not excessive.

**Pins.** Pins must be calculated for shearing, bending and bearing stresses, but one of the latter two will in most cases determine the size. When groups of bars are connected to the same pin, as in the lower chord of truss bridges, the size of the bars must be so chosen and the bars so placed that at no point on the pin will there be any excessive bending stress. When the size of pin has been determined from the bending stress, the thickness of the bars or web of the post should be investigated to provide sufficient bearing area, the bars being thickened or pin plates added if necessary.


The following is the formula for flexure applied to pins:  $M = f \pi d^3 + 32$  or  $= f A d + 8$ , in which  $M$  = moment of forces for any section through pin,  $f$  = fiber stress per square inch in bending,  $A$  = the area of section,  $d$  = diameter,  $\pi = 3.14159$ . The forces are assumed to act in a plane passing through the axis of the pin.

**EXAMPLE 1.**—A pin, see figure, has to carry a load of 64,000 pounds; required the size at 24,000 pounds fiber stress, assuming the distance between points of support to be 5 inches.

Bending moment  $= 64,000 \times 5 \div 4 = 80,000$  inch pounds; use a  $3\frac{3}{4}$  inch pin; allowed moment: 80,900 inch pounds.

**EXAMPLE 2.**—Required the thickness of metal in the top chord of a bridge to give sufficient bearing area to a  $3\frac{3}{4}$  inch pin, having to transmit a stress of 121,400 pounds at an allowed bearing pressure of 24,000 pounds per square inch.

The bearing value of a  $3\frac{3}{4}$  inch pin for 1 inch thickness of metal is 81,000 pounds; therefore, the thickness of metal required  $= 121,400 \div 81,000 = 1\frac{1}{2}$  inch, or each web of the chord must be  $\frac{3}{4}$  inch thick, including pin plates.

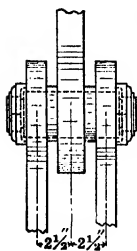

# CARNEGIE STEEL COMPANY

## RIVETS SHEARING AND BEARING VALUES

Values in Pounds, all Dimensions in Inches

### $\frac{3}{8}$ INCH RIVETS—Area .1104 Square Inch

Shear	Unit, Lbs. per Sq. In.	7000	8000	9000	10000	11000	12000
	Single Shear per Rivet	770	880	990	1100	1210	1320
	Double Shear per Rivet	1540	1760	1980	2200	2420	2640
Bearing	Unit, Lbs. per Sq. In.	14000	16000	18000	20000	22000	24000
	Thickness in Inches						
	$\frac{1}{8}$	660	750	840	940	1030	1130
	$\frac{1}{4}$	980	1130	1270	1410	1550	1690
	$\frac{3}{8}$	1310	1500	1690	1880	2060	2250
	$\frac{1}{2}$	1640	1880	2110	2340	2580	2810
	$\frac{5}{8}$	1910	2250	2530	2810	3090	3380

### $\frac{1}{2}$ INCH RIVETS—Area .1963 Square Inch

Shear	Unit, Lbs. per Sq. In.	7000	8000	9000	10000	11000	12000
	Single Shear per Rivet	1370	1570	1770	1960	2160	2360
	Double Shear per Rivet	2750	3140	3530	3930	4320	4710
Bearing	Unit, Lbs. per Sq. In.	14000	16000	18000	20000	22000	24000
	Thickness in Inches						
	$\frac{1}{8}$	1310	1500	1690	1880	2060	2250
	$\frac{1}{4}$	1750	2000	2250	2500	2750	3000
	$\frac{3}{8}$	2190	2500	2810	3130	3440	3750
	$\frac{1}{2}$	2630	3000	3380	3750	4130	4500
	$\frac{5}{8}$	3060	3500	3940	4380	4810	5250
	$\frac{3}{4}$	3500	4000	4500	5000	5500	6000

### $\frac{5}{8}$ INCH RIVETS—Area .3068 Square Inch

Shear	Unit, Lbs. per Sq. In.	7000	8000	9000	10000	11000	12000
	Single Shear per Rivet	2150	2450	2760	3070	3370	3680
	Double Shear per Rivet	4300	4910	5520	6140	6750	7360
Bearing	Unit, Lbs. per Sq. In.	14000	16000	18000	20000	22000	24000
	Thickness in Inches						
	$\frac{1}{8}$	1640	1880	2110	2340	2580	2810
	$\frac{1}{4}$	2190	2500	2810	3130	3440	3750
	$\frac{3}{8}$	2730	3130	3520	3910	4300	4690
	$\frac{1}{2}$	3280	3750	4220	4690	5160	5630
	$\frac{5}{8}$	3830	4380	4920	5470	6020	6560
	$\frac{3}{4}$	4380	5000	5630	6250	6880	7500
	$\frac{7}{8}$	4920	5630	6330	7030	7730	8440
	$\frac{15}{16}$	5470	6250	7040	7810	8590	9380

Values below dotted lines are greater than double shear.

# RIVETS AND PINS

## RIVETS SHEARING AND BEARING VALUES

Values in Pounds, Dimensions in Inches

### 3/4 INCH RIVETS—Area .4418 Square Inch

Shear	Unit, Lbs. per Sq. In.	7000	8000	9000	10000	11000	12000
	Single Shear per Rivet	3090	3530	3980	4420	4860	5300
Bearing	Double Shear per Rivet	6190	7070	7950	8840	9720	10600
	Unit, Lbs. per Sq. In.	14000	16000	18000	20000	22000	24000
Thickness in Inches	1/4	2630	3000	3380	3750	4130	4500
	1/8	3280	3750	4220	4690	5160	5630
	3/16	3940	4500	5060	5630	6190	6750
	1/2	4590	5250	5910	6560	7220	7880
	5/8	5250	6000	6750	7500	8250	9000
	3/4	5910	6750	7590	8440	9280	10130
	7/8	6560	7500	8440	9380	10310	11250
	1						

### 7/8 INCH RIVETS—Area .6013 Square Inch

Shear	Unit, Lbs. per Sq. In.	7000	8000	9000	10000	11000	12000
	Single Shear per Rivet	4210	4810	5410	6010	6610	7220
Bearing	Double Shear per Rivet	8420	9620	10820	12030	13230	14430
	Unit, Lbs. per Sq. In.	14000	16000	18000	20000	22000	24000
Thickness in Inches	1/4	3060	3500	3940	4380	4810	5250
	1/8	3830	4380	4920	5470	6020	6560
	3/16	4590	5250	5910	6560	7220	7880
	1/2	5360	6130	6890	7660	8420	9190
	5/8	6130	7000	7880	8750	9630	10500
	3/4	6890	7880	8860	9840	10830	11810
	7/8	7660	8750	9840	10940	12030	13130
	1	8420	9630	10830	12030	13230	14430

### 1 INCH RIVETS—Area .7854 Square Inch

Shear	Unit, Lbs. per Sq. In.	7000	8000	9000	10000	11000	12000
	Single Shear per Rivet	5500	6280	7070	7850	8640	9420
Bearing	Double Shear per Rivet	11000	12570	14140	15710	17280	18850
	Unit, Lbs. per Sq. In.	14000	16000	18000	20000	22000	24000
Thickness in Inches	1/4	3500	4000	4500	5000	5500	6000
	1/8	4380	5000	5630	6250	6880	7500
	3/16	5250	6000	6750	7500	8250	9000
	1/2	6130	7000	7880	8750	9630	10500
	5/8	7000	8000	9000	10000	11000	12000
	3/4	7880	9000	10130	11250	12380	13500
	7/8	8750	10000	11250	12500	13750	15000
	1	9630	11000	12380	13750	15130	16500
	3/4	10500	12000	13500	15000	16500	18000
	1 1/4	11380	13000	14630	16250	17880	19500

Values above upper dotted lines are less than single shear.  
Values below lower dotted lines are greater than double shear.



# CARNEGIE STEEL COMPANY

## PINS

### BEARING VALUES IN POUNDS ON METAL ONE INCH THICK

Bearing Value=Diameter of Pin x Bearing Stress per Square Inch

Pin		Bearing Stresses in Pounds per Square Inch				
Diameter, Inches	Area, Sq. In.	12000	15000	20000	22000	24000
1	.785	12000	15000	20000	22000	24000
1 1/4	1.227	15000	18800	25000	27500	30000
1 1/2	1.767	18000	22500	30000	33000	36000
1 3/4	2.405	21000	26300	35000	38500	42000
2	3.142	24000	30000	40000	44000	48000
2 1/4	3.976	27000	33800	45000	49500	54000
2 1/2	4.909	30000	37500	50000	55000	60000
2 3/4	5.940	33000	41300	55000	60500	66000
3	7.069	36000	45000	60000	66000	72000
3 1/4	8.296	39000	48800	65000	71500	78000
3 1/2	9.621	42000	52500	70000	77000	84000
3 3/4	11.045	45000	56300	75000	82500	90000
4	12.566	48000	60000	80000	88000	96000
4 1/4	14.186	51000	63800	85000	93500	102000
4 1/2	15.904	54000	67500	90000	99000	108000
4 3/4	17.721	57000	71300	95000	104500	114000
5	19.635	60000	75000	100000	110000	120000
5 1/4	21.648	63000	78800	105000	115500	126000
5 1/2	23.758	66000	82500	110000	121000	132000
5 3/4	25.967	69000	86300	115000	126500	138000
6	28.274	72000	90000	120000	132000	144000
6 1/4	30.680	75000	93800	125000	137500	150000
6 1/2	33.183	78000	97500	130000	143000	156000
6 3/4	35.785	81000	101300	135000	148500	162000
7	38.485	84000	105000	140000	154000	168000
7 1/4	41.282	87000	108800	145000	159500	174000
7 1/2	44.179	90000	112500	150000	165000	180000
7 3/4	47.173	93000	116300	155000	170500	186000
8	50.265	96000	120000	160000	176000	192000
8 1/4	53.456	99000	123800	165000	181500	198000
8 1/2	56.745	102000	127500	170000	187000	204000
8 3/4	60.132	105000	131300	175000	192500	210000
9	63.617	108000	135000	180000	198000	216000
9 1/4	67.201	111000	138800	185000	203500	222000
9 1/2	70.882	114000	142500	190000	209000	228000
9 3/4	74.662	117000	146300	195000	214500	234000
10	78.540	120000	150000	200000	220000	240000
10 1/4	82.516	123000	153800	205000	225500	246000
10 1/2	86.590	126000	157500	210000	231000	252000
10 3/4	90.763	129000	161300	215000	236500	258000
11	95.033	132000	165000	220000	242000	264000
11 1/4	99.402	135000	168800	225000	247500	270000
11 1/2	103.869	138000	172500	230000	253000	276000
11 3/4	108.434	141000	176300	235000	258500	282000
12	113.097	144000	180000	240000	264000	288000

# RIVETS AND PINS

## PINS

### BENDING MOMENTS IN INCH POUNDS

Bending Moment=(Diameter of Pin)<sup>3</sup> x 0.098175 x Stress per Square Inch

Pin		Fiber Stress in Pounds per Square Inch						
Diameter, Inches	Area, Sq. In.	15000	18000	20000	22000	22500	24000	25000
1	.785	1500	1800	2000	2200	2200	2400	2500
1 1/4	1.227	2900	3500	3800	4200	4300	4600	4800
1 1/2	1.767	5000	6000	6600	7300	7500	8000	8300
1 3/4	2.405	7900	9500	10500	11600	11800	12600	13200
2	3.142	11800	14100	15700	17300	17700	18800	19600
2 1/4	3.976	16800	20100	22400	24600	25200	26800	28000
2 1/2	4.909	23000	27600	30700	33700	34500	36800	38300
2 3/4	5.940	30600	36800	40800	44900	45900	49000	51000
3	7.069	39800	47700	53000	58300	59600	63600	66300
3 1/4	8.296	50600	60700	67400	74100	75800	80900	84300
3 1/2	9.621	63100	75800	84200	92600	94700	101000	105200
3 3/4	11.045	77700	93200	103500	113900	116500	124300	129400
4	12.566	94200	113100	125700	138200	141400	150800	157100
4 1/4	14.186	113000	135700	150700	165800	169600	180900	188400
4 1/2	15.904	134200	161000	178900	196800	201300	214700	223700
4 3/4	17.721	157800	189400	210400	231500	236700	252500	263000
5	19.635	184100	220900	245400	270000	276100	294500	306800
5 1/4	21.648	213100	255700	284100	312500	319600	339000	352200
5 1/2	23.758	245000	294000	326700	359300	367500	392000	408300
5 3/4	25.967	280000	336000	373300	410600	419200	447900	466600
6	28.274	318100	381700	424100	466500	477100	508900	530100
6 1/4	30.680	359500	431400	479400	527300	539300	575200	599200
6 1/2	33.183	404400	485300	539200	593100	606600	647100	674000
6 3/4	35.785	452900	543500	603900	664300	679400	724600	754800
7	38.485	505100	606100	673500	740800	757700	808200	841800
7 1/4	41.282	561200	673400	748200	823100	841800	897900	935300
7 1/2	44.179	621300	745500	828400	911200	931000	994000	1035400
7 3/4	47.173	685500	822600	914000	1005400	1028200	1096800	1142500
8	50.265	754000	904800	1005300	1105800	1131000	1206400	1256600
8 1/4	53.456	826900	992300	1102500	1212800	1240400	1323000	1378200
8 1/2	56.745	904400	1085300	1205800	1326400	1356600	1447000	1507300
8 3/4	60.132	986500	1183900	1315400	1446900	1479800	1578500	1644200
9	63.617	1073500	1288300	1431400	1574500	1610300	1717700	1789200
9 1/4	67.201	1165500	1398600	1554000	1709400	1748300	1864800	1942500
9 1/2	70.882	1262600	1515100	1683500	1851800	1893900	2020100	2104300
9 3/4	74.662	1364900	1637900	1819900	2001900	2047400	2183900	2274900
10	78.540	1472600	1767100	1963500	2159800	2208900	2356200	2454400
10 1/4	82.516	1585900	1903000	2114500	2325000	2378800	2537400	2643100
10 1/2	86.590	1704700	2045700	2273000	2506300	2557100	2727600	2841200
10 3/4	90.763	1829400	2195300	2439200	2683200	2744100	2927100	3049100
11	95.033	1960100	2352100	2613400	2874800	2940100	3136100	3266800
11 1/4	99.402	2096800	2510100	2795700	3075200	3145100	3354800	3494600
11 1/2	103.889	2239700	2687600	2986200	3284900	3359500	3583500	3732800
11 3/4	108.434	2388900	2866700	3185300	3503800	3583400	3822300	3981800
12	113.097	2544700	3053600	3392900	3732200	3817000	4071500	4241200

# CARNEGIE STEEL COMPANY

## ANGLES

### ALLOWABLE TENSION VALUES IN THOUSANDS OF POUNDS

Maximum Fiber Stress, 16000 Pounds per Square Inch

Size, Inches	Thick- ness, Inches	Weight per Foot, Pounds	Area, Inches <sup>2</sup>	Net Area and Stresses—Two Holes Deducted					
				¾ Inch Rivets		¾ Inch Rivets		¾ Inch Rivets	
				Area, Inches <sup>2</sup>	Stress	Area, Inches <sup>2</sup>	Stress	Area, Inches <sup>2</sup>	Stress
8 x 8	1	51.0	15.00	13.00	208.0	13.25	212.0		
8 x 8	1 1/8	48.1	14.12	12.24	195.8	12.48	199.7		
8 x 8	1 1/4	45.0	13.23	11.48	183.7	11.70	187.2		
8 x 8	1 1/2	42.0	12.34	10.72	171.5	10.92	174.7		
8 x 8	1 3/4	38.9	11.44	9.94	159.0	10.13	162.1		
8 x 8	1 7/8	35.8	10.53	9.16	146.6	9.33	149.3		
8 x 8	2	32.7	9.61	8.36	133.8	8.52	136.3	8.67	138.7
8 x 8	2 1/8	29.6	8.68	7.55	120.8	7.70	123.2	7.84	125.4
8 x 8	2 1/4	26.4	7.75	6.75	108.0	6.87	109.9	7.00	112.0
8 x 6	1	44.2	13.00	11.00	176.0	11.25	180.0		
8 x 6	1 1/8	41.7	12.25	10.37	165.9	10.61	169.8		
8 x 6	1 1/4	39.1	11.48	9.73	155.7	9.95	159.2		
8 x 6	1 1/2	36.5	10.72	9.10	145.6	9.30	148.8		
8 x 6	1 3/4	33.8	9.94	8.44	135.0	8.63	138.1		
8 x 6	1 7/8	31.2	9.15	7.78	124.5	7.95	127.2		
8 x 6	2	28.5	8.36	7.11	113.8	7.27	116.3	7.42	118.7
8 x 6	2 1/8	25.7	7.56	6.43	102.9	6.58	105.3	6.72	107.5
8 x 6	2 1/4	23.0	6.75	5.75	92.0	5.87	93.9	6.00	96.0
8 x 6	2 3/4	20.2	5.93	5.05	80.8	5.16	82.6	5.27	84.3
6 x 6	1 1/8	33.1	9.73	7.98	127.7	8.20	131.2		
6 x 6	1 1/4	31.0	9.09	7.47	119.5	7.67	122.7		
6 x 6	1 1/2	28.7	8.44	6.94	111.0	7.13	114.1		
6 x 6	1 3/4	26.5	7.78	6.41	102.6	6.58	105.3		
6 x 6	1 7/8	24.2	7.11	5.86	93.8	6.02	96.3	6.17	98.7
6 x 6	2	21.9	6.43	5.30	84.8	5.45	87.2	5.59	89.4
6 x 6	2 1/8	19.6	5.75	4.75	76.0	4.87	77.9	5.00	80.0
6 x 6	2 1/4	17.2	5.06	4.18	66.9	4.29	68.6	4.40	70.4
6 x 6	2 3/4	14.9	4.36	3.61	57.8	3.70	59.2	3.80	60.8
6 x 4	1 1/8	27.2	7.98	6.23	99.7	6.45	103.2		
6 x 4	1 1/4	25.4	7.47	5.85	93.6	6.05	96.8		
6 x 4	1 1/2	23.6	6.94	5.44	87.0	5.63	90.1		
6 x 4	1 3/4	21.8	6.40	5.03	80.5	5.20	83.2		
6 x 4	1 7/8	20.0	5.86	4.61	73.8	4.77	76.3	4.92	78.7
6 x 4	2	18.1	5.31	4.18	66.9	4.33	69.3	4.47	71.5
6 x 4	2 1/8	16.2	4.75	3.75	60.0	3.87	61.9	4.00	64.0
6 x 4	2 1/4	14.3	4.18	3.30	52.8	3.41	54.6	3.52	56.3
6 x 4	2 3/4	12.3	3.61	2.86	45.8	2.95	47.2	3.05	48.8
5 x 3 1/2	5/8	16.8	4.92	3.67	58.7	3.83	61.3	3.98	63.7
5 x 3 1/2	3/4	15.2	4.47	3.34	53.4	3.49	55.8	3.63	58.1
5 x 3 1/2	7/8	13.6	4.00	3.00	48.0	3.12	49.9	3.25	52.0
5 x 3 1/2	1	12.0	3.53	2.65	42.4	2.76	44.2	2.87	45.9
5 x 3 1/2	1 1/8	10.4	3.05	2.30	36.8	2.39	38.2	2.49	39.8
5 x 3 1/2	1 1/4	8.7	2.56	1.93	30.9	2.01	32.2	2.09	33.4
5 x 3	3/4	12.8	3.75	2.75	44.0	2.87	45.9	3.00	48.0
5 x 3	7/8	11.3	3.31	2.43	38.9	2.54	40.6	2.65	42.4
5 x 3	1	9.8	2.86	2.11	33.8	2.20	35.2	2.30	36.8
5 x 3	1 1/8	8.2	2.40	1.77	28.3	1.85	29.6	1.93	30.9

# TENSION VALUES

## ANGLES

### ALLOWABLE TENSION VALUES IN THOUSANDS OF POUNDS

Maximum Fiber Stress, 16000 Pounds per Square Inch

Size, Inches	Thick- ness, Inches	Weight per Foot, Pounds	Area, Inches <sup>2</sup>	Net Areas and Stresses—One Hole Deducted					
				¾ Inch Rivets		¾ Inch Rivets		¾ Inch Rivets	
				Area, Inches <sup>2</sup>	Stress	Area, Inches <sup>2</sup>	Stress	Area, Inches <sup>2</sup>	Stress
6 x 6	¾	33.1	9.73	8.85	141.6	8.96	143.4		
6 x 6	⅞	31.0	9.09	8.28	132.5	8.38	134.1		
6 x 6	⅞	28.7	8.44	7.69	123.0	7.78	124.5		
6 x 6	⅞	26.5	7.78	7.09	113.4	7.18	114.9		
6 x 6	⅞	24.2	7.11	6.48	103.7	6.56	105.0	6.64	106.2
6 x 6	⅞	21.9	6.43	5.87	93.9	5.94	95.0	6.01	96.2
6 x 6	⅞	19.6	5.75	5.25	84.0	5.31	85.0	5.37	85.9
6 x 6	⅞	17.2	5.06	4.62	73.9	4.68	74.9	4.73	75.7
6 x 6	⅞	14.9	4.36	3.98	63.7	4.03	64.5	4.08	65.3
6 x 4	¾	27.2	7.98	7.10	113.6	7.21	115.4		
6 x 4	⅞	25.4	7.47	6.66	106.6	6.76	108.2		
6 x 4	⅞	23.6	6.94	6.19	99.0	6.28	100.5		
6 x 4	⅞	21.8	6.40	5.71	91.4	5.80	92.8		
6 x 4	⅞	20.0	5.86	5.23	83.7	5.31	85.0	5.39	86.2
6 x 4	⅞	18.1	5.31	4.75	76.0	4.82	77.1	4.89	78.2
6 x 4	⅞	16.2	4.75	4.25	68.0	4.31	69.0	4.37	69.9
6 x 4	⅞	14.3	4.18	3.74	59.8	3.80	60.8	3.85	61.6
6 x 4	⅞	12.3	3.61	3.23	51.7	3.28	52.5	3.33	53.3
5 x 3½	¾	16.8	4.92	4.29	68.6	4.37	69.9	4.45	71.2
5 x 3½	⅞	15.2	4.47	3.91	62.6	3.98	63.7	4.05	64.8
5 x 3½	⅞	13.6	4.00	3.50	56.0	3.56	57.0	3.62	57.9
5 x 3½	⅞	12.0	3.53	3.09	49.4	3.15	50.4	3.20	51.2
5 x 3½	⅞	10.4	3.05	2.67	42.7	2.72	43.5	2.77	44.3
5 x 3½	⅞	8.7	2.56	2.25	36.0	2.29	36.6	2.33	37.3
5 x 3	¾	15.7	4.61	3.98	63.7	4.06	65.0	4.14	66.2
5 x 3	⅞	14.3	4.18	3.62	57.9	3.69	59.0	3.76	60.2
5 x 3	⅞	12.8	3.75	3.25	52.0	3.31	53.0	3.37	53.9
5 x 3	⅞	11.3	3.31	2.87	45.9	2.93	46.9	2.98	47.7
5 x 3	⅞	9.8	2.86	2.48	39.7	2.53	40.5	2.58	41.3
5 x 3	⅞	8.2	2.40	2.09	33.4	2.13	34.1	2.17	34.7
4 x 4	¾	15.7	4.61	3.98	63.7	4.06	65.0	4.14	66.2
4 x 4	⅞	14.3	4.18	3.62	57.9	3.69	59.0	3.76	60.2
4 x 4	⅞	12.8	3.75	3.25	52.0	3.31	53.0	3.37	53.9
4 x 4	⅞	11.3	3.31	2.87	45.9	2.93	46.9	2.98	47.7
4 x 4	⅞	9.8	2.86	2.48	39.7	2.53	40.5	2.58	41.3
4 x 4	⅞	8.2	2.40	2.09	33.4	2.13	34.1	2.17	34.7
4 x 4	⅞	6.6	1.94	1.69	27.0	1.72	27.5	1.75	28.0
4 x 3	¾	11.1	3.25	2.75	44.0	2.81	45.0	2.87	45.9
4 x 3	⅞	9.8	2.87	2.43	38.9	2.49	39.8	2.54	40.6
4 x 3	⅞	8.5	2.48	2.10	33.6	2.15	34.4	2.20	35.2
4 x 3	⅞	7.2	2.09	1.78	28.5	1.82	29.1	1.86	29.8
4 x 3	⅞	5.8	1.69	1.44	23.0	1.47	23.5	1.50	24.0

# CARNEGIE STEEL COMPANY

## ANGLES

### ALLOWABLE TENSION VALUES IN THOUSANDS OF POUNDS

Maximum Fiber Stress, 16000 Pounds per Square Inch

Size, Inches	Thick- ness, Inches	Weight per Foot, Pounds	Area, Inches <sup>2</sup>	Net Areas and Stresses—One Hole Deducted					
				½ Inch Rivets		¾ Inch Rivets		⅝ Inch Rivets	
				Area, Inches <sup>2</sup>	Stress	Area, Inches <sup>2</sup>	Stress	Area, Inches <sup>2</sup>	Stress
3 ½ x 3 ½	½	13.6	3.98	3.35	53.6	3.43	54.0	3.51	56.2
3 ½ x 3 ½	⅝	12.4	3.62	3.06	49.0	3.13	50.1	3.20	51.2
3 ½ x 3 ½	⅞	11.1	3.25	2.75	44.0	2.81	45.0	2.87	45.9
3 ½ x 3 ½	1	9.8	2.87	2.43	38.9	2.49	39.8	2.54	40.6
3 ½ x 3 ½	1 ¼	8.5	2.48	2.10	33.6	2.15	34.4	2.20	35.2
3 ½ x 3 ½	1 ½	7.2	2.09	1.78	28.5	1.82	29.1	1.86	29.8
3 ½ x 3 ½	1 ¾	5.8	1.69	1.44	23.0	1.47	23.5	1.50	24.0
3 ½ x 3	½	10.2	3.00	2.50	40.0	2.56	41.0	2.62	41.9
3 ½ x 3	⅝	9.1	2.65	2.21	35.4	2.27	36.3	2.32	37.1
3 ½ x 3	⅞	7.9	2.30	1.92	30.7	1.97	31.5	2.02	32.3
3 ½ x 3	1	6.6	1.93	1.62	25.9	1.66	26.6	1.70	27.2
3 ½ x 3	1 ¼	5.4	1.56	1.31	21.0	1.34	21.4	1.37	21.9
3 ½ x 2 ½	½	9.4	2.75	2.25	36.0	2.31	37.0	2.37	37.9
3 ½ x 2 ½	⅝	8.3	2.43	1.99	31.8	2.05	32.8	2.10	33.6
3 ½ x 2 ½	⅞	7.2	2.11	1.73	27.7	1.78	28.5	1.83	29.3
3 ½ x 2 ½	1	6.1	1.78	1.47	23.5	1.51	24.2	1.55	24.8
3 ½ x 2 ½	1 ¼	4.9	1.44	1.19	19.0	1.22	19.5	1.25	20.0
3 x 3	½	9.4	2.75	2.25	36.0	2.31	37.0	2.37	37.9
3 x 3	⅝	8.3	2.43	1.99	31.8	2.05	32.8	2.10	33.6
3 x 3	⅞	7.2	2.11	1.73	27.7	1.78	28.5	1.83	29.3
3 x 3	1	6.1	1.78	1.47	23.5	1.51	24.2	1.55	24.8
3 x 3	1 ¼	4.9	1.44	1.19	19.0	1.22	19.5	1.25	20.0
3 x 2 ½	½	6.6	1.92	1.54	24.6	1.59	25.4	1.64	26.2
3 x 2 ½	⅝	5.6	1.62	1.31	21.0	1.35	21.6	1.39	22.2
3 x 2 ½	⅞	4.5	1.31	1.06	17.0	1.09	17.4	1.12	17.9
2 ½ x 2 ½	½	5.9	1.73			1.40	22.4	1.45	23.2
2 ½ x 2 ½	⅝	5.0	1.47			1.20	19.2	1.24	19.8
2 ½ x 2 ½	⅞	4.1	1.19			0.97	15.5	1.00	16.0
2 ½ x 2 ½	1	3.07	0.90			0.74	11.8	0.76	12.2
2 ½ x 2	½	5.3	1.55			1.22	19.5	1.27	20.3
2 ½ x 2	⅝	4.5	1.31			1.04	16.6	1.08	17.3
2 ½ x 2	⅞	3.62	1.06			0.84	13.4	0.87	13.9
2 ½ x 2	1	2.75	0.81			0.65	10.4	0.67	10.7
2 x 2	½	4.7	1.36					1.08	17.3
2 x 2	⅝	3.92	1.15					0.92	14.7
2 x 2	⅞	3.19	0.94					0.75	12.0
2 x 2	1	2.44	0.71					0.57	9.1
2 x 1 ½	½	3.39	1.00					0.77	12.3
2 x 1 ½	⅝	2.77	0.81					0.62	9.9
2 x 1 ½	⅞	2.12	0.62					0.48	7.7

# TENSION VALUES

## BARS

### ALLOWABLE TENSION VALUES IN THOUSANDS OF POUNDS

#### ROUND BARS

#### SQUARE BARS

Size, Inches	Area, Inches <sup>2</sup>	Weight per Foot, Pounds	Unit Stress 16,000 Lbs. per Square Inch	Unit Stress 20,000 Lbs. per Square Inch	Size, Inches	Area, Inches <sup>2</sup>	Weight per Foot, Pounds	Unit Stress 16,000 Lbs. per Square Inch	Unit Stress 20,000 Lbs. per Square Inch
$\frac{1}{8}$	0.012	0.042	0.2	0.3	$\frac{1}{8}$	0.016	0.053	0.3	0.3
$\frac{1}{4}$	0.028	0.094	0.4	0.6	$\frac{1}{4}$	0.035	0.119	0.6	0.7
$\frac{1}{4}$	0.049	0.167	0.8	1.0	$\frac{1}{4}$	0.063	0.212	1.0	1.3
$\frac{3}{8}$	0.077	0.261	1.2	1.5	$\frac{3}{8}$	0.098	0.333	1.6	2.0
$\frac{3}{8}$	0.110	0.375	1.8	2.2	$\frac{3}{8}$	0.141	0.478	2.3	2.8
$\frac{1}{2}$	0.150	0.511	2.4	3.0	$\frac{1}{2}$	0.191	0.651	3.1	3.8
$\frac{1}{2}$	0.196	0.667	3.1	3.9	$\frac{1}{2}$	0.250	0.850	4.0	5.0
$\frac{5}{8}$	0.249	0.845	4.0	5.0	$\frac{5}{8}$	0.316	1.08	5.1	6.3
$\frac{5}{8}$	0.307	1.04	4.9	6.1	$\frac{5}{8}$	0.391	1.33	6.3	7.8
$\frac{3}{4}$	0.371	1.26	5.9	7.4	$\frac{3}{4}$	0.473	1.61	7.6	9.5
$\frac{3}{4}$	0.442	1.50	7.1	8.8	$\frac{3}{4}$	0.563	1.91	9.0	11.3
$\frac{7}{8}$	0.519	1.76	8.3	10.4	$\frac{7}{8}$	0.660	2.25	10.6	13.2
$\frac{7}{8}$	0.601	2.04	9.6	12.0	$\frac{7}{8}$	0.766	2.60	12.3	15.3
$\frac{7}{8}$	0.690	2.35	11.0	13.8	$\frac{7}{8}$	0.879	2.99	14.1	17.6
1	0.785	2.67	12.6	15.7	1	1.00	3.40	16.0	20.0
$1\frac{1}{8}$	0.887	3.01	14.2	17.7	$1\frac{1}{8}$	1.13	3.84	18.1	22.6
$1\frac{1}{8}$	0.994	3.38	15.9	19.9	$1\frac{1}{8}$	1.27	4.30	20.3	25.3
$1\frac{1}{8}$	1.11	3.77	17.7	22.2	$1\frac{1}{8}$	1.41	4.80	22.6	28.2
$1\frac{1}{8}$	1.23	4.17	19.6	24.5	$1\frac{1}{8}$	1.56	5.31	25.0	31.3
$1\frac{1}{2}$	1.35	4.60	21.6	27.1	$1\frac{1}{2}$	1.72	5.86	27.6	34.5
$1\frac{1}{2}$	1.48	5.05	23.8	29.7	$1\frac{1}{2}$	1.89	6.43	30.3	37.8
$1\frac{1}{2}$	1.62	5.52	26.0	32.5	$1\frac{1}{2}$	2.07	7.03	33.1	41.3
$1\frac{1}{2}$	1.77	6.01	28.3	35.3	$1\frac{1}{2}$	2.25	7.65	36.0	45.0
$1\frac{3}{4}$	1.92	6.52	30.7	38.4	$1\frac{3}{4}$	2.44	8.30	39.1	48.8
$1\frac{3}{4}$	2.07	7.05	33.2	41.5	$1\frac{3}{4}$	2.64	8.98	42.3	52.8
$1\frac{3}{4}$	2.24	7.60	35.8	44.7	$1\frac{3}{4}$	2.85	9.68	45.6	57.0
$1\frac{3}{4}$	2.41	8.18	38.5	48.1	$1\frac{3}{4}$	3.06	10.41	49.0	61.3
$1\frac{3}{4}$	2.58	8.77	41.3	51.6	$1\frac{3}{4}$	3.29	11.17	52.6	65.7
$1\frac{3}{4}$	2.76	9.39	44.2	55.2	$1\frac{3}{4}$	3.52	11.95	56.3	70.3
$1\frac{3}{4}$	2.95	10.02	47.2	59.0	$1\frac{3}{4}$	3.75	12.76	60.1	75.1
2	3.14	10.68	50.3	62.8	2	4.00	13.60	64.0	80.0
$2\frac{1}{8}$	3.34	11.36	53.5	66.8	$2\frac{1}{8}$	4.25	14.46	68.1	85.1
$2\frac{1}{8}$	3.55	12.06	56.7	70.9	$2\frac{1}{8}$	4.52	15.35	72.3	90.3
$2\frac{1}{8}$	3.76	12.78	60.1	75.2	$2\frac{1}{8}$	4.79	16.27	76.6	95.7
$2\frac{1}{8}$	3.98	13.52	63.6	79.5	$2\frac{1}{8}$	5.06	17.22	81.0	101.3
$2\frac{1}{2}$	4.20	14.28	67.2	84.0	$2\frac{1}{2}$	5.35	18.19	85.6	107.0
$2\frac{1}{2}$	4.43	15.07	70.9	88.6	$2\frac{1}{2}$	5.64	19.18	90.3	112.8
$2\frac{1}{2}$	4.67	15.86	74.7	93.3	$2\frac{1}{2}$	5.94	20.20	95.1	118.8
$2\frac{1}{2}$	4.91	16.69	78.5	98.2	$2\frac{1}{2}$	6.25	21.25	100.0	125.0
$2\frac{3}{4}$	5.16	17.53	82.5	103.1	$2\frac{3}{4}$	6.57	22.33	105.1	131.3
$2\frac{3}{4}$	5.41	18.40	86.6	108.2	$2\frac{3}{4}$	6.89	23.43	110.3	137.8
$2\frac{3}{4}$	5.67	19.29	90.8	113.5	$2\frac{3}{4}$	7.22	24.56	115.6	144.5
$2\frac{3}{4}$	5.94	20.20	95.0	118.8	$2\frac{3}{4}$	7.56	25.71	121.0	151.3
$2\frac{3}{4}$	6.21	21.12	99.4	124.3	$2\frac{3}{4}$	7.91	26.90	126.6	158.2
$2\frac{3}{4}$	6.49	22.07	103.9	129.8	$2\frac{3}{4}$	8.27	28.10	132.3	165.3
$2\frac{3}{4}$	6.78	23.04	108.4	135.5	$2\frac{3}{4}$	8.63	29.34	138.1	172.6
3	7.07	24.03	113.1	141.4	3	9.00	30.60	144.0	180.0

## CARNEGIE STEEL COMPANY


### GRILLAGE FOUNDATIONS

**Grillage Beams.** In the design of foundations for columns, piers and walls, provision must be made for the uniform distribution of the load over the footing. This is best done by the use of a grillage of steel beams and concrete. This method of construction eliminates deep excavations and large masses of masonry and is, therefore, truly economical. For heavy loads on soils of small bearing capacity, three tiers of beams may be necessary; while for lighter loads or better soils two tiers, or even one, may suffice.

The lower tier should rest upon a solid bed of concrete of sufficient thickness to distribute the load to the soil. Good practice requires the spaces between the beams in all the tiers to be filled with, and the beams enclosed in, concrete not less than four inches thick.

The clear distance between the flanges of the beams in each tier should not be less than  $2\frac{1}{2}$  inches, nor more than three times the flange width. The first requirement is necessary to permit the introduction and proper tamping of the concrete, the second, to insure uniform distribution of the load. When separators are used to hold the beams in position, they should be of gas pipe, as cast iron separators tend to break the continuity of the concrete. Grillage beams should not be painted, as concrete does not adhere well to painted surfaces but is itself an excellent preservative of steel.

To determine the area in square feet required for the foundation, divide the total load on the column, pier or wall by the allowable pressure per square foot on the soil. This gives the area of the footing, the shape of which is determined by local conditions. On the assumption that the loads on the soil are uniformly distributed, the number, size and weight of the beams required are determined from the maximum bending moment, the maximum shear, or the maximum web resistance to buckling, as follows:—Let



$W$  = Total load on the foundation, in pounds.

$L$  = Length of beam, in feet.

$a$  = Length of loaded portion, in feet.

$d$  = Depth of beam, in inches.

$t$  = Thickness of beam web, in inches.

$n$  = Number of beams in a tier.

$f_b$  = Allowable unit web buckling resistance.

The maximum bending moment occurs at the center of the beam and is equal in foot pounds to  $W(L-a) \div 8$ ; this formula is identical with the formula of maximum bending moment for a beam of length  $(L-a)$  under a uniformly distributed load,  $w$ .

The proper size of beam in any tier as regards flexure at a fiber stress of 16,000 pounds per square inch may be found in the beam

## GRILLAGE FOUNDATIONS

safe load table for the length corresponding to  $(L-a)$ , by dividing the total load by the number of beams.

Or may be found from the table of maximum bending moments, by dividing the total bending moment by the number of beams;

Or from the table of properties, by dividing by the number of beams in the tier the total section modulus required, which is equal to  $\frac{3W(L-a)}{32,000}$

Note, however, that the load on the beam for any span must not exceed the maximum tabular safe load for shear.

The maximum vertical shear occurs at the edge of the column base or at a distance in feet of  $\frac{L-a}{2}$  from each end of the beam and is equal to  $\frac{W}{L} \times \frac{L-a}{2}$

Web thickness,  $t$ , to resist average shear  $= \frac{W}{L} \times \frac{L-a}{2} \times \frac{1}{n \times d \times 10,000}$


Or, the average vertical shear  $= \frac{W}{L} \times \frac{L-a}{2} \times \frac{1}{n \times d \times t}$ , which must not exceed 10,000 pounds per square inch.

The maximum buckling stress occurs on a length in inches of  $12a + d/2$  and is equal in total per linal inch of web to  $\frac{W}{12a + d/2}$ .

The required thickness of web,  $t$ , to resist buckling  $= \frac{W}{n \times (12a + d/2) \times fb}$ .

Or the average web resistance per square inch to buckling  $= \frac{W}{n \times (12a + d/2) \times t}$  which must not exceed the tabular values for the allowable buckling resistance on beam webs.

**Rolled Steel Slabs.** To distribute the loads from columns over girders, grillage beams, etc., solid slabs of rolled steel may be advantageously used in the place of cast iron or riveted steel bases, etc. The size of the slab is usually fixed by the dimensions of the column and its thickness is determined from the maximum bending moment, on the assumption of uniform loading, as follows:—Let



$W$  = Total load, in pounds.

$A$  = Width of slab, in inches.

$B$  = Length of slab, in inches.

$t$  = Thickness of slab, in inches.



$a$  = Outside dimension of column, in inches.

$b$  = Outside dimension of column, in inches.

The maximum bending moment will occur at the center of the slab and equals, in inch pounds,  $\frac{W(A-a)}{8}$  or  $\frac{W(B-b)}{8}$ , and at a fiber stress of 16,000 pounds per square inch, the required thickness of slab,  $t$ ,  $= \sqrt{\frac{3W(A-a)}{64,000B}}$  or  $= \sqrt{\frac{3W(B-b)}{64,000A}}$



# CARNEGIE STEEL COMPANY

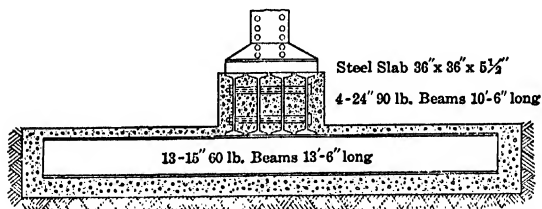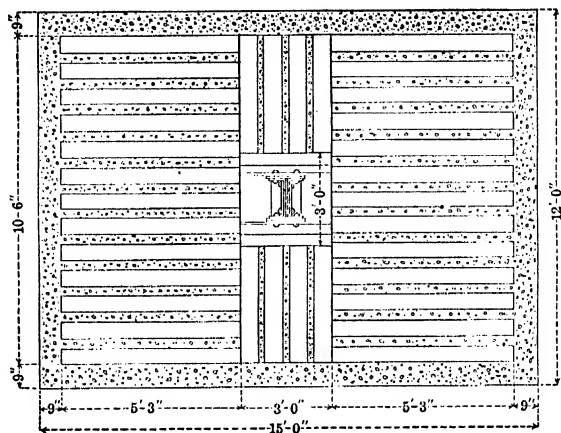


**EXAMPLE:** Required to design a grillage foundation for a column load of 1,040,000 pounds on soil with an allowable bearing capacity of 6,000 pounds per square foot. Column composed of 1 web plate, 14" x 1/2", 4 flange angles, 6" x 4" x 5/8" and 4 flange plates, 14" x 1/2", outside dimensions 14" x 18".

Required area of footing =  $1,040,000 \div 6,000 = 173.33$  square feet.

Use area 12' 0" x 15' 0" = 180 square feet.

Assume 3' 0" square as the dimensions of the rolled steel slab or column base and allow 9" for concrete on the sides and ends of beams, then the dimensions of the steel grillage will be 10' 6" x 13' 6", concrete being assumed of sufficient thickness and strength to distribute to the edges.



Rolled Steel Slab

Thickness required,  $t = \sqrt{\frac{3 \times 1,040,000 \times 22}{64,000 \times 36}} = 5.46$  in.

Use 5 1/2".

## GRILLAGE FOUNDATIONS

**Beams—Section Modulus Method.**

Bottom tier— $L=13.5$  feet;  $a=3.0$  feet.

Required total section modulus,  $S, = \frac{3 \times 1,040,000 \times 10.5}{32,000} = 1,023.75 \text{ in.}^3$

Use 13—15" 60 lb. beams—Total section modulus= $1,055.6 \text{ in.}^3$

Average shear= $\frac{1,040,000}{13.5} \times \frac{10.5}{2} \times \frac{1}{13 \times 15 \times .59} = 3,515 \text{ lbs. per sq. in.}$

Average buckling stress= $\frac{1,040,000}{13 \times 43.5 \times .59} = 3,120 \text{ lbs. per sq. in.}$

Top tier— $L=10.5$  feet;  $a=3.0$  feet.


Required total section modulus,  $S, = \frac{3 \times 1,040,000 \times 7.5}{32,000} = 731.25 \text{ in.}^3$

Use 4—24" 90 lb. beams—Total section modulus= $746.0 \text{ in.}^3$

Average shear= $\frac{1,040,000}{10.5} \times \frac{7.5}{2} \times \frac{1}{4 \times 24 \times .63} = 6,140 \text{ lbs. per sq. in.}$

Average buckling stress= $\frac{1,040,000}{4 \times 48 \times .63} = 8,600 \text{ lbs. per sq. in.}$

**Plate Girder Grillage Foundations.** In those cases where columns carry very heavy loads, plate girders are used for the top tier of the grillage rather than beams. In the case of symmetrical foundations, the method of computation is the same as has already been illustrated in the case of beams. The following example indicates the procedure in the quite frequent case of unsymmetrical loading conditions:

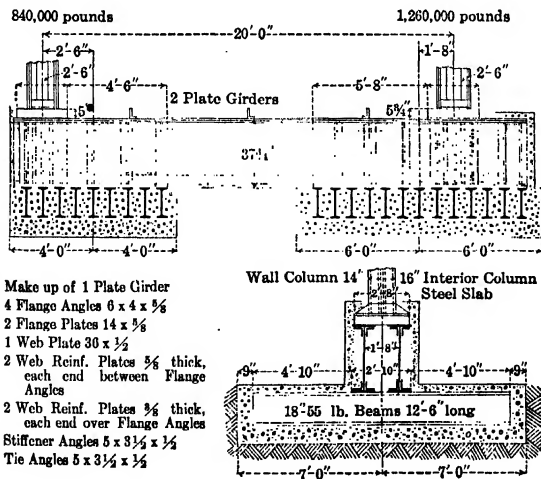

# CARNEGIE STEEL COMPANY

**EXAMPLE:**—Required to design a grillage foundation under an exterior or wall column carrying a load of 840,000 pounds, and an interior column with a load of 1,260,000 pounds, on soil with an allowable bearing capacity of 8,000 pounds per square foot.

$$\text{Required footing area of wall column} = \frac{840,000}{8,000} = 105 \text{ square feet.}$$

$$\text{Use area } 8' 0'' \times 14' 0'' = 112 \text{ square feet.}$$

$$\text{Required area of interior column footing} = \frac{1,260,000}{8,000} = 157.5 \text{ square feet.}$$

$$\text{Use area } 12' 0'' \times 14' 0'' = 168 \text{ square feet.}$$

With these dimensions and areas, the load on the soil will be uniform at 7,500 pounds per square foot, and the footings the same width, both of which are desirable from the standpoint of uniform settlement.

**Roller Steel Slabs for Column Footings:** Assume a width of 30" and a length of 32", then the required thickness will be as follows:—

$$\text{Wall column, } t = \sqrt{\frac{3 \times 840,000 \times (32 - 14)}{64,000 \times 30}} = 4.86 \text{ in.; use } 5''.$$

$$\text{Interior column, } t = \sqrt{\frac{3 \times 1,260,000 \times (32 - 16)}{64,000 \times 30}} = 5.61 \text{ in.; use } 5\frac{1}{2}''.$$

**Plate Girders:** Maximum bending moment occurs at the inner beams of the respective footings, and is equal to the load on the column multiplied by the distance of its center from the center of moments.

$$M \text{ max. from wall column} = 840,000 \times 2' 6'' = 2,100,000 \text{ foot pounds.}$$

$$M \text{ max. from interior column} = 1,260,000 \times 1' 8'' = 2,100,000 \text{ foot pounds.}$$

$$\text{Required section modulus of two girders} = \frac{2,100,000 \times 12}{16,000} = 1,575.0 \text{ in.}^3$$

Select from girder safe load table, page 278, two girders composed each of 1 web plate 36" x  $\frac{1}{2}$ ", 4 angles 6" x 4" x  $\frac{5}{8}$ ", and 2 flange plates 14" x  $\frac{5}{8}$ ";—  
Total section modulus,  $S = 2 \times 792.3 = 1,584.6 \text{ in.}^3$

Maximum shear occurs at the inside edge of the steel slab under the interior column, and is equal in total for the two girders to the load carried by the portion of the footing between that point and the inside edge of the footing, or  $\frac{1,260,000 \times 68}{126} = 680,000$  or 340,000 pounds per girder.

At 10,000 pounds per square inch, the 36" x  $\frac{1}{2}$ " plate girder web is good for 180,000 pounds; therefore, it is necessary to use reinforcing web plates where the shear exceeds that amount.

**Beams, Lower Tier, Interior Column:**

$$\text{Required total section modulus, } S = \frac{3 \times 1,260,000 \times 9.67}{32,000} = 1,142.3 \text{ in.}^3$$

$$\text{Use } 13-18'' \text{ 55 lb. beams—Total section modulus} = 1,149.2 \text{ in.}^3$$

$$\text{Average shear} = \frac{1,260,000}{12.5} \times \frac{9.67}{2} \times \frac{1}{13 \times 18 \times .46} = 4,520 \text{ lbs. per sq. in.}$$

$$\text{Average buckling stress} = \frac{1,260,000}{13 \times 43 \times .46} = 4,900 \text{ lbs. per sq. in.}$$

For exterior column use 9-18" 55 lb. beams.

**NOTE.**—In order to facilitate manufacture and shipment, it is desirable to use for the entire foundation as few sizes and weights of beams as possible, and the rolled steel slabs should be of the same thickness or at least of as few thicknesses as really convenient.

## GIRDERS

### RIVETED BEAM AND PLATE GIRDERS

Where single rolled beams are insufficient to carry the loads, the required capacity may be secured by fabrication in various methods.

Two beams can be used, connected together by bolts and separators. The total strength of these is twice that of the single beam of the same depth and weight. Care should be taken, however, to see that the loads are applied on them equally, and where it is necessary for the beams to act as a unit, these separators should be of plates and angles and not of cast iron. If the loading is not uniform on the two sections, their strength must be computed separately.

The use of single beam girders with plates top and bottom to sustain a given load is often more economical in material than the use of two beams connected by bolts and separators.

Box girders formed of two beams with flange plates riveted thereto are often used for supporting interior walls in buildings. They are not, however, as economical in material as single beams with flange plates or plate girders. Their interior surfaces do not admit of repainting and they should, therefore, not be used in exposed places.

The most economical section to sustain heavy loads is the single web plate girder and it is sufficient for all ordinary purposes. When not so, two single web plate girders may be used, together with tie plates extending clear across the angles, or box girders may be made of four flange angles, two web plates and top and bottom flange plates. In case there is unequal distribution of the load, the two girders or half girders must be figured as separate units.

In the design of beam or plate girders, care must be taken to see that the web is of sufficient thickness to resist buckling stress and, therefore, attention is called to the construction specifications and to the remarks made on page 210 as to shearing stresses in general.

The tables which follow give first, a selected line of riveted beam girders of approximately twice the carrying capacity of the single beams of which the sections are built; second, a selected line of riveted plate girders of various depths and carrying capacities such as are customary in building work; third, elements of riveted plate girders of various depths from which it is possible to select economical sections for almost any ordinary condition of loading. In addition to the properties, the first two tables give the safe loads in thousands of pounds uniformly distributed.





In accordance with the construction specifications, these girder tables are based upon the section modulus of the gross area of the section, with bending stress allowed at 16,000 pounds per square inch.

# CARNEGIE STEEL COMPANY

## RIVETED BEAM GIRDERS

ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16000 Pounds per Square Inch

Span in Feet									Coefficients of Deflection
	1-Beam 27"x83 lbs. 2-Plates 12"x3/4"		1-Beam 24"x80 lbs. 2-Plates 12"x3/4"		1-Beam 24"x80 lbs. 2-Plates 10"x5/8"		1-Beam 20"x80 lbs. 2-Plates 10"x3/4"		
	Safe Loads	Increase in Safe Loads for 1/16 Inch Increase in Thickness of Flange Plates	Safe Loads	Increase in Safe Loads for 1/16 Inch Increase in Thickness of Flange Plates	Safe Loads	Increase in Safe Loads for 1/16 Inch Increase in Thickness of Flange Plates	Safe Loads	Increase in Safe Loads for 1/16 Inch Increase in Thickness of Flange Plates	
13	366	17.5	312	14.2	259	11.7	235	9.7	2.80
14	340	16.3	289	13.2	240	10.9	218	9.0	3.24
15	317	15.2	270	12.3	224	10.1	204	8.4	3.72
16	297	14.3	253	11.5	210	9.5	191	7.9	4.24
17	280	13.4	238	10.9	198	9.0	180	7.4	4.78
18	264	12.7	225	10.3	187	8.4	170	7.0	5.36
19	250	12.0	213	9.7	177	8.0	161	6.6	5.98
20	238	11.4	203	9.2	168	7.6	153	6.3	6.62
21	227	10.9	193	8.8	160	7.2	146	6.0	7.30
22	216	10.4	184	8.4	153	6.9	139	5.7	8.01
23	207	9.9	176	8.0	146	6.6	133	5.5	8.76
24	198	9.5	169	7.7	140	6.3	127	5.3	9.53
25	190	9.1	162	7.4	135	6.1	122	5.0	10.35
26	183	8.8	156	7.1	129	5.9	118	4.8	11.19
27	176	8.4	150	6.8	125	5.6	113	4.7	12.07
28	170	8.1	145	6.6	120	5.4	109	4.5	12.98
29	164	7.9	140	6.4	116	5.2	105	4.3	13.92
30	159	7.6	135	6.2	112	5.1	102	4.2	14.90
31	153	7.4	131	6.0	109	4.9	99	4.1	15.91
32	149	7.1	127	5.8	105	4.8	96	3.9	16.95
33	144	6.9	123	5.6	102	4.6	93	3.8	18.03
34	140	6.7	119	5.4	99	4.5	90	3.7	19.13
35	136	6.5	116	5.3	96	4.3	87	3.6	20.28
Area	42.41 inches <sup>2</sup>		41.32 inches <sup>2</sup>		35.82 inches <sup>2</sup>		38.73 inches <sup>2</sup>		
S <sub>1-1</sub>	446.0 inches <sup>3</sup>		380.0 inches <sup>3</sup>		315.5 inches <sup>3</sup>		286.7 inches <sup>3</sup>		
Weight	144.2 lbs. per ft.		141.2 lbs. per ft.		122.5 lbs. per ft.		131.0 lbs. per ft.		

Safe loads above horizontal lines exceed the web resistance and girders should be provided with stiffeners; for limiting conditions see explanatory notes and Construction Specifications.





Weights given for girders do not include stiffeners, rivet heads or other details.

# GIRDERS

## RIVETED BEAM GIRDERS—Concluded

ALLOWABLE UNIFORM LOAD IN THOUSANDS OF POUNDS

Maximum Bending Stress, 16000 Pounds per Square Inch

Span in Feet									Coefficients of Deflection
	1-Beam 20'' x 65 lbs. 2-Plates 10'' x 5/8''		1-Beam 18'' x 55 lbs. 2-Plates 9'' x 5/8''		1-Beam 15'' x 60 lbs. 2-Plates 9'' x 5/8''		1-Beam 15'' x 42 lbs. 2-Plates 8'' x 1/2''		
	Safe Loads	Increase in Safe Loads for 1/16 Inch Increase in Thickness of Flange Plates	Safe Loads	Increase in Safe Loads for 1/16 Inch Increase in Thickness of Flange Plates	Safe Loads	Increase in Safe Loads for 1/16 Inch Increase in Thickness of Flange Plates	Safe Loads	Increase in Safe Loads for 1/16 Inch Increase in Thickness of Flange Plates	
9	279	14.2	218	11.5	189	9.4	137	8.5	1.34
10	251	12.7	196	10.3	170	8.5	123	7.6	1.66
11	228	11.6	178	9.4	155	7.7	112	6.9	2.00
12	209	10.6	164	8.6	142	7.1	102	6.4	2.38
13	193	9.8	151	7.9	131	6.5	95	5.9	2.80
14	179	9.1	140	7.4	122	6.1	88	5.5	3.24
15	167	8.5	131	6.9	113	5.7	82	5.1	3.72
16	157	8.0	123	6.5	106	5.3	77	4.8	4.24
17	148	7.5	115	6.1	100	5.0	72	4.5	4.78
18	139	7.1	109	5.7	95	4.7	68	4.2	5.36
19	132	6.7	103	5.4	90	4.5	65	4.0	5.98
20	125	6.4	98	5.2	85	4.3	61	3.8	6.62
21	119	6.1	93	4.9	81	4.0	59	3.6	7.30
22	114	5.8	89	4.7	77	3.9	56	3.5	8.01
23	109	5.5	85	4.5	74	3.7	53	3.3	8.76
24	105	5.3	82	4.3	71	3.5	51	3.2	9.53
25	100	5.1	79	4.1	68	3.4	49	3.1	10.35
26	97	4.9	76	4.0	65	3.3	47	2.9	11.19
27	93	4.7	73	3.8	63	3.1	46	2.8	12.07
28	90	4.6	70	3.7	61	3.0	44	2.7	12.98
29	87	4.4	68	3.6	59	2.9	42	2.6	13.92
30	84	4.2	65	3.4	57	2.8	41	2.5	14.90
Area	31.58 inches <sup>2</sup>		27.18 inches <sup>2</sup>		28.92 inches <sup>2</sup>		20.48 inches <sup>2</sup>		
S <sub>1-1</sub>	235.2 inches <sup>3</sup>		184.1 inches <sup>3</sup>		159.5 inches <sup>3</sup>		115.3 inches <sup>3</sup>		
Weight	107.5 lbs. per ft.		93.3 lbs. per ft.		98.3 lbs. per ft.		69.2 lbs. per ft.		

Safe loads above horizontal lines exceed the web resistance and girders should be provided with stiffeners; for limiting conditions see explanatory notes and Construction Specifications.

Weights given for girders do not include stiffeners, rivet heads or other details.

# CARNEGIE STEEL COMPANY

## RIVETED PLATE GIRDERS

SAFE LOADS IN THOUSANDS OF POUNDS UNIFORMLY DISTRIBUTED

Maximum Bending Stress, 16000 Pounds Per Square Inch

Span in Feet	Dimensions in Inches								Coefficients of Deflection
	Web Plate Flange Angles Flange Plates	Web Plate Flange Angles Flange Plates	Web Plate Flange Angles Flange Plates	Web Plate Flange Angles Flange Plates	Web Plate Flange Angles Flange Plates	Web Plate Flange Angles Flange Plates	Web Plate Flange Angles Flange Plates	Web Plate Flange Angles Flange Plates	
	1-30x $\frac{1}{2}$ 4-6x $\frac{1}{2}$ 2-14x $\frac{1}{2}$	1-30x $\frac{3}{8}$ 4-6x $\frac{1}{2}$ 2-14x $\frac{1}{2}$	1-30x $\frac{3}{8}$ 4-6x $\frac{1}{2}$ 2-14x $\frac{1}{2}$	1-30x $\frac{3}{8}$ 4-6x $\frac{1}{2}$ 2-14x $\frac{1}{2}$	1-30x $\frac{3}{8}$ 4-6x $\frac{1}{2}$ 2-14x $\frac{1}{2}$	1-28x $\frac{3}{8}$ 4-5x $\frac{3}{8}$ 2-12x $\frac{1}{2}$	1-28x $\frac{1}{2}$ 4-6x $\frac{1}{2}$ 2-14x $\frac{1}{2}$	1-28x $\frac{3}{8}$ 4-6x $\frac{1}{2}$ 2-14x $\frac{1}{2}$	
20	325	331	301	274	196	196	299	278	6.62
21	310	315	287	261	187	186	285	265	7.30
22	296	301	274	249	178	178	272	253	8.01
23	283	288	262	238	171	170	260	242	8.76
24	271	276	251	228	164	163	249	232	9.53
25	260	265	241	219	157	156	239	223	10.35
26	250	255	232	211	151	150	230	214	11.19
27	241	245	223	203	145	145	222 <sup>1</sup>	206	12.07
28	232	236	215	196	140	140	214	199	12.98
29	224	228	208	189	135	135	206	192	13.92
30	217	221	201	183	131	130	199	186	14.90
31	210	214	194	177	127	126	193	180	15.91
32	203	207	188	171	123	122	187	174	16.95
33	197	201	183	166	119	119	181	169	18.03
34	191	195	177	161	115	115	176	164	19.13
35	186	189	172	157	112	112	171	159	20.28
36	181	184	167	152	109	109	166	155	21.45
37	176	179	163	148	106	106	162	150	22.66
38	171	174	159	144	103	103	157	147	23.90
39	167	170	155	141	101	100	153	143	25.18
40	163	166	151	137	98	98	150	139	26.48
41	159	161	147	134	96	95	146	136	27.82
42	155	158	144	131	94	93	142	133	29.20
Area	55.50	52.19	47.75	44.25	34.89	34.70	54.50	47.00	In. <sup>2</sup>
St.-1	609.7	620.6	568.1	514.0	368.1	366.7	560.7	521.9	In. <sup>3</sup>
Wt. per Ft.	188.9	177.8	162.6	150.7	118.3	118.1	185.5	160.0	Lbs.

Safe loads above horizontal lines exceed the end resistance and girders should be provided with stiffeners; for limiting conditions see explanatory notes and Construction Specifications.


Weights given for girders do not include stiffeners, rivet heads, or other details.

# GIRDERS

## RIVETED PLATE GIRDERS—Continued

SAFE LOADS IN THOUSANDS OF POUNDS UNIFORMLY DISTRIBUTED

Maximum Bending Stress, 16000 Pounds Per Square Inch

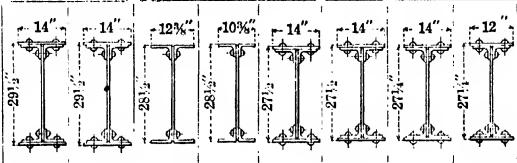Span in Feet									Coefficients of Deflection
	Dimensions in Inches								
	Web Plate 1-28x $\frac{3}{8}$ 4-6x4 $\frac{1}{2}$ Flange Plates 2-14x $\frac{1}{2}$	Web Plate 1-28x $\frac{3}{8}$ 4-6x4 $\frac{1}{2}$ Flange Angles 2-14x $\frac{1}{2}$	Web Plate 1-28x $\frac{3}{8}$ 4-6x4 $\frac{1}{2}$ Flange Angles	Web Plate 1-28x $\frac{3}{8}$ 4-5x3 $\frac{1}{2}$ Flange Angles	Web Plate 1-28x $\frac{3}{8}$ 4-5x3 $\frac{1}{2}$ Flange Angles	Web Plate 1-26x $\frac{3}{8}$ 4-5x3 $\frac{1}{2}$ Flange Plates 2-14x $\frac{1}{2}$	Web Plate 1-26x $\frac{3}{8}$ 4-5x3 $\frac{1}{2}$ Flange Plates 2-14x $\frac{1}{2}$	Web Plate 1-25x $\frac{3}{8}$ 4-5x3 $\frac{1}{2}$ Flange Angles 2-12x $\frac{3}{8}$	
18	281	219	168	148	258	229	202	176	5.36
19	266	236	160	140	244	217	192	167	5.98
20	253	224	152	133	232	206	182	150	6.62
21	241	214	144	127	221	196	173	151	7.30
22	230	204	138	121	211	187	166	144	8.01
23	220	195	132	116	202	179	158	138	8.76
24	211	187	126	111	193	172	152	132	9.53
25	202	180	121	106	186	165	146	127	10.35
26	195	173	117	102	178	158	140	122	11.19
27	187	166	112	98	172	153	135	118	12.07
28	181	160	108	95	159	147	130	114	12.98
29	174	155	105	92	160	142	126	110	13.92
30	169	150	101	89	155	137	121	106	14.90
31	163	145	98	86	150	133	118	103	15.91
32	158	140	95	83	145	129	114	99	16.95
33	153	136	92	81	141	125	110	96	18.03
34	149	132	89	78	136	121	107	93	19.13
35	145	128	87	76	133	118	104	91	20.28
36	141	125	84	74	129	114	101	88	21.45
37	137	121	82	72	125	111	98	86	22.66
38	133	118	80	70	122	108	96	84	23.90
39	130	115	78	68	119	106	93	81	25.18
40	126	112	76	66	116	103	91	79	26.48
Area S <sub>1-1</sub>	43.50	38.94	29.50	26.50	42.75	38.19	34.69	30.95	In. <sup>2</sup>
Wt. per Ft.	474.3	420.8	284.3	249.1	435.1	388.1	341.5	298.0	Lbs.

Safe loads above horizontal lines exceed the end resistance and girders should be provided with stiffeners; for limiting conditions see explanatory notes and Construction Specifications.

Weights given for girders do not include stiffeners, rivet heads, or other details.




# CARNEGIE STEEL COMPANY

## RIVETED PLATE GIRDERS—Concluded

SAFE LOADS IN THOUSANDS OF POUNDS UNIFORMLY DISTRIBUTED

Maximum Bending Stress, 16000 Pounds Per Square Inch

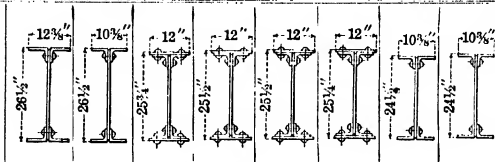
Span in Feet									Coefficients of Deflection
	Dimensions in Inches								
	Web Plate Flange Angles	Web Plate Flange Angles	Web Plate Flange Angles	Web Plate Flange Angles	Web Plate Flange Angles	Web Plate Flange Angles	Web Plate Flange Angles	Web Plate Flange Angles	
18	1-26x3/4 4-6x4x1/2	1-34 4-5x3 1/2x1/2	1-24x3/4 4-5x3 1/2x1/2	1-24x3/4 4-5x3 1/2x1/2	1-24x3/4 4-5x3 1/2x1/2	1-24x3/4 4-5x3 1/2x1/2	1-24x3/4 4-5x3 1/2x1/2	1-24x3/4 4-5x3 1/2x1/2	
19	153	127	212	204	181	161	121	98	
20	145	121	202	193	172	152	115	93	
21	138	115	192	183	163	144	109	88	
22	131	110	184	175	155	138	104	84	
23	126	105	176	167	148	131	99	80	
24	120	101	168	159	142	126	95	77	
25	115	97	162	153	136	120	91	74	
26	110	93	155	147	131	116	87	71	
27	106	90	150	141	126	111	84	68	
28	102	86	144	136	121	107	81	65	
29	99	86	144	131	117	103	78	63	
30	95	83	139	126	113	100	75	61	
31	92	81	135	122	109	96	73	59	
32	89	78	130	118	105	93	70	57	
33	86	76	126	115	102	90	68	55	
34	84	73	122	111	99	88	66	53	
35	81	71	119	108	96	85	64	52	
36	79	69	115	105	93	83	62	50	
37	77	67	112	102	91	80	61	49	
38	75	65	109	99	88	78	59	48	
39	73	64	106	96	86	76	57	46	
40	71	62	104	94	84	74	56	45	
40	69	60	101	92	82	72	55	44	
Area	28.75	25.75	40.00	37.00	33.20	30.20	25.00	21.20	
S <sub>1-1</sub>	258.9	226.6	378.5	343.6	306.1	270.9	204.6	165.5	
Wt. per Ft.	98.0	87.6	136.0	125.8	113.0	102.8	85.0	72.2	

Safe loads above horizontal lines exceed the end resistance and girders should be provided with stiffeners; for limiting conditions see explanatory notes and Construction Specifications.

Weights given for girders do not include stiffeners, rivet heads, or other details.

# GIRDERS

## RIVETED PLATE GIRDERS



To obtain a girder suitable to carry any specified loading, determine the maximum end reaction in pounds and the maximum bending moment in inch-pounds.

Select from the table a girder having the desired depth, a thickness of web as determined by the maximum end reaction and a suitable section modulus as determined by dividing the bending moment by the permissible stress per square inch.

For limiting conditions see explanatory notes and Construction Specifications.

Weights given do not include stiffeners, rivet heads, or other details.

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plate	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
136.6	24 x 5/16	4 x 3 x 3/8		59.5		50.6
168.6		4 x 3 x 1/2		60.9		50.6
198.7		5 x 3 1/2 x 1/2		70.9		50.6
236.1		5 x 3 1/2 x 3/8		92.7		50.6
238.0		5 x 3 1/2 x 1/2	12 x 1/2	79.9	40.8	50.6
372.9		5 x 3 1/2 x 1/2	12 x 3/8	70.9	51.0	50.6
408.5		5 x 3 1/2 x 3/8	12 x 3/8	92.7	51.0	50.6
142.5	24 x 3/8	4 x 3 x 3/8		64.6		60.8
165.5		5 x 3 1/2 x 3/8		72.2		60.8
174.5		4 x 3 x 1/2		75.0		60.8
204.5		4 x 3 x 3/8		85.0		60.8
204.6		5 x 3 1/2 x 1/2		85.0		60.8
242.0		5 x 3 1/2 x 3/8		97.8		60.8
270.9		5 x 3 1/2 x 3/8	12 x 3/8	72.2	30.6	60.8
306.1		5 x 3 1/2 x 3/8	12 x 1/2	72.2	40.8	60.8
343.6		5 x 3 1/2 x 1/2	12 x 1/2	85.0	40.8	60.8
378.5		5 x 3 1/2 x 1/2	12 x 3/8	85.0	51.0	60.8
414.1		5 x 3 1/2 x 3/8	12 x 3/8	97.8	51.0	60.8
151.5	26 x 5/16	4 x 3 x 3/8		61.6		56.3
176.8		5 x 3 1/2 x 3/8		69.2		56.3
186.6		4 x 3 x 1/2		72.0		56.3
201.2		6 x 4 x 3/8		76.8		56.3
219.6		5 x 3 1/2 x 1/2		82.0		56.3
252.0		6 x 4 x 1/2		92.4		56.3
260.7		5 x 3 1/2 x 3/8		94.8		56.3
291.3		5 x 3 1/2 x 3/8	12 x 3/8	60.2	30.6	56.3
301.0		6 x 4 x 3/8		107.6		56.3
329.5		5 x 3 1/2 x 3/8	12 x 1/2	69.2	40.8	56.3
334.8		6 x 4 x 3/8	14 x 3/8	76.8	35.7	56.3
370.7		5 x 3 1/2 x 1/2	12 x 1/2	82.0	40.8	56.3
379.4		6 x 4 x 3/8	14 x 1/2	76.8	47.6	56.3
408.6		5 x 3 1/2 x 1/2	12 x 3/8	82.0	51.0	56.3

**CARNEGIE STEEL COMPANY**

**RIVETED PLATE GIRDERS—Continued**

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plate	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
428.4	26 x 7/16	6x 4 x 1/2	14 x 1/4	92.4	47.6	56.3
447.9		5x3 1/2 x 3/8	12 x 5/8	94.8	51.0	56.3
472.7		6x 4 x 1/2	14 x 5/8	92.4	59.5	56.3
519.5		6x 4 x 5/8	14 x 5/8	107.6	59.5	56.3
563.4		6x 4 x 5/8	14 x 3/4	107.6	71.4	56.3
158.5	26 x 3/4	4x 3 x 3/8		67.2		67.5
183.8		5x3 1/2 x 3/8		74.8		67.5
193.5		4x 3 x 1/2		77.6		67.5
208.1		6x 4 x 3/4		82.4		67.5
226.5		4x 3 x 5/8		87.6		67.5
226.6		5x3 1/2 x 1/2		87.6		67.5
258.0		6x 4 x 1/2		98.0		67.5
267.6		5x3 1/2 x 5/8		100.4		67.5
298.0		5x3 1/2 x 3/8	12 x 3/8	74.8	30.6	67.5
307.9		6x 4 x 5/8		113.2		67.5
336.2		5x3 1/2 x 5/8	12 x 1/2	74.8	40.8	67.5
341.5		6x 4 x 3/8	14 x 3/8	82.4	35.7	67.5
354.4		6x 4 x 3/4		127.6		67.5
377.4		5x3 1/2 x 1/2	12 x 1/2	87.6	40.8	67.5
386.1		6x 4 x 5/8	14 x 1/2	82.4	47.6	67.5
415.2		5x3 1/2 x 1/2	12 x 5/8	87.6	51.0	67.5
435.1		6x 4 x 1/2	14 x 1/2	98.0	47.6	67.5
454.5		5x3 1/2 x 5/8	12 x 5/8	100.4	51.0	67.5
479.3		6x 4 x 1/2	14 x 5/8	98.0	59.5	67.5
526.1		6x 4 x 5/8	14 x 5/8	113.2	59.5	67.5
569.9		6x 4 x 5/8	14 x 3/4	113.2	71.4	67.5
613.9		6x 4 x 3/4	14 x 3/4	127.6	71.4	67.5
200.4	26 x 1/2	4x 3 x 1/2		83.1		78.8
233.4		4x 3 x 5/8		93.1		78.8
233.5		5x3 1/2 x 1/2		93.1		78.8
265.8		6x 4 x 1/2		103.5		78.8
274.5		5x3 1/2 x 5/8		105.9		78.8
314.8		6x 4 x 5/8		118.7		78.8
361.3		6x 4 x 3/4		133.1		78.8
384.0		5x3 1/2 x 1/2	12 x 1/2	93.1	40.8	78.8
421.8		5x3 1/2 x 1/2	12 x 5/8	93.1	51.0	78.8
441.7		6x 4 x 1/2	14 x 1/2	103.5	47.6	78.8
461.1		5x3 1/2 x 5/8	12 x 5/8	105.9	51.0	78.8
485.9		6x 4 x 1/2	14 x 5/8	103.5	59.5	78.8
532.7		6x 4 x 5/8	14 x 5/8	118.7	59.5	78.8
576.5		6x 4 x 5/8	14 x 3/4	118.7	71.4	78.8
620.5		6x 4 x 3/4	14 x 3/4	133.1	71.4	78.8

## GIRDERS

## RIVETED PLATE GIRDERS—Continued

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plate	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
185.6	27 x 9/16	5 x 3 1/2 x 3/8		70.3		56.3
211.0		6 x 4 x 3/8		77.9		56.3
230.3		5 x 3 1/2 x 1/2		83.1		56.3
264.1		6 x 4 x 1/2		93.5		56.3
273.2		5 x 3 1/2 x 3/8		95.9		56.3
304.5		5 x 3 1/2 x 3/8	12 x 3/8	70.3	30.6	56.3
315.3		6 x 4 x 3/8		108.7		56.3
344.2		5 x 3 1/2 x 3/8	12 x 1/2	70.3	40.8	56.3
349.8		6 x 4 x 3/8	14 x 3/8	77.9	35.7	56.3
387.3		5 x 3 1/2 x 1/2	12 x 1/2	83.1	40.8	56.3
396.2		6 x 4 x 3/8	14 x 1/2	77.9	47.6	56.3
426.7		5 x 3 1/2 x 1/2	12 x 5/8	83.1	51.0	56.3
447.4		6 x 4 x 1/2	14 x 1/2	93.5	47.6	56.3
467.7		5 x 3 1/2 x 5/8	12 x 5/8	95.9	51.0	56.3
493.4		6 x 4 x 1/2	14 x 5/8	93.5	59.5	56.3
542.4		6 x 4 x 3/8	14 x 5/8	108.7	59.5	56.3
588.0		6 x 4 x 3/8	14 x 3/4	108.7	71.4	56.3
193.1	27 x 3/4	5 x 3 1/2 x 3/8		76.0		67.5
218.5		6 x 4 x 3/8		83.6		67.5
237.8		5 x 3 1/2 x 1/2		88.8		67.5
271.5		6 x 4 x 1/2		99.2		67.5
280.6		5 x 3 1/2 x 5/8		101.6		67.5
311.7		5 x 3 1/2 x 3/8	12 x 3/8	76.0	30.6	67.5
322.7		6 x 4 x 3/8		114.4		67.5
351.4		5 x 3 1/2 x 3/8	12 x 1/2	76.0	40.8	67.5
357.1		6 x 4 x 3/8	14 x 3/8	83.6	35.7	67.5
371.4		6 x 4 x 3/8		128.8		67.5
394.5		5 x 3 1/2 x 1/2	12 x 1/2	88.8	40.8	67.5
403.4		6 x 4 x 3/8	14 x 1/2	83.6	47.6	67.5
417.9		6 x 4 x 3/8		143.2		67.5
433.8		5 x 3 1/2 x 1/2	12 x 5/8	88.8	51.0	67.5
454.6		6 x 4 x 1/2	14 x 1/2	99.2	47.6	67.5
474.8		5 x 3 1/2 x 5/8	12 x 5/8	101.6	51.0	67.5
500.5		6 x 4 x 1/2	14 x 5/8	99.2	59.5	67.5
549.5		6 x 4 x 3/8	14 x 5/8	114.4	59.5	67.5
595.1		6 x 4 x 3/8	14 x 3/4	114.4	71.4	67.5
641.2		6 x 4 x 3/8	14 x 3/4	128.8	71.4	67.5
245.2	27 x 1/2	5 x 3 1/2 x 1/2		94.6		78.8
279.0		6 x 4 x 1/2		105.0		78.8
288.1		5 x 3 1/2 x 3/8		107.4		78.8
330.2		6 x 4 x 3/8		120.2		78.8

**CARNEGIE STEEL COMPANY**

**RIVETED PLATE GIRDERS—Continued**

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plate	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
378.8	27 x 7/16	6 x 4 x 3/4		134.6		78.8
401.7		5 x 3 1/2 x 1/2	12 x 1/2	94.6	40.8	78.8
425.3		6 x 4 x 3/4		149.0		78.8
440.9		5 x 3 1/2 x 1/2	12 x 5/8	94.6	51.0	78.8
461.8		6 x 4 x 1/2	14 x 1/2	105.0	47.6	78.8
482.0		5 x 3 1/2 x 5/8	12 x 5/8	107.4	51.0	78.8
507.7		6 x 4 x 1/2	14 x 5/8	105.0	59.5	78.8
556.6		6 x 4 x 5/8	14 x 5/8	120.2	59.5	78.8
602.4		6 x 4 x 5/8	14 x 3/4	120.2	71.4	78.8
648.2		6 x 4 x 3/4	14 x 3/4	134.6	71.4	78.8
194.5	28 x 5/16	5 x 3 1/2 x 5/8		71.4		56.3
221.0		6 x 4 x 3/8		79.0		56.3
241.1		5 x 3 1/2 x 1/2		84.2		56.3
276.3		6 x 4 x 1/2		94.6		56.3
285.8		5 x 3 1/2 x 5/8		97.0		56.3
317.8		5 x 3 1/2 x 5/8	12 x 5/8	71.4	30.6	56.3
329.7		6 x 4 x 3/8		109.8		56.3
359.0		5 x 3 1/2 x 5/8	12 x 1/2	71.4	40.8	56.3
365.0		6 x 4 x 3/8	14 x 5/8	79.0	35.7	56.3
404.0		5 x 3 1/2 x 1/2	12 x 1/2	84.2	40.8	56.3
413.1		6 x 4 x 3/8	14 x 1/2	79.0	47.6	56.3
444.8		5 x 3 1/2 x 1/2	12 x 5/8	84.2	51.0	56.3
466.5		6 x 4 x 1/2	14 x 1/2	94.6	47.6	56.3
487.6		5 x 3 1/2 x 5/8	12 x 5/8	97.0	51.0	56.3
514.2		6 x 4 x 1/2	14 x 5/8	94.6	59.5	56.3
505.4		6 x 4 x 5/8	14 x 5/8	109.8	59.5	56.3
612.7		6 x 4 x 3/4	14 x 3/4	109.8	71.4	56.3
202.5	28 x 1/2	5 x 3 1/2 x 5/8		77.3		67.5
229.0		6 x 4 x 3/8		84.9		67.5
249.1		5 x 3 1/2 x 1/2		90.1		67.5
284.3		6 x 4 x 1/2		100.5		67.5
293.8		5 x 3 1/2 x 5/8		102.0		67.5
325.6		5 x 3 1/2 x 5/8	12 x 5/8	77.3	30.6	67.5
337.7		6 x 4 x 3/8		115.7		67.5
366.7		5 x 3 1/2 x 5/8	12 x 1/2	77.3	40.8	67.5
372.8		6 x 4 x 3/8	14 x 5/8	84.9	35.7	67.5
388.5		6 x 4 x 3/4		130.1		67.5
411.7		5 x 3 1/2 x 1/2	12 x 1/2	90.1	40.8	67.5
420.8		6 x 4 x 3/8	14 x 1/2	84.9	47.6	67.5
437.0		6 x 4 x 5/8		144.5		67.5
462.5		5 x 3 1/2 x 1/2	12 x 3/4	90.1	51.0	67.5

## GIRDERS

## RIVETED PLATE GIRDERS—Continued

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
474.3	28 x $\frac{3}{8}$	6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	100.5	47.6	67.5
495.3		5 x 3 $\frac{1}{2}$ x $\frac{5}{8}$	12 x $\frac{5}{8}$	102.9	51.0	67.5
521.9		6 x 4 x $\frac{1}{2}$	14 x $\frac{5}{8}$	100.5	59.5	67.5
573.1		6 x 4 x $\frac{5}{8}$	14 x $\frac{5}{8}$	115.7	59.5	67.5
620.4		6 x 4 x $\frac{5}{8}$	14 x $\frac{3}{4}$	115.7	71.4	67.5
668.6		6 x 4 x $\frac{3}{4}$	14 x $\frac{3}{4}$	130.1	71.4	67.5
257.1	28 x $\frac{7}{16}$	5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$		96.1		78.8
292.4		6 x 4 x $\frac{1}{2}$		106.5		78.8
301.8		5 x 3 $\frac{1}{2}$ x $\frac{5}{8}$		108.9		78.8
345.8		6 x 4 x $\frac{5}{8}$		121.7		78.8
396.5		6 x 4 x $\frac{3}{4}$		136.1		78.8
419.5		5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	12 x $\frac{1}{2}$	96.1	40.8	78.8
445.1		6 x 4 x $\frac{7}{8}$		150.5		78.8
460.2		5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	12 x $\frac{5}{8}$	96.1	51.0	78.8
482.0		6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	106.5	47.6	78.8
503.0		5 x 3 $\frac{1}{2}$ x $\frac{5}{8}$	12 x $\frac{5}{8}$	108.9	51.0	78.8
520.6		6 x 4 x $\frac{1}{2}$	14 x $\frac{5}{8}$	106.5	59.5	78.8
580.8		6 x 4 x $\frac{5}{8}$	14 x $\frac{5}{8}$	121.7	59.5	78.8
628.0		6 x 4 x $\frac{5}{8}$	14 x $\frac{3}{4}$	121.7	71.4	78.8
676.2		6 x 4 x $\frac{3}{4}$	14 x $\frac{3}{4}$	136.1	71.4	78.8
221.8	30 x $\frac{3}{8}$	5 x 3 $\frac{1}{2}$ x $\frac{3}{8}$		79.9		74.3
250.5		6 x 4 x $\frac{3}{8}$		87.5		74.3
272.1		5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$		92.7		74.3
310.3		6 x 4 x $\frac{1}{2}$		103.1		74.3
320.5		5 x 3 $\frac{1}{2}$ x $\frac{5}{8}$		105.5		74.3
353.8		5 x 3 $\frac{1}{2}$ x $\frac{3}{4}$	12 x $\frac{3}{8}$	79.9	30.6	74.3
366.2		5 x 3 $\frac{1}{2}$ x $\frac{3}{4}$		117.5		74.3
368.1		6 x 4 x $\frac{5}{8}$		118.3		74.3
397.8		5 x 3 $\frac{1}{2}$ x $\frac{3}{8}$	12 x $\frac{1}{2}$	79.9	40.8	74.3
404.7		6 x 4 x $\frac{3}{8}$	14 x $\frac{3}{8}$	87.5	35.7	74.3
423.1		6 x 4 x $\frac{3}{4}$		132.7		74.3
446.6		5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	12 x $\frac{1}{2}$	92.7	40.8	74.3
456.1		6 x 4 x $\frac{3}{8}$	14 x $\frac{1}{2}$	87.5	47.6	74.3
475.8		6 x 4 x $\frac{7}{8}$		147.1		74.3
490.3		5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	12 x $\frac{5}{8}$	92.7	51.0	74.3
514.0		6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	103.1	47.6	74.3
536.7		5 x 3 $\frac{1}{2}$ x $\frac{5}{8}$	12 x $\frac{5}{8}$	105.5	51.0	74.3
565.1		6 x 4 x $\frac{1}{2}$	14 x $\frac{5}{8}$	103.1	59.5	74.3
620.6		6 x 4 x $\frac{5}{8}$	14 x $\frac{5}{8}$	118.3	59.5	74.3
671.3		6 x 4 x $\frac{5}{8}$	14 x $\frac{3}{4}$	118.3	71.4	74.3
723.8		6 x 4 x $\frac{3}{4}$	14 x $\frac{3}{4}$	132.7	71.4	74.3

**CARNEGIE STEEL COMPANY**

**RIVETED PLATE GIRDERS—Continued**

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
281.4	30 x ½	5 x 3½ x ½		99.0		86.6
319.5		6 x 4 x ½		109.4		86.6
329.7		5 x 3½ x ¾		111.8		86.6
375.5		5 x 3½ x ¾		123.8		86.6
377.3		6 x 4 x ¾		124.6		86.6
432.3		6 x 4 x ¾		139.0		86.6
455.5		5 x 3½ x ½	12 x ½	99.0	40.8	86.6
485.0		6 x 4 x ¾		153.4		86.6
499.2		5 x 3½ x ½	12 x ¾	99.0	51.0	86.6
523.0		6 x 4 x ½	14 x ½	109.4	47.6	86.6
545.6		5 x 3½ x ¾	12 x ¾	111.8	51.0	86.6
574.0		6 x 4 x ½	14 x ¾	109.4	59.5	86.6
629.5		6 x 4 x ¾	14 x ¾	124.6	59.5	86.6
680.1		6 x 4 x ¾	14 x ¾	124.6	71.4	86.6
732.6		6 x 4 x ¾	14 x ¾	139.0	71.4	86.6
290.6	30 x ½	5 x 3½ x ½		105.4		99.0
328.8		6 x 4 x ½		115.8		99.0
338.9		5 x 3½ x ¾		118.2		99.0
384.7		5 x 3½ x ¾		130.2		99.0
386.5		6 x 4 x ¾		131.0		99.0
441.5		6 x 4 x ¾		145.4		99.0
464.4		5 x 3½ x ½	12 x ½	105.4	40.8	99.0
494.2		6 x 4 x ¾		159.8		99.0
508.0		5 x 3½ x ½	12 x ¾	105.4	51.0	99.0
531.9		6 x 4 x ½	14 x ½	115.8	47.6	99.0
554.5		5 x 3½ x ¾	12 x ¾	118.2	51.0	99.0
582.8		6 x 4 x ½	14 x ¾	115.8	59.5	99.0
638.3		6 x 4 x ¾	14 x ¾	131.0	59.5	99.0
688.9		6 x 4 x ¾	14 x ¾	131.0	71.4	99.0
741.3		6 x 4 x ¾	14 x ¾	145.4	71.4	99.0
251.7	33 x ¾	5 x 3½ x ¾		83.7		81.0
283.7		6 x 4 x ¾		91.3		81.0
307.7		5 x 3½ x ½		96.6		81.0
308.4		6 x 6 x ¾		101.7		121.5
350.3		6 x 4 x ½		106.9		81.0
361.5		5 x 3½ x ¾		109.3		81.0
383.6		6 x 6 x ¾		120.5		121.5
396.9		5 x 3½ x ¾	12 x ¾	83.7	30.6	81.0
412.5		5 x 3½ x ¾		121.3		81.0
414.7		6 x 4 x ¾		122.1		81.0
445.5		5 x 3½ x ¾	12 x ½	83.7	40.8	81.0
453.4		6 x 4 x ¾	14 x ¾	91.3	35.7	81.0

## GIRDERS

## RIVETED PLATE GIRDERS—Continued

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plate	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
455.9	33 x 3/8	6 x 6 x 3/8		138.9		121.5
476.1		6 x 4 x 3/4		136.5		81.0
477.6		6 x 6 x 3/8	14 x 3/8	101.7	35.7	121.5
499.8		5 x 3 1/2 x 1 1/2	12 x 1/2	96.5	40.8	81.0
510.0		6 x 4 x 3/8	14 x 1/2	91.3	47.6	81.0
525.4		6 x 6 x 3/4		156.9		121.5
534.1		6 x 6 x 3/8	14 x 1/2	101.7	47.6	121.5
548.0		5 x 3 1/2 x 1 1/2	12 x 3/8	99.5	51.0	81.0
574.7		6 x 4 x 1/2	14 x 1/2	106.9	47.6	81.0
590.6		6 x 6 x 3/8	14 x 3/8	101.7	59.5	121.5
592.6		6 x 6 x 3/8		174.5		121.5
599.9		5 x 3 1/2 x 3/8	12 x 3/8	109.3	51.0	81.0
607.1		6 x 6 x 1/2	14 x 1/2	120.5	47.6	121.5
630.9		6 x 4 x 1/2	14 x 3/8	106.9	59.5	81.0
663.1		6 x 6 x 1/2	14 x 3/8	120.5	59.5	121.5
693.0		6 x 4 x 3/8	14 x 3/8	123.1	59.5	81.0
719.2		6 x 6 x 1/2	14 x 3/4	120.5	71.4	121.5
732.7		6 x 6 x 3/8	11 x 3/4	138.9	59.5	121.5
748.9		6 x 4 x 3/8	14 x 3/4	122.1	71.4	81.0
788.3		6 x 6 x 3/8	14 x 3/4	138.9	71.4	121.5
807.6		6 x 4 x 3/4	14 x 3/4	136.5	71.4	81.0
854.9		6 x 6 x 3/4	14 x 3/4	156.9	71.4	121.5
318.9	33 x 7/16	5 x 3 1/2 x 1/2		103.5		94.5
361.5		6 x 4 x 1/2		113.9		94.5
372.7		5 x 3 1/2 x 3/8		116.3		94.5
394.8		6 x 6 x 1/2		127.5		141.8
423.7		5 x 3 1/2 x 3/4		128.3		94.5
425.8		6 x 4 x 3/8		129.1		94.5
467.0		6 x 6 x 3/8		145.9		141.8
487.2		6 x 4 x 3/4		143.5		94.5
510.7		5 x 3 1/2 x 1/2	12 x 1/2	103.5	40.8	94.5
536.6		6 x 6 x 3/4		163.9		141.8
558.8		5 x 3 1/2 x 3/4	12 x 3/8	103.5	51.0	94.5
585.6		6 x 4 x 1/2	14 x 1/2	113.9	47.6	94.5
603.8		6 x 6 x 3/8		181.5		141.8
610.6		5 x 3 1/2 x 3/8	12 x 3/8	116.3	51.0	94.5
617.9		6 x 6 x 1/2	14 x 1/2	127.5	47.6	141.8
641.7		6 x 4 x 1/2	14 x 3/8	113.9	59.5	94.5
673.9		6 x 6 x 1/2	14 x 3/8	127.5	59.5	141.8
703.8		6 x 4 x 3/8	14 x 3/8	129.1	59.5	94.5



**CARNEGIE STEEL COMPANY**

**RIVETED PLATE GIRDERS—Continued**

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
720.0	33 x 3/16	6x 6 x 1/2	14 x 3/4	127.5	71.4	141.8
743.5		6x 6 x 5/8	14 x 5/8	145.9	59.5	141.8
759.6		6x 4 x 5/8	14 x 3/4	129.1	71.4	94.5
799.0		6x 6 x 5/8	14 x 3/4	145.9	71.4	141.8
818.3		6x 4 x 3/4	14 x 3/4	143.5	71.4	94.5
865.6		6x 6 x 3/4	14 x 3/4	163.9	71.4	141.8
330.0	33 x 1/2	5x3 1/2 x 1/2		110.5		108.0
372.6		6x 4 x 1/2		120.9		108.0
383.0		5x3 1/2 x 5/8		123.3		108.0
406.0		6x 6 x 1/2		131.5		162.0
434.9		5x3 1/2 x 3/4		135.3		108.0
437.0		6x 4 x 5/8		136.1		108.0
478.2		6x 6 x 5/8		152.9		108.0
498.4		6x 4 x 3/4		150.5		108.0
521.5		5x3 1/2 x 1/2	12 x 1/2	110.5	40.8	108.0
547.8		6x 6 x 3/4		170.9		162.0
569.5		5x3 1/2 x 3/4	12 x 5/8	110.5	51.0	108.0
590.4		6x 4 x 1/2	14 x 1/2	120.9	47.6	108.0
615.0		6x 6 x 1/2		188.5		162.0
621.4		5x3 1/2 x 5/8	12 x 5/8	123.3	51.0	108.0
628.8		6x 6 x 1/2	14 x 1/2	134.5	47.6	162.0
652.5		6x 4 x 1/2	14 x 5/8	120.9	59.5	108.0
684.6		6x 6 x 1/2	14 x 5/8	134.5	59.5	162.0
714.5		6x 4 x 5/8	14 x 5/8	136.1	59.5	108.0
740.6		6x 6 x 1/2	14 x 3/4	134.5	71.4	162.0
754.3		6x 6 x 5/8	14 x 5/8	152.9	59.5	162.0
770.3		6x 4 x 5/8	14 x 3/4	136.1	71.4	108.0
809.7		6x 6 x 5/8	14 x 3/4	152.9	71.4	162.0
829.0		6x 4 x 3/4	14 x 3/4	150.5	71.4	108.0
876.3		6x 6 x 3/4	14 x 3/4	170.9	71.4	162.0
318.0	36 x 1/2	6x 4 x 3/4		95.1		87.8
344.4		5x3 1/2 x 1/2		100.3		87.8
346.0		6x 6 x 3/8		105.5		135.0
391.4		6x 4 x 1/2		110.7		87.8
403.7		5x3 1/2 x 5/8		113.1		87.8
430.3		6x 6 x 1/2		124.3		135.0
460.0		5x3 1/2 x 3/4		125.1		87.8
462.4		6x 4 x 5/8		125.9		87.8
503.3		6x 4 x 3/4	14 x 1/2	95.1	35.7	87.8
510.5		6x 6 x 5/8		142.7		135.0
530.2		6x 4 x 3/4		140.3		87.8
531.6		6x 6 x 5/8	14 x 3/4	105.5	35.7	135.0

## GIRDERS

## RIVETED PLATE GIRDERS—Continued

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
554.3	36 x $\frac{3}{8}$	5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	12 x $\frac{1}{2}$	100.3	40.8	87.8
565.1		6 x 4 x $\frac{3}{8}$	14 x $\frac{1}{2}$	95.1	47.6	87.8
593.2		6 x 6 x $\frac{3}{8}$	14 x $\frac{1}{2}$	105.5	47.6	135.0
595.3		6 x 4 x $\frac{7}{8}$		154.7		87.8
606.8		5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	12 x $\frac{5}{8}$	100.3	51.0	87.8
636.5		6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	110.7	47.6	87.8
654.9		6 x 6 x $\frac{3}{8}$	14 x $\frac{5}{8}$	105.5	59.5	135.0
664.2		5 x 3 $\frac{1}{2}$ x $\frac{5}{8}$	12 x $\frac{5}{8}$	113.1	51.0	87.8
674.4		6 x 6 x $\frac{1}{2}$	14 x $\frac{1}{2}$	124.3	47.6	135.0
698.0		6 x 4 x $\frac{1}{2}$	14 x $\frac{5}{8}$	110.7	59.5	87.8
735.5		6 x 6 x $\frac{1}{2}$	14 x $\frac{5}{8}$	124.3	59.5	135.0
766.6		6 x 4 x $\frac{5}{8}$	14 x $\frac{5}{8}$	125.9	59.5	87.8
796.8		6 x 6 x $\frac{1}{2}$	14 x $\frac{3}{4}$	124.3	71.4	135.0
813.1		6 x 6 x $\frac{5}{8}$	14 x $\frac{5}{8}$	142.7	59.5	135.0
827.6		6 x 4 x $\frac{5}{8}$	14 x $\frac{3}{4}$	125.9	71.4	87.8
873.8		6 x 6 x $\frac{5}{8}$	14 x $\frac{3}{4}$	142.7	71.4	135.0
892.8		6 x 4 x $\frac{3}{4}$	14 x $\frac{3}{4}$	140.3	71.4	87.8
357.7	36 x $\frac{7}{16}$	5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$		108.0		102.4
404.7		6 x 4 x $\frac{1}{2}$		118.4		102.4
417.0		5 x 3 $\frac{1}{2}$ x $\frac{3}{4}$		120.8		102.4
443.6		6 x 6 x $\frac{1}{2}$		132.0		157.5
473.3		5 x 3 $\frac{1}{2}$ x $\frac{3}{4}$		132.8		102.4
475.7		6 x 4 x $\frac{3}{8}$		133.6		102.4
523.8		6 x 6 x $\frac{3}{8}$		150.4		157.5
543.5		6 x 4 x $\frac{3}{4}$		148.0		102.4
567.2		5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	12 x $\frac{1}{2}$	108.0	40.8	102.4
608.6		6 x 4 x $\frac{3}{8}$		162.4		102.4
619.7		5 x 3 $\frac{1}{2}$ x $\frac{1}{2}$	12 x $\frac{5}{8}$	108.0	51.0	102.4
649.5		6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	118.4	47.6	102.4
677.1		5 x 3 $\frac{1}{2}$ x $\frac{5}{8}$	12 x $\frac{5}{8}$	120.8	51.0	102.4
687.3		6 x 6 x $\frac{1}{2}$	14 x $\frac{1}{2}$	132.0	47.6	157.5
710.8		6 x 4 x $\frac{1}{2}$	14 x $\frac{5}{8}$	118.4	59.5	102.4
748.4		6 x 6 x $\frac{1}{2}$	14 x $\frac{5}{8}$	132.0	59.5	157.5
779.5		6 x 4 x $\frac{3}{8}$	14 x $\frac{5}{8}$	133.6	59.5	102.4
809.5		6 x 6 x $\frac{1}{2}$	14 x $\frac{3}{4}$	132.0	71.4	157.5
825.9		6 x 6 x $\frac{3}{8}$	14 x $\frac{5}{8}$	150.4	59.5	157.5
840.4		6 x 4 x $\frac{5}{8}$	14 x $\frac{3}{4}$	133.6	71.4	102.4
886.6		6 x 6 x $\frac{5}{8}$	14 x $\frac{3}{4}$	150.4	71.4	157.5
905.5		6 x 4 x $\frac{3}{4}$	14 x $\frac{3}{4}$	148.0	71.4	102.4

**CARNEGIE STEEL COMPANY**

**RIVETED PLATE GIRDERS—Continued**

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
418.0		6 x 4 x $\frac{1}{2}$		126.0		117.0
456.9		6 x 6 x $\frac{1}{2}$		139.6		180.0
489.0		6 x 4 x $\frac{5}{8}$		141.2		117.0
537.1		6 x 6 x $\frac{5}{8}$		158.0		180.0
556.9		6 x 4 x $\frac{3}{4}$		155.6		117.0
614.5		6 x 6 x $\frac{3}{4}$		176.0		180.0
621.9		6 x 4 x $\frac{7}{8}$		170.0		117.0
662.5		6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	126.0	47.6	117.0
689.2		6 x 6 x $\frac{7}{8}$		193.6		180.0
700.3		6 x 6 x $\frac{1}{2}$	14 x $\frac{1}{2}$	139.6	47.6	180.0
723.7		6 x 4 x $\frac{1}{2}$	14 x $\frac{5}{8}$	126.0	59.5	117.0
761.3	36 x $\frac{1}{2}$	6 x 6 x $\frac{1}{2}$	14 x $\frac{5}{8}$	139.6	59.5	180.0
792.3		6 x 4 x $\frac{5}{8}$	14 x $\frac{5}{8}$	141.2	59.5	117.0
822.3		6 x 6 x $\frac{1}{2}$	14 x $\frac{3}{4}$	139.6	71.4	180.0
838.8		6 x 6 x $\frac{5}{8}$	14 x $\frac{5}{8}$	158.0	59.5	180.0
853.2		6 x 4 x $\frac{5}{8}$	14 x $\frac{3}{4}$	141.2	71.4	117.0
899.4		6 x 6 x $\frac{5}{8}$	14 x $\frac{3}{4}$	158.0	71.4	180.0
918.3		6 x 4 x $\frac{3}{4}$	14 x $\frac{3}{4}$	155.6	71.4	117.0
973.7		6 x 6 x $\frac{3}{4}$	14 x $\frac{3}{4}$	176.0	71.4	180.0
1039.4		6 x 4 x $\frac{3}{4}$	14 x 1	155.6	95.2	117.0
1094.1		6 x 6 x $\frac{3}{4}$	14 x 1	176.0	95.2	180.0
1101.1		6 x 4 x $\frac{7}{8}$	14 x 1	170.0	95.2	117.0
1164.9		6 x 6 x $\frac{7}{8}$	14 x 1	193.6	95.2	180.0
444.7		6 x 4 x $\frac{1}{2}$		141.3		146.3
483.5		6 x 6 x $\frac{1}{2}$		154.9		225.0
515.7		6 x 4 x $\frac{5}{8}$		156.5		146.3
563.7		6 x 6 x $\frac{5}{8}$		173.3		225.0
583.5		6 x 4 x $\frac{3}{4}$		170.9		146.3
641.2		6 x 6 x $\frac{3}{4}$		191.3		225.0
648.5		6 x 4 x $\frac{7}{8}$		185.3		146.3
688.4	36 x $\frac{3}{4}$	6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	141.3	47.6	146.3
715.8		6 x 6 x $\frac{3}{4}$		208.9		225.0
726.2		6 x 6 x $\frac{1}{2}$	14 x $\frac{1}{2}$	154.9	47.6	
749.4		6 x 4 x $\frac{1}{2}$	14 x $\frac{5}{8}$	141.3	59.5	146.3
787.0		6 x 6 x $\frac{1}{2}$	14 x $\frac{5}{8}$	154.9	59.5	225.0
818.1		6 x 4 x $\frac{5}{8}$	14 x $\frac{5}{8}$	156.5	59.5	146.3
847.9		6 x 6 x $\frac{1}{2}$	14 x $\frac{3}{4}$	154.9	71.4	225.0
864.6		6 x 6 x $\frac{5}{8}$	14 x $\frac{5}{8}$	173.3	59.5	225.0
878.8		6 x 4 x $\frac{5}{8}$	14 x $\frac{3}{4}$	156.5	71.4	146.3
924.9		6 x 6 x $\frac{5}{8}$	14 x $\frac{3}{4}$	173.3	71.4	225.0

## GIRDERS

## RIVETED PLATE GIRDERS—Continued

Section Modulus, Axis 1-1, Inches <sup>4</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
943.9	36 x ½	6 x 4 x ¾	14 x ¾	170.9	71.4	146.3
999.3		6 x 6 x ¾	14 x ¾	191.3	71.4	225.0
1045.9		6 x 6 x ¾	14 x 1	173.3	95.2	225.0
1064.7		6 x 4 x ¾	14 x 1	170.9	95.2	146.3
1119.3		6 x 6 x ¾	14 x 1	191.3	95.2	225.0
1126.3		6 x 4 x ¾	14 x 1	185.3	95.2	146.3
1190.1		6 x 6 x ¾	14 x 1	208.9	95.2	225.0
390.2	• 42 x ½	6 x 4 x ¾		102.8		101.3
427.5		6 x 6 x ¾		113.2		157.5
477.2		6 x 4 x ¾		118.4		101.3
527.2		6 x 6 x ¾		132.0		157.5
561.4		6 x 4 x ¾		133.6		101.3
606.6		6 x 4 x ¾	14 x ¾	102.8	35.7	101.3
623.5		6 x 6 x ¾		150.4		157.5
638.3		6 x 4 x ¾	16 x ¾	102.8	40.8	101.3
642.1		6 x 4 x ¾		148.0		101.3
643.2		6 x 6 x ¾	14 x ¾	113.2	35.7	157.5
675.1		6 x 6 x ¾	16 x ¾	113.2	40.8	157.5
678.6		6 x 4 x ¾	14 x ¾	102.8	47.6	101.3
715.2		6 x 6 x ¾	14 x ¾	113.2	47.6	157.5
716.5		6 x 6 x ¾		168.4		157.5
719.5		6 x 4 x ¾		162.4		101.3
757.7		6 x 6 x ¾	16 x ¾	113.2	54.4	157.5
763.7		6 x 4 x ¾	14 x ¾	118.4	47.6	101.3
787.2		6 x 6 x ¾	14 x ¾	113.2	59.5	157.5
806.2		6 x 4 x ¾	16 x ¾	118.4	54.4	101.3
806.4		6 x 6 x ¾		186.0		157.5
812.7		6 x 6 x ¾	14 x ¾	132.0	47.6	157.5
835.5		6 x 4 x ¾	14 x ¾	118.4	59.5	101.3
855.2		6 x 6 x ¾	16 x ¾	132.0	54.4	157.5
884.2		6 x 6 x ¾	14 x ¾	132.0	59.5	157.5
917.3		6 x 4 x ¾	14 x ¾	133.6	59.5	101.3
937.3		6 x 6 x ¾	16 x ¾	132.0	68.0	157.5
955.7		6 x 6 x ¾	14 x ¾	132.0	71.4	157.5
970.4		6 x 4 x ¾	16 x ¾	133.6	68.0	101.3
977.6		6 x 6 x ¾	14 x ¾	150.4	59.5	157.5
988.7		6 x 4 x ¾	14 x ¾	133.6	71.4	101.3
1030.8		6 x 6 x ¾	16 x ¾	150.4	68.0	157.5
1048.6		6 x 6 x ¾	14 x ¾	150.4	71.4	157.5
1066.6		6 x 4 x ¾	14 x ¾	148.0	71.4	101.3
1112.4		6 x 6 x ¾	16 x ¾	150.4	81.6	157.5

## CARNEGIE STEEL COMPANY

## RIVETED PLATE GIRDERS—Continued

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
1130.4	42 x $\frac{3}{8}$	6 x 4 x $\frac{3}{4}$	16 x $\frac{3}{4}$	148.0	81.6	101.3
1138.5		6 x 6 x $\frac{3}{4}$	14 x $\frac{3}{4}$	168.4	71.4	157.5
1194.1		6 x 6 x $\frac{5}{8}$	16 x $\frac{7}{8}$	150.4	95.2	157.5
1202.3		6 x 6 x $\frac{3}{4}$	16 x $\frac{3}{4}$	168.4	81.6	157.5
1283.5		6 x 6 x $\frac{3}{4}$	16 x $\frac{7}{8}$	168.4	95.2	157.5
1286.4		6 x 4 x $\frac{7}{8}$	16 x $\frac{7}{8}$	162.4	95.2	101.3
1369.9		6 x 6 x $\frac{7}{8}$	16 x $\frac{7}{8}$	186.0	95.2	157.5
495.3	42 x $\frac{7}{16}$	6 x 4 x $\frac{1}{2}$		127.3		118.1
545.4		6 x 6 x $\frac{1}{2}$		140.9		183.8
579.5		6 x 4 x $\frac{5}{8}$		142.5		118.1
641.6		6 x 6 x $\frac{5}{8}$		159.3		183.8
660.2		6 x 4 x $\frac{3}{4}$		156.9		118.1
734.7		6 x 6 x $\frac{3}{4}$		177.3		183.8
737.6		6 x 4 x $\frac{7}{8}$		171.3		118.1
781.5		6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	127.3	47.6	118.1
824.0		6 x 4 x $\frac{1}{2}$	16 x $\frac{1}{2}$	127.3	54.4	118.1
824.6		6 x 6 x $\frac{7}{8}$		191.9		183.8
830.4		6 x 6 x $\frac{1}{2}$	14 x $\frac{1}{2}$	140.9	47.6	183.8
853.1		6 x 4 x $\frac{1}{2}$	14 x $\frac{5}{8}$	127.3	59.5	118.1
872.9		6 x 6 x $\frac{1}{2}$	16 x $\frac{1}{2}$	140.9	54.4	183.8
901.8		6 x 6 x $\frac{1}{2}$	14 x $\frac{5}{8}$	140.9	59.5	183.8
934.9		6 x 4 x $\frac{5}{8}$	14 x $\frac{5}{8}$	142.5	59.5	118.1
954.9		6 x 6 x $\frac{1}{2}$	16 x $\frac{5}{8}$	140.9	68.6	183.8
973.2		6 x 6 x $\frac{1}{2}$	14 x $\frac{3}{4}$	140.9	71.4	183.8
988.1		6 x 4 x $\frac{5}{8}$	16 x $\frac{5}{8}$	142.5	68.0	118.1
995.3		6 x 6 x $\frac{5}{8}$	14 x $\frac{5}{8}$	159.3	59.5	183.8
1006.2		6 x 4 x $\frac{5}{8}$	14 x $\frac{3}{4}$	142.5	71.4	118.1
1048.4		6 x 6 x $\frac{5}{8}$	16 x $\frac{5}{8}$	159.3	68.0	183.8
1066.2		6 x 6 x $\frac{5}{8}$	14 x $\frac{3}{4}$	159.3	71.4	183.8
1084.1		6 x 4 x $\frac{3}{4}$	14 x $\frac{3}{4}$	156.9	71.4	118.1
1129.9		6 x 6 x $\frac{5}{8}$	16 x $\frac{3}{4}$	159.3	81.6	183.8
1147.9		6 x 4 x $\frac{3}{4}$	16 x $\frac{3}{4}$	156.9	81.6	118.1
1156.0		6 x 6 x $\frac{3}{4}$	14 x $\frac{3}{4}$	177.3	71.4	183.8
1211.6		6 x 6 x $\frac{5}{8}$	16 x $\frac{7}{8}$	159.3	95.2	183.8
1219.8		6 x 6 x $\frac{3}{4}$	16 x $\frac{3}{4}$	177.3	81.6	183.8
1300.9		6 x 6 x $\frac{3}{4}$	16 x $\frac{7}{8}$	177.3	95.2	183.8
1387.3		6 x 6 x $\frac{7}{8}$	16 x $\frac{7}{8}$	194.9	95.2	183.8
513.5	42 x $\frac{1}{2}$	6 x 4 x $\frac{1}{2}$		136.2		135.0
563.5		6 x 6 x $\frac{1}{2}$		140.8		210.0
597.7		6 x 4 x $\frac{5}{8}$		151.4		135.0
659.8		6 x 6 x $\frac{5}{8}$		168.2		210.0
678.4		6 x 4 x $\frac{3}{4}$		165.8		135.0

## GIRDERS

## RIVETED PLATE GIRDERS—Continued

Section Modulus, Axis 1-1, Inches <sup>3</sup> ,	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
752.8		6 x 6 x $\frac{3}{4}$		186.2		210.0
755.8		6 x 4 x $\frac{3}{8}$		180.2		135.0
799.2		6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	136.2	47.6	135.0
841.7		6 x 4 x $\frac{1}{2}$	16 x $\frac{1}{2}$	136.2	54.4	135.0
842.7		6 x 6 x $\frac{3}{8}$		203.8		210.0
848.1		6 x 6 x $\frac{1}{2}$	14 x $\frac{1}{2}$	149.8	47.6	210.0
870.8		6 x 4 x $\frac{1}{2}$	14 x $\frac{5}{8}$	136.2	59.5	135.0
890.6		6 x 6 x $\frac{1}{2}$	16 x $\frac{1}{2}$	149.8	54.4	210.0
919.4		6 x 6 x $\frac{1}{2}$	14 x $\frac{5}{8}$	149.8	59.5	210.0
952.6		6 x 4 x $\frac{5}{8}$	14 x $\frac{5}{8}$	151.4	59.5	135.0
972.6		6 x 6 x $\frac{1}{2}$	16 x $\frac{5}{8}$	149.8	68.0	210.0
990.8		6 x 6 x $\frac{1}{2}$	14 x $\frac{3}{4}$	149.8	71.4	210.0
1005.7		6 x 4 x $\frac{5}{8}$	16 x $\frac{5}{8}$	151.4	68.0	135.0
1012.9	42 x $\frac{1}{2}$	6 x 6 x $\frac{5}{8}$	14 x $\frac{5}{8}$	168.2	59.5	210.0
1023.7		6 x 4 x $\frac{5}{8}$	14 x $\frac{3}{4}$	151.4	71.4	135.0
1066.0		6 x 6 x $\frac{5}{8}$	16 x $\frac{5}{8}$	168.2	68.0	210.0
1083.7		6 x 6 x $\frac{5}{8}$	14 x $\frac{3}{4}$	168.2	71.4	210.0
1101.7		6 x 4 x $\frac{3}{4}$	14 x $\frac{3}{4}$	165.8	71.4	135.0
1147.5		6 x 6 x $\frac{5}{8}$	16 x $\frac{3}{4}$	168.2	81.6	210.0
1165.4		6 x 4 x $\frac{3}{4}$	16 x $\frac{3}{4}$	165.8	81.6	135.0
1173.6		6 x 6 x $\frac{3}{4}$	14 x $\frac{3}{4}$	186.2	71.4	210.0
1229.0		6 x 6 x $\frac{5}{8}$	16 x $\frac{5}{8}$	168.2	95.2	210.0
1237.4		6 x 6 x $\frac{3}{4}$	16 x $\frac{3}{4}$	186.2	81.6	210.0
1318.4		6 x 6 x $\frac{3}{4}$	16 x $\frac{5}{8}$	186.2	95.2	210.0
1321.2		6 x 4 x $\frac{7}{8}$	16 x $\frac{7}{8}$	180.2	95.2	135.0
1404.7		6 x 6 x $\frac{7}{8}$	16 x $\frac{7}{8}$	203.8	95.2	210.0
466.9	48 x $\frac{3}{8}$	6 x 4 x $\frac{3}{8}$		110.4		121.5
512.7		6 x 6 x $\frac{3}{8}$		120.8		180.0
567.4		6 x 4 x $\frac{1}{2}$		126.0		121.5
628.9		6 x 6 x $\frac{1}{2}$		139.6		180.0
664.9		6 x 4 x $\frac{5}{8}$		141.2		121.5
714.4		6 x 4 x $\frac{3}{8}$	14 x $\frac{3}{8}$	110.4	35.7	121.5
741.3		6 x 6 x $\frac{3}{8}$		158.0		180.0
750.8		6 x 4 x $\frac{3}{8}$	16 x $\frac{3}{8}$	110.4	40.8	121.5
758.5		6 x 4 x $\frac{1}{2}$		155.6		121.5
759.5		6 x 6 x $\frac{3}{8}$	14 x $\frac{3}{8}$	120.8	35.7	180.0
795.9		6 x 6 x $\frac{3}{8}$	16 x $\frac{3}{8}$	120.8	40.8	180.0
797.0		6 x 4 x $\frac{3}{8}$	14 x $\frac{1}{2}$	110.4	47.6	121.5
841.9		6 x 6 x $\frac{3}{8}$	14 x $\frac{1}{2}$	120.8	47.6	180.0
848.3		6 x 4 x $\frac{7}{8}$		170.0		121.5
850.1		6 x 6 x $\frac{3}{4}$		176.0		180.0
890.4		6 x 6 x $\frac{3}{8}$	16 x $\frac{1}{2}$	120.8	54.4	180.0
895.5		6 x 4 x $\frac{1}{2}$	14 x $\frac{1}{2}$	126.0	47.6	121.5

**CARNEGIE STEEL COMPANY**

**RIVETED PLATE GIRDERS—Continued**

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
924.3	48 x 3/8	6 x 6 x 3/8	14 x 3/8	120.8	59.5	180.0
944.0		6 x 4 x 1/2	16 x 1/2	126.0	54.4	121.5
955.2		6 x 6 x 3/8		193.6		180.0
955.8		6 x 6 x 1/2	14 x 1/2	139.6	47.6	180.0
977.7		6 x 4 x 1/2	14 x 3/8	126.0	59.5	121.5
1004.3		6 x 6 x 1/2	16 x 1/2	139.6	54.4	180.0
1037.6		6 x 6 x 1/2	14 x 3/8	139.6	59.5	180.0
1072.7		6 x 4 x 3/8	14 x 3/8	141.2	59.5	121.5
1098.2		6 x 6 x 1/2	16 x 3/8	139.6	68.0	180.0
1119.5		6 x 6 x 1/2	14 x 3/4	139.6	71.4	180.0
1133.3		6 x 4 x 3/8	16 x 3/8	141.2	68.0	121.5
1147.1		6 x 6 x 3/8	14 x 3/8	158.0	59.5	180.0
1154.4		6 x 4 x 3/8	14 x 3/4	141.2	71.4	121.5
1207.8		6 x 6 x 3/8	16 x 3/8	158.0	68.0	180.0
1228.4		6 x 6 x 3/8	14 x 3/4	158.0	71.4	180.0
1245.2		6 x 4 x 3/4	14 x 3/4	155.6	71.4	121.5
1301.2		6 x 6 x 3/8	16 x 3/4	158.0	81.6	180.0
1317.9		6 x 4 x 3/4	16 x 3/4	155.6	81.6	121.5
1334.0		6 x 6 x 3/4	14 x 3/4	176.0	71.4	180.0
1394.7		6 x 6 x 3/8	16 x 3/8	158.0	95.2	180.0
1406.7		6 x 6 x 3/4	16 x 3/4	176.0	81.6	180.0
1498.1		6 x 4 x 7/8	16 x 7/8	170.0	95.2	121.5
1490.7		6 x 6 x 3/4	16 x 7/8	176.0	95.2	180.0
1601.3		6 x 6 x 7/8	16 x 7/8	193.6	95.2	180.0
591.2	48 x 3/16	6 x 4 x 1/2		136.2		141.8
652.7		6 x 6 x 1/2		149.8		210.0
688.7		6 x 4 x 3/8		151.4		141.8
765.0		6 x 6 x 3/8		168.2		210.0
782.3		6 x 4 x 3/4		165.8		141.8
872.1		6 x 4 x 7/8		180.2		141.8
873.8		6 x 6 x 3/4		186.2		210.0
918.8		6 x 4 x 1/2	14 x 1/2	136.2	47.6	141.8
967.3		6 x 4 x 1/2	16 x 1/2	136.2	54.4	141.8
979.0		6 x 6 x 7/8		203.8		210.0
979.0		6 x 6 x 1/2	14 x 1/2	149.8	47.6	210.0
1000.8		6 x 4 x 1/2	14 x 3/8	136.2	59.5	141.8
1027.6		6 x 6 x 1/2	16 x 1/2	149.8	54.4	210.0
1060.8		6 x 6 x 1/2	14 x 3/8	149.8	59.5	210.0
1095.8		6 x 4 x 3/8	14 x 3/8	151.4	59.5	141.8
1121.4		6 x 6 x 1/2	16 x 3/8	149.8	68.0	210.0
1142.5		6 x 6 x 3/4	14 x 3/4	149.8	71.4	210.0
1158.5		6 x 4 x 3/8	16 x 3/8	151.4	68.0	141.8

## GIRDERS

## RIVETED PLATE GIRDERS—Continued

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
1170.3	48 x 7/16	6 x 6 x 5/8	14 x 5/8	168.2	59.5	210.0
1177.4		6 x 4 x 5/8	14 x 3/4	151.4	71.4	141.8
1230.9		6 x 6 x 5/8	16 x 5/8	168.2	68.0	210.0
1251.5		6 x 6 x 5/8	14 x 3/4	168.2	71.4	210.0
1268.2		6 x 4 x 3/4	14 x 3/4	165.8	71.4	141.8
1324.3		6 x 6 x 5/8	16 x 3/4	168.2	81.6	210.0
1341.0		6 x 4 x 3/4	16 x 3/4	165.8	81.6	141.8
1357.0		6 x 6 x 3/4	14 x 3/4	186.2	71.4	210.0
1417.7		6 x 6 x 5/8	16 x 3/4	168.2	95.2	210.0
1429.8		6 x 6 x 3/4	16 x 3/4	186.2	81.6	210.0
1521.0		6 x 4 x 7/8	16 x 3/4	180.2	95.2	141.8
1522.7		6 x 6 x 3/4	16 x 3/4	186.2	95.2	210.0
1624.2		6 x 6 x 7/8	16 x 3/4	203.8	95.2	210.0
615.0	48 x 1/2	6 x 4 x 1/2		146.4		162.0
676.4		6 x 6 x 1/2		160.0		240.0
712.4		6 x 4 x 5/8		161.6		162.0
788.8		6 x 6 x 5/8		178.4		240.0
806.0		6 x 4 x 3/4		176.0		162.0
895.8		6 x 4 x 7/8		190.4		162.0
897.6		6 x 6 x 3/4		196.4		240.0
942.1		6 x 4 x 1/2	14 x 1/2	146.4	47.6	162.0
990.6		6 x 4 x 1/2	16 x 1/2	146.4	54.4	162.0
1002.3		6 x 6 x 1/2	14 x 1/2	160.0	47.6	240.0
1002.7		6 x 6 x 3/8		214.0		240.0
1024.0		6 x 4 x 1/2	14 x 5/8	146.4	59.5	162.0
1050.8		6 x 6 x 1/2	16 x 1/2	160.0	54.4	240.0
1083.9		6 x 6 x 1/2	14 x 5/8	160.0	59.5	240.0
1119.0		6 x 4 x 5/8	14 x 5/8	161.6	59.5	162.0
1144.5		6 x 6 x 1/2	16 x 5/8	160.0	68.0	240.0
1165.6		6 x 6 x 1/2	14 x 3/4	160.0	71.4	240.0
1170.6		6 x 4 x 5/8	16 x 5/8	161.6	68.0	162.0
1193.4		6 x 6 x 5/8	14 x 5/8	178.4	59.5	240.0
1200.5		6 x 4 x 5/8	14 x 3/4	161.6	71.4	162.0
1254.1		6 x 6 x 5/8	16 x 5/8	178.4	68.0	240.0
1274.5		6 x 6 x 5/8	14 x 3/4	178.4	71.4	240.0
1291.2		6 x 4 x 3/4	14 x 3/4	176.0	71.4	162.0
1347.3		6 x 6 x 5/8	16 x 3/4	178.4	81.6	240.0
1384.0		6 x 4 x 3/4	16 x 3/4	176.0	81.6	162.0
1380.0		6 x 6 x 3/4	14 x 3/4	196.4	71.4	240.0
1440.6		6 x 6 x 5/8	16 x 5/8	178.4	95.2	240.0
1452.8		6 x 6 x 3/4	16 x 3/4	196.4	81.6	240.0
1543.9		6 x 4 x 7/8	16 x 7/8	190.4	95.2	162.0
1545.6		6 x 6 x 3/4	16 x 7/8	196.4	95.2	240.0
1647.1		6 x 6 x 7/8	16 x 7/8	214.0	95.2	240.0



**CARNEGIE STEEL COMPANY**

**RIVETED PLATE GIRDERS—Concluded**

Section Modulus, Axis 1-1, Inches <sup>3</sup>	Size in Inches			Weight per Foot, Pounds		Maximum End Reaction in Thousands of Pounds
	Web Plates	Flange Angles	Flange Plates	Web Plate and Flange Angles	Flange Plates	
194.7	24 x 7/16	6 x 6 x 3/8		85.1		67.5
245.7		6 x 6 x 1/2		103.9		67.5
294.2		6 x 6 x 5/8		122.3		67.5
340.7		6 x 6 x 3/4		140.3		67.5
200.6	24 x 3/8	6 x 6 x 3/8		90.2		81.0
251.5		6 x 6 x 1/2		109.0		81.0
300.1		6 x 6 x 5/8		127.4		81.0
346.6		6 x 6 x 3/4		145.4		81.0
216.6	26 x 5/16	6 x 6 x 3/8		87.2		78.8
272.9		6 x 6 x 1/2		106.0		78.8
326.7		6 x 6 x 5/8		124.4		78.8
378.2		6 x 6 x 3/4		142.4		78.8
223.5	26 x 3/8	6 x 6 x 3/8		92.8		94.5
279.8		6 x 6 x 1/2		111.6		94.5
333.6		6 x 6 x 5/8		130.0		94.5
385.2		6 x 6 x 3/4		148.0		94.5
230.4	26 x 1/2	6 x 6 x 3/8		98.3		110.3
286.7		6 x 6 x 1/2		117.1		110.3
340.5		6 x 6 x 5/8		135.5		110.3
392.1		6 x 6 x 3/4		153.5		110.3
227.8	27 x 5/16	6 x 6 x 3/8		88.3		78.8
286.8		6 x 6 x 1/2		107.1		78.8
343.1		6 x 6 x 5/8		125.5		78.8
397.3		6 x 6 x 3/4		143.5		78.8
235.2	27 x 3/8	6 x 6 x 3/8		94.0		94.5
294.2		6 x 6 x 1/2		112.8		94.5
350.6		6 x 6 x 5/8		131.2		94.5
404.7		6 x 6 x 3/4		149.2		94.5
242.7	27 x 1/2	6 x 6 x 3/8		99.8		110.3
301.7		6 x 6 x 1/2		118.6		110.3
358.1		6 x 6 x 5/8		137.0		110.3
412.2		6 x 6 x 3/4		155.0		110.3
271.2	30 x 3/8	6 x 6 x 3/8		97.9		108.0
338.3		6 x 6 x 1/2		116.7		108.0
402.6		6 x 6 x 5/8		135.1		108.0
464.4		6 x 6 x 3/4		153.1		108.0
280.4	30 x 1/2	6 x 6 x 3/8		104.2		126.0
347.5		6 x 6 x 1/2		123.0		126.0
411.8		6 x 6 x 5/8		141.4		126.0
473.6		6 x 6 x 3/4		159.4		126.0
289.6	30 x 3/4	6 x 6 x 3/8		110.6		144.0
356.7		6 x 6 x 1/2		129.4		144.0
421.0		6 x 6 x 5/8		147.8		144.0
482.8		6 x 6 x 3/4		165.8		144.0

## COLUMN SAFE LOADS

### COLUMNS AND STRUTS

Compression members in structures are called posts, struts or columns. No exact theoretical formula has been found which will give the strength of such members under various conditions of loading. The formulas in current use are based on the assumption that the members under stress may fail by direct compression, by compression and bending combined, or by bending alone. The empirical formulas based on these assumptions practically agree with results obtained by experiment on full size members. These experiments show that steel columns of ordinary sizes and lengths fail at nearly a constant stress which corresponds to the yield point of that material, and that the load which will cause a column to fail decreases in the ratio of its length to its least lateral dimension.

**Radius of Gyration.** As the strength of a column depends on its ability to resist flexural stress, the moment of inertia of its cross section is an important factor in the determination of its carrying capacity. For the purpose of computation, however, it is much more convenient to use the radius of gyration which depends on the moment of inertia.

**Ratio of Slenderness.** The ratio of slenderness is the unsupported length of a compression member divided by its radius of gyration, and the unsupported length of a column is determined by such points of support as will prevent deflection of the column in the direction which corresponds to the particular radius of gyration under consideration. Columns of unsymmetrical section have more than one radius of gyration. It is, therefore, necessary to determine the ratio of slenderness for the different radii of gyration of such columns and to use the proper ratio in any particular case.

The unit stresses for different ratios of slenderness given in the construction specifications and on page 288 are consistent with present practice in column construction and their use does not involve the refinements of the more complicated formulas, which refinements are often vitiated by uncertainties in the application of loads or other practical features.

The construction specifications limit the maximum ratio of slenderness to 120 for main members under steady stresses. For secondary members under temporary stress, such as those used in wind bracing, higher ratios may be used, but in no case should the ratio exceed 200.

**Form and Size of Section.** Important as it may be to have the metal in the column section distributed as far as possible from the neutral axis, that is, with as large a radius of gyration as possible, considerations of ease in fabrication and simplicity in connections are of greater weight. The economical column section is not that which affords the least weight of metal in the shaft, but that which, with a reasonable radius of gyration, provides the least weight of member, shaft and details with the minimum amount of riveting. Modern practice, therefore, eliminates earlier forms of construction which represented the minimum amount of metal for the maximum radius of gyration, such, for example, as the column composed of three I-beams or one I-beam and two channels placed either with the flanges in or the flanges out. The Z-bar column has also fallen into disuse, likewise a number of patented sections and other sections shown in earlier editions of this publication.

The most practical column is one the surfaces of which are readily accessible for painting and, therefore, it is desirable to use open angle and plate columns rather than closed channel and plate columns.

The column sections should be of such size as to permit ready framing of beams and girders thereto and so placed in the construction as to permit the simplest details. Experience indicates that eight inches is the smallest desirable dimension in ordinary building work. For struts and light loads, smaller angle columns are still in use, while the H-beams are excellent for such purposes. I-beams and single angles may be used with economy where the conditions of lengths and loading permit.

**Explanation of Tables.** The tables which immediately follow give the safe loads in thousands of pounds on H-beam and I-beam columns and on a selected line of channel and angle columns which, in the light of experience, seem to be desirable for use in ordinary building and bridge construction. In addition to the safe loads, they give moments of inertia and radii of gyration about both axes of symmetry, areas of sections, and weights in pounds per foot without allowance for rivet heads or other details.

These tables have been computed for the least radius of gyration in accordance with the formula given in the construction specifications. The values may be adjusted to other formulas or to different values of the ratio of slenderness by use of the comparative table on page 288. This table is also suitable for use in figuring columns so braced against flexure, that their safe strength may be computed for the greater radius of gyration.

## COLUMN SAFE LOADS

**Combined Bending and Compression Stresses.** It is assumed in the tables that the loads are direct and equally distributed over the cross section of the column or balanced on opposite sides thereof. In the case of beams carried on brackets or other forms of eccentric loading, bending stresses are produced which should be taken into consideration and the column sections so proportioned that the combined fiber stresses do not exceed the allowable axial compressive stresses. There is no direct simple solution of this problem; the following trial method is suited to the tables:—



Let

$W$  = Direct load in pounds.

$W_1$  = Eccentric load in pounds.

$M$  = Bending moment due to eccentric load in inch pounds =  $W_1 x$

$I$  = Moment of inertia of column in direction of bending.

$n$  = Extreme fiber distance in direction of bending.

$A$  = Area of column section, in square inches.

$f$  = Allowable axial unit compression in pounds per square inch; then  $f$  should be equal to or greater than  $\frac{W + W_1}{A} + \frac{Mn}{I}$  the fiber stresses due to compression and bending respectively.

**RULE:**—Assume a section in excess of that required for the direct compression  $W + W_1$  and compute the combined fiber stress. If it works out too large or too small, try again.

**EXAMPLE:**—Required to select a plate and angle column 20 feet long to sustain a balanced load of 210,000 pounds and an eccentric load of 40,000 pounds applied 15 inches from the column center on axis 1-1.

Assume a section made up of 14"x½" web plate, four angles 6"x4"x½" and two flange plates 14"x½", page 307.

$A = 32.47$ ,  $I_{1-1} = 1351$ ,  $r_{2-2} = 3.09$ , ratio of slenderness =  $20 \times 12 + 3.09 = 77$ .

Allowable fiber stress, 19,000—100  $1/r = 11,300$  pounds per square inch, Page 288.

Actual fiber stress =  $\frac{210,000 + 40,000}{32.47} + \frac{40,000 \times 15 \times 7.625}{1351} = 7,700 + 3,390 = 11,090$  pounds per square inch.

# CARNEGIE STEEL COMPANY


## COMPARISON OF COMPRESSION FORMULAS ALLOWABLE UNIT STRESSES IN POUNDS PER SQUARE INCH

$\frac{1}{r}$	A. B. Co.	A. R. E. Ass'n Chicago	Gordon	New York	Philadelphia	Boston
	See Construction Specifications	$16000-70\frac{1}{r}$ 14000 max.	$\frac{12500}{1+\frac{l^2}{36000r^2}}$	$15200-58\frac{1}{r}$	$\frac{16250}{1+\frac{l^2}{11000r^2}}$	$\frac{16000}{1+\frac{l^2}{20000r^2}}$
0	13000	14000	12500	15200	16250	16000
5	13000	14000	12490	14910	16215	15980
10	13000	14000	12460	14620	16100	15920
15	13000	14000	12420	14330	15925	15820
20	13000	14000	12365	14040	15680	15690
25	13000	14000	12285	13750	15375	15515
30	13000	13900	12195	13460	15020	15310
35	13000	13550	12090	13170	14620	15075
40	13000	13200	11970	12880	14185	14815
45	13000	12850	11835	12590	13725	14530
50	13000	12500	11690	12300	13240	14220
55	13000	12150	11530	12010	12745	13900
60	13000	11800	11365	11720	12240	13560
65	12500	11450	11185	11430	11740	13210
70	12000	11100	11000	11140	11240	12850
75	11500	10750	10810	10850	10750	12490
80	11000	10400	10615	10560	10275	12120
85	10500	10050	10410	10270	9810	11755
90	10000	9700	10205	9980	9360	11390
95	9500	9350	9995	9690	8930	11025
100	9000	9000	9785	9400	8510	10670
105	8500	8650	9570	9110	8115	10315
110	8000	8300	9355	8820	7740	9970
115	7500	7950	9140	8530	7380	9630
120	7000	7600	8930	8240	7035	9300
125	6750	7250	8715		6715	
130	6500	6900	8510		6405	
135	6250	6550	8300		6115	
140	6000	6200	8095		5840	
145	5750	5850	7890			
150	5500	5500	7690			
155	5250		7495			
160	5000		7305			
165	4750		7120			
170	4500		6935			
175	4250		6755			
180	4000		6580			
185	3750		6410			
190	3500		6240			
195	3250		6080			
200	3000		5920			


Name of Formula	Abbreviation	Maximum Ratio of $l/r$	
		Main Members	Bracing Struts
American Bridge Company	A. B.	120	200
American Railway Engineering Ass'n	A. R. E.	100	120
Chicago Building Law	C.	120	150
Gordon	G.	..	..
New York Building Law	N. Y.	120	..
Philadelphia Building Law	P.	140	..
Boston Building Law	B.	120	..

# COLUMN SAFE LOADS

COMPARATIVE DIAGRAM OF COMPRESSION FORMULAS

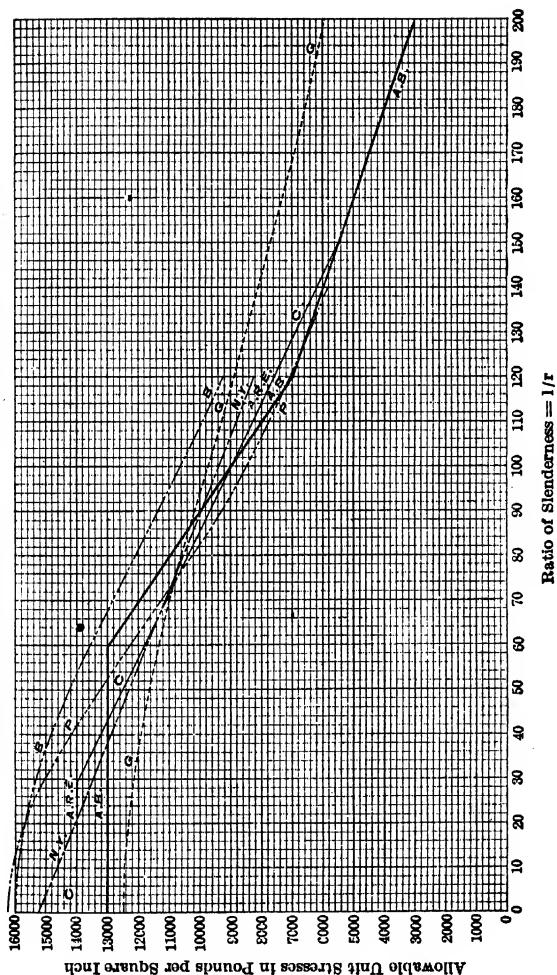

# CARNEGIE STEEL COMPANY



## BEAM COLUMNS

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.  
Weights do not include details.

Effective Length in Feet	Depth and Weight of Sections													
	H Beams				I Beams									
	8 in. 34 lbs.	6 in. 23.8 lbs.	5 in. 18.7 lbs.	4 in. 13.6 lbs.	15 in. 42 lbs.	12 in. 31½ lbs.	10 in. 25 lbs.	9 in. 21 lbs.	8 in. 18 lbs.	7 in. 15 lbs.	6 in. 12¼ lbs.	5 in. 9¼ lbs.	4 in. 7½ lbs.	
2	130.0	91.0	71.5	52.0	162.2	120.4	95.8	82.0	69.3	57.5	46.9	37.3	28.7	
3	130.0	91.0	71.5	52.0	162.2	120.4	95.8	82.0	69.3	57.5	46.9	37.3	28.5	
4	130.0	91.0	71.5	52.0	162.2	120.4	95.8	82.0	69.3	56.8	44.5	33.3	24.0	
5	130.0	91.0	71.5	50.7	162.2	120.4	94.4	77.8	63.2	50.0	38.5	28.0	19.5	
6	130.0	91.0	71.5	45.7	153.9	109.9	85.3	69.4	55.6	43.2	32.5	22.7	15.2	
7	130.0	91.0	66.0	40.6	140.1	98.9	76.2	61.0	48.0	36.4	26.5	18.8	13.0	
8	130.0	86.7	60.5	35.6	126.2	87.9	67.1	52.6	40.4	30.3	22.9	16.1	10.8	
9	130.0	80.9	55.0	30.5	112.3	76.9	58.0	44.2	35.0	26.9	19.9	13.5	8.5	
10	125.8	75.1	49.5	26.7	98.5	65.9	50.2	40.0	31.2	23.5	16.8	10.8		
11	119.4	69.3	44.0	24.2	86.0	59.9	45.7	35.8	27.4	20.1	13.8			
12	113.0	63.5	38.5	21.7	79.0	54.4	41.1	31.5	23.6	16.7	10.8			
13	106.6	57.7	35.8	19.2	72.1	48.0	36.5	27.3	19.8	13.3				
14	100.2	51.9	33.0	16.8	65.2	43.4	32.0	23.1	16.0					
15	93.8	47.6	30.3	14.1	58.2	37.9	27.4	18.9						
16	87.3	44.7	27.5		51.3	32.4	22.0							
17	80.9	41.8	24.8		44.4	26.9								
18	74.5	38.9	22.0		37.4									
19	69.0	36.0	19.3											
20	65.8	33.1	16.5											
21	62.6	30.2												
22	59.4	27.3												
23	56.2	24.4												
24	53.0	21.5												
25	49.8													
26	46.6													
27	43.4													
28	40.2													
29	37.0													
30	33.7													
31	30.5													
<hr/>														
Area, in. <sup>2</sup>	10.00	7.00	5.50	4.00	12.48	9.26	7.37	6.31	5.33	4.42	3.61	2.87	2.21	
I <sub>1-1</sub> , in. <sup>4</sup>	115.4	45.1	23.8	10.7	441.8	215.8	122.1	84.9	56.9	36.2	21.8	12.1	6.0	
I <sub>1-1</sub> , in. <sup>4</sup>	3.40	2.54	2.08	1.63	5.95	4.83	4.07	3.67	3.27	2.86	2.46	2.05	1.64	
I <sub>2-2</sub> , in. <sup>4</sup>	35.1	14.7	7.9	3.6	14.6	9.5	6.9	5.2	3.5	2.7	1.9	1.2	0.77	
I <sub>2-2</sub> , in. <sup>4</sup>	1.87	1.45	1.20	0.95	1.08	1.01	0.97	0.90	0.84	0.78	0.72	0.65	0.59	
Weight, Lbs. per Foot	34	23.8	18.7	13.6	42	31½	25	21	18	15	12¼	9¼	7½	

Safe load values above upper zigzag line are for ratios of l/r not over 60, those between the zigzag lines are for ratios up to 120 l/r and those below lower zigzag line are for ratios not over 200 l/r.


# COLUMNS

## 10 INCH CHANNEL COLUMNS

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	2-10 in. Chan. Latticed				2-10 in. Channels, 2-12 in. Plates																	
	15 lb. Channels, Single Lattice	20 lb. Channels, Single Lattice	25 lb. Channels, Single Lattice	30 lb. Channels, Single Lattice	15 lb. Channels, $\frac{5}{16}$ in. Plates	15 lb. Channels, $\frac{3}{8}$ in. Plates	15 lb. Channels, $\frac{7}{16}$ in. Plates	15 lb. Channels, $\frac{1}{2}$ in. Plates	20 lb. Channels, $\frac{5}{16}$ in. Plates	20 lb. Channels, $\frac{3}{8}$ in. Plates	20 lb. Channels, $\frac{7}{16}$ in. Plates	20 lb. Channels, $\frac{1}{2}$ in. Plates	25 lb. Channels, $\frac{5}{16}$ in. Plates	25 lb. Channels, $\frac{3}{8}$ in. Plates	25 lb. Channels, $\frac{7}{16}$ in. Plates	30 lb. Channels, $\frac{5}{16}$ in. Plates	30 lb. Channels, $\frac{3}{8}$ in. Plates	30 lb. Channels, $\frac{7}{16}$ in. Plates	35 lb. Channels, $\frac{5}{16}$ in. Plates	35 lb. Channels, $\frac{3}{8}$ in. Plates	35 lb. Channels, $\frac{7}{16}$ in. Plates	
11	116	153	191	213	233	252	272	289	309	328	348	367	386	405	424	443	463					
12	116	153	191	213	233	252	272	289	309	328	348	367	386	405	424	443	463					
13	116	153	191	213	233	252	272	289	309	328	348	367	386	405	424	443	463					
14	116	153	191	213	233	252	272	289	309	328	348	367	386	405	424	443	463					
15	116	153	191	213	233	252	272	289	309	328	348	367	386	405	424	443	463					
16	116	153	191	213	233	252	272	289	309	328	348	367	386	405	424	443	463					
17	116	153	191	213	233	252	272	289	309	328	348	367	386	405	424	443	463					
18	116	152	186	213	233	252	271	286	305	324	343	359	378	392	411	424	444					
19	115	148	181	208	227	245	264	278	297	315	334	349	367	381	399	412	431					
20	112	144	176	203	221	239	257	271	289	307	325	339	357	370	388	400	418					
21	109	140	171	197	215	232	250	263	280	298	316	329	347	359	376	387	405					
22	106	136	165	192	209	226	243	256	272	289	307	319	336	348	364	375	392					
23	103	132	160	186	203	219	236	248	264	281	297	310	326	337	353	362	379					
24	100	128	155	181	197	213	229	240	256	272	288	300	316	326	341	350	366					
25	98	124	150	175	191	206	222	233	248	263	279	290	305	314	330	338	354					
26	95	120	145	170	185	200	215	225	240	255	270	280	295	303	318	325	341					
27	92	116	140	164	179	193	208	217	231	246	261	270	285	292	306	313	328					
28	89	112	134	159	173	187	201	210	223	237	252	260	274	281	295	301	315					
29	86	108	129	153	167	180	194	202	215	229	242	251	264	270	283	288	302					
30	83	104	124	148	161	174	187	195	207	220	233	241	253	259	271	276	289					
31	80	100	119	142	155	167	180	187	199	211	224	231	243	248	260	263	276					
32	77	96	114	137	149	161	173	179	191	203	215	221	233	237	248	251	263					
33	75	92	109	131	143	154	166	172	183	194	206	211	222	226	237	239	250					
34	72	88	103	126	137	148	159	164	174	185	196	201	212	216	227	232	243					
35	69	84	101	120	131	141	152	157	166	177	187	194	205	211	221	226	237					
Area, in. <sup>2</sup>	8.92	11.76	14.70	16.42	17.92	19.42	20.92	22.26	23.76	25.26	26.76	28.20	29.70	31.14	32.64	34.08	35.58					
I <sub>x</sub> -I <sub>y</sub> , in. <sup>4</sup>	134	458	182	333	376	420	465	444	489	534	581	559	606	583	630	608	655					
r <sub>x</sub> -r <sub>y</sub> , in.	3.87	3.89	3.52	4.50	4.58	4.65	4.71	4.49	4.53	4.60	4.68	4.45	4.52	4.53	4.59	4.42	4.29					
r <sub>x</sub> -r <sub>y</sub> , in.	123	148	171	213	231	249	267	274	292	310	328	333	351	354	372	372	390					
Weight, Lbs. per Foot	37.8	47.8	57.8	55.5	60.6	65.7	70.8	75.7	80.8	85.9	91.0	95.9	101.0	105.9	111.0	115.9	121.0					

Safe load values above upper zigzag line are for ratio of l/r not over 60, those between the zigzag lines are for ratios up to 120 l/r, and those below lower zigzag line are for ratios not over 200 l/r.




# CARNEGIE STEEL COMPANY

## 10 INCH CHANNEL COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	2-10 in. Channels Latticed				2-10 in. Channels, 2-14 in. Plates															
	15 lb. Channels, Single Lattice	20 lb. Channels, Single Lattice	25 lb. Channels, Single Lattice	30 lb. Channels, Single Lattice	15 lb. Channels, 2 1/2 in. Plates	15 lb. Channels, 3 in. Plates	15 lb. Channels, 3 1/2 in. Plates	20 lb. Channels, 3 1/2 in. Plates	20 lb. Channels, 4 in. Plates	20 lb. Channels, 4 1/2 in. Plates	20 lb. Channels, 5 in. Plates	25 lb. Channels, 5 in. Plates	25 lb. Channels, 5 1/2 in. Plates	25 lb. Channels, 6 in. Plates	25 lb. Channels, 6 1/2 in. Plates	25 lb. Channels, 7 in. Plates	25 lb. Channels, 7 1/2 in. Plates	25 lb. Channels, 8 in. Plates		
11	116	153	191	229	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
12	116	153	191	229	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
13	116	153	191	229	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
14	116	153	191	229	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
15	116	153	191	229	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
16	116	153	191	229	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
17	116	153	191	229	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
18	116	153	189	224	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
19	116	150	184	218	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
20	114	146	179	211	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
21	111	142	174	205	252	275	298	312	335	358	380	396	419	441	464	486	509	531	554	
22	109	139	169	199	251	273	295	308	330	352	374	388	410	432	453	475	497	519	541	
23	106	135	164	193	240	267	289	302	323	344	365	379	401	422	443	464	485	506	527	
24	103	131	159	187	241	261	282	295	316	337	357	371	392	412	433	453	474	494	515	
25	100	127	154	180	235	256	276	288	308	329	349	367	387	406	426	446	466	486	506	
26	98	123	149	174	230	250	270	282	301	321	341	353	373	393	412	432	452	472	492	
27	95	119	144	168	225	244	263	275	294	313	332	345	364	383	402	421	440	459	478	
28	92	115	139	162	219	238	257	268	287	306	324	336	355	373	392	410	429	447	466	
29	89	112	134	156	214	232	250	261	279	298	316	327	346	364	382	400	418	436	454	
30	87	108	129	149	209	226	244	255	272	290	308	319	336	354	372	390	407	425	443	
31	84	104	124	143	203	220	238	248	265	282	299	310	327	344	361	378	395	412	429	
32	81	100	119	137	198	214	231	241	258	275	291	301	318	335	351	368	384	400	417	
33	78	96	114	131	193	209	225	235	251	267	283	293	309	325	341	357	373	389	405	
34	75	92	109	125	187	203	219	228	243	259	274	284	300	315	331	347	362	378	394	
35	73	88	104	121	182	197	212	221	236	251	266	275	291	306	320	335	350	365	380	
Area, in. <sup>2</sup>	8.92	11.76	14.70	17.64	10.42	21.17	22.92	24.01	25.70	27.51	29.26	30.45	32.20	33.95	35.70					
I <sub>1-1</sub> , in. <sup>4</sup>	134	158	182	207	416	468	520	491	544	597	652	622	676	732	790					
I <sub>2-2</sub> , in. <sup>4</sup>	3.87	3.60	3.52	3.42	4.63	4.70	4.76	4.52	4.50	4.66	4.72	4.52	4.58	4.64	4.70					
I <sub>3-3</sub> , in. <sup>4</sup>	197	241	284	323	369	398	426	442	470	499	527	541	570	598	627					
Weight, Lbs. per Foot	39.3	49.4	59.4	63.4	65.7	71.7	77.6	81.7	87.6	93.6	99.5	103.8	109.5	115.5	121.4					

Safe load values above upper zigzag line are for ratios of  $l/r$  not over 80, those between the zigzag lines are for ratios up to 120  $l/r$ , and those below lower zigzag line are for ratios not over 200  $l/r$ .


# COLUMNS

## 10 INCH CHANNEL COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	2-10 in. Channels, 2-14 in. Plates													
	30 lb. Channels, 1 1/16 in. Plates	30 lb. Channels, 3/4 in. Plates	30 lb. Channels, 15/16 in. Plates	30 lb. Channels, 1 1/8 in. Plates	30 lb. Channels, 1 1/16 in. Plates	30 lb. Channels, 1 1/8 in. Plates	30 lb. Channels, 1 1/16 in. Plates	30 lb. Channels, 1 1/8 in. Plates	30 lb. Channels, 1 1/16 in. Plates	30 lb. Channels, 1 1/8 in. Plates	30 lb. Channels, 1 1/16 in. Plates	30 lb. Channels, 1 1/8 in. Plates	30 lb. Channels, 1 1/16 in. Plates	30 lb. Channels, 1 1/8 in. Plates
11	480	502	525	548	571	593	609	632	654	677	700	723	723	723
12	480	502	525	548	571	593	609	632	654	677	700	723	723	723
13	480	502	525	548	571	593	609	632	654	677	700	723	723	723
14	480	502	525	548	571	593	609	632	654	677	700	723	723	723
15	480	502	525	548	571	593	609	632	654	677	700	723	723	723
16	480	502	525	548	571	593	609	632	654	677	700	723	723	723
17	480	502	525	548	571	593	609	632	654	677	700	723	723	723
18	480	502	525	548	571	593	609	632	654	677	700	723	723	723
19	480	502	525	548	571	593	609	632	654	677	700	723	723	723
20	480	502	525	548	571	593	609	632	654	677	700	723	723	723
21	477	500	522	544	567	589	602	624	647	669	691	714	714	714
22	467	488	510	532	554	575	588	610	632	654	675	697	697	697
23	456	477	499	520	541	562	575	596	617	639	660	681	681	681
24	446	466	487	508	529	549	561	582	603	624	644	665	665	665
25	435	455	475	495	516	536	547	568	588	608	628	648	648	648
26	424	444	464	483	503	522	533	553	573	593	612	632	632	632
27	414	432	452	471	490	509	520	539	559	578	596	616	616	616
28	403	421	440	459	478	496	506	525	544	563	581	599	599	599
29	392	410	429	446	465	483	492	511	529	547	565	583	583	583
30	382	399	417	434	452	469	479	496	514	532	549	567	567	567
31	371	388	405	422	440	456	465	482	500	517	533	550	550	550
32	360	377	394	410	427	443	451	468	485	502	517	534	534	534
33	350	365	382	398	414	430	437	454	470	487	502	518	518	518
34	339	354	370	385	401	415	424	440	455	471	486	502	502	502
35	328	343	359	373	389	403	410	425	441	456	470	485	485	485
Area, in. <sup>2</sup>	36.89	38.64	40.39	42.14	43.89	45.64	46.83	48.58	50.33	52.08	53.83	55.58	55.58	55.58
I <sub>x</sub> , in. <sup>4</sup>	757	814	873	932	994	1056	1018	1080	1144	1209	1275	1343	1343	1343
I <sub>y</sub> , in. <sup>4</sup>	4.53	4.50	4.65	4.70	4.76	4.81	4.66	4.72	4.77	4.82	4.87	4.92	4.92	4.92
I <sub>xy</sub> , in. <sup>4</sup>	637	666	695	723	752	780	788	816	845	874	902	931	931	931
r <sub>x</sub> , in.	4.16	4.15	4.15	4.14	4.14	4.13	4.10	4.10	4.10	4.10	4.09	4.09	4.09	4.09
Weight, lbs. per foot	125.5	131.4	137.4	143.3	149.3	155.2	159.3	165.2	171.2	177.1	183.1	189.0	189.0	189.0

Safe load values above heavy line are for ratios of  $l/r$  not over 60, those below heavy line are for ratios not over 120  $l/r$ .


# CARNEGIE STEEL COMPANY

## 12 INCH CHANNEL COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	2-12 in. Channels Latticed				2-12 in. Channels, 2-14 in. Plates															
	20 1/2 lb. Channels, Single Lattice	25 lb. Channels, Single Lattice	30 lb. Channels, Single Lattice	35 lb. Channels, Single Lattice	20 1/2 lb. Channels, 3/8 in. Plates	20 1/2 lb. Channels, 1/2 in. Plates	20 1/2 lb. Channels, 3/4 in. Plates	20 1/2 lb. Channels, 1 in. Plates	20 1/2 lb. Channels, 1 1/8 in. Plates	20 1/2 lb. Channels, 1 1/4 in. Plates	20 1/2 lb. Channels, 1 1/2 in. Plates	20 1/2 lb. Channels, 1 3/4 in. Plates	20 1/2 lb. Channels, 2 in. Plates	25 lb. Channels, 1 1/8 in. Plates	25 lb. Channels, 1 1/4 in. Plates	25 lb. Channels, 1 1/2 in. Plates	25 lb. Channels, 1 3/4 in. Plates	25 lb. Channels, 2 in. Plates	25 lb. Channels, 1 1/8 in. Plates	25 lb. Channels, 1 1/4 in. Plates
11	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
12	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
13	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
14	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
15	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
16	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
17	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
18	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
19	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
20	157	191	229	268	293	316	339	362	384	396	419	441	464	487	464	487	464	487	464	487
21	157	191	229	265	293	316	339	362	384	396	418	440	463	485	463	485	463	485	463	485
22	157	190	225	259	290	312	334	355	377	387	409	431	453	474	453	474	453	474	453	474
23	155	186	220	253	283	305	326	347	369	378	400	421	443	464	443	464	443	464	443	464
24	152	182	215	248	277	298	319	339	360	370	390	411	432	453	432	453	432	453	432	453
25	149	178	210	242	271	291	312	332	352	361	381	401	422	442	422	442	422	442	422	442
26	146	174	205	236	265	284	304	324	344	352	372	392	412	431	392	412	392	412	392	412
27	142	170	200	230	258	277	297	316	335	344	363	382	402	421	382	402	382	402	382	402
28	139	166	195	224	252	271	290	308	327	335	354	372	391	410	372	391	372	391	372	391
29	136	162	190	218	246	264	282	300	318	326	344	362	381	399	362	381	362	381	362	381
30	133	158	185	212	239	257	275	292	310	318	335	353	371	388	353	371	353	371	353	371
31	129	154	180	206	233	250	268	284	302	309	326	343	361	377	343	361	343	361	343	377
32	126	150	175	200	227	243	260	277	293	300	317	333	350	367	333	350	333	350	333	367
33	123	146	170	194	220	236	253	269	285	291	307	323	340	356	323	340	323	340	323	356
34	120	142	165	188	214	230	246	261	277	283	298	314	330	345	314	330	314	330	314	345
35	117	138	160	182	208	223	238	253	268	274	289	304	320	334	304	320	304	320	304	334
Area, in. <sup>2</sup>	12.06	14.70	17.64	20.58	22.56	24.31	26.06	27.81	29.56	30.45	32.20	33.95	35.70	37.45	35.70	37.45	35.70	37.45	35.70	37.45
I <sub>1-1</sub> , in. <sup>4</sup>	256	288	323	359	401	443	485	527	569	584	626	668	710	752	668	710	668	710	668	752
I <sub>2-2</sub> , in. <sup>4</sup>	4.61	4.43	4.28	4.17	4.06	3.95	3.84	3.73	3.62	3.51	3.40	3.29	3.18	3.07	3.29	3.18	3.07	3.18	3.07	3.29
Weight, Lbs. per Foot	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4	50.4

Safe load values above zigzag line are for ratios of l/r not over 60, those below zigzag line are for ratios not over 120 l/r.


# COLUMNS

## 12 INCH CHANNEL COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii, see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	2-12 in. Channels, 2-14 in. Plates													
	30 lb. Channels, 1/4 in. Plates	30 lb. Channels, 1/2 in. Plates	30 lb. Channels, 1 1/4 in. Plates	30 lb. Channels, 1 1/2 in. Plates	30 lb. Channels, 1 3/4 in. Plates	30 lb. Channels, 1 in. Plates	35 lb. Channels, 1 1/4 in. Plates	35 lb. Channels, 1 1/2 in. Plates	35 lb. Channels, 1 in. Plates	35 lb. Channels, 1 1/4 in. Plates	35 lb. Channels, 1 1/2 in. Plates	35 lb. Channels, 1 3/4 in. Plates	35 lb. Channels, 1 1/2 in. Plates	35 lb. Channels, 1 1/4 in. Plates
11	502	525	548	571	593	609	632	654	677	700	723	745	768	791
12	502	525	548	571	593	609	632	654	677	700	723	745	768	791
13	502	525	548	571	593	609	632	654	677	700	723	745	768	791
14	502	525	548	571	593	609	632	654	677	700	723	745	768	791
15	502	525	548	571	593	609	632	654	677	700	723	745	768	791
16	502	525	548	571	593	609	632	654	677	700	723	745	768	791
17	502	525	548	571	593	609	632	654	677	700	723	745	768	791
18	502	525	548	571	593	609	632	654	677	700	723	745	768	791
19	502	525	548	571	593	609	632	654	677	700	723	745	768	791
20	502	525	548	571	593	609	632	654	677	700	723	745	768	791
21	498	521	543	565	588	601	623	645	668	689	712	734	757	779
22	487	509	531	553	575	587	609	631	653	674	695	717	739	761
23	470	497	518	540	561	573	594	616	637	658	679	700	722	743
24	465	486	506	527	548	559	580	601	622	642	663	684	704	725
25	453	474	494	514	535	545	566	586	607	626	646	667	687	708
26	442	462	482	502	522	532	552	571	591	610	630	650	670	689
27	431	451	469	489	508	518	537	557	576	594	614	633	652	672
28	420	439	457	476	495	504	523	542	561	578	597	616	635	654
29	409	427	445	463	482	490	509	527	545	563	581	599	617	635
30	397	415	432	450	468	477	494	512	530	547	564	582	600	618
31	386	404	420	438	455	463	480	497	515	531	548	565	583	600
32	375	392	408	425	442	449	466	483	499	515	532	548	565	582
33	364	380	396	412	428	435	452	468	484	499	515	531	548	564
34	352	368	383	399	415	421	437	453	469	483	499	515	530	546
35	341	357	371	386	402	408	423	438	453	467	482	498	513	528
Area, in. <sup>2</sup>	38.64	40.39	42.14	43.89	45.64	46.83	48.58	50.33	52.08	53.83	55.58	57.33	59.08	60.83
I <sub>1-1</sub> , in. <sup>4</sup>	1174	1258	1340	1424	1509	1459	1544	1630	1719	1808	1890	1992	2087	2183
r <sub>1-1</sub> , in.	5.52	5.58	5.64	5.70	5.75	5.58	5.64	5.69	5.74	5.80	5.85	5.89	5.94	5.99
I <sub>2-2</sub> , in. <sup>4</sup>	659	688	717	745	774	778	808	837	865	894	922	951	980	1008
r <sub>2-2</sub> , in.	4.13	4.13	4.12	4.12	4.12	4.08	4.08	4.08	4.08	4.07	4.07	4.07	4.07	4.07
Weight, lbs. per foot	131.4	137.4	143.3	149.3	155.2	159.3	165.2	171.2	177.1	183.1	189.0	195.0	200.9	206.9

Safe load values above heavy line are for ratios of  $l/r$  not over 80, those below heavy line are for ratios not over 120  $l/r$ .


# CARNEGIE STEEL COMPANY

## 12 INCH CHANNEL COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet		2-12 in. Channels, 2-16 in. Plates											
		30 lb. Channels, 1 1/16 in. Plates		30 lb. Channels, 1 in. Plates		30 lb. Channels, 1 1/16 in. Plates		30 lb. Channels, 1 1/8 in. Plates		30 lb. Channels, 1 3/16 in. Plates		30 lb. Channels, 1 1/4 in. Plates	
11		619	645	671	697	723	749	762	788	814	840		
12		610	645	671	697	723	749	762	788	814	840		
13		610	645	671	697	723	749	762	788	814	840		
14		619	645	671	697	723	749	762	788	814	840		
15		610	645	671	697	723	749	762	788	814	840		
16		619	645	671	697	723	749	762	788	814	840		
17		619	645	671	697	723	749	762	788	814	840		
18		619	645	671	697	723	749	762	788	814	840		
19		619	645	671	697	723	749	762	788	814	840		
20		619	645	671	697	723	749	762	788	814	840		
21		619	645	671	697	723	749	762	788	814	840		
22		619	645	671	697	723	749	762	788	814	840		
23		619	645	671	697	723	749	762	788	814	840		
24		619	645	671	697	723	749	762	788	814	840		
25		610	635	660	686	711	736	747	772	797	822		
26		599	623	648	673	697	721	732	756	781	805		
27		587	611	635	659	683	707	718	741	766	789		
28		575	599	622	646	669	693	703	726	750	773		
29		563	586	609	633	655	678	688	711	734	757		
30		552	574	596	619	642	664	674	696	719	741		
31		540	562	583	606	628	649	659	681	703	724		
32		528	549	571	593	614	635	644	665	687	708		
33		516	537	558	579	600	621	630	650	672	692		
34		504	525	545	566	586	606	615	635	656	676		
35		493	512	532	553	572	592	600	620	640	660		
Area, in. <sup>2</sup>		47.64	49.64	51.64	53.64	55.64	57.64	58.58	60.58	62.58	64.58		
I <sub>x</sub> -1, in. <sup>4</sup>		1581	1678	1777	1878	1980	2084	2015	2119	2225	2333		
I <sub>x</sub> -2, in. <sup>4</sup>		5.76	5.81	5.87	5.92	5.97	6.01	5.87	5.91	5.96	6.01		
I <sub>y</sub> -3, in. <sup>4</sup>		1121	1164	1206	1249	1292	1334	1349	1392	1434	1477		
I <sub>y</sub> -4, in. <sup>4</sup>		4.85	4.84	4.83	4.83	4.82	4.81	4.80	4.79	4.79	4.78		
Weight, Lbs. per Foot		162.0	168.8	175.6	182.4	189.2	196.0	199.2	206.0	212.8	219.6		

Safe load values above signag line are for ratios of  $l/r$  not over 60, those below signag line are for ratios not over 120  $l/r$ .

## 12 INCH CHANNEL COLUMNS—Continued


Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

A diagram of a rectangular frame. The top horizontal member is labeled 18" and 2. The bottom horizontal member is labeled 16" and 2. The left vertical member is labeled 12" and 1. The right vertical member is labeled 10" and 1. The frame is composed of four corner joints, each represented by a small circle with a cross inside.

Safe load values above heavy line are for ratings of lift not over 20, those below heavy line are for ratings not over 120 l/z.

# CARNEGIE STEEL COMPANY

## 15 INCH CHANNEL COLUMNS—Continued



### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii: see Construction Specifications.


Weights do not include rivet heads or other details.

Effective Length in Feet	2-15 in. Channels Latticed				2-15 in. Channels, 2-16 in. Plates											
	33 lb. Channels, Single Lattice	35 lb. Channels, Single Lattice	40 lb. Channels, Single Lattice	45 lb. Channels, Single Lattice	33 lb. Channels, 5/16 in. Plates	33 lb. Channels, 3/8 in. Plates	33 lb. Channels, 1/2 in. Plates	33 lb. Channels, 5/8 in. Plates	33 lb. Channels, 3/4 in. Plates	33 lb. Channels, 7/8 in. Plates	35 lb. Channels, 5/16 in. Plates	35 lb. Channels, 3/8 in. Plates	35 lb. Channels, 1/2 in. Plates	35 lb. Channels, 5/8 in. Plates	35 lb. Channels, 3/4 in. Plates	35 lb. Channels, 7/8 in. Plates
11	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
12	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
13	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
14	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
15	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
16	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
17	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
18	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
19	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
20	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
21	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
22	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
23	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
24	257	268	306	344	413	439	465	491	517	528	554	580	606	632		
25	257	266	301	336	407	432	457	482	507	517	542	567	592	617		
26	252	261	295	329	400	424	448	473	498	507	531	555	580	605		
27	247	256	289	322	392	415	440	464	488	497	520	544	569	592		
28	243	251	284	316	384	407	431	454	478	486	510	533	557	580		
29	238	246	278	309	376	399	422	445	468	476	499	522	545	568		
30	233	241	272	302	368	390	413	435	458	466	488	511	533	556		
31	228	236	266	296	360	382	404	426	448	456	478	499	522	543		
32	224	231	260	289	352	373	395	416	438	446	467	488	510	531		
33	219	226	254	282	345	365	386	407	428	436	456	477	498	519		
34	214	221	249	276	337	357	377	398	418	425	446	466	487	507		
35	209	216	243	269	329	348	368	388	408	415	435	454	475	494		
Area, in.²	19.80	20.58	23.52	26.48	31.80	33.80	35.80	37.80	39.80	40.58	42.58	44.58	46.58	48.58		
I <sub>x</sub> -1, in.⁴	625	640	695	750	1334	1459	1586	1715	1847	1861	1994	2129	2267	2406		
I <sub>x</sub> -2, in.⁴	5.62	5.58	5.43	5.32	6.48	6.57	6.66	6.74	6.81	6.77	6.84	6.91	6.98	7.04		
I <sub>y</sub> -1, in.⁴	491	504	552	597	747	789	832	875	917	930	973	1016	1058	1101		
I <sub>y</sub> -2, in.⁴	4.88	4.96	4.84	4.75	4.85	4.83	4.82	4.81	4.80	4.79	4.78	4.77	4.77	4.76		
Weight, Lbs. per Foot	80.2	84.2	92.1	102.2	106.8	113.6	120.4	127.2	134.0	138.0	144.8	151.6	158.4	165.2		

Safe load values above sigsag line are for ratios of l/r not over 60, those below sigsag line are for ratios not over 120 l/r.

# COLUMNS

## 15 INCH CHANNEL COLUMNS—Continued



### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.


Effective Length in Feet		2-15 in. Channels, 2-16 in. Plates															
		40 lb. Channels, 1 1/10 in. Plates	40 lb. Channels, 1 1/8 in. Plates	40 lb. Channels, 1 1/10 in. Plates	40 lb. Channels, 1 in. Plates	40 lb. Channels, 1 1/10 in. Plates	40 lb. Channels, 1 1/8 in. Plates	45 lb. Channels, 1 1/10 in. Plates	45 lb. Channels, 1 1/8 in. Plates	45 lb. Channels, 1 1/10 in. Plates	45 lb. Channels, 1 1/8 in. Plates	45 lb. Channels, 1 1/10 in. Plates	45 lb. Channels, 1 1/8 in. Plates	45 lb. Channels, 1 1/10 in. Plates	45 lb. Channels, 1 1/8 in. Plates	45 lb. Channels, 1 1/10 in. Plates	45 lb. Channels, 1 1/8 in. Plates
11	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
12	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
13	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
14	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
15	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
16	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
17	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
18	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
19	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
20	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
21	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
22	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
23	644	670	696	722	748	774	786	812	838	864	890	916	942	968			
24	639	665	690	715	741	767	777	802	827	853	879	904	930	956			
25	627	651	677	701	727	752	761	786	811	836	861	886	912	937			
26	614	638	663	687	712	737	746	770	794	819	844	868	893	918			
27	602	625	649	673	697	721	730	754	778	802	826	850	874	898			
28	589	612	636	659	683	706	715	738	761	785	808	832	856	879			
29	577	599	622	645	668	691	699	722	745	768	791	814	837	860			
30	564	586	609	631	653	676	684	705	728	751	773	796	818	841			
31	551	573	595	616	639	661	668	689	711	734	756	778	800	822			
32	539	560	581	602	624	646	653	673	695	716	738	760	781	803			
33	526	547	568	588	609	630	637	657	678	699	720	741	763	784			
34	514	534	554	574	595	615	622	641	662	682	703	723	744	764			
35	501	520	541	560	580	600	606	625	645	665	685	705	725	745			
Area, in. <sup>2</sup>		49.52	51.52	53.52	55.52	57.52	59.52	60.48	62.48	64.48	66.48	68.48	70.48	72.48	74.48		
I <sub>1-1</sub> , in. <sup>4</sup>		2322	2461	2602	2746	2891	3039	2946	3094	3244	3396	3550	3707	3865	4026		
I <sub>2-2</sub> , in. <sup>4</sup>		0.85	0.91	0.97	1.03	1.09	1.15	0.98	1.04	1.09	1.15	1.20	1.25	1.30	1.35		
I <sub>3-3</sub> , in. <sup>4</sup>		1106	1149	1192	1234	1277	1320	1322	1365	1408	1450	1493	1536	1578	1621		
Weight, Lbs. per Foot		4.73	4.72	4.72	4.71	4.71	4.71	4.68	4.67	4.67	4.67	4.67	4.67	4.67	4.67		
Weight, Lbs. per Foot		168.4	175.2	182.0	188.8	195.6	202.4	205.6	212.4	219.2	226.0	232.8	239.6	246.4	253.2		

Safe load values above heavy line are for ratios of  $l/r$  not over 60, those below heavy line are for ratios not over 120  $l/r$ .



# CARNEGIE STEEL COMPANY

## 15 INCH CHANNEL COLUMNS—Continued



### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.

Effective Length in Feet	2-15 in. Channels, 2-18 in. Plates															
	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates	33 lb. Channels, 2 in. Plates
11	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
12	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
13	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
14	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
15	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
16	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
17	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
18	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
19	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
20	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
21	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
22	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
23	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
24	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
25	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
26	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
27	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
28	433	462	491	521	550	560	589	619	648	677	686	715	745	774	803	832
29	428	450	484	512	539	549	577	605	632	660	668	696	723	751	779	807
30	421	449	476	503	530	540	567	594	621	649	657	684	711	738	766	793
31	414	441	468	494	521	530	557	584	610	637	645	672	698	725	752	779
32	407	433	459	486	512	521	547	574	599	626	634	660	686	712	738	764
33	400	426	451	477	503	512	537	563	589	615	622	648	673	698	725	750
34	393	418	443	469	494	502	527	553	578	603	610	636	660	685	711	736
35	386	411	435	460	485	493	518	543	567	592	599	624	648	672	698	722
Area, in. <sup>2</sup>	33.30	35.55	37.80	40.05	42.30	43.08	45.33	47.58	49.83	52.08	52.77	55.02	57.27	59.52	61.77	64.02
I <sub>1-1</sub> , in. <sup>4</sup>	1423	1564	1707	1852	1999	2014	2164	2316	2470	2627	2525	2682	2841	3002	3166	3333
I <sub>2-2</sub> , in. <sup>4</sup>	6.54	6.63	6.72	6.80	6.87	6.84	6.91	6.98	7.04	7.10	6.92	6.98	7.04	7.10	7.16	7.21
I <sub>3-3</sub> , in. <sup>4</sup>	1069	1130	1190	1251	1312	1332	1393	1453	1514	1575	1589	1649	1710	1771	1832	1892
I <sub>4-4</sub> , in. <sup>4</sup>	5.87	5.84	5.81	5.78	5.75	5.75	5.74	5.73	5.72	5.71	5.70	5.69	5.68	5.67	5.66	5.65
Weight, lbs. per foot	111.9	116.6	122.2	127.2	132.9	134.5	142.5	146.5	154.2	161.8	169.5	177.1	184.8	192.4	200.2	207.7

Safe load values above zigzag line are for ratios of l/r not over 60, those below zigzag line are for ratios not over 120 l/r.


# COLUMNS

## 15 INCH CHANNEL COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.


Weights do not include rivet heads or other details.



Effective Length in Feet	2-15 in. Channels, 2-18 in. Plates															
	45 lb. Channels, 1 1/2 in. Plates	45 lb. Channels, 1 3/8 in. Plates	45 lb. Channels, 1 3/4 in. Plates	45 lb. Channels, 1 7/8 in. Plates	45 lb. Channels, 2 in. Plates	45 lb. Channels, 2 1/8 in. Plates	45 lb. Channels, 2 1/4 in. Plates	45 lb. Channels, 2 3/8 in. Plates	45 lb. Channels, 2 1/2 in. Plates	45 lb. Channels, 2 5/8 in. Plates	45 lb. Channels, 3 in. Plates	45 lb. Channels, 3 1/8 in. Plates	45 lb. Channels, 3 1/4 in. Plates	45 lb. Channels, 3 3/8 in. Plates	45 lb. Channels, 3 1/2 in. Plates	45 lb. Channels, 3 5/8 in. Plates
11	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
12	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
13	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
14	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
15	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
16	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
17	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
18	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
19	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
20	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
21	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
22	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
23	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
24	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
25	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
26	841	871	900	929	958	988	1017	1046	1075	1105	1134	1163	1222	1280		
27	841	871	900	929	958	987	1015	1044	1073	1102	1131	1159	1216	1275		
28	829	857	885	913	942	970	998	1026	1054	1083	1112	1139	1195	1253		
29	814	843	870	897	926	953	980	1009	1036	1064	1092	1119	1174	1231		
30	800	828	855	882	909	936	963	991	1017	1045	1073	1099	1153	1208		
31	786	813	839	866	893	919	945	973	999	1026	1053	1079	1132	1186		
32	771	798	824	850	877	902	928	955	980	1007	1034	1059	1111	1164		
33	757	783	809	834	860	885	911	937	962	988	1014	1039	1090	1142		
34	743	768	793	818	844	868	893	919	943	969	995	1019	1069	1120		
35	728	754	778	802	827	852	876	901	925	950	975	999	1048	1098		
Area, in. <sup>2</sup>	64.73	66.98	69.23	71.48	73.73	75.98	78.23	80.48	82.73	84.98	87.23	89.48	93.98	98.48		
I <sub>x</sub> -1, in. <sup>4</sup>	3321	3387	3556	3727	3900	4076	4255	4436	4619	4805	4994	5185	5575	5976		
I <sub>x</sub> -2, in. <sup>4</sup>	7.05	7.11	7.17	7.22	7.27	7.32	7.37	7.42	7.47	7.52	7.57	7.61	7.70	7.79		
I <sub>y</sub> -1, in. <sup>4</sup>	1903	1964	2025	2086	2146	2207	2268	2329	2389	2450	2511	2572	2693	2815		
I <sub>y</sub> -2, in. <sup>4</sup>	5.42	5.42	5.41	5.40	5.40	5.39	5.38	5.38	5.37	5.37	5.37	5.36	5.35	5.35		
Weight, Lbs. per Foot	220.1	227.7	235.4	243.0	250.0	258.3	266.0	273.6	281.3	288.9	296.6	304.2	319.5	334.8		

Safe load values above signag line are for ratios of  $l/r$  not over 60, those below signag line are for ratios not over 120  $l/r$ .

# CARNEGIE STEEL COMPANY



## 15 INCH CHANNEL COLUMNS—Concluded

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.

Effective Length in Feet	2-15 in. Channels				2-15 in. 45 lb. Channels											
	35 lb.		45 lb.													
	2-18 x 2 2-14 x 5/8 Web Plates	2-18 x 2 2-14 x 5/8 Flange Plates	2-18 x 2 2-14 x 5/8 Web Plates	2-18 x 2 2-14 x 5/8 Flange Plates	2-20 x 2 2-14 x 5/8 Web Plates	2-20 x 2 2-14 x 5/8 Flange Plates	2-20 x 2 2-14 x 5/8 Web Plates	2-20 x 2 2-14 x 5/8 Flange Plates	2-20 x 2 2-14 x 5/8 Web Plates	2-20 x 2 2-14 x 5/8 Flange Plates	2-20 x 2 2-14 x 5/8 Web Plates	2-20 x 2 2-14 x 5/8 Flange Plates	2-20 x 2 2-14 x 5/8 Web Plates	2-20 x 2 2-14 x 5/8 Flange Plates	2-20 x 2 2-14 x 5/8 Web Plates	2-20 x 2 2-14 x 5/8 Flange Plates
11	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
12	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
13	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
14	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
15	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
16	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
17	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
18	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
19	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
20	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
21	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
22	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
23	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
24	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
25	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
26	1340	1408	1485	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
27	1331	1394	1465	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
28	1307	1369	1439	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
29	1284	1344	1413	1547	1612	1677	1742	1807	1872	1937	2002	2067	2132	2197	2262	2327
30	1261	1320	1387	1543	1607	1670	1735	1798	1863	1926	1991	2054	2118	2182	2246	2310
31	1238	1295	1361	1519	1582	1644	1708	1770	1834	1896	1960	2022	2085	2147	2210	2272
32	1214	1270	1335	1495	1557	1618	1681	1742	1805	1866	1929	1989	2052	2113	2174	2235
33	1191	1246	1309	1471	1532	1592	1654	1714	1776	1836	1897	1957	2019	2078	2138	2198
34	1168	1221	1283	1447	1507	1566	1627	1686	1747	1806	1866	1925	1985	2044	2103	2162
35	1145	1197	1257	1424	1482	1540	1600	1658	1718	1775	1835	1893	1952	2010	2068	2126
Area, in. <sup>2</sup>	103.08	108.32	114.23	118.98	123.98	128.98	133.98	138.98	143.98	148.98	153.98	158.98	163.98	168.98	173.98	178.98
I <sub>1-1</sub> , in. <sup>4</sup>	6037	6123	6233	6397	6643	7300	7769	8251	8744	9251	9770	10301	10846	11405	11977	12562
I <sub>2-2</sub> , in. <sup>4</sup>	7.65	7.52	7.39	7.33	7.43	7.52	7.61	7.70	7.79	7.88	7.97	8.05	8.13	8.21	8.29	8.37
I <sub>3-3</sub> , in. <sup>4</sup>	2019	3021	3148	4240	4407	4573	4740	4907	5073	5240	5407	5573	5740	5907	6073	6240
I <sub>4-4</sub> , in. <sup>4</sup>	5.32	5.28	5.25	5.97	5.96	5.95	5.95	5.94	5.94	5.93	5.93	5.92	5.92	5.91	5.91	5.90
Weight, lbs. per foot	350.5	368.4	388.4	404.5	421.5	438.5	455.5	472.5	489.5	506.5	523.5	540.5	557.5	574.5	591.5	608.5

Safe load values above zigzag line are for ratios of  $l/r$  not over 60, those below zigzag line are for ratios not over 120  $l/r$ .


# COLUMNS

## PLATE AND ANGLE COLUMNS

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	Web Plate 6 x 1/4			Web Plate 8 x 1/4			Web Plate 8 x 5/16			Web Plate 8 x 3/8		
	4 Angles 2 1/2 x 2 x 1/4	4 Angles 3 x 2 x 1/4	4 Angles 3 x 2 1/2 x 1/4	4 Angles 3 x 2 1/2 x 1/4	4 Angles 3 x 2 1/2 x 5/16	4 Angles 3 1/2 x 2 1/2 x 1/4	4 Angles 3 1/2 x 2 1/2 x 5/16	4 Angles 3 1/2 x 2 1/2 x 5/16	4 Angles 3 1/2 x 2 1/2 x 3/8	4 Angles 4 x 3 x 5/16	4 Angles 4 x 3 x 3/8	4 Angles 4 x 3 x 1/2
6	09	81	88	94	110	101	119	125	142	141	161	208
7	63	78	82	86	103	101	119	125	142	141	161	208
8	56	72	76	79	95	96	115	120	138	141	161	208
9	49	66	69	72	87	89	107	112	130	136	158	206
10	43	60	63	65	78	83	100	104	121	128	149	196
11	38	54	56	57	70	76	92	96	112	121	140	185
12	35	49	50	50	62	70	85	89	104	113	131	174
13	32	43	45	47	56	63	78	81	95	105	123	163
14	28	40	42	43	52	57	70	73	86	97	114	152
15	25	37	39	39	48	52	63	66	77	89	105	141
16	22	34	35	36	44	49	60	62	73	81	97	130
17	18	32	32	32	40	46	56	58	68	75	88	120
18		29	29	28	36	43	52	54	64	71	83	110
19		26	26	25	32	39	49	50	60	67	79	105
20		23	22	28	30	36	45	47	55	63	74	100
21	20				33	41	43	51	59	70	82	94
22					30	38	39	47	55	66	68	89
23					27	34	35	42	51	61	63	83
24					23	30		31	38	48	57	78
25								34	44	53	63	72
26									40	48	49	67
27									36	44	45	62
28										39	40	56
29												
30												
Area, in. <sup>2</sup>	5.74	6.20	6.74	7.24	8.48	7.76	9.12	9.62	10.94	10.86	12.42	16.00
I <sub>1-1</sub> , in. <sup>4</sup>	34.3	39.1	42.6	81.2	96.9	90.1	107	110	127	122	141	178
I <sub>2-2</sub> , in. <sup>4</sup>	2.45	2.50	2.51	3.35	3.38	3.41	3.43	3.38	3.40	3.35	3.36	3.33
I <sub>3-3</sub> , in. <sup>4</sup>	6.2	10.3	10.3	10.3	12.9	16.0	20.2	20.7	24.9	30.3	36.3	50.2
r <sub>2-2</sub> , in.	1.04	1.28	1.24	1.19	1.23	1.44	1.49	1.47	1.51	1.67	1.71	1.77
Weight, Lbs. per Foot	19.6	21.5	23.1	24.8	29.2	26.4	31.2	32.9	37.3	37.3	42.5	54.5

Safe load values above and to right of upper sigsag line are for ratios of l/r not over 60, those between the sigsag lines are for ratios up to 120 l/r, and those below lower sigsag line are for ratios not over 200 l/r.


# CARNEGIE STEEL COMPANY

## PLATE AND ANGLE COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	Web Plate 10 x 1/4		Web Plate 10 x 5/16		Web Plate 10 x 3/8						Web Plate 10 x 1/2		Web Pl. 10x5/8	
	4 Angles 3 x 2 1/2 x 1/4	4 Angles 3 1/2 x 2 1/2 x 1/4	4 Angles 3 1/2 x 2 1/2 x 5/16	4 Angles 3 1/2 x 2 1/2 x 5/16	4 Angles 4 x 3 x 3/8	4 Angles 4 x 3 x 3/8	4 Angles 4 x 3 x 3/8	4 Angles 4 x 3 x 3/8	4 Angles 4 x 3 x 3/8	4 Angles 5 x 3 1/2 x 3/8	4 Angles 5 x 3 1/2 x 3/8	4 Angles 6 x 4 x 1/2	4 Angles 6 x 4 x 1/2	4 Angles 6 x 4 x 5/8
6	90	107	125	133	149	170	178	198	207	232	236	266	296	312
7	91	107	125	133	149	170	178	198	207	232	236	266	296	312
8	82	100	119	125	149	170	178	198	207	232	236	266	296	312
9	74	93	111	117	142	164	170	192	207	232	236	266	296	312
10	66	86	103	108	133	154	160	181	207	232	236	266	296	312
11	58	79	95	99	125	145	150	170	203	230	236	266	296	312
12	52	71	87	91	116	135	140	160	194	220	230	266	296	312
13	48	64	79	82	108	126	130	149	185	210	235	266	296	312
14	44	57	71	73	99	117	121	138	175	200	226	257	288	302
15	40	54	65	68	91	107	111	127	166	190	218	248	278	291
16	36	50	61	64	82	98	101	116	157	180	209	238	267	280
17	32	47	57	60	77	90	93	106	148	170	201	229	257	269
18	28	43	53	55	73	85	88	101	139	160	192	220	247	258
19	24	40	49	51	69	81	83	95	130	150	184	210	237	247
20	20	36	45	47	64	76	78	90	121	140	175	201	226	236
21	33	41	42	60	71	73	84	112	130	167	191	216	225	250
22	29	37	38	56	67	68	79	107	123	158	182	208	214	238
23	25	34	34	51	62	63	74	103	118	150	172	195	203	226
24	30	30	47	57	58	58	68	98	113	141	163	185	192	214
25			43	52	53	53	63	93	108	132	154	175	181	203
26					39	48	48	57	89	103	126	144	164	170
27					34	43	43	52	84	98	121	139	157	164
28								47	80	93	117	134	152	158
29									75	88	113	130	149	153
30									71	83	109	125	141	147
Area, in. <sup>2</sup>	7.74	8.26	8.62	10.25	11.48	13.05	13.67	15.23	15.95	17.87	18.19	20.47	22.75	24.00
I <sub>1-1</sub> , in. <sup>4</sup>	134	148	170	181	201	235	237	287	279	315	319	381	401	412
I <sub>2-2</sub> , in. <sup>4</sup>	418	429	438	430	418	422	417	419	418	420	419	420	420	414
I <sub>3-3</sub> , in. <sup>4</sup>	10.8	16.7	20.2	20.7	30.3	38.3	37.2	43.5	70.6	82.3	119	139	160	165
I <sub>4-4</sub> , in. <sup>4</sup>	1.15	1.39	1.45	1.42	1.62	1.67	1.65	1.69	2.10	2.15	2.56	2.81	2.65	2.62
Weight, Lbs. per Foot	26.5	28.1	32.9	35.0	39.4	44.6	46.8	52.0	54.4	60.8	62.0	70.0	77.6	81.8

Safe load values above and to right of upper zigzag line are for ratios of l/r not over 80, those between the zigzag lines are for ratios up to 120 l/r, and those below lower zigzag line are for ratios not over 200 l/r.


# COLUMNS

## PLATE AND ANGLE COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	Web Plate 12 x 1/4			Web Pl. 12 x 5/16			Web Plate 12 x 3/8			Web Plate 12 x 1/2			Web Plate 12 x 1/2		
	4 Angles 3 1/2 x 2 1/2 x 1/4	4 Angles 3 1/2 x 2 1/2 x 5/16	4 Angles 4 x 3 x 1/4	4 Angles 4 x 3 x 5/16	4 Angles 4 x 3 x 3/8	4 Angles 4 x 3 x 1/2	4 Angles 5 x 3 1/2 x 3/8	4 Angles 5 x 3 1/2 x 1/2	4 Angles 6 x 4 x 1/4	4 Angles 6 x 4 x 3/8	4 Angles 6 x 4 x 1/2	4 Angles 6 x 4 x 3/4	4 Angles 6 x 4 x 1/2	4 Angles 6 x 4 x 3/4	4 Angles 6 x 4 x 1/2
6	114	132	148	157	178	187	217	242	266	276	305	325	354	383	411
7	112	132	148	157	178	187	217	242	266	276	305	325	354	383	411
8	104	123	148	157	178	187	217	242	266	276	305	325	354	383	411
9	96	115	140	147	169	177	217	242	266	276	305	325	354	383	411
10	89	106	131	138	159	167	217	242	266	276	305	325	354	383	411
11	81	98	123	129	149	156	210	237	264	276	305	325	354	383	411
12	73	89	114	120	139	145	201	226	252	270	305	325	354	383	411
13	65	80	106	111	129	134	191	215	241	274	305	323	354	383	411
14	59	72	97	101	119	124	181	205	229	264	295	312	342	373	403
15	55	67	89	92	109	113	171	194	218	254	284	300	330	359	389
16	52	63	80	84	99	102	162	184	206	244	274	288	317	346	375
17	48	58	76	79	92	93	152	173	195	234	263	277	305	333	361
18	44	54	71	75	87	91	142	162	184	224	252	265	292	319	347
19	40	50	67	70	82	85	132	152	172	214	241	253	280	306	333
20	36	45	63	65	77	80	123	141	161	204	230	242	267	293	318
21	32	41	59	61	72	75	115	130	149	194	220	230	255	279	304
22	28	37	55	56	67	69	110	125	141	184	209	218	242	266	290
23	33	50	52	62	62	64	105	120	135	174	198	207	230	253	276
24	46	47	57	58	100	114	129	164	187	195	217	239	262	284	294
25	42	42	52	53	95	109	123	155	176	183	204	226	248	269	278
26	38	38	47	48	91	104	118	147	166	173	192	213	234	254	262
27			42	86	98	112	142	160	167	185	203	220	239	247	256
28				81	93	106	137	154	162	179	196	213	230	239	248
29				76	88	101	132	149	156	173	189	206	223	231	240
30				71	82	95	127	143	150	166	183	199	215	223	232
Area, in. <sup>2</sup>	8.76	10.12	11.36	12.11	13.67	14.42	16.70	18.62	20.50	21.22	23.50	25.00	27.24	29.44	31.60
I <sub>1-1</sub> , in. <sup>4</sup>	222	264	295	304	360	358	421	478	528	544	605	623	688	741	794
I <sub>2-2</sub> , in. <sup>4</sup>	5.04	5.11	5.09	5.01	5.06	4.99	5.02	5.05	5.07	5.08	5.07	4.99	5.01	5.02	5.01
I <sub>3-3</sub> , in. <sup>4</sup>	16.0	20.2	22.6	20.3	26.3	27.3	30.6	32.3	34.6	33.9	36.0	35.5	38.8	40.6	42.8
I <sub>4-4</sub> , in. <sup>4</sup>	1.35	1.41	1.61	1.58	1.63	1.61	2.06	2.10	2.15	2.56	2.61	2.57	2.61	2.65	2.69
Weight, Lbs. per Foot	29.8	34.6	39.0	41.6	46.8	49.3	56.9	63.3	69.7	72.5	80.1	85.2	92.8	100.4	107.8

Safe load values above and to right of upper signa line are for ratios of l/r not over 60, those between signa lines are for ratios up to 120 l/r, and those below lower signa line are for ratios not over 200 l/r.


# CARNEGIE STEEL COMPANY

## PLATE AND ANGLE COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	Web Plate 12 x 3/8				Web Plate 12 x 1/2				Web Plate 12 x 5/8			
	4 Angles 6 x 4 x 3/8 2 Plates 14 x 1/2	4 Angles 6 x 4 x 3/8 2 Plates 14 x 1/2	4 Angles 6 x 4 x 3/8 2 Plates 14 x 1/2	4 Angles 6 x 4 x 3/8 2 Plates 14 x 1/2	4 Angles 6 x 4 x 1/2 2 Plates 14 x 1/2	4 Angles 6 x 4 x 1/2 2 Plates 14 x 1/2	4 Angles 6 x 4 x 1/2 2 Plates 14 x 1/2	4 Angles 6 x 4 x 1/2 2 Plates 14 x 1/2	4 Angles 6 x 4 x 5/8 2 Plates 14 x 5/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 5/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 5/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 5/8
11	383	428	458	487	507	553	582	610	630	675	721	766
12	383	428	458	487	507	553	582	610	630	675	721	766
13	383	428	458	487	507	553	582	610	630	675	721	766
14	383	428	458	487	507	553	582	610	630	675	721	766
15	383	428	458	487	507	553	582	610	630	675	721	766
16	370	428	458	487	506	553	582	610	630	675	721	766
17	368	419	447	475	491	542	569	596	613	663	714	763
18	357	407	434	461	476	526	553	579	594	644	694	742
19	346	395	421	447	461	510	536	562	576	625	674	721
20	334	383	407	433	447	495	520	544	558	606	654	700
21	323	370	394	419	432	479	503	527	540	587	634	679
22	312	358	381	405	417	463	487	509	522	568	614	658
23	301	346	368	391	403	448	470	492	504	548	594	637
24	289	334	355	377	388	432	454	475	486	529	574	616
25	278	322	342	363	373	416	437	457	468	510	554	595
26	267	310	329	349	358	401	421	440	450	491	534	574
27	256	297	316	335	344	385	404	422	431	472	514	553
28	244	285	303	321	329	369	388	405	413	453	494	532
29	233	273	290	307	314	354	371	388	395	434	474	511
30	222	261	277	293	299	338	354	370	377	415	454	490
31	211	249	264	279	285	323	338	353	359	396	434	469
32	203	237	250	265	272	307	321	336	341	377	414	448
33	197	228	242	257	264	294	309	323	331	361	394	427
34	191	221	235	250	257	287	301	315	322	351	381	409
35	186	215	229	243	249	279	293	306	313	342	371	399
Area, in. <sup>2</sup>	29.44	32.94	35.22	37.50	39.00	42.50	44.74	46.94	48.44	51.94	55.44	58.94
I <sub>1-1</sub> , in. <sup>4</sup>	916	1073	1136	1197	1215	1377	1437	1495	1513	1682	1856	2037
I <sub>2-2</sub> , in. <sup>4</sup>	5.58	5.71	5.85	5.95	5.58	5.69	5.67	5.64	5.59	5.69	5.79	5.88
r <sub>1-1</sub> , in.	29.1	34.8	36.8	38.8	39.4	43.1	47.2	49.2	49.9	55.6	61.3	67.1
r <sub>2-2</sub> , in.	3.14	3.25	3.23	3.22	3.18	3.26	3.25	3.24	3.21	3.27	3.33	3.37
Weight, Lbs. per Foot	100.2	112.1	120.1	127.7	132.8	144.7	152.3	159.9	165.0	176.9	188.8	200.7

Safe load values above and to right of upper zigzag line are for ratios of  $l/r$  not over 80, those between zigzag lines are for ratios up to 120  $l/r$ , and those below lower zigzag line are for ratios not over 200  $l/r$ .


# COLUMNS

## PLATE AND ANGLE COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	Web Plate 12 x 5/8								Web Plate 14 x 3/4							
	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/2	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/4	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/2	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/4	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/2	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/4	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/2	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/4	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/2	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/4	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/2
11	812	857	903	948	994	1039	1085	1130	392	422	452	474	497			
12	812	857	903	948	994	1039	1085	1130	392	422	452	474	497			
13	812	857	903	948	994	1039	1085	1130	392	422	452	474	497			
14	812	857	903	948	994	1039	1085	1130	392	422	452	474	497			
15	812	857	903	948	994	1039	1085	1130	392	422	452	474	497			
16	812	857	903	948	994	1039	1085	1130	387	415	444	470	497			
17	812	857	903	948	994	1039	1085	1130	375	403	431	456	482			
18	791	840	888	937	986	1034	1082	1130	363	390	417	442	468			
19	769	817	864	912	960	1007	1054	1101	352	377	404	428	453			
20	747	794	840	887	934	980	1026	1072	340	365	390	415	439			
21	725	771	817	862	908	953	998	1043	328	352	377	401	425			
22	703	748	793	837	882	926	970	1014	317	340	363	387	410			
23	681	725	769	812	856	899	942	985	305	327	350	373	396			
24	659	703	745	787	830	872	914	956	293	314	336	359	381			
25	637	679	721	762	805	845	886	927	281	302	323	345	367			
26	615	657	697	738	779	818	858	898	270	289	309	331	353			
27	593	634	673	713	753	791	830	869	258	276	296	317	338			
28	571	611	649	688	727	764	802	840	246	264	282	303	324			
29	549	588	625	663	701	737	774	811	235	251	269	289	309			
30	527	565	601	638	675	710	746	782	223	239	255	275	295			
31	505	542	577	613	649	684	718	753	211	227	243	261	281			
32	483	519	553	588	623	657	690	725	205	220	236	251	267			
33	461	496	529	563	597	630	662	696	200	214	229	244	260			
34	439	473	505	538	571	603	634	667	194	208	222	237	253			
35	427	456	484	513	545	576	606	638	188	201	216	230	245			
Area, in. <sup>2</sup>	62.44	65.04	69.44	72.94	76.44	79.94	83.44	86.94	30.19	32.47	34.75	36.50	38.25			
I <sub>1-1</sub> , in. <sup>4</sup>	2224	2418	2618	2825	3038	3259	3486	3721	1261	1351	1436	1539	1643			
I <sub>2-2</sub> , in. <sup>4</sup>	5.97	6.06	6.14	6.22	6.30	6.38	6.46	6.54	6.46	6.45	6.43	6.49	6.55			
I <sub>3-3</sub> , in. <sup>4</sup>	728	785	842	899	956	1014	1071	1128	291	311	331	360	388			
Weight, lbs. per foot	212.6	224.5	236.4	248.3	260.2	272.1	284.0	295.9	102.8	110.8	118.4	124.3	130.3			

Safe load values above and to right of upper signag line are for ratios of  $l/r$  not over 60, those between signag lines are for ratios up to 120  $l/r$ , and those below lower signag line are for ratios not over 200  $l/r$ .




CARNEGIE STEEL COMPANY

PLATE AND ANGLE COLUMNS—Continued

SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	Web Plate 14 x 5/8		Web Plate 14 x 1/2		Web Plate 14 x 3/4							
	4 Angles 6 x 4 x 1/2 2 Plates 14 x 5/8	4 Angles 6 x 4 x 1/2 2 Plates 14 x 3/4	4 Angles 6 x 4 x 1/2 2 Plates 14 x 1/2	4 Angles 6 x 4 x 1/2 2 Plates 14 x 5/8	4 Angles 6 x 4 x 1/2 2 Plates 14 x 3/4	4 Angles 6 x 4 x 1/2 2 Plates 14 x 1/2	4 Angles 6 x 4 x 1/2 2 Plates 14 x 5/8	4 Angles 6 x 4 x 1/2 2 Plates 14 x 3/4	4 Angles 6 x 4 x 1/2 2 Plates 14 x 1/2	4 Angles 6 x 4 x 1/2 2 Plates 14 x 5/8	4 Angles 6 x 4 x 1/2 2 Plates 14 x 3/4	4 Angles 6 x 4 x 1/2 2 Plates 14 x 1/2
11	520	543	566	595	623	646	601	737	782	828	873	919
12	520	543	566	595	623	646	601	737	782	828	873	919
13	520	543	566	595	623	646	601	737	782	828	873	919
14	520	543	566	595	623	646	601	737	782	828	873	919
15	520	543	566	595	623	646	601	737	782	828	873	919
16	520	543	566	595	623	643	601	737	782	828	873	919
17	507	533	551	578	605	624	675	720	776	826	873	919
18	493	517	535	561	587	606	655	705	754	803	852	901
19	478	502	518	544	569	587	635	684	733	780	829	876
20	463	487	502	527	551	568	615	664	711	758	805	851
21	448	472	486	510	533	549	596	643	689	735	782	827
22	433	456	470	493	515	530	576	622	668	713	758	802
23	418	441	454	476	497	511	556	602	646	690	734	778
24	403	426	437	459	479	493	536	581	625	667	711	753
25	388	410	421	442	461	474	517	560	603	645	687	728
26	374	395	405	424	443	455	497	540	581	622	664	704
27	359	380	389	407	425	436	477	519	560	600	640	679
28	344	364	373	390	407	417	457	498	538	577	617	655
29	329	349	356	373	390	399	438	477	516	554	593	630
30	314	334	340	356	372	380	418	457	495	532	569	605
31	299	318	324	339	354	361	398	436	473	509	546	581
32	284	303	308	322	336	345	378	415	452	487	522	556
33	275	290	298	312	327	336	365	396	430	464	499	532
34	267	282	290	304	318	326	356	385	415	444	475	507
35	260	275	282	295	309	317	346	375	404	432	461	489
Area, in. <sup>2</sup>	40.00	41.75	43.50	45.74	47.94	49.69	53.19	56.09	60.19	63.69	67.19	70.89
I <sub>x</sub> -I, in. <sup>4</sup>	1749	1857	1855	1970	2053	2081	2302	2329	2764	3006	3255	3512
I <sub>y</sub> -I, in. <sup>4</sup>	6.61	6.67	6.58	6.59	6.54	6.47	6.58	6.68	6.73	6.87	6.98	7.05
I <sub>x</sub> -I, in. <sup>4</sup>	417	446	451	472	492	499	556	613	671	728	785	842
I <sub>y</sub> -I, in. <sup>4</sup>	3.23	3.27	3.22	3.21	3.20	3.17	3.23	3.29	3.34	3.38	3.42	3.45
Weight, Lbs. per Foot	136.2	142.2	148.1	155.7	163.3	169.3	181.2	193.1	205.0	216.9	228.8	240.7

Safe load values above and to right of upper signig line are for ratios of 1/r not over 60, those between the signig lines are for ratios up to 120 1/r, and those below lower signig line are for ratios not over 200 1/r.


# COLUMNS

## PLATE AND ANGLE COLUMNS—Continued

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.



Effective Length in Feet	Web Plate 14 x 5/8											
	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 1/2	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8	4 Angles 6 x 4 x 5/8 2 Plates 14 x 1 3/8
11	964	1010	1055	1101	1146	1198	1250	1315	1367	1419	1471	1523
12	964	1010	1055	1101	1146	1198	1250	1315	1367	1419	1471	1523
13	964	1010	1055	1101	1146	1198	1250	1315	1367	1419	1471	1523
14	964	1010	1055	1101	1146	1198	1250	1315	1367	1419	1471	1523
15	964	1010	1055	1101	1146	1198	1250	1315	1367	1419	1471	1523
16	964	1010	1055	1101	1146	1198	1250	1315	1367	1419	1471	1523
17	964	1010	1055	1101	1146	1198	1250	1315	1367	1419	1471	1523
18	949	998	1046	1095	1144	1198	1250	1315	1367	1419	1471	1523
19	924	971	1018	1067	1114	1198	1250	1315	1367	1419	1471	1523
20	898	945	991	1038	1084	1198	1250	1308	1364	1419	1471	1523
21	872	918	963	1010	1055	1174	1229	1277	1333	1388	1443	1497
22	847	892	935	981	1025	1146	1201	1246	1301	1356	1409	1463
23	821	865	908	953	996	1119	1172	1216	1269	1323	1375	1428
24	796	839	880	924	966	1091	1144	1185	1237	1290	1342	1393
25	770	812	853	895	937	1064	1115	1154	1206	1258	1308	1359
26	744	786	825	867	907	1036	1087	1123	1174	1225	1274	1324
27	719	759	797	838	877	1009	1058	1093	1142	1192	1241	1289
28	693	732	770	810	848	981	1030	1062	1111	1160	1207	1254
29	668	706	742	781	818	954	1001	1031	1079	1127	1173	1220
30	642	679	715	753	789	926	973	1000	1047	1094	1139	1185
31	617	653	687	724	759	899	944	970	1015	1062	1106	1150
32	591	626	659	696	730	871	916	939	984	1029	1072	1115
33	565	600	632	667	700	843	887	908	952	996	1038	1081
34	540	573	604	639	671	816	859	877	920	964	1005	1046
35	517	546	577	610	641	788	830	847	889	931	971	1011
Area, in. <sup>2</sup>	74.19	77.09	81.19	84.69	88.19	92.19	93.19	101.19	105.19	109.19	113.19	117.19
I <sub>1-1</sub> , in. <sup>4</sup>	3776	4048	4327	4615	4910	5120	5457	5484	5830	6187	6552	6928
I <sub>2-2</sub> , in. <sup>4</sup>	7.13	7.22	7.30	7.38	7.46	7.45	7.53	7.36	7.44	7.53	7.61	7.69
I <sub>3-3</sub> , in. <sup>4</sup>	899	956	1014	1071	1128	1493	1579	1581	1666	1752	1837	1922
Weight, lbs. per foot	252.6	264.5	276.4	288.3	300.2	313.8	327.4	344.2	357.8	371.4	385.0	398.6

Safe load values above and to right of upper sigsag line are for ratios of l/r not over 60, those between the sigsag lines are for ratios up to 120 l/r and those below lower sigsag line are for ratios not over 200 l/r.


# CARNEGIE STEEL COMPANY

## PLATE AND ANGLE COLUMNS—Concluded

### SAFE LOADS IN THOUSANDS OF POUNDS

Allowable Fiber Stress per square inch, 13,000 pounds for lengths of 60 radii or under, reduced for lengths over 60 radii; see Construction Specifications.

Weights do not include rivet heads or other details.




Effective Length in Feet	Two Web Plates 14 x 1/4						Two Web Plates 14 x 5/8					
	4 Angles 6 x 6 x 5/8 2 Plates 16 x 2 1/2	4 Angles 8 x 6 x 5/8 2 Plates 16 x 2 1/2	4 Angles 8 x 6 x 5/8 2 Plates 18 x 2 1/2	4 Angles 8 x 6 x 5/8 2 Plates 18 x 2 3/4	4 Angles 8 x 6 x 5/8 2 Plates 18 x 2 1/2	4 Angles 8 x 6 x 5/8 2 Plates 18 x 2 3/4	4 Angles 8 x 6 x 5/8 2 Plates 18 x 2 1/2	4 Angles 8 x 6 x 5/8 2 Plates 20 x 2 1/2	4 Angles 8 x 6 x 5/8 2 Plates 20 x 2 3/4	4 Angles 8 x 6 x 5/8 2 Plates 20 x 3	4 Angles 8 x 6 x 5/8 2 Plates 20 x 3 1/2	
11	1592	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
12	1592	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
13	1592	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
14	1592	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
15	1592	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
16	1592	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
17	1592	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
18	1592	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
19	1592	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
20	1590	1657	1728	1787	1845	1904	1949	2027	2092	2157	2222	
21	1553	1653	1728	1787	1845	1904	1949	2027	2092	2157	2222	
22	1516	1616	1728	1787	1845	1904	1949	2027	2092	2157	2222	
23	1479	1580	1728	1787	1845	1904	1949	2027	2092	2157	2222	
24	1443	1543	1695	1756	1818	1879	1918	2027	2092	2157	2222	
25	1406	1507	1661	1721	1781	1842	1879	2027	2092	2157	2222	
26	1369	1470	1626	1685	1744	1804	1841	2009	2077	2146	2214	
27	1332	1434	1592	1650	1708	1766	1802	1972	2039	2107	2175	
28	1295	1397	1557	1614	1671	1729	1763	1935	2002	2068	2135	
29	1258	1360	1522	1578	1635	1691	1724	1899	1964	2029	2095	
30	1222	1324	1488	1543	1598	1653	1686	1862	1926	1991	2055	
31	1185	1287	1453	1507	1561	1616	1647	1825	1889	1952	2016	
32	1148	1251	1419	1471	1525	1578	1608	1789	1851	1913	1976	
33	1111	1214	1384	1436	1488	1541	1569	1752	1813	1874	1936	
34	1074	1177	1349	1400	1451	1503	1530	1715	1775	1836	1896	
35	1038	1141	1315	1365	1415	1465	1492	1679	1738	1797	1857	
Area, in. <sup>2</sup>	122.44	127.44	132.94	137.44	141.94	146.44	149.94	155.94	160.94	165.94	170.94	
I <sub>1-1</sub> , in. <sup>4</sup>	7014	7254	7659	7981	8415	8859	8916	9248	9741	10248	10767	
I <sub>2-2</sub> , in. <sup>4</sup>	7.57	7.54	7.54	7.62	7.70	7.78	7.71	7.70	7.78	7.86	7.94	
I <sub>3-3</sub> , in. <sup>4</sup>	1946	2229	2831	2953	3074	3196	3222	4049	4216	4383	4549	
Weight, Lbs. per Foot	416.4	433.6	462.3	467.6	482.9	498.2	510.1	530.5	547.5	564.5	581.5	

Safe load values above and to right of zigzag line are for ratios of l/r not over 60, those below zigzag line are for ratios not over 120 l/r.

## COLUMN DETAILS

### TYPICAL COLUMN DETAILS

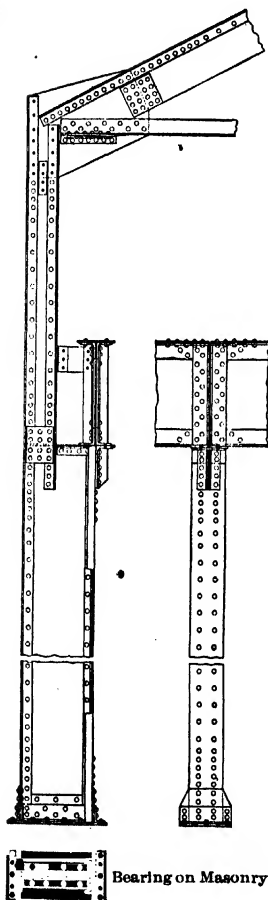

MILL BUILDING COLUMN

Simplicity in details is essential to economical construction. To eliminate bending or secondary stresses, it is desirable in making designs and details that loads be transmitted from beams, girders and trusses to columns directly and with the minimum number of connecting pieces, rivets, or bolts, and that the rivets or bolts be stressed in shear or bearing only.

The column connections shown on this page and the two pages which follow represent the best modern practice and conform to these fundamental conditions and cover the range of cases met with in ordinary mill and office building construction.

Where columns rest on steel slabs or castings, the loads are transmitted directly into the footing, and shoe angles may be provided for proper anchorage. Where they rest on masonry, gusset plates may be required to distribute the load.


Columns should be milled to accurate bearing at joints, with splice plates sufficient to hold the sections in line and to resist bending stresses. Horizontal bearing plates must be used between column sections of different forms or general dimensions. Rivet spacing in column shafts and at beam connections should be uniform to permit the use of multiple punches; spacing should be in multiples of one-quarter inch.

Erection requirements should not be overlooked; beams should frame with ample clearances, particularly to column webs, and rivets should be countersunk or flattened where necessary to swing beams into position.

CARNEGIE STEEL COMPANY

TYPICAL COLUMN DETAILS

OFFICE BUILDING CONSTRUCTION

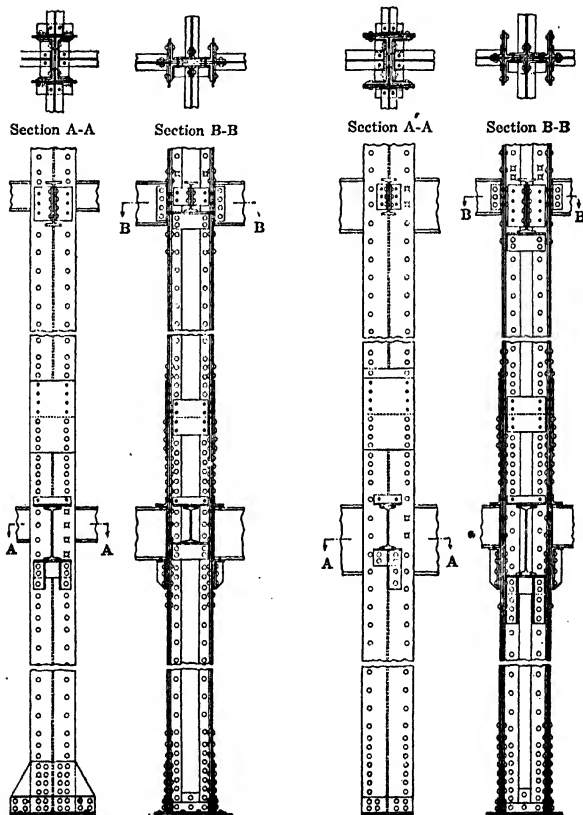

TYPICAL ANGLE COLUMN

Bearing on Masonry


TYPICAL ANGLE COLUMN

Bearing on Steel


# COLUMN DETAILS

## TYPICAL COLUMN DETAILS






### OFFICE BUILDING CONSTRUCTION



Section A-A




Section B-B

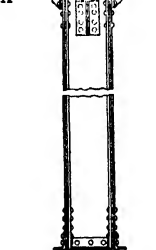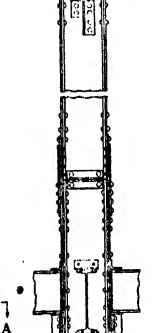


TYPICAL CHANNEL COLUMN

Bearing on Steel




TYPICAL SPLICE

Angle Column to Channel Column



TYPICAL SPLICE

Angle Columns, different sizes



TYPICAL SPLICE

Channel Columns, different sizes

# CARNEGIE STEEL COMPANY

## CAST IRON COLUMNS

### ALLOWABLE UNIT STRESSES IN POUNDS PER SQUARE INCH

#### For Various Ratios of Slenderness

Proposed formula of New York Building Law:  $9000 - 40 l/r$  lbs. per square inch

$l/r$	Lbs. per Sq. In.	$l/r$	Lbs. per Sq. In.	$l/r$	Lbs. per Sq. In.
10	8600	30	7800	50	7000
11	8560	31	7760	51	6960
12	8520	32	7720	52	6920
13	8480	33	7680	53	6880
14	8440	34	7640	54	6840
15	8400	35	7600	55	6800
16	8360	36	7560	56	6760
17	8320	37	7520	57	6720
18	8280	38	7480	58	6680
19	8240	39	7440	59	6640
20	8200	40	7400	60	6600
21	8160	41	7360	61	6560
22	8120	42	7320	62	6520
23	8080	43	7280	63	6480
24	8040	44	7240	64	6440
25	8000	45	7200	65	6400
26	7960	46	7160	66	6360
27	7920	47	7120	67	6320
28	7880	48	7080	68	6280
29	7840	49	7040	69	6240
				70	6200

The safe load for a cast iron column of given dimensions is determined from the above table by obtaining the ratio of  $l/r$  and multiplying the corresponding unit stress by the sectional area of column.

Example:—Required the safe load of a cast iron column, 15 inches square,  $\frac{3}{4}$  inch in thickness, and 16 feet long.

From table of Hollow Square Sections, page 193, the radius of gyration is 5.78 inches and the sectional area is 49.44 square inches; hence the ratio of  $l/r = 16 \times 12 \div 5.78 = 33.2$ , corresponding to a stress of 7672 pounds per square inch, giving a total safe load of  $49.44 \times 7672 = 379300$  pounds.

The minimum size of a cast iron column of a certain length to safely support a given load is determined as follows:


Divide the length in inches by 70; the quotient is the minimum allowable radius of gyration required. Divide the total load by 6200 pounds; the quotient is the minimum sectional area.

Example:—Required the minimum size of a round cast iron column, 20 feet long, to support a load of 235000 pounds.

The minimum radius of gyration is  $20 \times 12 \div 70 = 3.43$  inches; the minimum area is  $235000 \div 6200 = 37.90$  square inches. From table of Hollow Round Sections, page 192, the nearest minimum size for this radius of gyration and this area is found to be a column 11 inches in diameter and  $1\frac{1}{4}$  inches in thickness.

# CAST IRON COLUMNS

## ROUND CAST IRON COLUMNS



ALLOWABLE LOADS IN THOUSANDS OF POUNDS

By Proposed New York Building Law Formula

Weights do not include details

Outer Dia., Inches	Thick-ness, Inches	Area, Inches <sup>2</sup>	Weight per Foot, Pounds	Least Radius, Inches	Effective Length of Column in Feet											
					8	10	12	14	16	18	20	22	24	26	28	
6	$\frac{1}{4}$	8.64	27.0	1.95	61	56										
	$\frac{3}{8}$	10.55	33.0	1.91	74	68										
	$\frac{1}{2}$	12.37	38.7	1.88	86	80										
	$\frac{3}{4}$	14.09	44.0	1.84	97	90										
7	$\frac{5}{8}$	12.52	39.1	2.27	92	86	81									
	$\frac{3}{4}$	14.73	46.0	2.23	107	101	95									
	$\frac{7}{8}$	16.84	52.6	2.19	122	115	107									
	1	18.85	58.9	2.15	136	128	119									
8	$\frac{5}{8}$	17.08	53.4	2.58	128	122	116	100								
	$\frac{3}{4}$	19.59	61.2	2.54	147	139	132	124								
	1	21.99	68.7	2.50	164	156	147	139								
	$1\frac{1}{8}$	24.30	75.9	2.46	181	171	162	152								
9	$\frac{3}{4}$	22.34	69.8	2.89	171	164	157	149	142							
	1	25.13	78.5	2.85	192	184	175	167	158							
	$1\frac{1}{8}$	27.83	87.0	2.81	212	203	193	184	174							
	$1\frac{1}{4}$	30.43	95.1	2.78	232	221	211	200	190							
10	1	28.28	88.4	3.20	221	212	204	195	187	178						
	$1\frac{1}{8}$	31.37	98.0	3.16	244	235	225	216	206	197						
	$1\frac{1}{4}$	34.36	107.4	3.13	267	257	246	235	225	214						
	$1\frac{1}{2}$	37.26	116.4	3.09	289	277	266	254	243	231						
11	$1\frac{1}{8}$	34.90	109.1	3.51	276	266	257	247	238	228	219					
	$1\frac{1}{4}$	38.29	119.7	3.48	302	292	281	271	260	250	239					
	$1\frac{1}{2}$	41.48	129.9	3.44	328	316	305	293	281	270	258					
	$1\frac{3}{4}$	44.77	139.0	3.40	352	340	327	314	302	289	277					
12	$1\frac{1}{4}$	42.22	131.9	3.83	338	327	316	306	295	285	274	264				
	$1\frac{1}{2}$	45.90	143.4	3.79	367	355	343	332	320	308	297	285				
	$1\frac{3}{4}$	49.48	154.6	3.75	395	382	369	357	344	331	319	306				
	1	52.97	165.5	3.71	422	408	394	381	367	353	340	326				
13	$1\frac{3}{8}$	50.22	156.9	4.14	405	394	382	370	359	347	336	324	312			
	$1\frac{1}{2}$	54.19	169.4	4.10	437	424	412	399	386	374	361	348	335			
	$1\frac{3}{4}$	58.07	181.5	4.06	468	454	440	427	413	399	385	372	358			
	1	61.85	193.3	4.03	498	483	468	454	439	424	409	395	380			
14	$1\frac{3}{8}$	58.91	184.1	4.45	479	467	454	441	429	416	403	390	378			
	$1\frac{1}{2}$	63.18	197.4	4.41	514	500	486	472	459	445	431	417	404			
	$1\frac{3}{4}$	67.35	210.5	4.38	547	532	518	503	488	473	459	444	429			
	1	71.42	223.2	4.34	580	564	548	532	516	501	485	469	453			
15	$1\frac{3}{8}$	68.29	213.4	4.76	560	546	532	518	504	491	477	463	449	436		
	$1\frac{1}{2}$	72.85	227.0	4.73	597	582	567	552	537	523	508	493	478	463		
	$1\frac{3}{4}$	77.31	241.6	4.69	632	617	601	585	569	553	538	522	506	490		
	2	81.08	255.3	4.65	668	651	634	617	600	583	566	550	533	516		
16	$1\frac{3}{4}$	78.34	244.8	5.08	646	631	616	601	587	572	557	542	527	513	498	
	$1\frac{1}{2}$	83.20	260.0	5.04	685	670	654	638	622	606	590	574	559	543	527	
	2	87.97	274.9	5.00	724	707	690	673	657	640	623	606	589	572	555	
	$2\frac{1}{4}$	92.63	289.5	4.96	762	744	726	708	690	672	654	636	619	601	583	



# CARNEGIE STEEL COMPANY

## SQUARE CAST IRON COLUMNS

ALLOWABLE LOADS IN THOUSANDS OF POUNDS

By Proposed New York Building Law Formula

Weights do not include details

Outer Width, Inches	Thickness, Inches	Area, Inches <sup>2</sup>	Weight per Foot, Pounds	Least Radius, Inches	Effective Length of Column in Feet											
					8	10	12	14	16	18	20	22	24	26	28	
6	$\frac{1}{2}$	11.00	34.4	2.26	80	76	71									
	$\frac{3}{4}$	13.44	42.0	2.21	98	92	86									
	1	15.75	49.2	2.17	114	107	100									
	$1\frac{1}{4}$	17.94	56.1	2.12	129	121	113									
7	$\frac{1}{2}$	15.94	49.8	2.62	120	114	108	103								
	$\frac{3}{4}$	18.75	58.6	2.57	141	134	127	120								
	1	20.44	63.9	2.53	153	145	137	130								
	$1\frac{1}{4}$	24.00	75.0	2.48	179	170	160	151								
8	$\frac{1}{2}$	21.75	68.0	2.98	168	161	154	147	140							
	$\frac{3}{4}$	24.94	77.9	2.93	192	184	175	167	159							
	1	28.00	87.5	2.89	215	205	196	187	178							
	$1\frac{1}{4}$	30.94	96.7	2.84	237	228	216	205	195							
9	$\frac{1}{2}$	27.44	85.8	3.34	215	208	200	192	184	176						
	$\frac{3}{4}$	32.00	100.0	3.29	251	241	232	223	213	204						
	1	35.44	110.8	3.25	277	267	256	246	235	225						
	$1\frac{1}{4}$	38.75	121.1	3.21	302	291	279	268	256	244						
10	$\frac{1}{2}$	36.00	112.5	3.70	287	277	268	258	249	240	231					
	$\frac{3}{4}$	39.94	124.8	3.65	317	307	296	286	275	265	254					
	1	43.75	136.7	3.61	347	336	324	312	301	289	277					
	$1\frac{1}{4}$	47.44	148.3	3.57	376	363	350	338	325	312	299					
11	$\frac{1}{2}$	44.44	138.9	4.06	358	347	337	326	316	305	295	284				
	$\frac{3}{4}$	48.75	152.3	4.01	392	380	369	357	345	334	322	310				
	1	52.94	165.4	3.97	425	412	400	387	374	361	348	336				
	$1\frac{1}{4}$	57.00	178.1	3.93	457	443	429	416	402	388	374	360				
12	$\frac{1}{2}$	53.78	168.1	4.42	437	426	414	402	391	379	367	356	344			
	$\frac{3}{4}$	58.44	182.6	4.37	475	462	449	436	423	410	398	385	372			
	1	63.00	196.9	4.33	511	497	483	469	455	441	427	413	399			
	$1\frac{1}{4}$	67.44	210.8	4.29	547	532	516	501	486	471	456	441	426			
13	$\frac{1}{2}$	63.94	199.8	4.78	524	511	498	486	473	460	447	434	421	409		
	$\frac{3}{4}$	69.00	215.6	4.74	565	551	537	523	509	495	481	467	453	439		
	1	73.94	231.1	4.69	605	590	575	560	544	529	514	499	484	469		
	$1\frac{1}{4}$	78.75	246.1	4.65	644	627	611	595	579	562	546	530	514	497		
14	$\frac{1}{2}$	75.00	234.4	5.14	619	605	591	577	563	549	535	521	507	493	479	
	$\frac{3}{4}$	80.44	251.4	5.10	663	648	633	618	603	588	572	557	542	527	512	
	1	85.75	267.9	5.05	707	690	674	658	641	625	609	593	576	560	544	
	$1\frac{1}{4}$	90.94	284.2	5.01	749	731	714	696	679	662	644	627	609	592	574	
15	$\frac{1}{2}$	86.94	271.7	5.50	722	707	691	676	661	646	631	616	600	585	570	
	$\frac{3}{4}$	92.75	289.8	5.46	769	753	737	721	704	688	672	655	639	623	606	
	1	98.44	307.6	5.41	816	799	782	764	746	729	711	694	676	659	642	
	$1\frac{1}{4}$	104.00	325.0	5.37	862	843	824	806	787	769	750	731	713	694	676	
16	$\frac{1}{2}$	99.75	311.7	5.86	832	816	800	783	767	751	734	718	702	685	669	
	$\frac{3}{4}$	105.94	331.1	5.82	884	866	849	831	814	796	779	761	744	726	709	
	1	112.00	350.0	5.77	934	915	896	878	859	840	822	803	785	766	747	
	$1\frac{1}{4}$	117.94	368.0	5.73	982	963	943	923	903	883	864	844	824	804	785	

## FLOOR CONSTRUCTION

### FLOORS AND FLOOR LOADS

**Kinds of Loads.** Two kinds of loads are carried by structures. Live loads consist of the weight of carriages, cranes or other handling devices and their supported loads, machinery, merchandise, persons or other moving objects, the support of which is the purpose of the structure, including also wind stresses. Dead loads consist of the actual weight of the structure itself with the walls, floors, partitions, roofs, and all other permanent construction and fixtures. The dead loads stress the structure at all times and it must, therefore, be proportioned to sustain them at all times without reduction. The live loads may be taken at their full values or reduced in accordance with the probabilities that the structure as a whole or its principal members will not be subject at all times to the full theoretical live loading.

**Dead Loads.** The permanent load should be calculated from known weights per unit of the material composing floors, partitions, walls, or other permanent construction. The weight assumed for the steel frame itself should be checked after the sections are determined and then the sizes readjusted if necessary.

**Live Loads.** Live loads vary with the character of the structures. In buildings they consist of uniform loads per square foot of floor area, concentrated loads, such as heavy safes, which may be applied at any point of the floor, and uniform loads per lineal foot of beams or girders. The load which produces the maximum bending moment or reaction is to be used in proportioning sections. The floor system between beams must of course be of sufficient strength to transmit any concentrated load to the beam.

In cities the minimum live loads to be used on the various classes of buildings are fixed by public ordinances, and are given on page 312 for the principal cities of the United States in accordance with the most recent building laws, which are intended to cover general conditions and do not include machinery or other concentrations. If such concentrations, like safes, armatures, generators, or printing presses, occur on floors, special provision should be made for them in the floor framing. Flat roofs of buildings which may be loaded with people, should be treated the same as floors and the same uniform live loads used as given in the table for dwellings, hotels or assembly rooms.

# CARNEGIE STEEL COMPANY

## FLOORS AND ROOFS

### MINIMUM LIVE LOADS, POUNDS PER SQUARE FOOT

#### By Building Laws of Various Cities

Kind of Building	Boston, 1912	New York, 1906	Philadelphia, 1913	Baltimore, 1908	Pittsburgh, 1913	Cleveland, 1911	Chicago, 1911	St. Louis, 1910	San Francisco 1910
Apartments.....	50	60	70	60	50	50	40	60	60
Public Rooms <sup>a</sup> and Halls.....	100					80			
Assembly Halls.....	125	90	120		125	100		100	125
Fixed Seat Auditoriums.....				75	125	80	100		75
Movable Seat Auditoriums.....				125		100	100		125
Churches.....		90		75	125	150	100		125
Dance Halls.....	200				150				
Drill Rooms.....	200				150				
Riding Schools.....	200								
Theaters.....		90		75	125		100		125
Dwellings.....	50	60	70	60	50	40	40	60	60
Public Rooms <sup>a</sup> .....	100								
Hotels.....	50	60	70	60	70	50	50	60	60
First Floors.....								100	
Corridors.....						80			
Office Floors.....	100					80			
Public Rooms <sup>a</sup> .....	100								
Manufacturing.....	125	120	120	125			100		125
Light Factories.....	120	120	150		125			150	
Mercantile.....									
Heavy Storehouses.....		150	150	250	200	200			250
Retail Stores.....	125		120	125	125	125	100	150	125
Warehouses.....	250	150	150		200		100	150	250
Offices.....	100	75	100	75	70	60	50	70	60
First Floor.....	100	150		150				150	150
Corridors.....						100			
Schools (Class Rooms).....	60	75		75	70	60	40	100	75
Assembly Rooms—Halls.....	125	90			70	80	75		125
Sidewalks.....		300		200		200			150
Stables—Carriage Houses.....		75		100		80	100		75
Area less than 500 sq. ft.....							40		
Stairways and Landings.....	70					80	100		
Fire Escapes.....	70					80			
Roofs—Flat <sup>c</sup> .....	40	50		40	50d	40	25	40	30
Horizontal Projection.....									
Steep Roofs.....		30		20	50d		25		20
Superficial Surface.....			30		50d	40			
Wind Pressure.....		30	30 <sup>e</sup>	30	25	30 <sup>e</sup>	20	30	20

a Area greater than 500 square feet.

b First Floors 200.

c Slopes less than 20 degrees.

d Dead and live, except for one story steel frame buildings, corrugated iron roofs, 35 pounds.

e High Buildings, built up districts, 35 pounds; 14 stories or over, 25 pounds at tenth story, 2½ pounds less each story below.

Figures for manufacturing establishments do not include machinery.

## FLOOR CONSTRUCTION

**Reduced Live Loads.** Floor beams in buildings should be computed to sustain floor by floor the full live and dead loads. It is not probable that all the floors will be fully loaded at all times, and, therefore, good practice permits a reduction of the theoretical live load in the computations of column sections. The New York and Pittsburgh building laws do not permit any reduction on columns supporting the roof and top floor. These building laws permit for buildings more than five stories in height on columns supporting each succeeding floor a reduction of 5 per cent of the total live floor load until 50 per cent is reached, which reduced load is to be used for the columns supporting the remaining floors. Pittsburgh building law, however, does not permit any reduction of live floor loads over 150 pounds per square foot (bulk storage). The Chicago building law requires columns to sustain the full live load on roofs, 85 per cent of the full live floor load on the top floor with a .5 per cent reduction on each succeeding floor down to 50 per cent.

When the character of the loading will permit, it is also considered good practice to reduce the live load on the main girders to which the primary supporting beams are framed. The amount of the reduction will depend on the probable distribution of the loads.

**Foundation Loads.** Footings should be so designed that the loads they sustain per unit of area shall be as nearly uniform as possible, and the dead loads carried by the footings should include the actual weight of the superstructure and foundations down to the bottom of the footing. The live load should be assumed to be the same as the live load in the lowest tier of columns or in the footings under walls. According to the proposed New York building law, the area of the footing which has the largest percentage of live load to total load shall be determined by dividing the total load by the unit working stress. From the area thus calculated all the other footings of the building shall be proportioned according to the ratios of their respective dead loads only. In no case shall the load per square foot under any portion of any footing due to the combined dead, live, and wind loads, exceed the safe sustaining power of the soil upon which the footing rests.

**Fireproof Floor Systems.** A modern office or mercantile building is essentially a steel framed structure which supports the dead load of the building and its contents and is itself protected on all sides by refractory materials. The floors are made fireproof by the use of terra cotta tiles or arches or of a composite flooring made of concrete or reinforced concrete. While brick arches may still be used in special locations where great floor strength is needed, and concrete arches are sometimes thrown between the beams,

## CARNEGIE STEEL COMPANY

modern practice is limited substantially to the hollow tile arch sprung between the beams and the reinforced concrete slab laid on their tops, the ceiling construction being modified to suit. Each system has advantages of its own.

**Terra Cotta Arches.** Hollow tile arches fill the total depth of the floor beams, and, therefore, tend to stiffen and brace the building; their weight per square foot is light as compared with other forms of fireproof floor construction of equal strength. Hollow terra cotta floor arches are made either flat or segmental. The segmental arch will develop much greater strength than the flat arch of the same width and depth, and may be designed to carry a given load with tile of less depth than flat arches. They are, therefore, more economical, though not always acceptable from the standpoint of architectural appearance. In office buildings the ceilings under such arches are usually suspended. A correctly designed and constructed flat arch will always develop the full strength of the steel beam which supports it.

When arch blocks are the same depth as the beams, they are usually laid to project  $1\frac{1}{2}$  inches below the bottom of the beams, and the space above the arch is filled in either with cinder concrete, in which can be laid pipes, conduits, and wooden nailing strips supporting wood flooring, or with thin terra cotta blocks made for this purpose, or with a layer of plastic composition of cement, which forms the wearing surface for the floor.

**Thrust of Floor Arches.** All forms of terra cotta arches produce side thrust on the floor beams. In the flat arch the blocks have tapered faces and the central block or key wedges the others together; in the segmental arch the thrust is that due to all arch action. These thrusts it is found necessary to counterbalance by means of tie rods which connect the floor beams and relieve them from the tendency to deflect sidewise. In the central bays, owing to the action of adjacent arches, the tie rods are sometimes omitted, but it is necessary to investigate outer beams and channels around openings for additional thrust stresses so that the combined fiber stresses produced by vertical loading and horizontal thrusts may not be excessive. With flat arches  $\frac{3}{4}$  inch tie rods spaced apart not over fifteen times the width of the beam flanges will usually be sufficient. The total thrust of arch, the net area of tie rods required, the maximum distance between tie rods and the section of outer beams for any condition, may be found as follows:

## FLOOR CONSTRUCTION

Let

- $w$  =load on arch, in pounds per square foot.  
 $L$  =span of arch, in feet.  
 $L_b$  =length of floor beam supporting the arch, in feet.  
 $R$  =effective rise of arch, in inches.  
 $p$  =thrust of arch per lineal foot, in pounds.  
 $P$  =total thrust of arch per panel, in pounds.  
 $A$  =total net area of tie rods per panel, in square inches.  
 $a$  =net area of one tie rod, in square inches.  
 $L_s$  =spacing of tie rods, center to center, in feet.  
 $f$  =allowable combined fiber stress not to exceed 16,000 pounds per square inch.

$S_{1-1}$  =Section Modulus of beam, axis 1-1, in inches<sup>3</sup>.

$S_{2-2}$  =Section Modulus of beam, axis 2-2, in inches<sup>3</sup>.

$M_{1-1}$  =Bending Moment due to vertical loading, inch pounds.

$M_{2-2}$  =Bending Moment due to arch thrust, inch pounds; then,

$$p = \frac{3wL^2}{2R} \qquad P = \frac{3wL^2L_b}{2R}$$

$$A = \frac{3wL^2L_b}{2fR} = \frac{wL^2L_b}{10667R}$$

$$L_s = \frac{2fAR}{3wL^2} = \frac{10667aR}{wL^2}$$

$$M_{1-1} = \frac{(\frac{1}{2}wL L_b) L_b L^2}{8} = \frac{3w L_b^3}{4}$$

$$M_{2-2} = \frac{(pL_s) L_s L^2}{12} = pL_s^2$$

$$f = \frac{M_{1-1}}{S_{1-1}} + \frac{M_{2-2}}{S_{2-2}}$$

In the formula given for  $M_{2-2}$ , the beam is considered continuous and supported at intervals by the tie rods. In segmental arches the effective rise is equal to the vertical distance between the highest point of the concave surface and the springing line or chord; the effective rise of a flat arch may be taken at 2.4 inches less than the arch depth.

The net areas of the usual size tie rods are as follows:—

Diameter of Rod, Inches	$\frac{3}{8}$	$\frac{1}{2}$	$\frac{5}{8}$	1
Net area, a, square inches. ....	0.202	0.302	0.420	0.550

# CARNEGIE STEEL COMPANY

**EXAMPLE.**—A floor panel 18 feet by 6 feet, made of 12 inch flat terra cotta blocks, is to support a uniform load, live and dead, of 150 pounds per square foot. Required the total thrust, total area of rods per panel, maximum spacing of rods, and the proper size beam to carry one-half of the panel without other lateral support than the tie rods.

Entire panel load is  $18 \times 6 \times 150 = 16,200$  pounds. Assume a 12 inch 31.5 pound beam and  $\frac{3}{4}$  inch tie rods, then we have—

$$\text{Thrust of arch per lineal foot, } p = \frac{3 \times 150 \times 6 \times 6}{2(12 - 2.4)} = 840 \text{ pounds.}$$

$$\text{Total thrust of arch, } P = \frac{3 \times 150 \times 6 \times 6 \times 18}{2(12 - 2.4)} = 15,200 \text{ pounds.}$$

$$\text{Total area of tie rods, } A = \frac{150 \times 6 \times 6 \times 18}{10,667(12 - 2.4)} = 0.95 \text{ square inches.}$$

$$\text{Maximum spacing of tie rods, } L_s = \frac{10667 \times .302 \times (12 - 2.4)}{150 \times 6 \times 6} = 5.73 \text{ feet.}$$

$$\text{Bending Moment, vertical loading, } M_{1-1} = \frac{6 \times 18 \times 150 \times 18 \times 12}{8 \times 2} = 218,700 \text{ in. lbs.}$$

$$\text{Bending Moment, horizontal thrust, } M_{2-2} = \frac{840 \times 5.73 \times 5.73 \times 12}{12} = 27,580 \text{ in. lbs.}$$

$$\text{Combined fiber stress, } f = \frac{218,700}{36} + \frac{27,580}{3.8} = 13,330 \text{ pounds per square inch.}$$

If tie rods are spaced 6' 0" centers, then the

$$\text{Bending Moment, horizontal thrust, } M_{2-2} = 840 \times 6 \times 6 = 30,240 \text{ inch pounds.}$$

$$\text{Combined fiber stress, } f = \frac{218,700}{36} + \frac{30,240}{3.8} = 14,030 \text{ pounds per square inch.}$$

When used, tie rods should be placed in the line of thrust if possible, usually 3 inches above the bottom of the beam.

## MAXIMUM SPACING OF $\frac{3}{4}$ INCH TIE RODS, LOADS OF 100 POUNDS PER SQUARE FOOT

Span, Feet	Effective Rise of Arch, R, in Inches											
	4	5	6	7	8	9	10	11	12	13	14	15
3	14.3											
4	8.1	10.1	12.1	14.1								
5	5.2	6.4	7.7	9.0	10.3	11.6	12.9	14.2				
6	3.6	4.5	5.4	6.3	7.2	8.1	8.9	9.8	10.7	11.6	12.5	13.4
7		3.3	3.9	4.6	5.3	5.9	6.6	7.2	7.9	8.5	9.2	9.9
8			3.0	3.5	4.0	4.5	5.0	5.5	6.0	6.5	7.0	7.6
9					3.2	3.6	4.0	4.4	4.8	5.2	5.6	6.0
10							3.2	3.5	3.9	4.3	4.5	4.8

For any other loading, multiply tabular values by 100 and divide by total new load per square foot.

The tables which follow give the weights per square foot for terra cotta arches, both flat and segmental, of various depths, their area in square inches, and the safe loads they will sustain on various spans. These tables should be used as a general guide only, as conditions may make it possible to design more economical arches for a given load than indicated by the tables. Where a paneled ceiling is not objectionable, for example, a shallow arch may be used on raised skewbacks with a considerable economy in material.

## FLOOR CONSTRUCTION

### FLAT TERRA COTTA ARCHES MANUFACTURERS' STANDARD SAFE LOADS IN POUNDS PER SQUARE FOOT Factor of Safety = 7

Span of Arch, Ft.-In.	Depth of Arch Blocks, Inches					
	6	7	8	9	10	12
	Area of Arch Blocks, Square Inches					
	31	34	37	40	43	49
3-0	458	588	735	901	1084	1487
3-3	386	496	622	763	916	1262
3-6	330	424	531	653	785	1083
3-9	284	365	459	565	679	938
4-0	247	318	399	493	593	820
4-3	216	278	350	433	521	722
4-6	190	245	309	382	461	640
4-9	168	217	274	340	410	571
5-0	149	193	244	304	367	511
5-3		172	218	272	330	460
5-6		154	196	245	297	416
5-9		139	176	222	269	378
6-0			159	201	244	344
6-3			144	183	222	314
6-6			131	166	203	287
6-9				152	186	264
7-0				139	170	243
7-6					144	206
8-0						177
8-6						153
9-0						132
9-6						
10-0						

This table and the two following are employed in computing the safe loads of floor arches of hollow terra cotta blocks. The area given is that of a cross section at right angles to the webs, and, generally, end-construction blocks of various shapes but of the same depth and cross-sectional area have equal strength.

The weight of the terra cotta arch has been deducted from the safe load given in the tables, so that only the dead load of the concrete fill, plastering, etc., must be deducted to obtain the net safe live load for any arch and span; blocks of different areas and for other factors of safety are calculated as follows:

**EXAMPLE.**—Required the load per square foot for a 5'-6" span and 8 inch arch blocks with three horizontal and four vertical webs,  $\frac{3}{4}$  inch thick, set in end construction, cross-section through webs of blocks parallel to webs of beams.

Sectional area of the blocks is  $8'' \times \frac{3}{4}'' \times 4 + (12'' - 4 \times \frac{3}{4}'' ) \times \frac{3}{4}'' \times 3 = 44.25$  sq. in. at 0.06 pounds per cu. in., the weight is  $44.25 \times 12 \times 0.06 = 32$  pounds.

The net safe load of the 8 inch block given in the table is 196 pounds. Adding the weight of the block,  $37 \times 12 \times 0.06 = 26$  pounds, the total safe load is 222 pounds. The net safe load for blocks with an area of 44.25 sq. in. and a safety factor of 5 is  $(44.25 + 37 \times 12 \times 0.06) \div 5 = 340$  pounds per sq. ft.



# CARNEGIE STEEL COMPANY

## SEGMENTAL TERRA COTTA ARCHES

MANUFACTURERS' STANDARD

SAFE LOADS IN POUNDS PER SQUARE FOOT

Factor of Safety=7

Span of Arch, Ft.-In.	Rise of Arch, In.	Depth of Arch Blocks, Inches				Span of Arch, Ft.-In.	Rise of Arch, In.	Depth of Arch Blocks, Inches			
		4	6	8	10			4	6	8	10
		Area of Arch Blocks, Sq. Inches						Area of Arch Blocks, Sq. Inches			
		28	36	43	47			28	36	43	47
4-0	$\frac{3}{4}$	702	902	1078	1178	7-6	$\frac{3}{4}$	366	471	563	615
	1	920	1184	1414	1545		1	482	621	741	810
	$1\frac{1}{4}$	1155	1485	1774	1939		$1\frac{1}{4}$	602	774	925	1011
	$1\frac{1}{2}$	1353	1740	2079	2272		$1\frac{1}{2}$	715	920	1099	1201
	$1\frac{3}{4}$	1545	1986	2373	2593		$1\frac{3}{4}$	815	1049	1253	1369
	2	1736	2233	2667	2915	2	915	1176	1405	1536	
4-6	$\frac{3}{4}$	616	792	946	1034	8-0	$\frac{3}{4}$	341	439	525	573
	1	812	1044	1247	1363		1	457	588	703	768
	$1\frac{1}{4}$	1020	1313	1568	1713		$1\frac{1}{4}$	562	724	864	944
	$1\frac{1}{2}$	1196	1539	1838	2009		$1\frac{1}{2}$	668	859	1026	1122
	$1\frac{3}{4}$	1381	1775	2121	2318		$1\frac{3}{4}$	767	987	1179	1288
	2	1536	1975	2350	2578	2	854	1099	1312	1434	
5-0	$\frac{3}{4}$	551	709	847	926	8-6	$\frac{3}{4}$	319	411	491	536
	1	744	957	1143	1249		1	428	551	658	719
	$1\frac{1}{4}$	911	1172	1400	1530		$1\frac{1}{4}$	527	678	810	885
	$1\frac{1}{2}$	1072	1379	1647	1800		$1\frac{1}{2}$	626	806	963	1052
	$1\frac{3}{4}$	1238	1592	1902	2078		$1\frac{3}{4}$	719	926	1106	1208
	2	1379	1773	2118	2315	2	807	1037	1239	1354	
5-6	$\frac{3}{4}$	499	641	766	837	9-0	$\frac{3}{4}$	300	386	461	504
	1	672	864	1032	1128		1	403	518	619	677
	$1\frac{1}{4}$	826	1062	1269	1387		$1\frac{1}{4}$	501	645	770	842
	$1\frac{1}{2}$	984	1266	1512	1652		$1\frac{1}{2}$	590	758	906	990
	$1\frac{3}{4}$	1119	1439	1719	1879		$1\frac{3}{4}$	677	871	1041	1137
	2	1258	1619	1933	2113	2	759	977	1167	1275	
6-0	$\frac{3}{4}$	455	585	699	764	9-6	$\frac{3}{4}$	283	364	435	475
	1	612	788	941	1028		1	380	480	584	638
	$1\frac{1}{4}$	753	969	1157	1265		$1\frac{1}{4}$	472	608	726	793
	$1\frac{1}{2}$	898	1154	1379	1507		$1\frac{1}{2}$	561	721	862	942
	$1\frac{3}{4}$	1022	1315	1570	1716		$1\frac{3}{4}$	639	823	983	1074
	2	1148	1476	1763	1927	2	717	923	1102	1204	
6-6	$\frac{3}{4}$	428	551	658	719	10-0	$\frac{3}{4}$	267	344	411	449
	1	562	724	864	944		1	359	462	552	603
	$1\frac{1}{4}$	701	902	1077	1177		$1\frac{1}{4}$	447	576	688	751
	$1\frac{1}{2}$	823	1058	1264	1382		$1\frac{1}{2}$	531	683	816	892
	$1\frac{3}{4}$	947	1218	1455	1590		$1\frac{3}{4}$	610	784	937	1024
	2	1055	1358	1622	1772	2	683	879	1050	1147	
7-0	$\frac{3}{4}$	304	508	606	662	10-6	$\frac{3}{4}$	251	330	394	429
	1	520	669	799	873		1	342	442	528	577
	$1\frac{1}{4}$	648	834	996	1089		$1\frac{1}{4}$	426	547	655	717
	$1\frac{1}{2}$	762	981	1171	1280		$1\frac{1}{2}$	504	646	776	849
	$1\frac{3}{4}$	876	1127	1346	1471		$1\frac{3}{4}$	581	749	891	974
	2	983	1264	1510	1650	2	650	837	1000	1092	


# FLOOR CONSTRUCTION

## SEGMENTAL TERRA COTTA ARCHES—CONCLUDED


Span of Arch, Ft.-In.	Rise of Arch, In.	Depth of Arch Blocks, Inches				Span of Arch, Ft.-In.	Rise of Arch, In.	Depth of Arch Blocks, Inches			
		4	6	8	10			4	6	8	10
		Area of Arch Blocks, Sq. Inches						Area of Arch Blocks, Sq. Inches			
		28	36	43	47			28	36	43	47
11-0	$\frac{3}{4}$	244	315	376	411	17-0	$\frac{3}{4}$	151	194	232	254
	1	327	421	503	550		1	205	265	316	345
	$1\frac{1}{4}$	404	519	621	678		$1\frac{1}{4}$	256	330	394	430
	$1\frac{1}{2}$	479	617	737	805		$1\frac{1}{2}$	304	392	468	512
	$1\frac{3}{4}$	551	709	847	925		$1\frac{3}{4}$	351	452	540	590
11-6	2	617	794	948	1036	18-0	2	393	506	605	661
	$\frac{3}{4}$	233	299	358	391		$\frac{3}{4}$	141	182	218	238
	1	312	401	480	524		1	192	248	296	324
	$1\frac{1}{4}$	388	499	596	652		$1\frac{1}{4}$	240	310	370	404
	$1\frac{1}{2}$	460	592	707	773		$1\frac{1}{2}$	287	370	442	482
12-0	$1\frac{3}{4}$	528	680	812	887	19-0	$1\frac{3}{4}$	330	425	507	554
	2	591	761	909	993		2	371	477	570	623
	$\frac{3}{4}$	222	285	341	372		$\frac{3}{4}$	134	173	206	225
	1	297	383	458	500		1	181	233	270	304
	$1\frac{1}{4}$	370	477	569	622		$1\frac{1}{4}$	227	293	350	382
12-6	$1\frac{1}{2}$	439	566	676	738	20-0	$1\frac{1}{2}$	271	348	416	455
	$1\frac{3}{4}$	505	649	776	848		$1\frac{3}{4}$	312	402	480	524
	2	565	727	869	949		2	351	451	539	589
	$\frac{3}{4}$	212	273	326	356		$\frac{3}{4}$	126	163	194	212
	1	284	366	437	478		1	172	221	265	289
13-0	$1\frac{1}{4}$	354	456	545	595	21-0	$1\frac{1}{4}$	215	277	331	361
	$1\frac{1}{2}$	420	541	646	706		$1\frac{1}{2}$	257	330	395	431
	$1\frac{3}{4}$	483	621	742	811		$1\frac{3}{4}$	296	381	455	497
	2	541	696	832	909		2	332	427	510	558
	$\frac{3}{4}$	203	261	312	341		22-0	$\frac{3}{4}$	119	153	183
14-0	1	272	351	419	458	1		163	209	250	273
	$1\frac{1}{4}$	339	437	522	570	$1\frac{1}{4}$		205	263	315	344
	$1\frac{1}{2}$	403	519	620	677	$1\frac{1}{2}$		243	314	375	409
	$1\frac{3}{4}$	463	596	712	778	$1\frac{3}{4}$		281	361	432	472
14-6	2	521	670	801	875	23-0	2	315	406	485	530
	$\frac{3}{4}$	186	240	287	313		$\frac{3}{4}$	113	145	174	190
	1	253	326	390	426		1	154	199	237	259
	$1\frac{1}{4}$	315	406	485	530		$1\frac{1}{4}$	194	250	298	326
	$1\frac{1}{2}$	374	482	575	629		$1\frac{1}{2}$	232	299	357	399
15-0	$1\frac{3}{4}$	430	553	661	722	24-0	$1\frac{3}{4}$	268	344	412	450
	2	481	619	740	808		2	301	377	462	505
	$\frac{3}{4}$	174	225	268	293		$\frac{3}{4}$	108	139	166	181
	1	234	302	361	394		1	147	190	227	247
	$1\frac{1}{4}$	292	377	450	491		$1\frac{1}{4}$	185	238	284	310
16-0	$1\frac{1}{2}$	347	447	534	583	24-0	$1\frac{1}{2}$	221	284	340	371
	$1\frac{3}{4}$	401	515	616	673		$1\frac{3}{4}$	255	328	392	428
	2	449	577	690	754		2	286	369	440	481
	$\frac{3}{4}$	162	209	249	272		$\frac{3}{4}$	102	132	157	172
	1	218	281	336	367		1	140	181	216	236
16-0	$1\frac{1}{4}$	274	353	421	460	24-0	$1\frac{1}{4}$	177	227	272	297
	$1\frac{1}{2}$	325	419	500	546		$1\frac{1}{2}$	211	272	325	355
	$1\frac{3}{4}$	374	481	575	628		$1\frac{3}{4}$	244	314	375	410
	2	420	540	645	705		2	274	353	421	460

# CARNEGIE STEEL COMPANY

## TERRA COTTA ARCHES For Floor Load of 150 Pounds per Square Foot

	Depth of Beam, Inches	Depth of Arch Blocks, Inches	Depth of Arch, Inches	Span of Arch, Feet	Approx. Weight, Lbs. per Sq. Ft.					
					Steel	Terra Cotta	Concrete	Flooring	Ceiling	Total
	6	6	11	5 1/4	6	22	30	4	5	67
	7	6	12	5 1/4	7	22	38	4	5	70
	8	6	13	5 1/4	8	22	45	4	5	84
	7	7	12	6	8	24	30	4	5	71
	8	7	13	6	8	24	38	4	5	79
	9	7	14	6	8	24	45	4	5	86
	8	8	13	6 1/2	8	27	30	4	5	74
	9	8	14	6 1/2	8	27	38	4	5	82
	10	8	15	6 1/2	8	27	45	4	5	89
	9	9	14	7 1/2	8	29	30	4	5	76
	10	9	15	7 1/2	9	29	38	4	5	85
	12	9	17	7 1/2	9	29	53	4	5	100
	10	10	15	8	9	31	30	4	5	79
	12	10	17	8	9	31	45	4	5	94
	12	12	17	9 1/2	10	35	30	4	5	84
	15	12	20	9 1/2	10	35	53	4	5	107
	15	15	20	11	12	42	30	4	5	93

For flat arches on raised skews, where the top of the arch is level with the top of the floor beam, deduct about 7 pounds per inch of difference between the height of the floor beam and the arch.

	Depth of Beam, Inches	Depth of Arch Blocks, Inches	Rise of Arch, Inches	Span of Arch, Feet	Approx. Weight, Lbs. per Sq. Ft.					
					Steel	Terra Cotta	Concrete	Flooring	Ceiling	Total
	6	4	3/4	4 1/2	7	20	27	4	5	63
	7	4	1	5	7	20	28	4	5	64
	8	4	1 1/4	5 1/2	7	20	29	4	5	65
	9	4	1 1/2	6	8	20	30	4	5	67
	8	6	3/4	5	8	26	27	4	5	70
	9	6	1	5 1/2	8	26	28	4	5	71
	10	6	1 1/4	6	9	26	29	4	5	73
	12	6	1 1/2	6 1/2	9	26	30	4	5	74
	10	8	3/4	5 1/2	9	31	27	4	5	76
	12	8	1	6	9	31	28	4	5	77
	12	8	1 1/4	6 1/2	10	31	29	4	5	79
	15	8	1 1/2	7	10	31	30	4	5	80
	12	10	3/4	5 1/2	10	34	27	4	5	80
	12	10	1	6 1/2	11	34	28	4	5	82
	15	10	1 1/4	7	11	34	29	4	5	83
	15	10	1 1/2	7 1/2	12	34	30	4	5	85

## TERRA COTTA PARTITION, CEILING, ROOFING AND FURRING BLOCKS

Thick-ness, Inches	Approx. Weight, Pounds per Sq. Foot				Thick-ness, Inches	Approx. Weight, Pounds per Sq. Foot			
	Partition	Ceiling	Roofing	Furring		Partition	Ceiling	Roofing	Furring
1 1/2				9	4	16-18		22	
2	12-14	12		10	5	18-20			
3	15-17	20	20		6	24-26			

## FLOOR CONSTRUCTION

### REINFORCED CONCRETE BEAMS AND FLOOR SLABS

To give a complete mathematical analysis of the stresses which occur in reinforced concrete structures is not within the scope of this book. For such an analysis reference may be made to standard text books on the theory and practice of reinforced concrete.

**Girders and Floor Beams.** The arrangement of girders and floor beams follows the same principles as in structural steel construction. On short spans floor cross beams may be omitted or used only at columns to secure lateral stiffness. Beams are usually designed as tee beams, and thereby a part of the floor slab is utilized as a part of the beam. The width of the slab thus considered to act as part of the beam should not exceed five times the slab thickness.

**Floor Slabs.** Reinforcement may be of small rods, wires or metal fabric, the latter especially on short spans. Cross reinforcement of small rods or wires about two feet apart laid parallel to the beam supporting the slab should be used to prevent cracks, shrinkage, etc. If the length of the slab exceeds  $1\frac{1}{2}$  times its width, the entire load should be carried by transverse reinforcement. The distribution of the load on a rectangular slab supported on four sides and reinforced in both directions may be approximately determined by the formula  $R = l^4 + (l^4 + b^4)$ , where  $R$  is the ratio of the load,  $l$  the length and  $b$  the width of the slab. An effective bond should be provided at the junction of beam and slab, and if the principal reinforcement of the slab is parallel to the beam, transverse reinforcement should be used extending over the beam and well into the slab.

**Spacing of Reinforcing Bars.** The lateral spacing of parallel bars should not be less than  $2\frac{1}{2}$  diameters, nor should the clear vertical space between layers of bars be less than  $\frac{1}{2}$  inch. The distance from the edge or side of the beam or slab should not be less than two diameters.

**Shear or Web Reinforcement.** In the calculation of web reinforcement, concrete may be assumed to carry  $\frac{1}{4}$  to  $\frac{1}{3}$  of the total shear; the remainder to be taken by additional reinforcement arranged in intervals equal to the depth of the beam. The usual method of reinforcing beams against failure by diagonal tension or shear is to use bent rods or stirrups in either vertical or inclined position. The longitudinal spacing of such rods or stirrups should not exceed  $\frac{3}{4}$  of the depth of the beam.

**Formulas.** The following formulas are those approved by the Committee of the American Society of Civil Engineers on Concrete and Reinforced Concrete (Proceedings, Vol. XXXIX—No. 2, February, 1913.)

# CARNEGIE STEEL COMPANY

## REINFORCED CONCRETE BEAMS—NOTATION

### Rectangular Beams, Reinforcement for Tension only.

- $f_s$  = Tensile unit stress in steel, in pounds per sq. inch.
- $f_c$  = Compressive unit stress in concrete, in pounds per sq. inch.
- $E_s$  = Modulus of elasticity of steel, in pounds per sq. inch.
- $E_c$  = Modulus of elasticity of concrete, in pounds per sq. inch.
- $n$  = Elasticity ratio,  $E_s \div E_c$ .
- $M$  = Bending moment, in inch pounds.
- $M_s$  = Moment of resistance of steel, in inch pounds.
- $M_c$  = Moment of resistance of concrete, in inch pounds.
- $A$  = Area of steel section, in square inches.
- $b$  = Width of beam, in inches.
- $d$  = Depth of beam to center of steel reinforcement, in inches.
- $k$  = Ratio of depth of neutral axis to effective depth,  $d$ .
- $j$  = Ratio of lever arm of resisting couple to depth,  $d$ .
- $z$  = Distance, top to resultant of compression, in inches.
- $jd$  = Arm of resisting couple, in inches  $= d - z$ .
- $p$  = Ratio of steel area to area of rectangle,  $bd$ ,  $= A \div bd$ .
- $kd$  = Distance from top of beam to neutral axis, in inches.

### Tee Beams.

- $b$  = Width of flange, in inches.
- $b'$  = Width of stem, in inches.
- $t$  = Thickness of flange, in inches.
- $p$  = Ratio of steel area to area of rectangle,  $bd$ ,  $= A \div bd$ .

### Rectangular Beams, Reinforced for Compression.

- $A'$  = Area of compressive steel, in square inches.
- $p'$  = Steel ratio for compressive steel.
- $f'_s$  = Unit compressive stress in steel, in pounds per sq. inch.
- $C$  = Total compressive stress in concrete, in pounds per sq. inch.
- $C'$  = Total compressive stress in steel, in pounds per sq. inch.
- $d'$  = Depth to center of compressive steel, in inches.
- $z$  = Depth to resultant of  $C + C'$ , in inches.


### Shear and Bond.

- $V$  = Total shear, in pounds.
- $f_v$  = Unit shearing stress in concrete, in pounds per sq. inch.
- $f_u$  = Unit bonding stress in concrete, in pounds per sq. inch.
- $\Sigma_o$  = Sum of the perimeters of the tension bars.

## FLOOR CONSTRUCTION

### REINFORCED CONCRETE BEAMS—FORMULAS

#### Rectangular Beams, Reinforced for Tension only.



$$kd = d \left[ \sqrt{2pn + (pn)^2} - pn \right]$$

$$z = \frac{1}{2}kd$$

$$M_s = f_s A_j d = f_s p j b d^2$$


$$M_c = f_c k j b d^2$$

$$f_s = \frac{M}{A_j d} = \frac{M}{p j b d^2}$$

$$f_c = \frac{2M}{j k b d^2} = \frac{2p f_s}{k}$$

$$\text{Steel ratio, balanced reinforcement, } p = \frac{1}{2} \left[ \frac{f_s}{f_c} \left( \frac{f_s}{n f_c} + 1 \right) \right]$$

#### Tee Beams.

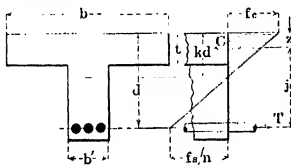

$$kd = \frac{2ndA + bt^2}{2nA + 2bt}$$

Neutral axis in flange—  
use formulas for rectangular beams.

Neutral axis in stem—

$$z = \frac{t(3kd - 2t)}{3(2kd - t)}$$


$$M_s = f_s A_j d$$

$$M_c = \frac{f_c b t (kd - \frac{1}{2}t) j d}{kd}$$

$$f_s = \frac{M}{A_j d} = \frac{f_c n(1-k)}{k}$$

$$f_c = \frac{M k d}{b t (kd - \frac{1}{2}t) j d}$$

#### Rectangular Beams, Reinforced for Compression.

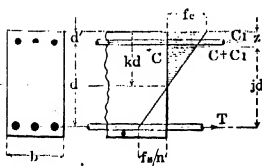

$$kd = d \left[ \sqrt{2n(p + p' \frac{d'}{d}) + n^2(p + p')^2} - n(p + p') \right]$$

$$z = \frac{\frac{1}{2}k^2 d + 2p' n d' (k - \frac{d'}{d})}{k^2 + 2p' n (k - \frac{d'}{d})}$$

$$f_s = \frac{M}{p j b d^2} = \frac{n f_c (1-k)}{k}$$

$$f_s' = \frac{n f_c (k - \frac{d'}{d})}{k}$$

$$f_c = \frac{6M}{b d^2 \left[ 3k - k^2 + \frac{6p' n}{k} (k - \frac{d'}{d}) (1 - \frac{d'}{d}) \right]}$$

#### Shear and Bond.

##### Rectangular Beams

$$f_v = \frac{V}{b j d}$$

$$f_u = \frac{V}{j d \sum o}$$

##### T Beams

$$f_v = \frac{V}{b' j d}$$

$$f_u = \frac{V}{j d \sum o}$$

# CARNEGIE STEEL COMPANY

The formulas are based upon the following assumptions:

1. The applied forces are perpendicular to the neutral plane.
2. The deformation of any fiber is proportional to its distance from the neutral axis.
3. The resisting moment of the beam is the sum of the moments above the neutral axis, due to the concrete area in compression, and of those below the neutral axis, due to the steel area in tension.
4. The tensile strength of the concrete is negligible.

**Bending Moments.** If slabs and girders are reinforced over supports to take care of negative bending moments, they act as continuous beams, and the bending moment at the center of the span will be reduced. It is considered good practice to use the following values:

Floor slabs,  $M$  at center and at supports  $= \frac{1}{12} w l^2$ .

Beams,  $M$  at center and at supports  $= \frac{1}{12} w l^2$  for interior spans, and  $\frac{1}{10} w l^2$  for end spans.

If beams are freely supported at ends,  $M = \frac{1}{8} w l^2$ .

**Columns.** Columns may be reinforced by means of longitudinal bars, by bands or hoops, or by both. The general effect of the banding or hooping is to permit the use of somewhat higher working stresses; the value  $p$ , given in the formula which follows, refers to longitudinal steel reinforcement only:

$P$  = total load on columns, in pounds.

$A_c$  = area of concrete, in square inches.

$A_s$  = area of steel, in square inches.

$f_k$  = unit compressive stress in steel, in pounds per sq. inch:

$P = f_c (A_c + n A_s) \quad f_k = n f_c$ .

**Working Stresses.** The following working stresses are in current use for reinforcing bars of medium structural steel and good Portland cement and gravel concrete of a 1:2:4 or 1:2½:5 mixture:

$f_c$  = unit compressive stress of concrete..... 650 lbs. per sq. in.

$f_v$  = unit shearing stress of concrete,

straight reinforcement..... 30 to 40 " " "

special shear reinforcement.... 60 to 100 " " "

$f_u$  = unit bond stress of concrete,

smooth rods..... 60 to 80 " " "

deformed bars..... 100 to 175 " " "

$f_s$  = unit tensile stress of steel..... 16,000 " " "

$f_k$  = unit compressive stress of steel.. 10,000 " " "

$n = E_s + E_c = 15$ .

For approximate calculations, the arm of the resisting couple,  $jd$ , may be taken at  $\frac{3}{4}d$ , and ordinarily accepted working stresses will not be exceeded if the steel ratio,  $p$ , does not exceed 0.01.

## FLOOR CONSTRUCTION

**Explanation of Tables.** Reinforced Concrete Slabs: The tables given on page 332 are based upon the preceding formulas for rectangular beams, and upon fiber stresses of 650 pounds per square inch for concrete, 20,000 pounds for steel wire reinforcement, and 16,000 pounds for steel bar or rod reinforcement.

The bending moments are given in foot pounds per foot of width; below and to the left of the zigzag lines the values are determined by the maximum allowable fiber stress on steel; above and to the right they are determined by the maximum allowable stresses in concrete.

The first column gives the total thickness of the slab, the second, the distance from the center of the steel to the bottom of the slab, and the third the approximate weight of concrete slabs one foot square.

**EXAMPLE.**—Required the reinforcement for a slab continuous at four sides and 5 inches thick to carry a superimposed load of 150 pounds per square foot over a clear span of 8 feet.

Assuming the weight of the concrete slab in pounds at twelve times the thickness of the slab in inches, then the weight of the slab per foot is  $12 \times 5 = 60$  pounds, and the total weight,  $W$ , for a span of 8 feet is  $(60 + 150) \times 8 = 1680$  pounds.

$$M = WL : 12 = 1680 \times 8 \div 12 = 1120 \text{ foot-pounds.}$$

If triangle mesh is used, the steel area required by upper table, page 332, computed for a 5 inch slab, is, by interpolation, 0.185 square inches, equivalent by table, page 333, to triangle mesh style number 41.

If medium structural steel bars or rods are used, the required area, by the lower table, page 332, is 0.24 square inches, and the sizes may be taken from page 118.



# CARNEGIE STEEL COMPANY

## REINFORCED CONCRETE SLABS

### BENDING MOMENTS IN FOOT POUNDS PER FOOT OF WIDTH

Allowable Fiber Stress: Steel, 20,000 and Concrete, 650 Pounds per Sq. Inch

$$E_s \div E_c = 15$$

Slab of 1 Sq. Ft.			Area of Steel Reinforcement in Square Inches per Foot of Width															
Thickness, Inches	Distance Between Reinforcing Bars, in.	Weight, Pounds	.04	.06	.08	.10	.12	.14	.16	.18	.20	.25	.30	.35	.40	.45	.50	
2 1/2	3 1/4	30	108	160	211	261	295	311	325	342	353	377	500					
3	3 1/4	36	110	207	273	338	404	468	499	520	538	574	599					
3 1/2	3 1/4	42	173	256	338	419	490	578	656	724	750	808	858	900				
4	3 1/4	48	205	304	401	498	594	689	783	876	969	1068	1135	1194	1245			
4 1/2	3 1/4	54	237	352	465	577	688	798	907	1015	1123	1354	1439	1516	1584	1644		
5	1	60		377	500	621	740	857	972	1087	1201	1486	1605	1690	1766	1834	1894	
5 1/2	1	66		421	560	697	832	963	1097	1228	1359	1682	1950	2056	2151	2236	2312	
6	1	72			624	777	928	1076	1222	1367	1512	1875	2234	2449	2563	2666	2700	
6 1/2	1	78			691	859	1025	1189	1352	1514	1675	2075	2469	2858	3002	3124	3235	
7	1	84				939	1120	1300	1479	1657	1833	2271	2703	3131	3466	3609	3741	
7 1/2	1 1/4	90				978	1168	1356	1543	1729	1913	2370	2821	3268	3711	3863	4005	
8	1 1/4	96					1260	1460	1670	1872	2072	2568	3057	3542	4023	4387	4556	
8 1/2	1 1/4	102					1358	1578	1797	2015	2231	2765	3292	3815	4334	4850	5122	
9	1 1/2	108						1637	1863	2088	2311	2864	3412	3953	4493	5026	5410	
9 1/2	1 1/2	114						1749	1990	2231	2471	3063	3649	4230	4806	5378	5945	
10	1 1/2	120							2110	2375	2630	3261	3886	4506	5129	5730	6335	

Allowable Fiber Stress: Steel, 16,000 and Concrete, 650 Pounds per Sq. Inch

$$E_s \div E_c = 15$$


Slab of 1 Sq. Ft.			Area of Steel Reinforcement in Square Inches per Foot of Width													
Thickness, Inches	Distance, in. Inches	Weight, Pounds	.10	.20	.30	.40	.50	.60	.70	.80	.90	1.00	1.10	1.25	1.50	
2½	3	30	209	353												
3	3	36	272	525	599											
3½	3	42	335	650	858											
4	3½	48	398	775	1135	1245										
4½	3½	54	461	900	1235	1584										
5	1	60	497	961	1412	1766	1894									
5½	1	66	558	1087	1600	2101	2312									
6	1	72	621	1213	1787	2349	2700	2922								
6½	1	78	686	1340	1975	2596	3205	3431								
7	1	84	751	1466	2162	2844	3515	3974	4173							
7½	1½	90	783	1531	2257	2969	3669	4254	4465							
8	1½	96		1658	2446	3218	3977	4728	5097	5309	5494	5674				
8½	1½	102		1785	2634	3467	4288	5099	5734	5982	6206	6410				
9	1½	108		1849	2730	3594	4444	5283	6069	6338	6574	6790				
9½	1½	114		1977	2919	3845	4757	5656	6543	7063	7330	7575				
10	1½	120		2104	3109	4096	5068	6027	6974	7826	8120	8392				
10½	1½	126			3205	4222	5224	6213	7192	8163	8528	8817	9079	9432	9939	
11	1½	132			3395	4475	5537	6588	7625	8652	9359	9981	10722	10898	11337	
11½	1½	138			3586	4726	5850	6960	8035	9145	10224	10875	10898	11337	11969	
12	2	144			3681	4852	6007	7148	8276	9393	10600	11037	11376	11858	12494	

Concrete mixture 1:2:4 or 1:2 1/2:5 carefully graded.

## FLOOR CONSTRUCTION

### TRIANGLE MESH CONCRETE REINFORCEMENT

AMERICAN STEEL AND WIRE COMPANY STANDARD

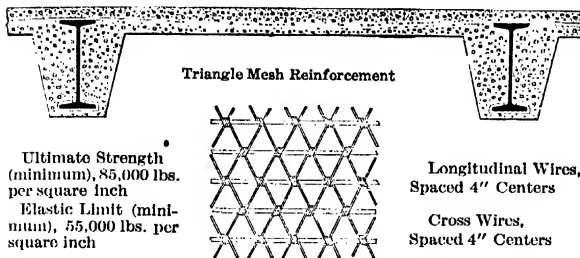

Triangle Mesh is a woven fabric of cold drawn steel wire, providing a continuous reinforcement, an even distribution of metal, and a perfect bond.

Made with both single and stranded tension members in lengths up to 300 feet and in widths up to 58 inches.

#### TRIANGLE MESH—STYLES, AREAS, AND WEIGHTS


Style Number	Longitudinal Wires			Cross Wires		Total Area for One Foot Width, Sq. In.	Approximate Weight of 100 Sq. Ft., Pounds
	Number in Each	A. S. & W. Co. Gage No.	Area per Foot, Sq. In.	A. S. & W. Co. Gage No.	Area per Foot, Sq. In.		
* 1	1	6	.087	14	.025	.102	43
5	1	8	.062	14	.025	.077	34
6	1	10	.043	14	.025	.058	27
* 7	1	12	.026	14	.025	.041	21
*23	1	1/4"	.147	12 1/2	.038	.170	72
24	1	4	.119	12 1/2	.038	.142	62
25	1	5	.101	12 1/2	.038	.124	55
*26	1	6	.087	12 1/2	.038	.110	50
*27	1	8	.062	12 1/2	.038	.085	41
28	1	10	.043	12 1/2	.038	.066	34
29	1	12	.026	12 1/2	.038	.049	28
31	2	4	.238	12 1/2	.038	.261	106
32	2	5	.202	12 1/2	.038	.225	92
33	2	6	.174	12 1/2	.038	.196	82
34	2	8	.124	12 1/2	.038	.146	63
35	2	10	.086	12 1/2	.038	.109	50
36	2	12	.052	12 1/2	.038	.075	37
*38	3	4	.358	12 1/2	.038	.380	151
39	3	5	.303	12 1/2	.038	.325	130
40	3	6	.260	12 1/2	.038	.283	114
41	3	8	.185	12 1/2	.038	.208	87
*42	3	10	.129	12 1/2	.038	.151	66
43	3	12	.078	12 1/2	.038	.101	47

Rolls—Lengths: 150, 200 and 300 feet. Widths: 18, 22, 26, 30, 34, 38, 42, 46, 50, 54, and 58 inches.

Triangle Mesh is furnished either with or without galvanizing; unless otherwise specified material will be shipped not galvanized.

Styles marked \* are usually carried in stock by American Steel and Wire Company.

## BUCKLE PLATES

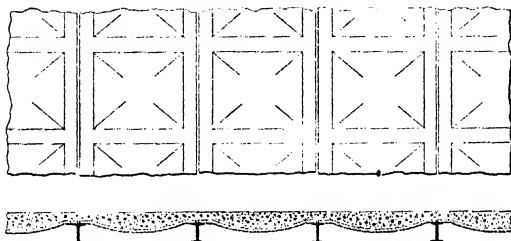

Buckle Plates, as generally used on highway bridges with paved floors, are subjected to a concentrated live load due to the weight of a wagon or truck wheel and to a uniform dead load due to the weight of the roadway paving.

Buckle Plates should be placed with the buckle turned down; then the live load which can be placed on a buckle in addition to the uniform dead load can be obtained from the following formula. Let:

$P$  = Total allowable concentrated load on buckle plate, in pounds.

$w$  = Uniform load, in pounds per square foot.

$d$  = Rise of buckle, in inches.

$l$  = Length of buckle, in inches.

$b$  = Width of buckle, in inches.

$t$  = Thickness of buckle plate, in inches,

$P = t \left( \frac{300 f d t - 0.525 w l b}{6 d + 15 t} \right)$  pounds, per buckle. •

The following table gives, for a fiber stress of 9000 pounds, the maximum concentrated live load in pounds allowed on buckles (turned down), in addition to a uniform load assumed to be the average weight of paving, etc., of 120 pounds per square foot.

Thickness of Buckle Plate, Inches	Rise, $d$ , in Inches			
	2	2½	3	3½
¼	20000	22000	22000	22500
⅜	30000	33000	34000	34000
½	41000	45000	47000	47500
¾	53000	58000	61000	63000

The total allowable uniformly distributed load which a buckle plate will safely support may be obtained from the formula:


$W = 12 f d t$  pounds, per buckle.

When the buckles are turned up, use one-third of above values.

# FLOOR PLATES

## BUCKLE PLATES

AMERICAN BRIDGE COMPANY STANDARD

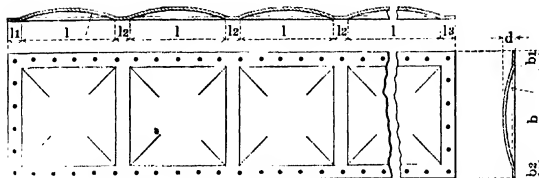

Die Number	Size of Buckle		Rise d <sub>1</sub> In.	Radii of Buckle		Number of Buckles in One Plate	Widths of Flanges and Fillets		
	Side l, Ft.-In.	Side b, Ft.-In.		Side l, Ft.-In.	Side b, Ft.-In.		End Flanges l <sub>1</sub> , l <sub>2</sub>	Fillets l <sub>2</sub>	Side Flanges b <sub>1</sub> , b <sub>2</sub>
1	3-11	4-6	3 1/2	6-8 3/8	8-0 7/8	1 to 8			
2	4-6	3-11	3 1/2	8-9 7/8	6-8 3/8	1 to 7			
3	3-11	3-6	3	7-9 1/2	6-3	1 to 8			
4	3-6	3-11	3	6-3	7-9 1/2	1 to 9			
5	3-9	3-9	3	7-1 1/8	7-1 1/8	1 to 8			
6	3-1	3-9	3	4-10 3/8	7-1 1/8	1 to 10			
7	3-9	3-1	3	7-1 1/8	4-10 3/8	1 to 8			
8	3-8	3-8	2 1/2	10-2	10-2	1 to 8			
9	2-8	3-8	2 1/2	5-5	10-2	1 to 11			
10	3-8	2-8	2 1/2	12-2	5-5	1 to 8			
11	2-8	3-8	2 1/2	3-7 1/2	10-2	1 to 14			
12	3-8	2-2	2 1/2	10-2	3-7 1/2	1 to 8			
13	3-0	3-0	2	6-10	6-10	1 to 10			
14	2-9	2-9	3	3-10 3/8	3-10 3/8	1 to 11			
19	2-6	2-9	2 1/2	3-10 3/8	4-7 7/8	1 to 12			
20	2-9	2-6	2 1/2	4-7 7/8	3-10 3/8	1 to 11			
21	2-6	2-6	2 1/2	3-10 3/8	3-10 3/8	1 to 12			
22	3-5	3-6	3	5-11 1/8	6-3	1 to 9			
23	3-6	3-5	3	6-3	5-11 1/8	1 to 9			
24	3-6	3-9	3	0-3	7-1 1/8	1 to 9			
25	3-9	3-6	3	7-1 1/8	6-3	1 to 9			
26	3-2	3-1	3	5-13 1/8	4-10 3/8	1 to 9			
27	3-1	3-2	3	4-10 3/8	5-13 1/8	1 to 10			
28	3-0	3-1	3	4-7 1/2	4-10 3/8	1 to 10			
29	3-1	3-0	3	4-10 3/8	4-7 1/2	1 to 10			
30	2-6	2-0	2 1/2	3-10 3/8	2-6 1/8	1 to 12			
31	2-0	2-6	2 1/2	2-6 1/8	3-10 3/8	1 to 15			
32	5-6	6-3	3 1/2	13-13 1/8	5-4 3/8	1 to 5			
33	3-6	5-6	3	5-4 3/8	13-13 1/8	1 to 9			
34	4-0	4-0	3	8-1 1/2	8-1 1/2	1 to 7			

Plates are steel 1/4", 1/8", 3/8" or 1/2" thick.

Plates of greater length than given in table may be made by splicing with bars, angles, or tees.

All plates are made with buckles up, unless otherwise ordered. When buckles are turned down, a drain hole should be punched in the center of each buckle and should be shown on sketch.

Buckles of different sizes should not be used as it increases the cost of the plate.

Connection holes are generally for 3/8", 1/2" or 3/4" rivets or bolts. Different sized holes in same plate will increase the cost of the plate.

Spacing for holes lengthwise of plate should be in multiples of 3" and should not exceed 12".


Odd spaces to be at end of plate and in even 1/4". Minimum spacing crosswise 4 1/4", usually 6".

The number must be shown on drawings.

Sketches for Buckle Plates should indicate allowable overrun in length and width.

**CARNEGIE STEEL COMPANY**

**TROUGH PLATES**



**ELEMENTS OF TROUGH PLATES**

Single Section			Riveted Section			
Section Index	Size, Inches	Weight per Foot, Pounds	a, Inches	d, Inches	Weight per Square Foot, Pounds	Section Modulus, One Foot Width, Inches <sup>3</sup>
M 14	9½ x 3¾	23.2	8	6½	34.8	15.58
M 13	9½ x 3¾	21.4	8	6¾	32.1	14.28
M 12	9½ x 3¾	19.7	8	6¼	29.6	13.00
M 11	9½ x 3¾	18.0	8	6½	27.0	11.79
M 10	9½ x 3¾	16.3	8	6	24.5	10.69

**ALLOWABLE UNIFORM LOAD IN POUNDS PER SQUARE FOOT**

Span in Feet	Fiber Stress, 16000 Lbs. per Sq. In.					Fiber Stress, 12000 Lbs. per Sq. In.				
	M 14	M 13	M 12	M 11	M 10	M 14	M 13	M 12	M 11	M 10
5	6647	6093	5547	5030	4561	4986	4570	4160	3773	3421
6	4616	4231	3852	3493	3167	3462	3173	2889	2620	2376
7	3392	3109	2830	2567	2327	2543	2331	2124	1925	1745
8	2597	2380	2167	1965	1782	1948	1785	1625	1474	1336
9	2052	1880	1712	1553	1408	1539	1410	1284	1164	1058
10	1662	1523	1387	1258	1140	1246	1142	1046	943	855
11	1373	1259	1146	1039	942	1030	944	860	780	707
12	1154	1058	963	873	792	866	793	722	655	594
13	983	901	821	744	675	738	676	615	558	506
14	848	777	707	642	582	636	583	531	481	436
15	739	677	616	559	507	554	509	462	419	381
16	649	595	542	491	435	487	446	406	368	334
17	575	527	480	435	395	431	395	360	328	296
18	513	470	428	388	352	385	353	321	291	264
19	460	422	384	349	316	345	316	288	261	237
20	415	381	347	314	285	312	286	260	236	214

The values given in above tables are the safe loads per square foot of floor surface and are based upon the average resistance of the riveted portion within distance, a.


The weight of the plates are included in the safe loads and must be deducted to obtain the net superimposed safe load.

Safe loads for other fiber stresses than those given in table may be obtained from the values given by direct proportion of the fiber stresses.

The weight per square foot does not include the weight of rivet heads or other details.

## FLOOR PLATES

### CORRUGATED PLATES



#### ELEMENTS OF CORRUGATED PLATES

Single Section			Riveted Section			
Section Index	Size, Inches	Weight per Foot, Pounds	a, Inches	d, Inches	Weight per Square Foot, Pounds	Section Modulus, One Foot Width, Inches <sup>3</sup>
M 35	12 $\frac{1}{8}$ x 2 $\frac{7}{8}$	23.7	12 $\frac{1}{8}$	2 $\frac{7}{8}$	23.3	4.39
M 34	12 $\frac{1}{8}$ x 2 $\frac{1}{2}$	20.8	12 $\frac{1}{8}$	2 $\frac{1}{2}$	20.4	3.84
M 33	12 $\frac{1}{8}$ x 2 $\frac{3}{4}$	17.8	12 $\frac{1}{8}$	2 $\frac{3}{4}$	17.5	3.28
M 32	8 $\frac{3}{4}$ x 1 $\frac{7}{8}$	12.0	8 $\frac{3}{4}$	1 $\frac{7}{8}$	16.5	1.95
M 31	8 $\frac{3}{4}$ x 1 $\frac{5}{8}$	10.1	8 $\frac{3}{4}$	1 $\frac{5}{8}$	13.8	1.55
M 30	8 $\frac{3}{4}$ x 1 $\frac{1}{2}$	8.1	8 $\frac{3}{4}$	1 $\frac{1}{2}$	11.5	1.10

#### ALLOWABLE UNIFORM LOAD IN POUNDS PER SQUARE FOOT

Span in Feet	Fiber Stress, 16000 lbs. per sq. in.						Fiber Stress, 12000 lbs. per sq. in.					
	M 35	M 34	M 33	M 32	M 31	M 30	M 35	M 34	M 33	M 32	M 31	M 30
5	1873	1638	1400	832	661	469	1405	1229	1050	624	496	352
6	1301	1138	972	578	459	326	976	853	729	433	344	244
7	956	836	714	425	337	240	717	627	536	318	253	180
8	732	640	547	325	258	183	549	480	410	244	194	138
9	578	506	432	257	204	145	434	379	324	193	153	109
10	468	410	350	208	165	117	351	307	262	156	124	88
11	387	339	289	172	137	97	290	255	217	129	103	73
12	325	284	243	144	115	82	244	213	182	108	86	61
13	277	242	207	123	98	69	208	182	155	92	73	52
14	239	209	179	106	84	60	179	157	134	80	63	45
15	208	182	156	92	74	52	156	137	117	69	51	39

The values given in above tables are the safe loads per square foot of floor surface and are based upon the average resistance of the riveted portion within distance, *a*.


The weight of the plates are included in the safe loads and must be deducted to obtain the net superimposed safe load.

Safe loads for other fiber stresses than those given in table may be obtained from the values given by direct proportion of the fiber stresses.

The weight per square foot does not include the weight of splice bars, rivet heads or other details.

# CARNEGIE STEEL COMPANY

## CHECKERED PLATES

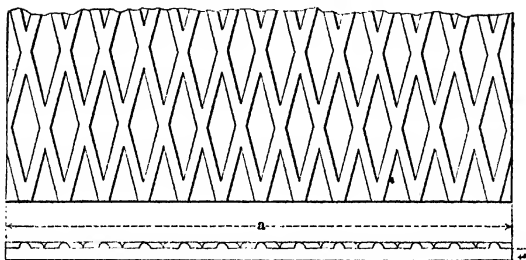

### ELEMENTS OF CHECKERED PLATES

Section Index	Width, a		Thickness, t, Inches	Weight per Square Foot, Pounds	Section Modulus for One Foot Width, Inches <sup>3</sup>
	Minimum, Inches	Maximum, Inches			
M 54	12	60	$\frac{1}{2}$	21.4	0.500
M 53	12	60	$\frac{7}{16}$	18.9	0.383
M 52	12	60	$\frac{7}{8}$	16.3	0.281
M 51	12	60	$\frac{1}{4}$	13.8	0.195
M 50	12	60	$\frac{3}{4}$	11.2	0.125
M 49	12	48	$\frac{1}{8}$	8.7	0.070

### ALLOWABLE UNIFORM LOAD IN POUNDS PER SQUARE FOOT

Span in Feet	Fiber Stress, 16000 Pounds per Square Inch						Fiber Stress, 12000 Pounds per Square Inch					
	M 54	M 53	M 52	M 51	M 50	M 49	M 54	M 53	M 52	M 51	M 50	M 49
1	5333	4083	3000	2083	1333	746	4000	3064	2248	1560	1000	560
2	1333	1021	750	520	333	187	1000	766	562	390	250	140
3	593	454	333	232	148	83	444	340	250	173	111	62
4	333	255	188	130	83	47	250	191	141	97	63	
5	213	163	120	83	53		160	122	90	62		
6	148	113	83	58			111	85	62			
7	109	83	61				82	63				
8	83	64					62					
9	66											

The values given in above table are the safe loads per square foot of plates supported on two sides only and are based upon the resistance of rectangular sections, 12 inches by the net section, t.

The weight of the plates are included in the safe loads and must be deducted to obtain the net superimposed safe load.

Safe loads for other fiber stresses than those given in table may be obtained from the values given by direct proportion of the fiber stresses.

## ROOF CONSTRUCTION

### ROOFS AND ROOF LOADS

The design of roofs and the selection of suitable roofing materials depend on the character of the building, whether monumental, public, residence, mill or shop; permanent or temporary; geographical location as regards allowance for snow and wind loads, and also availability of materials and familiarity of workmen with the construction; atmospheric conditions as concerns presence of industrial or other plants producing deleterious gases; water-tightness or resistance of the roof layers to penetration of water, snow or ice under storm and long continued exposure; wind resistance or the strength of materials to resist displacement of the entire surface or disruption between points of support; type and pitch of roof, whether self-supporting on wide spans or requiring the use of sheathing, and whether materials can be laid safely on steep surfaces.

A good roof on a permanent structure should be fireproof from within as well as without, made of refractory materials supported by equally refractory framing. It should last without repair as long as the building stands without repair. Its maintenance cost should be low and its materials purchased on the probable life and service of the structure.

**Snow Loads.** The snow loads on roofs vary with the geographical location, the altitude and humidity of the place, and with the slope of the roof. Where snow is likely to occur, the minimum load per horizontal square foot of roof should be taken at 25 pounds for all slopes up to 20 degrees; this load to be reduced one pound for each degree of increase in slope up to 45 degrees, above which no snow load need be considered. In severe climates these loads should be increased in accordance with actual conditions. Regard should also be taken to the possibility of partial snow load with local concentration.

**Wind Loads.** These vary also with the geographical location and the slope of the roof, and, when not fixed by building laws, are usually taken as acting horizontally at 40 pounds per square foot on vertical surfaces of the most exposed structures, and 30 pounds on less exposed structures. On inclined surfaces only the normal components of the wind pressure need be considered. The following normal pressures are based on the formula given by Hutton:

$P_n = P(\sin \alpha) 1.84 \cos \alpha - 1$ , where  $P$  is the direct horizontal pressure assumed at 30 pounds per square foot on the vertical surface and  $P_n$  the normal pressure on a unit of surface, sloping at angle  $\alpha$  with the horizontal.



# CARNEGIE STEEL COMPANY

## NORMAL WIND PRESSURE, IN POUNDS PER SQUARE FOOT

Slope $\alpha^\circ$	Pressure, Pn, per Square Foot, Pounds	Slope $\alpha^\circ$	Pressure, Pn, per Square Foot, Pounds	Slope $\alpha^\circ$	Pressure, Pn, per Square Foot, Pounds	Slope $\alpha^\circ$	Pressure, Pn, per Square Foot, Pounds
5	3.9	20	13.8	35	22.6	50	28.6
10	7.2	25	17.0	40	25.0	55	29.6
15	10.7	30	19.9	45	27.0	60	30.0

For other pressures than 30 pounds per square foot, the values given above change in proportion. For slopes\*over  $60^\circ$  the values given for  $60^\circ$  are applied.

**Combined Roof Loads.** In climates corresponding to that of Pittsburgh, and where the roof loads are not fixed by building laws, ordinary roofs up to 80 feet span should carry the following minimum loads per square foot of exposed surface, applied vertically, to provide for dead, wind and snow loads combined.

Roof Covering		Roof Load per Square Foot, Pounds
Gravel or Composition	on boards, flat slope, 1 to 6 or less	50
Roofing	on boards, steep slope, more than 1 to 6	45
Roofing	on 3 inch flat tile or cinder concrete	60
Corrugated sheeting	on boards or purlins	40
Slate	on boards or purlins	50
Slate	on 3 inch flat tile or cinder concrete	65
Tile	on steel purlins	55
Glass		45

For roofs in climates where no snow is likely to occur, reduce these loads by 10 pounds per square foot, but no roof or any part thereof should be designed for a total live and dead load less than 40 pounds per square foot.

**Roof Covering.** As stated above, suitable protection of a building against rain, snow, etc., depends on the character and location of the building, and the slope or pitch of the roof. Tin, tar, gravel, asphalt roofings and similar compositions are used for flat roofs; slate, tiles, and tin are used for slant roofs of public buildings and residences, shingles for smaller dwelling houses, and corrugated sheeting for shops and warehouses. Slate, tile, tin, and shingles are usually attached to a layer of planking, called sheathing, which in turn is supported by rafters, often called jack rafters, resting upon the roof purlins, or placed directly upon the purlins of the roof.

## ROOF CONSTRUCTION

### APPROXIMATE WEIGHT OF ROOFING MATERIAL

Roofing Material	Weight per Sq. Foot, Pounds
Copper, No. 22 B. W. G.	1 $\frac{1}{4}$
Corrugated galvanized iron, No. 20 B. W. G.	2 $\frac{1}{4}$
Corrugated galvanized iron, No. 26 B. W. G.	1 $\frac{3}{4}$
Felt, 2 layers	2 $\frac{1}{2}$
Felt and asphalt or coal-tar	1 $\frac{3}{4}$
Glass, $\frac{1}{8}$ inch thick	13 $\frac{1}{2}$
Lath and plaster ceiling	6-8
Lead, $\frac{1}{8}$ inch thick	7 $\frac{1}{2}$
Mackite, 1 inch thick, with plaster	10
Sheathing, hemlock, 1 inch thick	2
Sheathing, white pine, spruce, 1 inch thick	2 $\frac{1}{4}$ -2 $\frac{1}{2}$
Sheathing, yellow pine, 1 inch thick	3 $\frac{1}{2}$
Shingles, 6x18 inches, 6 inches to weather	2
Skylight, glass $\frac{3}{8}$ to $\frac{1}{2}$ inch, including frame	4-10
Slag roof, 4-ply, with cement and sand	4 $\frac{1}{2}$
Slate, $\frac{1}{2}$ inch thick, 3 inch double lap	6 $\frac{1}{2}$
Slate, $\frac{3}{8}$ inch thick, 3 inch double lap	1 $\frac{1}{2}$
Terneplate, 10	6 $\frac{1}{2}$
Terneplate, 12	6 $\frac{1}{2}$
Terneplate, 14	6 $\frac{1}{2}$
Terneplate, 16	6 $\frac{1}{2}$
Terneplate, 18	6 $\frac{1}{2}$
Terneplate, 20	6 $\frac{1}{2}$
Terneplate, 22	6 $\frac{1}{2}$
Terneplate, 24	6 $\frac{1}{2}$
Terneplate, 26	6 $\frac{1}{2}$
Terneplate, 28	6 $\frac{1}{2}$
Terneplate, 30	6 $\frac{1}{2}$
Terneplate, 32	6 $\frac{1}{2}$
Terneplate, 34	6 $\frac{1}{2}$
Terneplate, 36	6 $\frac{1}{2}$
Terneplate, 38	6 $\frac{1}{2}$
Terneplate, 40	6 $\frac{1}{2}$
Terneplate, 42	6 $\frac{1}{2}$
Terneplate, 44	6 $\frac{1}{2}$
Terneplate, 46	6 $\frac{1}{2}$
Terneplate, 48	6 $\frac{1}{2}$
Terneplate, 50	6 $\frac{1}{2}$
Terneplate, 52	6 $\frac{1}{2}$
Terneplate, 54	6 $\frac{1}{2}$
Terneplate, 56	6 $\frac{1}{2}$
Terneplate, 58	6 $\frac{1}{2}$
Terneplate, 60	6 $\frac{1}{2}$
Terneplate, 62	6 $\frac{1}{2}$
Terneplate, 64	6 $\frac{1}{2}$
Terneplate, 66	6 $\frac{1}{2}$
Terneplate, 68	6 $\frac{1}{2}$
Terneplate, 70	6 $\frac{1}{2}$
Terneplate, 72	6 $\frac{1}{2}$
Terneplate, 74	6 $\frac{1}{2}$
Terneplate, 76	6 $\frac{1}{2}$
Terneplate, 78	6 $\frac{1}{2}$
Terneplate, 80	6 $\frac{1}{2}$
Terneplate, 82	6 $\frac{1}{2}$
Terneplate, 84	6 $\frac{1}{2}$
Terneplate, 86	6 $\frac{1}{2}$
Terneplate, 88	6 $\frac{1}{2}$
Terneplate, 90	6 $\frac{1}{2}$
Terneplate, 92	6 $\frac{1}{2}$
Terneplate, 94	6 $\frac{1}{2}$
Terneplate, 96	6 $\frac{1}{2}$
Terneplate, 98	6 $\frac{1}{2}$
Terneplate, 100	6 $\frac{1}{2}$

**Roof Trusses.** Trusses are used where wide roof openings are to be spanned; they form a structure of compression and tension members and produce vertical reactions under vertical loads; the total load of the roof, that is, the weight of the truss, purlins, roof covering, ceiling, and often also the snow and wind load, is usually considered a uniformly distributed load, equally divided between the two supports and producing equal and vertical end reactions.

The purlins usually rest on the upper chord of the truss, transmitting to the latter the load of the roof covering, the wind and snow load, that of the jack rafters and their own, and are often so arranged as to carry the dead load directly to the truss joints or panel points to avoid transverse stresses. The distance between two consecutive joints of the top chord is the panel length, the distance between two adjacent trusses the bay length.

The transverse strength of the sheathing or of the corrugated iron used for the roof covering generally determines the spaces between the jack rafters or the purlins. These purlins or rafters are small steel shapes, such as beams, channels and angles, or wooden beams, if the roof is not of fireproof construction.


**Weight of Trusses.** As a basis for the preliminary design of a steel truss for a given span,  $L$ , and a roof load of about 40 pounds per square foot, the approximate weight is:

$$\frac{1}{2} (\sqrt{L} + \frac{1}{2} L) \text{ pounds per horizontal square foot.}$$


For greater loads multiply formula by ratio: load per sq. ft. + 40.

# CARNEGIE STEEL COMPANY

## TRUSSES—FORMULA FOR STRESSES AND LENGTHS



$$n = L/H = 2 \cot \alpha$$




### SIMPLE FINK TRUSS


Member	Stress	Length
Aa	$+\frac{1}{2}\sqrt{n^2+4}$ x W	$\frac{1}{4}L \sec \alpha$
Bb	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+1)$ x W	$\frac{1}{4}L \sec \alpha$
La	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
Lc	$-\frac{1}{2}n$ x W	$L(1-\frac{1}{2}\sec^2 \alpha)$
ab	$+\frac{n}{\sqrt{n^2+4}}$ x W	$\frac{1}{4}L \sec \alpha \tan \alpha$
bc	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$

### SIMPLE FAN TRUSS

Member	Stress	Length
Aa	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+5)$ x W	$\frac{1}{4}L \sec \alpha$
Bb	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+6)$ x W	$\frac{1}{4}L \sec \alpha$
Cc	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+1)$ x W	$\frac{1}{4}L \sec \alpha$
La	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
Ld	$-\frac{1}{2}n$ x W	$L(1-\frac{1}{2}\sec^2 \alpha)$
ab, bc	$+\frac{n}{\sqrt{n^2+4}}(\frac{1}{2}n^2+14)$ x W	$\frac{1}{4}L \sqrt{\frac{\sec^2 \alpha}{g}} + \sec^2 \alpha \tan^2 \alpha$
cd	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$



$$n = L/H = 2 \cot \alpha$$



### COMPOUND FINK TRUSS

Member	Stress	Length
Aa	$+\frac{1}{2}\sqrt{n^2+4}$ x W	$\frac{1}{4}L \sec \alpha$
Bb	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+5)$ x W	$\frac{1}{4}L \sec \alpha$
Cc	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+3)$ x W	$\frac{1}{4}L \sec \alpha$
Dd	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+1)$ x W	$\frac{1}{4}L \sec \alpha$
La	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
Lc	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
Lg	$-\frac{1}{2}n$ x W	$L(1-\frac{1}{2}\sec^2 \alpha)$
ab, ef	$+\frac{n}{\sqrt{n^2+4}}$ x W	$\frac{1}{4}L \sec \alpha \tan \alpha$
cd	$+\frac{n}{\sqrt{n^2+4}}$ x W	$\frac{1}{4}L \sec \alpha \tan \alpha$
bc, de	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
dg	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
fg	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$

### COMPOUND FAN TRUSS


Member	Stress	Length
Aa	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+11)$ x W	$\frac{1}{4}L \sec \alpha$
Bb	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+9)$ x W	$\frac{1}{4}L \sec \alpha$
Cc	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+7)$ x W	$\frac{1}{4}L \sec \alpha$
Dd	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+5)$ x W	$\frac{1}{4}L \sec \alpha$
Eg	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+3)$ x W	$\frac{1}{4}L \sec \alpha$
Fh	$+\frac{1}{2}\sqrt{n^2+4}(\frac{1}{2}n^2+1)$ x W	$\frac{1}{4}L \sec \alpha$
La	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
Ld	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
Li	$-\frac{1}{2}n$ x W	$L(1-\frac{1}{2}\sec^2 \alpha)$
ab, bc, fg, gh	$+\frac{n}{\sqrt{n^2+4}}(\frac{1}{2}n^2+14)$ x W	$\frac{1}{4}L \sqrt{\frac{\sec^2 \alpha}{g}} + \sec^2 \alpha \tan^2 \alpha$
de	$+\frac{n}{\sqrt{n^2+4}}$ x W	$\frac{1}{4}L \sec \alpha \tan \alpha$
cd, ef	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
gi	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$
hi	$-\frac{1}{2}n$ x W	$\frac{1}{4}L \sec^2 \alpha$

### Coefficients for Calculating Lengths of Truss Members


Values of n	3	2 1/2	2 cot 30°	4	2 1/2	5	6
Values of alpha	33°41'24"	30°15'23"	30°	26°33'54"	22°37'12"	21°48'5"	18°26'0"
sec alpha	1.2018	1.1577	1.1547	1.1180	1.0833	1.0770	1.0541
sec² alpha	1.4444	1.3403	1.3333	1.2500	1.1736	1.1600	1.1111
sec alpha tan alpha	0.8012	0.0753	0.6667	0.5590	0.4514	0.4308	0.3514
$\sqrt{\frac{\sec^2 \alpha}{g}} + \sec^2 \alpha \tan^2 \alpha$	0.8958	0.7778	0.7698	0.6718	0.5781	0.5608	0.4969

# ROOF CONSTRUCTION


## TRUSSES—COEFFICIENTS OF STRESSES




$$n = L/H = 2 \cot \alpha$$



n = Span ÷ Height = 2 cot α								n = Span ÷ Height = 2 cot α							
Member	3	24/7	2 cot 30°	4	24/5	5	6	Member	3	24/7	2 cot 30°	4	24/5	5	6
Aa	2.70	2.98	3.00	3.35	3.90	4.04	4.74	Aa	4.51	4.98	5.00	5.59	6.50	6.73	7.01
Bb	2.15	2.47	2.50	2.91	3.52	3.67	4.43	Bb	3.54	3.90	4.00	4.55	5.38	5.59	6.64
La	2.25	2.57	2.60	3.00	3.60	3.75	4.50	Cc	3.40	3.95	4.00	4.70	5.73	5.99	7.27
Lc	1.50	1.71	1.73	2.00	2.40	2.50	3.00	La	3.75	4.30	4.33	5.00	6.00	6.25	7.50
ab	0.83	0.86	0.87	0.89	0.92	0.93	0.95	Ld	2.25	2.57	2.60	3.00	3.60	3.75	4.50
bc	0.75	0.86	0.87	1.00	1.20	1.25	1.50	ab, bc	0.93	0.99	1.00	1.08	1.18	1.21	1.34
									1.50	1.71	1.73	2.00	2.40	2.50	3.00



$$n = L/H = 2 \cot \alpha$$



n = Span ÷ Height = 2 cot α								n = Span ÷ Height = 2 cot α							
Member	3	24/7	2 cot 30°	4	24/5	5	6	Member	3	24/7	2 cot 30°	4	24/5	5	6
Aa	6.31	6.96	7.00	7.83	9.10	9.42	11.07	Aa	9.92	10.91	11.00	12.30	14.30	14.81	17.39
Bb	5.76	6.44	6.50	7.38	8.72	9.05	10.75	Bb	8.05	9.91	10.00	11.25	13.18	13.66	16.13
Cc	5.20	5.94	6.00	6.93	8.33	8.68	10.43	Cc	8.81	9.91	10.00	11.40	13.53	14.07	16.76
Dd	4.65	5.43	5.50	6.48	7.95	8.31	10.12	Dd	8.25	9.40	9.50	10.96	13.15	13.70	16.44
La	5.25	6.00	6.07	7.00	8.40	8.75	10.50	Eg	7.28	8.41	8.50	9.91	12.02	12.55	15.18
Lc	4.50	5.14	5.20	6.00	7.20	7.50	9.00	Fh	7.14	8.40	8.50	10.06	12.38	12.95	15.93
Lg	3.00	3.43	3.46	4.00	4.80	5.00	6.00	La	8.25	9.43	9.53	11.00	13.20	13.75	16.50
ab, ef	0.83	0.86	0.87	0.89	0.92	0.93	0.95	Ld	6.75	7.71	7.79	9.00	10.80	11.25	13.50
cd	1.66	1.73	1.73	1.79	1.85	1.86	1.90	Li	4.50	5.14	5.20	6.00	7.20	7.50	9.00
bc, de	0.75	0.86	0.87	1.00	1.20	1.25	1.50	ab, bc, fg, gh	0.93	0.99	1.00	1.08	1.18	1.21	1.34
dg	1.50	1.71	1.73	2.00	2.40	2.50	3.00	de	2.50	2.59	2.60	2.68	2.77	2.79	2.85
fg	2.25	2.57	2.60	3.00	3.60	3.75	4.50	cd, ef	1.50	1.71	1.73	2.00	2.40	2.50	3.00
								ei	2.25	2.57	2.60	3.00	3.60	3.75	4.50
								hi	3.75	4.29	4.33	5.00	6.00	6.25	7.50


The pitch of a truss is the ratio of the rise or height to the span length of the truss.  
Pitch = H/L = 1/n, n = L/H = 1/pitch.

To obtain the stress in any member of a given truss, multiply the corresponding coefficient by the panel load W.


Compression members are designated by + and tension members by —

# CARNEGIE STEEL COMPANY

## TRUSSES—FORMULAS FOR STRESSES AND LENGTHS



$$n = L/H = 2 \cot \alpha$$




PRATT TRUSS—4 PANELS


Member	Stress	Length
Aa, Bb	$+\frac{3}{4}\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
La	$-\frac{3}{4}n \times W \frac{1}{4}$	$L$
Lc	$-\frac{1}{2}n \times W \frac{1}{2}$	$L$
ab	$+1 \times W \frac{1}{2}$	$h$
bc	$-\frac{1}{4}\sqrt{n^2+16} \times W \frac{1}{4}\sqrt{L^2+16h^2}$	

PRATT TRUSS—6 PANELS

Member	Stress	Length
Aa, Bb	$+\frac{5}{4}\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
Cd	$+\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
La	$-\frac{5}{4}n \times W \frac{1}{4}$	$L$
Lc	$-n \times W \frac{1}{4}$	$L$
Le	$-\frac{1}{2}n \times W \frac{1}{2}$	$L$
ab	$+1 \times W \frac{1}{2}$	$h$
cd	$+\frac{3}{2} \times W \frac{3}{2}$	$h$
bc	$-\frac{1}{4}\sqrt{n^2+16} \times W \frac{1}{4}\sqrt{L^2+16h^2}$	
de	$-\frac{1}{4}\sqrt{n^2+36} \times W \frac{1}{4}\sqrt{L^2+36h^2}$	



$$n = L/H = 2 \cot \alpha$$



PRATT TRUSS—8 PANELS


Member	Stress	Length
Aa, Bb	$+\frac{7}{4}\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
Cd	$+\frac{5}{2}\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
Df	$+\frac{3}{4}\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
La	$-\frac{7}{4}n \times W \frac{1}{4}$	$L$
Lc	$-\frac{3}{2}n \times W \frac{1}{4}$	$L$
Le	$-\frac{1}{2}n \times W \frac{1}{2}$	$L$
Lg	$-n \times W \frac{1}{4}$	$L$
ab	$+1 \times W \frac{1}{2}$	$h$
cd	$+\frac{3}{2} \times W \frac{3}{2}$	$h$
ef	$+2 \times W \frac{3}{2}$	$h$
bc	$-\frac{1}{4}\sqrt{n^2+16} \times W \frac{1}{4}\sqrt{L^2+16h^2}$	
de	$-\frac{1}{4}\sqrt{n^2+36} \times W \frac{1}{4}\sqrt{L^2+36h^2}$	
fg	$-\frac{1}{4}\sqrt{n^2+64} \times W \frac{1}{4}\sqrt{L^2+64h^2}$	

PRATT TRUSS—10 PANELS


Member	Stress	Length
Aa, Bb	$+\frac{9}{4}\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
Cd	$+2\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
Df	$+\frac{5}{4}\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
Eh	$+\frac{3}{4}\sqrt{n^2+4} \times W \frac{1}{4}$	$L \sec \alpha$
La	$-\frac{9}{4}n \times W \frac{1}{4}$	$L$
Lc	$-2n \times W \frac{1}{4}$	$L$
Le	$-\frac{1}{2}n \times W \frac{1}{2}$	$L$
Lg	$-\frac{3}{2}n \times W \frac{1}{4}$	$L$
Li	$-\frac{1}{2}n \times W \frac{1}{2}$	$L$
ab	$+1 \times W \frac{1}{2}$	$h$
cd	$+\frac{3}{2} \times W \frac{3}{2}$	$h$
ef	$+2 \times W \frac{3}{2}$	$h$
gh	$+\frac{3}{2} \times W \frac{3}{2}$	$h$
bc	$-\frac{1}{4}\sqrt{n^2+16} \times W \frac{1}{4}\sqrt{L^2+16h^2}$	
de	$-\frac{1}{4}\sqrt{n^2+36} \times W \frac{1}{4}\sqrt{L^2+36h^2}$	
fg	$-\frac{1}{4}\sqrt{n^2+64} \times W \frac{1}{4}\sqrt{L^2+64h^2}$	
hi	$-\frac{1}{4}\sqrt{n^2+100} \times W \frac{1}{4}\sqrt{L^2+100h^2}$	

# ROOF CONSTRUCTION

## TRUSSES—COEFFICIENTS OF STRESSES




$$n = L/H = 2 \cot \alpha$$




$$n = L/H = 2 \cot \alpha$$

n = Span ÷ Height = 2 cot α								n = Span ÷ Height = 2 cot α							
Member	3	24/7	2 cot 30°	4	24/5	5	6	Member	3	24/7	2 cot 30°	4	24/5	5	6
Aa, Bb	2.70	2.98	3.00	3.35	3.90	4.04	4.74	Aa, Bb	4.51	4.96	5.00	5.59	6.50	6.73	7.91
La	2.25	2.57	2.60	3.00	3.00	3.75	4.50	Cd	3.61	3.97	4.00	4.47	5.20	5.39	6.32
Lc	1.50	1.71	1.73	2.00	2.40	2.50	3.00	La	3.75	4.29	4.33	5.00	6.00	6.25	7.50
ab	1.00	1.00	1.00	1.00	1.00	1.00	1.00	Lc	3.00	3.43	3.46	4.00	4.80	5.00	6.00
bc	1.25	1.32	1.32	1.41	1.56	1.60	1.80	Le	2.25	2.57	2.60	3.00	3.60	3.75	4.50
								ab	1.00	1.00	1.00	1.00	1.00	1.00	1.00
								ed	1.50	1.50	1.50	1.50	1.50	1.50	1.50
								bc	1.25	1.32	1.32	1.41	1.56	1.60	1.80
								de	1.68	1.73	1.73	1.80	1.92	1.95	2.12



$$n = L/H = 2 \cot \alpha$$



$$n = L/H = 2 \cot \alpha$$

n = Span ÷ Height = 2 cot α							n = Span ÷ Height = 2 cot α								
Member	3	24/7	2 cot 30°	4	24/5	5	6	Member	3	24/7	2 cot 30°	4	24/5	5	6
Aa, Bb	6.31	6.95	7.00	7.83	9.10	9.42	11.07	Aa, Bb	8.11	8.93	9.00	10.06	11.70	12.12	14.23
Cd	5.41	5.95	6.00	6.71	7.80	8.08	9.49	Cd	7.21	7.94	8.00	8.94	10.40	10.77	12.65
Df	4.51	4.97	5.00	5.59	6.50	6.73	7.91	Df	6.31	6.95	7.00	7.83	9.10	9.42	11.07
La	5.25	6.00	6.06	7.00	8.40	8.75	10.50	Eh	5.41	5.95	6.00	6.71	7.80	8.08	9.49
Lc	4.50	5.14	5.20	6.00	7.20	7.50	9.00	La	6.75	7.71	7.79	9.00	10.80	11.25	13.50
Le	3.75	4.29	4.33	5.00	6.00	6.25	7.50	Lc	6.00	6.88	6.93	8.00	9.60	10.00	12.00
Lg	3.00	3.43	3.46	4.00	4.80	5.00	6.00	Le	5.25	6.00	6.06	7.00	8.40	8.75	10.50
ab	1.00	1.00	1.00	1.00	1.00	1.00	1.00	Lg	4.50	5.14	5.20	6.00	7.20	7.50	9.00
cd	1.50	1.50	1.50	1.50	1.50	1.50	1.50	Li	3.75	4.29	4.33	5.00	6.00	6.25	7.50
ef	2.00	2.00	2.00	2.00	2.00	2.00	2.00	ab	1.00	1.00	1.00	1.00	1.00	1.00	1.00
bc	1.25	1.32	1.32	1.41	1.56	1.60	1.80	cd	1.50	1.50	1.50	1.50	1.50	1.50	1.50
de	1.68	1.73	1.73	1.80	1.92	1.95	2.12	ef	2.00	2.00	2.00	2.00	2.00	2.00	2.00
fg	2.14	2.18	2.18	2.24	2.33	2.36	2.50	bc	2.50	2.50	2.50	2.50	2.50	2.50	2.50
								de	1.25	1.32	1.32	1.41	1.56	1.60	1.80
								fg	1.68	1.73	1.73	1.80	1.92	1.95	2.12
								hi	2.14	2.18	2.18	2.24	2.33	2.36	2.50
									2.61	2.64	2.65	2.69	2.77	2.80	2.92

## CARNEGIE STEEL COMPANY

### CORRUGATED SHEETS

Corrugated sheets are used for roofs and sides of buildings. They are usually laid directly upon the roof purlins and held in place by means of clips of steel hoops which encircle the purlin and are placed about 12 inches apart. Special care must be taken that the projecting edges of the sheets at the eaves and gable ends of the roof are well secured, otherwise the wind will loosen the sheets.

Corrugated sheets are made in the sizes given on opposite page, the size most generally used has nominally  $2\frac{1}{2}$ -inch corrugations, actual width 2 $\frac{3}{4}$  inches, about  $\frac{1}{2}$  inch in depth. The gages frequently used for roofing are Nos. 20 and 22, U. S. Standard Gage.

By one corrugation is meant the double curve between corresponding points, and by depth of corrugation the greatest deviation of the curved surfaces from the straight line.

One and one-half corrugations are allowed for lap in the width of the sheet and 6 inches in the length for the usual quarter pitch roof; one corrugation in width and 4 inches in the length of the sheet is usually allowed for sidings.

Corrugated sheets of 2,  $2\frac{1}{2}$  and 3 corrugations are furnished in standard lengths of 5, 6, 7, 8, 9 and 10 feet and with a standard covering width of 24 inches, when laid with a lap of either one or one and one-half corrugations.

By experiment it has been determined that corrugated sheet steel,  $\frac{5}{8}$  inch deep and 0.035 inch thick, spanning 6 feet, began to give a permanent deflection with a load of 30 pounds per sq. foot, and that it collapsed with a load of 60 pounds per sq. foot. The distance between centers of purlins should, therefore, not exceed 6 feet and should preferably be less than this.

Approximately the uniformly distributed safe load of corrugated sheets may be obtained from the formulas given below, using the following notations:—

W=Total allowable uniform load, in pounds.

b=Curvilinear width of sheet, in inches ( $b=1.075 \times$  covering width).

l=Unsupported length of sheet, in inches.

t=Thickness of sheet, in inches.

d=Depth of corrugations, in inches.

f=Allowable fiber stress, in pounds per sq. inch.

$$\text{Then: } W = \frac{4bdt}{15} \times \frac{8f}{1} = \frac{32fbd}{151}$$

$$\text{for } f = 12000, \quad W = \frac{25,600 bdt}{1}$$

# ROOFS AND ROOFING

## CORRUGATED SHEETS

AMERICAN SHEET AND TIN PLATE COMPANY

### DESCRIPTION OF SHEETS

### AREAS OF SHEETS

Corrugations				Width, Inches		Length of Sheet, Inches	Sq. Ft. in 1 Sheet			Sheets in 100 Sq. Ft.		
Width, Inches		Depth, Inches	Number per Sheet	Full Sheet	Covering		Corrugations			Corrugations		
Nominal	Actual						5"	3" 2 1/2"	1 1/2"	5"	3" 2 1/2"	1 1/2"
5	5	3/8	6	28	25	60	11.67	10.83	10.42	8.57	9.23	9.60
3	3	1/2	9	26	24	72	14.00	13.00	12.50	7.14	7.69	8.00
*2 1/2	2 3/4	1 1/2	10 1/2	27 1/2	24	84	16.33	15.17	14.58	6.12	6.59	6.86
2 1/2	2 5/8	1 1/2	10	26	24	96	18.67	17.33	16.67	5.36	5.77	6.00
2	2	7/8	13	26	24	108	21.00	19.50	18.75	4.76	5.13	5.33
1 1/2	1 3/4	3/4	20	25	23 3/4	120	23.33	21.67	20.83	4.29	4.62	4.80
1 1/4	1 1/2	3/4	40	25	24 3/4	144	28.00	26.00	25.00	3.57	3.85	4.00

Standard lengths 5, 6, 7, 8, 9 and 10 ft. Maximum length, 12 ft. except for 5/8" corrugation. Sizes denoted \*2 1/2 are for the 27 1/2" width.

### PAINTED SHEETS—Weights in Pounds per 100 Square Feet.

Corrug., In.	Thickness, United States Standard Gage														
	10	12	14	16	18	20	21	22	23	24	25	26	27	28	29
5		470	336	269	215	162	148	135	122	108	95	81	75	68	
3		472	338	270	216	163	149	136	122	109	95	82	75	68	
*2 1/2	615	478	342	274	219	165	151	137	124	110	97	83	76	69	
2 1/2	607	472	338	270	216	163	149	136	122	109	95	82	75	68	
2				270	216	163	149	136	122	109	95	82	75	68	
1 1/2						169	155	141	127	113	99	85	78	71	
1 1/4										113	99	85	78	71	

### GALVANIZED SHEETS—Weights in Pounds per 100 Square Feet.

Corrug., In.	Thickness, United States Standard Gage														
	10	12	14	16	18	20	21	22	23	24	25	26	27	28	29
5		486	352	285	231	178	164	151	137	124	111	97	90	84	77
3		488	353	286	232	178	165	151	138	125	111	98	91	84	77
*2 1/2	631	494	358	290	235	181	167	153	140	126	113	99	92	85	78
2 1/2	623	488	353	286	232	178	165	151	138	125	111	98	91	84	77
2				286	232	178	165	151	138	125	111	98	91	84	77
1 1/2						186	172	158	144	130	116	102	95	88	81
1 1/4										130	116	102	95	88	81

The weights per 100 square feet given in preceding tables do not include allowances for end or side laps. The following table gives the approximate number of square feet of sheeting necessary to cover an area of 100 square feet and is based on sheets of standard width, 96 inches long. If longer or shorter sheets are used, the number of square feet required will vary accordingly.

### Sq. FEET OF 2 1/2 IN. STANDARD SHEETS TO COVER AREA OF 100 Sq. Ft.

Side Lap		End Lap, Inches					
		1	2	3	4	5	6
1	Corrugation	109	111	112	113	114	116
1 1/4	"	116	117	118	120	121	122
2	"	123	124	126	127	129	130



## STEEL SHEET PILING


The introduction of steel sheet piling in substitution for wood has made possible the extension and indeed the practical rejuvenation of the cofferdam method of making excavations. Its use has led to great ultimate economies, greater safety in working and to the extension in size and depth of open excavations to limits which otherwise were regarded as impossible of attainment. The cellular cofferdam, first used in the Black Rock Lock, Buffalo, is a very successful method for the elimination of the expensive, slow, and not always reliable, pneumatic caisson on work of large magnitude.

Steel sheet piling by its positive interlock enables the sub-surface diaphragms of diaphragm dams to be made with a certainty not possible with wooden sheet piling, and with an economy not possible with concrete by reason of the elimination of the excavation necessary in the case of the ordinary puddle core, concrete core or masonry core wall. A diaphragm made of such imperishable materials fulfills all the requirements of the ordinary core wall with the additional advantage of accommodating itself, by its flexibility, to slight irregularities of settlement in the dam. It is also used in the construction of curtain walls, sea walls and loading slips, foundations for cylinder piers, sewers and trenches, etc.

In addition to temporary cofferdams, steel sheet piling has found large use in the construction of permanent retaining walls for buildings. Driven before excavation in soils containing quicksand or water-bearing strata, its use prevents the undermining of adjacent building foundations by movement of the strata. It also prevents in many cases the delay, expense and danger of underpinning adjacent buildings. It may be employed in this way alone or reinforced by steel buckstays as shown in the illustration, which represents the method followed by D. H. Burnham & Company in constructing retaining walls for the Marshall Field and Stevens Building, Chicago, where sheeting with its attached buckstays was driven its full depth and the basement and sub-basement floors placed as the excavation went forward. The rigidity of the buckstays with the bracing supported by the floors eliminated the necessity and expense of shoring. After excavation concrete was filled in between the buckstays and the total expense did not exceed 60 per cent. of its cost by the ordinary method.

**Types.** The Carnegie Steel Company manufactures United States Steel Sheet Piling, Priestedt Interlocking Channel Bar Piling, and Symmetrical Interlock Channel Bar Piling.

## STEEL SHEET PILING

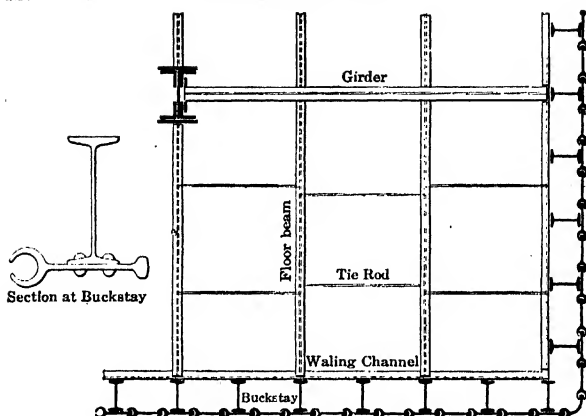

United States Steel Sheet Piling is a simple, plain, rolled section ready for use as it comes from the mill without further fabrication. Each piece is complete in itself and all pieces of the same width are interchangeable. Its profile incorporates the advantages of the ball and socket joint, with sufficient clearance in the interlock for ease in driving and sufficient space for the use of a packing substance between its adjacent edges to insure watertightness. United States Steel Sheet Piling is more easily driven and pulled than any other section hitherto placed on the market. The reason for this is believed to be the absence of a leading groove combined with the line contact obtained in the joints.

Friestedt Interlocking Channel Bar Piling is a fabricated section made of channels and zee bars; unsymmetrical as regards adjacent pieces, one channel having two zee bars full length and the next adjacent channel being plain, that is, without zee bars.

Symmetrical Interlock Channel Bar Piling is a fabricated section made of channels and zee bars in which each piece has a short zee bar on one edge and a long zee bar on the other. The long zee bar forms the interlock with the next adjacent section, while the short zee bar reinforces the top of the pile and serves to distribute the blow from the pile driving hammer over the width of the section.

All the sections have positive interlocks continuous throughout the entire length in both lateral and horizontal directions, affording maximum strength against sidewise deflection, distortion or separation of the pieces due to pressures, deformation in driving, etc.

## CARNEGIE STEEL COMPANY

**Strength of Section.** When driven and under pressure, steel sheet piling must have strength similar to that possessed by any other beam loaded equally or unequally with earth or water pressure, and the resistance of the piling to transverse bending can be calculated by the known laws of flexure from the properties of the section as given in the tables on page 351. In the case of Symmetrical Interlock Channel Bar Piling, the center line of the assemblment is not the center line of the individual members. Calculations are referred, therefore, to a theoretical neutral axis and give the properties of the sections on the assumption that when interlocked they will act as a unit. In the case of United States Steel Sheet Piling, the properties of the individual pieces are the same as the properties of the sections interlocked in place.

During driving the sections are forced to act as loaded columns, and the tables, therefore, show the radius of gyration of the sections for computing their compressive resistance under load or the blow of the pile driving hammer. The radius of gyration of the section, however, need not bear any definite proportion to its length and blocks of wood may be bolted to the leads of the pile driver if the piling shows a tendency to spring. As the piling actually enters the earth, it is supported laterally and stiffened by the adjacent soil, and the blows of the hammer need but overcome the friction. In an ordinary cofferdam braced in the usual manner, strength in the interlock to resist the tearing apart of the sections by direct tension in a longitudinal direction is not often required, but if it is, United States Steel Sheet Piling is recommended for use, as its longitudinal strength is greater than that of the fabricated sections. This interlock strength in a longitudinal direction depends on the type of section, the opening of the jaw, the character of the soil, etc., and can only be determined by tests. The average longitudinal strength per lineal inch of medium steel sections is as follows:


9" United States Steel Sheet Piling.....	5,600 pounds
12½" United States Steel Sheet Piling.....	9,500 "
15" 39 lb. Symmetrical Interlock Channel Bar Piling....	1,500 "

Steel sheet piling is usually made of medium steel manufactured to standard specifications. Where the construction is permanent and possible corrosion is a serious factor, it may be made of steel containing about 0.25% copper, experiments on which, as well as analyses of old structures, indicate that such an addition goes very far towards making the steel practically indestructible.

Full information on this specialty and its various uses is given in a separate pamphlet entitled "Steel Sheet Piling," copies of which can be had on request.

# STEEL SHEET PILING


## UNITED STATES STEEL SHEET PILING

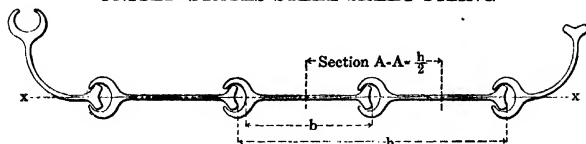

ELEMENTS OF SECTIONS, AXIS X-X

Section Index	Description	Section Interlocked or Single								Regular Corner, Weight, Pounds per Lineal Foot	
		Width b, Inches	Single Section		Weight, Lbs. per Sq. Ft.	I In. <sup>4</sup>	r In.	S In. <sup>3</sup>	S* In. <sup>3</sup>		h 2 In.
			Lbs. per Lin. Ft.	Area, Sq. In.							
M 105	12 1/2	43	12.72	39	9.20	0.85	4.53	4.10	13 1/4	43	
M 104	12 1/2	38	11.20	35	8.35	0.87	4.30	3.89	13 1/4	38	
M 103	9	16	4.71	21	1.45	0.56	1.13	1.47	9 1/4	16	

## SYMMETRICAL INTERLOCK CHANNEL BAR PILING

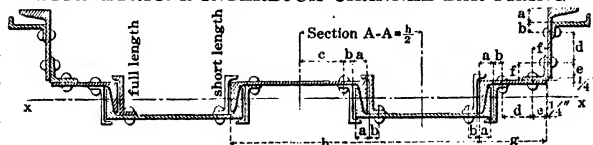

COMPOSITION AND DIMENSIONS OF SECTIONS

No.	Designation	Channels		Zees		Dimensions, Inches							
		In.	Lbs. per Ft.	In.	Lbs. per Ft.	a	b	c	d	e	f	g	$\frac{h}{2}$
1	10"x28 lbs.	10	15	3 1/2 x 3 1/4	4.8	1 1/4	1 1/4	3	2	1 1/2	1 1/4	5	9
2	10"x34 lbs.	10	20	3 1/2 x 3 1/4	4.8	1 1/4	1 1/4	3	2	1 1/2	1 1/4	5	9
3	12"x34 lbs.	12	20.5	3 1/2 x 3 1/4	8.6	1 1/4	1 1/4	3 1/2	2 1/4	1 1/2	1 1/4	6	10 1/2
4	12"x30 lbs.	12	25	3 1/2 x 3 1/4	8.6	1 1/4	1 1/4	3 1/2	2 1/4	1 1/2	1 1/4	6	10 1/2
5	15"x30 lbs.	15	33	4 1/2 x 3 1/4	9.2	1 1/4	1 1/4	4 1/2	3	1 1/2	1 1/4	7 1/2	13 1/2
6	15"x45 lbs.	15	40	4 1/2 x 3 1/4	9.2	1 1/4	1 1/4	4 1/2	3	1 1/2	1 1/4	7 1/2	13 1/2

ELEMENTS OF SECTIONS, AXIS X-X

No.	Description				Section Interlocked				Single Section			Regular Corner Weight Pounds per Lineal Foot
	Width, Inches	Single Section		Weight, Lbs. per Sq. Ft.	I In.4	r In.	S In.8	S* In.8	I In.4	r In.	S In.8	
		Lbs. per Lin. Ft.	Area, Sq. In.									
1	10	21	5.87	28	7.09	1.10	3.64	4.85	5.52	0.97	2.24	26
2	10	26	7.29	34	10.26	1.19	5.27	7.03	6.61	0.95	2.50	31
3	12	30	8.54	34	14.59	1.31	6.63	7.32	11.18	1.14	3.95	38
4	12	35	9.86	39	18.66	1.38	8.48	9.36	12.63	1.13	4.23	42
5	15	44	12.60	39	28.96	1.52	11.44	10.17	19.33	1.24	5.68	51
6	15	51	14.46	45	36.82	1.60	14.55	12.93	21.60	1.22	6.07	68

S\* is the average section modulus per horizontal foot of wall interlocked in place.

## STRUCTURAL TIMBER

The strength of structural timbers depends upon a number of factors; the kind of wood, the age of the tree, the time of the year in which it was felled, the method of sawing, the character of the seasoning and therewith its moisture content, the proportion of heartwood to sapwood and the proportion of knots to clear wood.

In consequence of these variable factors, the working unit stresses approved by the building laws of different cities vary widely, as well also as the unit stresses given in the proceedings of the various engineering associations. They go back in some cases to the studies made in 1895 by the Association of Railway Superintendents of Bridges and Buildings.

The most recent studies in this direction have been made by the American Railway Engineering Association, and the tables for wooden beams and columns which follow are based on the working unit stresses for structural timbers adopted by that Association. The table of working unit stresses has been reprinted, by permission, from the Manual, edition of 1911.

These unit stresses vary with the class of construction. They are intended, as noted, for railway bridges and trestles. For highway bridges and trestles and for buildings and similar structures, the unit stresses may be increased in accordance with the more quiescent character of the loading and freedom from deleterious weather conditions. The values are based on carefully selected timber purchased in accordance with the standard specifications of the Association and subject to careful inspection.

The commercial timbers which are in common use in building construction will not meet these specifications, and, therefore, the unit stresses approved by good building practice as evidenced in the building laws of various cities are rightly lower. The tables as they stand are in accord with the average practice as represented by these building laws, and may, therefore, be used as they stand for ordinary building work executed with the commercial grades of timber, such as can be purchased in the open market.

The allowable loads may be adjusted to other species of wood than those stated in the headings of the tables and to other unit stresses by the direct proportion which such unit stresses bear to those for which the tables are computed. In the case of columns the values may be adjusted to any working unit stress by direct proportion based on the relations of  $l/d$ .

# TIMBER SAFE LOADS

## WORKING UNIT STRESSES FOR STRUCTURAL TIMBER

ADOPTED BY THE AMERICAN RAILWAY ENGINEERING ASSOCIATION

The working unit stresses given in the table are intended for railroad bridges and trestles. For highway bridges and trestles, the unit stresses may be increased 25 per cent. For buildings and similar structures, in which the timber is protected from the weather and practically free from impact, the unit stresses may be increased 50 per cent. To compute the deflection of a beam under long continued loading instead of that when the load is first applied, only 50 per cent. of the corresponding modulus of elasticity given in the table is to be employed.

Kind of Timber	Unit Stresses in Pounds per Square Inch													
	Bending			Shearing			Compression							
	Extreme Fiber Stress	Modulus of Elasticity	Parallel to the Grain	Average Ultimate Stress	Working Stress	Longitudi- nal Stress in Beams	Elastic Limit	Perpendi- cular to the Grain	Parallel to the Grain	Working Stress	Length under 15 x d	Working Stresses Columns	Length over 15 x d	
Douglas Fir	Average					Average Ultimate Stress	Working Stress							
Longleaf Pine	6100	1200	1510000	690	170	270	110	630	310	3600	1200	900	1200	(1-1/600)
Shortleaf Pine	6500	1300	1610000	720	180	300	120	520	260	3800	1300	975	1300	(1-1/600)
White Pine	5600	1100	1480000	710	170	330	130	340	170	3400	1100	825	1100	(1-1/600)
Spruce	4400	900	1130000	400	100	180	70	290	150	3000	1000	750	1000	(1-1/600)
Norway Pine	4800	1000	1310000	600	150	170	70	370	180	3200	1100	825	1100	(1-1/600)
Tamarack	4200	800	1190000	590*	130	250	100		150	2600*	800	600	800	(1-1/600)
Western Hemlock	4600	900	1220000	670	170	260	100		220	3200*	1000	750	1000	(1-1/600)
Redwood	5800	1100	1480000	630	160	270*	100	440	220	3500	1200	900	1200	(1-1/600)
Bald Cypress	5000	900	800000	300	80			400	150	3300	900	675	900	(1-1/600)
Red Cedar	4800	900	1150000	500	120			340	170	3900	1100	825	1100	(1-1/600)
White Oak	4200	800	800000					470	230	2800	900	675	900	(1-1/600)
	5700	1100	1150000	840	210	270	110	920	450	3500	1300	975	1300	(1-1/600)

Unit stresses are for green timber and are to be used without increasing the live load stresses for impact. Value noted \* are for partially air dry timbers.

In the formulae given for columns, l=length of column, in inches, and d=least side or diameter, in inches.

Unit stresses are for green timber and are to be used without increasing the live load stresses for impact. Value noted\* are for partially air dry timbers.

In the formulas given for columns,  $l$ —length of column, in inches, and  $d$ —least side or diameter, in inches.

## WOODEN BEAMS

The safe load tables of wooden beams which follow, based upon the working unit stresses adopted by the American Railway Engineering Association, give the uniformly distributed safe loads for rectangular sections one inch thick; the safe load for a beam of any thickness is found by multiplying the tabular value by the thickness of the beam in inches. The safe loads include the weight of the beams and are computed on the assumption that the beams are braced against lateral deflection. These tables also give minimum and maximum spans and coefficients of deflection.

The maximum safe loads as limited by the allowable shearing stresses along horizontal axes of beams have been calculated from the formula: Maximum safe load =  $\frac{1}{3}$  x area of section x safe unit stress for longitudinal shear. These limits, indicated also by horizontal lines in the tables, should not be exceeded to avoid failure of the beam in horizontal direction of the grain of the wood.

The theoretical deflection in the center of the span for uniformly distributed and permanently applied loads is obtained from the coefficients of deflection by dividing the depth of the beam, in inches, into the corresponding coefficient; the result obtained only approximates the actual deflection, as the modulus of elasticity varies with the moisture content of the wood.

The deflection of beams intended to carry plastered ceilings should not exceed  $\frac{1}{360}$  of the span; the tables give the maximum spans for this limit and for uniform and permanently applied loads.

For loads concentrated in the center of the span, use one-half the values for the tabular loads and four-fifths of the coefficients of deflection. For special cases of loading, see pages 200 to 205.

**EXAMPLE 1.**—Required the thickness and the approximate deflection of a beam of white oak, 14 inches deep, supporting a uniformly distributed and permanent dead and live load of 10,000 pounds over a span of 19 feet.

The tabular value for a beam one inch thick and for a span of 19 feet is 1,261 pounds; the required thickness is therefore  $10,000 \div 1,261 = 8$  inches, and the deflection is  $20.72 \div 14 = 1.48$  inches.

**EXAMPLE 2.**—Required the safe load of a beam of white pine, 8 inches deep and 6 inches thick, without exceeding the longitudinal shearing stress.

The table gives for a corresponding beam 1 inch thick a safe load of 747 pounds; the total safe load is therefore  $6 \times 747 = 4,482$  pounds, or the safe load which can be safely supported over a span of 8.6 feet.

**EXAMPLE 3.**—Required the safe load, concentrated in the center of a span 26 feet long, and the deflection of a beam of longleaf pine, 18 inches deep and 12 inches thick.

The table gives for a corresponding beam 1 inch thick a uniformly distributed safe load of 1,800 pounds, or for a load in center of span  $1,800 \div 2 = 900$  pounds; for a beam 12 inches wide the safe load is therefore  $900 \times 12 = 10,800$  pounds, and the deflection is approximately  $\frac{1}{4} \times 32.75 \div 18 = 1.46$  inches.

# TIMBER SAFE LOADS

## RECTANGULAR WOODEN BEAMS—ONE INCH THICK

### MAXIMUM SAFE LOADS AND LIMITING SPANS

Depth of Beam, Inches	White Oak		Longleaf Pine		Shortleaf Pine		White Pine		Douglas Fir		Western Hemlock		Spruce	
	Max. Load, Lbs.	Min. Span, Ft.	Max. Load, Lbs.	Min. Span, Ft.	Max. Load, Lbs.	Min. Span, Ft.	Max. Load, Lbs.	Min. Span, Ft.	Max. Load, Lbs.	Min. Span, Ft.	Max. Load, Lbs.	Min. Span, Ft.	Max. Load, Lbs.	Min. Span, Ft.
2	293	1.7	320	1.8	347	1.5	187	2.1	293	1.8	267	1.8	187	2.4
4	587	3.3	640	3.6	693	3.1	373	4.3	587	3.6	533	3.7	373	4.8
6	880	5.0	960	5.4	1040	4.6	560	6.4	880	5.5	800	5.5	560	7.1
8	1173	6.7	1280	7.2	1387	6.2	747	8.6	1173	7.3	1067	7.3	747	9.5
10	1467	8.3	1600	9.0	1733	7.7	933	10.7	1467	9.1	1333	9.2	933	11.9
12	1760	10.0	1920	10.8	2080	9.2	1120	12.9	1760	10.9	1600	11.0	1120	14.3
14	2053	11.7	2240	12.6	2427	10.8	1307	15.9	2053	12.7	1867	12.8	1307	16.7
16	2347	13.3	2560	14.4	2773	12.3	1493	17.1	2347	14.5	2133	14.7	1493	19.0
18	2640	15.0	2880	16.3	3120	13.8	1680	19.3	2640	16.4	2400	16.5	1680	21.4
20	2933	16.7	3200	18.1	3467	15.4	1867	21.4	2933	18.2	2667	18.3	1867	23.8
22	3227	18.3	3520	19.9	3813	16.9	2053	23.6	3227	20.0	2933	20.2	2053	26.2
24	3520	20.0	3840	21.7	4160	18.5	2240	25.7	3520	21.8	3200	22.0	2240	28.6

### COEFFICIENTS OF DEFLECTION FOR PERMANENT LOADS

Span in Feet	White Oak	Longleaf Pine	Shortleaf Pine, Western Hemlock	White Pine, Douglas Fir	Spruce	Span in Feet	White Oak	Longleaf Pine	Shortleaf Pine, Western Hemlock	White Pine, Douglas Fir	Spruce
1	0.06	0.05	0.05	0.05	0.05	21	25.31	21.37	19.67	21.05	20.20
2	0.23	0.19	0.18	0.19	0.18	22	27.78	23.44	21.50	23.10	22.17
3	0.52	0.44	0.40	0.43	0.41	23	30.37	25.63	23.59	25.25	24.33
4	0.92	0.78	0.71	0.76	0.73	24	33.06	27.91	25.69	27.49	26.38
5	1.44	1.21	1.12	1.19	1.15	25	35.88	30.28	27.88	29.83	28.63
6	2.07	1.74	1.61	1.72	1.65	26	38.80	32.75	30.15	32.27	30.96
7	2.81	2.37	2.19	2.34	2.24	27	41.85	35.32	32.51	34.80	33.39
8	3.67	3.10	2.85	3.06	2.93	28	45.00	37.99	34.97	37.42	35.91
9	4.65	3.92	3.61	3.87	3.71	29	48.27	40.75	37.51	40.14	38.52
10	5.74	4.85	4.46	4.77	4.58	30	51.66	43.61	40.14	42.96	41.22
11	6.95	5.86	5.40	5.78	5.54	31	55.16	46.56	42.86	45.87	44.01
12	8.27	6.98	6.42	6.87	6.60	32	58.78	49.61	45.67	48.88	46.00
13	9.70	8.19	7.54	8.07	7.74	33	62.51	52.70	48.57	51.98	49.88
14	11.25	9.50	8.74	9.36	8.98	34	66.35	56.01	51.56	55.18	52.95
15	12.92	10.90	10.04	10.74	10.31	35	70.32	59.35	54.64	58.47	56.11
16	14.69	12.40	11.42	12.22	11.73	36	74.39	62.79	57.80	61.80	59.36
17	16.59	14.00	12.89	13.79	13.24	37	78.58	66.33	61.06	65.34	62.70
18	18.60	15.70	14.45	15.47	14.84	38	82.89	69.96	64.40	68.92	66.14
19	20.72	17.49	16.10	17.23	16.53	39	87.31	73.69	67.84	72.60	69.68
20	22.96	19.38	17.84	19.09	18.32	40	91.84	77.52	71.36	76.37	73.28

### MAXIMUM SPANS IN FEET FOR PERMANENT LOADS

Species of Timber	Depth of Beam in Inches											
	2	4	6	8	10	12	14	16	18	20	22	24
White Oak	2.3	4.7	7.0	9.3	11.6	13.9	16.3	18.6	20.9	23.2	25.6	27.9
Longleaf Pine	2.8	5.5	8.3	11.0	13.8	16.5	19.3	22.0	24.8	27.6	30.3	33.1
Shortleaf Pine	3.0	6.0	9.0	12.0	15.0	17.9	20.9	23.9	26.9	29.9	32.9	35.9
Western Hemlock	3.0	6.0	9.0	12.0	15.0	17.9	20.9	23.9	26.9	29.9	32.9	35.9
White Pine, Douglas Fir	2.8	5.6	8.4	11.2	14.0	16.7	19.5	22.3	25.1	27.9	30.7	33.5
Spruce	2.9	5.8	8.7	11.6	14.6	17.5	20.4	23.3	26.2	29.1	32.0	34.9



**CARNEGIE STEEL COMPANY**

**RECTANGULAR WOODEN BEAMS—ONE INCH THICK**

**DOUGLAS FIR**

**ALLOWABLE UNIFORM LOAD IN POUNDS**

**Maximum Bending Stress, 1200 Pounds per Square Inch**

Span in Feet	Depth of Beam in Inches											
	2	4	6	8	10	12	14	16	18	20	22	24
2	298											
3	267											
4	178	587										
5	133	533										
6	107	427										
7			890									
8	89	356	800									
9	76	305	686	1178								
10	67	267	600	1007	1467							
11					948							
12					853	1333						
13						1760						
14		194	436	776	1212	1745						
15		178	400	711	1111	1600	2038					
16			369	656	1026	1477	2010					
17			343	610	952	1371	1867	2347				
18			320	569	889	1280	1742	2276				
19												
20			300	533	833	1200	1633	2133	2640			
21				502	784	1129	1537	2008	2541			
22				474	741	1067	1452	1896	2400	2938		
23				449	702	1011	1375	1796	2274	2807	3327	
24				427	667	960	1307	1707	2160	2667	3227	
25												
26					635	914	1244	1625	2057	2540	3073	3620
27					606	873	1188	1552	1964	2424	2933	3491
28					580	835	1136	1484	1878	2319	2806	3339
29					556	800	1089	1422	1800	2222	2689	3200
30						768	1045	1365	1728	2133	2581	3072
31												
32						738	1005	1313	1662	2051	2482	2954
33						711	968	1264	1600	1975	2390	2844
34						686	933	1219	1543	1905	2305	2743
35							901	1177	1490	1839	2225	2648
36							871	1138	1440	1778	2151	2560
37												
38							843	1101	1394	1720	2082	2477
39							817	1067	1350	1667	2017	2400
40								1034	1309	1616	1956	2327
								1004	1271	1569	1898	2250
								975	1234	1524	1844	2194
								948	1200	1481	1793	2133
									1168	1441	1744	2076
									1137	1404	1698	2021
									1108	1368	1655	1969
									1080	1333	1613	1920

Horizontal lines indicate the limit for resistance to shear in the horizontal direction of the grain.

# TIMBER SAFE LOADS

## RECTANGULAR WOODEN BEAMS—ONE INCH THICK

### LONGLEAF PINE

#### ALLOWABLE UNIFORM LOAD IN POUNDS

Maximum Bending Stress, 1300 Pounds per Square Inch

Span in Feet	Depth of Beam in Inches											
	2	4	6	8	10	12	14	16	18	20	22	24
2	320											
3	289											
4	193	640										
5	144	578										
6	116	462										
7			960									
8	96	385	807									
9	83	330	743	1280								
10	72	289	650	1156	1000							
11		210	473	840	1313	1891						
12		193	433	770	1204	1733	2240					
13			400	711	1111	1600	2178					
14			371	660	1032	1486	2022	2560				
15			347	616	963	1387	1887	2465				
16			325	578	903	1300	1769	2311	2880			
17				544	850	1224	1665	2175	2753			
18				514	802	1156	1573	2054	2600	3200		
19				487	760	1095	1490	1946	2463	3041	3820	
20				462	722	1040	1416	1849	2340	2889	3496	
21					688	991	1348	1761	2229	2751	3329	3840
22					657	945	1287	1681	2127	2626	3178	3782
23					628	904	1231	1608	2035	2512	3040	3617
24					602	867	1180	1541	1950	2407	2913	3467
25						832	1132	1479	1872	2311	2796	3328
26						800	1089	1422	1800	2222	2689	3200
27						770	1049	1370	1733	2140	2589	3082
28						743	1011	1321	1671	2064	2497	2971
29							976	1275	1614	1992	2411	2869
30							944	1233	1560	1926	2330	2773
31							913	1193	1510	1864	2255	2684
32							885	1156	1463	1806	2185	2600
33								1121	1418	1751	2119	2521
34								1088	1377	1699	2056	2447
35								1057	1337	1651	1998	2377
36								1027	1300	1605	1942	2311
37									1265	1562	1890	2249
38									1232	1521	1840	2189
39									1200	1482	1793	2133
40									1170	1444	1748	2080

Horizontal lines indicate the limit for resistance to shear in the horizontal direction of the grain.

**CARNEGIE STEEL COMPANY**

**RECTANGULAR WOODEN BEAMS—ONE INCH THICK**

**SHORTLEAF PINE, WESTERN HEMLOCK AND WHITE OAK**

**ALLOWABLE UNIFORM LOAD IN POUNDS**

**Maximum Bending Stress, 1100 Pounds per Square Inch**

Span in Feet	Depth of Beam in Inches											
	2	4	6	8	10	12	14	16	18	20	22	24
2	847											
3	245	693										
4	183	652										
5	122	489	1040									
6	98	391	880	1387								
7	82	326	733	1304								
8	70	279	629	1117	1733							
9	61	245	550	978	1528	2080						
10		217	489	869	1358	1956	2427					
11		196	440	782	1222	1760	2396					
12		178	400	711	1111	1600	2178	2773				
13		163	367	652	1019	1467	1996	2607	3120			
14			338	602	940	1354	1843	2407	3046			
15			314	559	873	1257	1711	2235	2820	3467		
16			293	522	816	1173	1597	2086	2640	3259		
17			275	489	764	1100	1497	1956	2475	3055	3697	4180
18				460	719	1035	1400	1841	2320	2876	3480	4141
19				435	679	978	1331	1738	2200	2716	3287	3911
20				412	643	926	1261	1647	2084	2573	3113	3705
21				391	611	880	1198	1564	1980	2444	2958	3520
22					583	838	1141	1490	1886	2328	2817	3352
23					556	800	1089	1422	1800	2222	2689	3200
24					531	765	1042	1361	1722	2126	2572	3061
25					509	733	998	1304	1650	2037	2465	2933
26						704	958	1252	1584	1956	2366	2816
27						677	921	1203	1523	1880	2275	2708
28						652	887	1159	1467	1811	2191	2608
29						629	856	1118	1414	1746	2113	2514
30							826	1079	1366	1686	2040	2428
31							799	1043	1320	1630	1973	2348
32							773	1009	1278	1577	1908	2271
33							749	978	1238	1528	1849	2200
34								948	1200	1482	1793	2133
35								920	1165	1438	1740	2071
36								894	1131	1397	1690	2011
37								869	1100	1358	1643	1956
38									1070	1321	1599	1903
39									1042	1287	1557	1853
40									1015	1254	1517	1805
									990	1222	1479	1760

Upper, middle, and lower horizontal lines indicate the limits for resistance to shear in the horizontal direction of the grain of Shortleaf Pine, White Oak, and Hemlock respectively.

# TIMBER SAFE LOADS

## RECTANGULAR WOODEN BEAMS—ONE INCH THICK

### WHITE PINE

#### ALLOWABLE UNIFORM LOAD IN POUNDS

Maximum Bending Stress, 900 Pounds per Square Inch

Span in Feet	Depth of Beam in Inches											
	2	4	6	8	10	12	14	16	18	20	22	24
2	187											
3	133											
4	100	278										
5	80	320										
6	67	267	500									
7	57	229	514									
8	50	200	450	747								
9		178	400	711								
10		160	360	640								
					933							
11		145	327	582	909							
12		133	300	533	833	1120						
13			277	492	769	1108						
14			257	457	714	1029	1307					
15			240	427	667	960	1307					
16												
17			225	400	625	900	1225					
18				377	588	847	1153	1493				
19				356	556	800	1089	1422				
20				337	526	758	1032	1347	1680			
				320	500	720	980	1280	1620			
21					476	686	933	1219	1543	1867		
22					455	655	891	1164	1473	1818		
23					435	625	852	1113	1409	1739	2063	
24					417	600	817	1067	1350	1667	2017	
25						576	784	1024	1296	1600	1936	
												2240
26						554	754	985	1246	1538	1862	2215
27						533	726	948	1200	1481	1793	2133
28						514	700	914	1157	1429	1729	2057
29							676	883	1117	1379	1669	1986
30							653	853	1080	1333	1613	1920
31												
32						632	826	1045	1290	1561	1858	
33						613	800	1013	1250	1513	1800	
34							776	982	1212	1467	1746	
35							753	953	1176	1424	1694	
							731	926	1143	1383	1646	
36								711	900	1111	1344	1600
37									876	1081	1308	1557
38									853	1053	1274	1516
39									831	1026	1241	1477
40									810	1000	1210	1440

Horizontal lines indicate the limit for resistance to shear in the horizontal direction of the grain.

**CARNEGIE STEEL COMPANY**

**RECTANGULAR WOODEN BEAMS—ONE INCH THICK**

**SPRUCE**

**ALLOWABLE UNIFORM LOAD IN POUNDS**

**Maximum Bending Stress, 1000 Pounds per Square Inch**

Span in Feet	Depth of Beam in Inches											
	2	4	6	8	10	12	14	16	18	20	22	24
2	187											
3	148											
4	111	872										
5	89	356										
6	74	296										
7	63	254	590									
8	56	222	500									
9		198	444	747								
10		178	400	711								
11		162	364	646	638							
12		148	333	593	926							
13			308	547	855							
14			286	508	794	1120						
15			267	474	741	1067						
16			250	444	694	1000	1307					
17				418	654	941	1281					
18				395	617	889	1210					
19				374	585	842	1146	1403				
20				356	556	800	1089	1422				
21					529	762	1037	1354	1680			
22					505	727	990	1293	1636	4		
23					483	696	947	1237	1565	1867		
24					463	667	907	1185	1500	1852		
25						640	871	1138	1440	1778		
26						615	838	1094	1385	1709	2063	
27						593	807	1053	1333	1646	1992	
28						571	778	1016	1286	1587	1921	2240
29							751	981	1241	1533	1854	2207
30							726	948	1200	1481	1793	2138
31							703	918	1161	1434	1735	2065
32							681	889	1125	1389	1681	2000
33								862	1091	1347	1630	1939
34								837	1059	1307	1582	1882
35								813	1029	1270	1537	1829
36								790	1000	1235	1494	1778
37									973	1201	1453	1730
38									947	1169	1415	1684
39									923	1140	1379	1641
40									900	1111	1344	1600

Horizontal lines indicate the limit for resistance to shear in the horizontal direction of the grain.

## TIMBER SAFE LOADS

### WOODEN COLUMNS

The safe load tables of wooden columns which follow, based upon the working unit stresses adopted by the American Railway Engineering Association, give the allowable direct compressive loads for square and round columns.

The safe loads of rectangular columns may be found from the safe loads of square columns by direct proportion of areas, using the safe load unit stress of the square column whose side is equal to the least side of the rectangular section.

The following table gives the safe load in pounds per square inch of sectional area for ratios of

$$\frac{l}{d} = \frac{\text{effective length of column, in inches}}{\text{least side or diameter, in inches}},$$

ranging between limits of 15 and 30.

#### UNIT WORKING STRESSES IN POUNDS PER SQUARE INCH

$\frac{l}{d}$	Longleaf Pine, White Oak	Douglas Fir, Western Hemlock	Shortleaf Pine, Spruce, Bald Cypress	White Pine, Tamarack	Red Cedar, Redwood	Norway Pine
	1300 (1-1/d60)	1200 (1-1/d60)	1100 (1-1/d60)	1000 (1-1/d60)	900 (1-1/d60)	800 (1-1/d60)
15	975	900	825	750	675	600
16	953	880	807	733	660	587
17	931	860	788	717	645	573
18	910	840	770	700	630	560
19	888	820	752	683	615	547
20	867	800	733	667	600	533
21	845	780	715	650	585	520
22	823	760	697	633	570	507
23	802	740	678	617	555	493
24	780	720	660	600	540	480
25	758	700	642	583	525	467
26	737	680	623	567	510	553
27	715	660	605	550	495	440
28	693	640	587	533	480	427
29	672	620	568	517	465	413
30	650	600	550	500	450	400

**EXAMPLE 1.**—Required the allowable load for a column of white oak 10" x 8", 14 feet long.

The safe load given in the table for a square white oak column 8" x 8", 14 feet long, is 54,100 pounds. The load for the 10" x 8" section is  $10 \times 54,100 \div 8 = 67,600$  pounds.

**EXAMPLE 2.**—Required the allowable load for a spruce pile, 9" diameter and 18 feet long.

The unit stress given in the above table for the corresponding ratio of  $l/d$ ,  $18 \div 9 = 2$  is 660 pounds, and the sectional area for a 9" round is 63.62 square inches. The safe load, therefore, is  $63.62 \times 660 = 42,000$  pounds.

# CARNEGIE STEEL COMPANY

## SQUARE WOODEN COLUMNS

SAFE LOADS IN THOUSANDS OF POUNDS

American Railway Engineering Association Formulas

	Length, Feet	Side of Square, Inches								
		4	6	8	10	12	14	16	18	20
LONGLEAF PINE WHITE OAK 1300 (1—1600)	5	15.0								
	6	15.0								
	7	14.6								
	8	13.5	35.1							
	9	12.5	34.3							
	10	11.4	32.8	62.4						
	11	10.4	31.2	62.4						
	12		29.6	60.3						
	14		28.1	58.2	97.5					
	16		25.0	54.1	93.6	140.4				
	18			49.9	88.4	137.3	191.1			
	20			45.8	83.2	131.0	189.3	249.6		
DOUGLAS FIR WESTERN HEMLOCK 1200 (1—1600)	5	14.4								
	6	14.4								
	7	13.4								
	8	12.5	32.4							
	9	11.5	31.7							
	10	10.6	30.2	57.6						
	11	9.6	28.8	57.6						
	12		27.4	55.7						
	14		25.9	53.8	90.0					
	16		23.0	49.9	86.4	129.6				
	18			46.1	81.6	126.7	176.4			
	20			42.2	76.8	121.0	174.7	230.4		
SHORTLEAF PINE. SPRUCE 1100 (1—1600)	5	13.2								
	6	13.2								
	7	12.3								
	8	11.4	29.7							
	9	10.6	29.0							
	10	9.7	27.7	52.8						
	11	8.8	26.4	52.8						
	12		25.1	51.0						
	14		23.8	49.3	82.5					
	16		21.1	45.8	79.2	118.8				
	18			42.2	74.8	116.2	161.7			
	20			38.7	70.4	110.9	160.2	211.2		
WHITE PINE KARAKA 1000 (1—1600)	5	12.0								
	6	12.0								
	7	11.2								
	8	10.4	27.0							
	9	9.6	26.4							
	10	8.8	25.2	48.0						
	11	8.0	24.0	48.0						
	12		22.8	46.4						
	14		21.6	44.8	75.0					
	16		19.2	41.6	72.0	108.0				
	18			38.4	68.0	105.6	147.0			
	20			35.2	64.0	100.8	145.6	192.0		
				32.0	60.0	96.0	140.0	192.0	248.0	300.0

Loads in small figures above horizontal lines are the maximum allowable safe loads.

# TIMBER SAFE LOADS

## ROUND WOODEN COLUMNS

### SAFE LOADS IN THOUSANDS OF POUNDS

American Railway Engineering Association Formulas

	Length, Feet	Diameter, Inches								
		4	6	8	10	12	14	16	18	20
LONGLEAF PINE, WHITE OAK 1300 (1—1600)	5	12.3								
	6	12.3								
	7	11.4								
	8	10.6	27.6							
	9	9.8	27.0	49.0						
	10	9.0	25.7	49.0						
	11	8.2	24.5	47.4						
	12		23.3	45.7	76.6					
	14		22.1	42.5	73.5	110.8				
	16		19.6	39.2	69.4	107.8	150.1			
	18			35.9	65.3	102.9	148.7	196.0		
	20			32.7	61.3	98.0	142.9	196.0	248.1	306.8
DOUGLAS FIR, WESTERN HEMLOCK 1200 (1—1600)	5	11.3								
	6	11.3								
	7	10.6								
	8	9.8	25.4							
	9	9.1	24.0	45.2						
	10	8.3	23.7	43.7						
	11	7.5	22.6	42.2	70.7					
	12		21.5	40.1	67.9	101.8				
	14		20.4	39.2	64.1	99.5	138.6			
	16		18.1	36.2	60.3	95.0	137.2	181.0		
	18			33.2	56.5	90.5	132.0	181.0	229.0	282.7
	20			30.2						
SHORTLEAF PINE, SPRUCE 1100 (1—1600)	5	10.4								
	6	10.4								
	7	9.7								
	8	9.0	21.8							
	9	8.3	22.8	41.5						
	10	7.6	21.8	41.5						
	11	6.9	20.7	40.1						
	12		19.7	38.7	64.8					
	14		18.6	35.9	62.2	93.8				
	16			33.2	58.7	91.2	127.0			
	18			30.4	55.3	87.1	125.8	165.9		
	20			27.6	51.8	82.9	121.0	165.9	200.9	259.2
WHITE PINE, TAMARACK 1000 (1—1600)	5	9.4								
	6	9.4								
	7	8.8								
	8	8.2	21.2							
	9	7.5	20.7	37.7						
	10	6.9	19.8	37.7						
	11	6.3	18.0	36.4						
	12		17.9	35.2	58.9					
	14		15.1	32.7	56.5	84.8				
	16			30.2	53.4	82.9	115.5			
	18			27.6	50.3	79.2	114.4	150.8		
	20			25.1	47.1	75.4	110.0	150.8	190.9	235.6

Loads in small figures above horizontal lines are the maximum allowable safe loads.

Loads in small figures above horizontal lines are the maximum allowable safe loads.



# CARNEGIE STEEL COMPANY

## SPECIFIC GRAVITIES AND WEIGHTS

Substance	Specific Gravity	Weight, Pounds per Cu. Ft.	Substance	Specific Gravity	Weight, Pounds per Cu. Ft.
<b>Metals, Alloys, Ores</b>			<b>Timber, U. S. Seasoned</b>		
Aluminum, cast-hammered...	2.55-2.75	165	Ash, white-red...	0.62-0.65	40
"    bronze...	7.7	491	Cedar, white-red...	0.32-0.38	22
Brass, cast-rolled...	8.4-8.7	534	Chestnut...	0.66	41
Bronze, 7.9 to 14% Sn...	7.4-8.9	509	Cypress...	0.48	30
Copper, cast-rolled...	8.8-9.0	556	Fir, Douglas spruce...	0.51	32
"    ore, pyrites...	4.1-4.3	262	"    eastern...	0.40	25
Gold, cast-hammered...	19.25-19.35	1205	Elm, white...	0.72	45
Iron, cast, pig...	7.2	450	Hemlock...	0.42-0.52	29
"    wrought...	7.6-7.9	485	Hickory...	0.74-0.84	49
"    steel...	7.8-7.9	490	Locust...	0.73	46
"    spiegeleisen...	7.5	483	Maple, hard...	0.68	43
"    ferro-silicon...	6.7-7.3	437	"    white...	0.53	33
"    ore, hematite...	5.2	325	Oak, chestnut...	0.86	54
"    "    in bank...		160-180	"    live...	0.95	59
"    "    loose...		130-100	"    red, black...	0.65	41
"    "    limonite...	3.8-4.0	237	"    white...	0.74	46
"    "    magnetite...	4.9-5.2	315	Pine, Oregon...	0.51	32
"    slag...	2.5-3.0	172	"    red...	0.48	30
Lead...	11.37	710	"    white...	0.41	26
"    ore, galena...	7.3-7.6	465	"    yellow, long-leaf...	0.70	44
Manganese...	7.2-8.0	475	"    short-leaf...	0.61	38
"    ore, pyrolusite...	3.7-4.6	259	Poplar...	0.45	30
Mercury...	13.6	849	Redwood, California...	0.42	28
Nickel...	8.9-9.2	565	Spruce, white, black...	0.40-0.46	27
"    monel metal...	8.8-9.0	556	Walnut, black...	0.61	38
Platinum, cast-hammered...	21.1-21.5	1330	"    white...	0.41	26
Silver, cast-hammered...	10.4-10.6	656	Moisture Contents:		
Tin, cast-hammered...	7.2-7.5	459	Seasoned timber 15 to 20%...		
"    ore, cassiterite...	6.4-7.0	418	Green timber up to 50%...		
Zinc, cast-rolled...	6.9-7.2	440			
"    ore, blende...	3.9-4.2	253			
<b>Various Solids</b>			<b>Various Liquids</b>		
Cereals, oats, bulk...		32	Alcohol, 100%...	0.79	49
"    barley, "...		39	Acids, muriatic 40%...	1.20	75
"    corn, rye, "...		45	"    nitric 91%...	1.50	94
"    wheat, "...		48	"    sulphuric 87%...	1.80	112
Hay and Straw, bales...		20	Lye, soda... 66%...	1.70	106
Cotton, Flax, Hemp...	1.47-1.50	93	Oils, vegetable...	0.91-0.94	58
Fats...	0.90-0.97	58	"    mineral, lubricants...	0.90-0.93	57
Flour, loose...	0.40-0.50	28	Water, 4°C, max. density...	1.0	62.428
"    pressed...	0.70-0.80	47	"    100°C...	0.9584	59.830
Glass, common...	2.40-2.60	156	"    ice...	0.88-0.92	56
"    plate or crown...	2.45-2.72	161	"    snow, fresh fallen...	.125	8
"    crystal...	2.90-3.00	184	"    sea water...	1.02-1.03	64
Leather...	0.86-1.02	59	<b>Gases, Air = 1</b>		
Paper...	0.70-1.15	58	Air, 0°C, 760 mm...	1.0	.08071
Potatoes, piled...		42	Ammonia...	0.5920	.0478
Rubber, eucalyptus...	0.92-0.96	59	Carbon dioxide...	1.5291	.1234
Rubber goods...	1.0-2.0	94	Carbon monoxide...	0.9673	.0781
Salt, granulated, piled...		48	Gas, illuminating...	0.35-0.45	.028-.036
Salt peter...		67	"    natural...	0.47-0.48	.038-.039
Starch...	1.53	96	Hydrogen...	0.0693	.00559
Sulphur...	1.93-2.07	125	Nitrogen...	0.9714	.0784
Wool...	1.32	82	Oxygen...	1.1056	.0892

The specific gravities of solids and liquids refer to water at 4°C., those of gases to air at 0°C. and 760 mm pressure. The weights per cubic foot are derived from average specific gravities, except where stated that weights are for bulk, heaped or loose material, etc.

# PHYSICAL PROPERTIES OF SUBSTANCES

## SPECIFIC GRAVITIES AND WEIGHTS

Substance	Specific Gravity	Weight, Pounds per Cu. Ft.	Substance	Specific Gravity	Weight, Pounds per Cu. Ft.
<b>Ashlar Masonry</b>			<b>Minerals</b>		
Granite, syenite, gneiss	2.3-3.0	165	Asbestos	2.1-2.8	153
Limestone, marble	2.3-2.8	160	Barytes	4.50	281
Sandstone, bluestone	2.1-2.4	140	Basalt	2.7-3.2	184
<b>Mortar Rubble Masonry</b>			Bauxite	2.55	159
Granite, syenite, gneiss	2.2-2.8	155	Borax	1.7-1.8	109
Limestone, marble	2.2-2.6	150	Chalk	1.8-2.6	137
Sandstone, bluestone	2.0-2.2	130	Clay, marl	1.8-2.6	137
<b>Dry Rubble Masonry</b>			Dolomite	2.9	181
Granite, syenite, gneiss	1.9-2.3	130	Feldspar, orthoclase	2.5-2.6	159
Limestone, marble	1.9-2.1	125	Gneiss, serpentine	2.4-2.7	159
Sandstone, bluestone	1.8-1.9	110	Granite, syenite	2.5-3.1	175
<b>Brick Masonry</b>			Greenstone, trap	2.3-3.2	187
Pressed brick	2.2-2.3	140	Gypsum, alabaster	2.3-2.8	159
Common brick	1.8-2.0	120	Hornblende	3.0	187
Soft brick	1.5-1.7	100	Limestone, marble	2.5-2.8	165
<b>Concrete Masonry</b>			Magnetite	3.0	187
Cement, stone, sand	2.2-2.4	144	Phosphate rock, apatite	3.2	200
slag, etc.	1.9-2.3	130	Pyrophyllite	2.6-2.9	172
cinder, etc.	1.5-1.7	100	Quartz, natural	0.37-0.90	40
<b>Various Building Mat'l</b>			Quartz, flint	2.5-2.8	165
Ashes, cinders		40-45	Sandstone, bluestone	2.2-2.5	147
Cement, portland, loose		90	Shale, slate	2.7-2.9	175
" set	2.7-3.2	183	Soapstone, talc	2.6-2.8	169
Lime, gypsum, loose		53-64	<b>Stone, Quarried, Piled</b>		
Mortar, set	1.4-1.9	103	Basalt, granite, gneiss		96
Slags, bank slag		67-72	Limestone, marble, quartz		95
" screenings		98-117	Sandstone		82
" machine slag		90	Shale		92
" slag sand		49-55	Greenstone, hornblende		107
<b>Earth, etc., Excavated</b>			<b>Bituminous Substances</b>		
Clay, dry		63	Asphaltum	1.1-1.5	81
" damp, plastic		110	Coal, anthracite	1.4-1.7	97
Clay and gravel, dry		100	" bituminous	1.2-1.5	84
Earth, dry, loose		76	" lignite	1.1-1.4	78
" packed		95	" peat, turf, dry	0.65-0.55	47
" moist, loose		78	" charcoal, pine	0.28-0.44	23
" packed		96	" oak	0.47-0.57	33
" mud, flowing		108	" coke	1.0-1.4	75
" packed		115	Graphite	1.9-2.3	131
Riprap, limestone		80-85	Paraffine	0.87-0.91	56
" sandstone		90	Petroleum	0.87	54
" shale		105	" refined	0.79-0.82	50
Sand, gravel, dry, loose		90-105	" benzine	0.73-0.75	46
" packed		100-120	" gasoline	0.66-0.69	42
" wet		118-120	Pitch	1.07-1.15	69
<b>Excavations in Water</b>			Tar, bituminous	1.20	75
Sand or gravel		60	<b>Coal and Coke, Piled</b>		
" and clay		65	Coal, anthracite		47-58
Clay		80	" bituminous, lignite		40-54
River mud		90	" peat, turf		20-26
Soil		70	" charcoal		10-14
Stone riprap		65	" coke		23-32

The specific gravities of solids and liquids refer to water at 4°C., those of gases to air at 0°C. and 760 mm pressure. The weights per cubic foot are derived from average specific gravities, except where stated that weights are for bulk, heaped or loose material, etc.

**CARNEGIE STEEL COMPANY**

**CONTENTS OF STORAGE WAREHOUSES**

Material	Weights per Cubic Foot of Space, Pounds	Height of Pile, Feet	Weights per Square Foot of Floor, Pounds	Recommended Live Loads, Pounds per Square Foot
Groceries, Wines, Liquors, Etc.				
Beans, in bags.....	40	8	320	250 to 300
Canned Goods, in cases.....	58	6	348	
Coffee, Roasted, in bags.....	33	8	264	
Coffee, Green, in bags.....	39	8	312	
Dates, in cases.....	55	6	330	
Figs, in cases.....	74	5	370	
Flour, in barrels.....	40	5	200	
Molasses, in barrels.....	48	5	240	
Rice, in bags.....	58	6	348	
Salt Soda, in barrels.....	46	5	230	
Salt, in bags.....	70	5	350	
Soap Powder, in cases.....	38	8	304	
Starch, in barrels.....	25	6	150	
Sugar, in barrels.....	43	5	215	
Sugar, in cases.....	51	6	306	
Tea, in chests.....	25	8	200	
Wines and Liquors, in barrels.....	38	6	228	
Dry Goods, Cotton, Wool, Etc.				
Burlap, in bales.....	43	6	258	200 to 250
Coir Yarn, in bales.....	33	8	264	
Cotton, in bales, compressed.....	18	8	144	
Cotton Bleached Goods, in cases.....	28	8	224	
Cotton Flannel, in cases.....	12	8	96	
Cotton Sheeting, in cases.....	23	8	184	
Cotton Yarn, in cases.....	25	8	200	
Excelsior, compressed.....	19	8	152	
Hemp, Italian, compressed.....	22	8	176	
Hemp, Manila, compressed.....	30	8	240	
Jute, compressed.....	41	8	328	
Linen Damask, in cases.....	50	5	250	
Linen Goods, in cases.....	30	8	240	
Linen Towels, in cases.....	40	6	240	
Sisal, compressed.....	21	8	168	
Tow, compressed.....	29	8	232	
Wool, in bales, compressed.....	48			
Wool, in bales, not compressed.....	13	8	104	
Wool, Worsted, in cases.....	27	8	216	

# PHYSICAL PROPERTIES OF SUBSTANCES

## CONTENTS OF STORAGE WAREHOUSES

Material	Weights per Cubic Foot of Space, Pounds	Height of Pile, Feet	Weights per Square Foot of Floor, Pounds	Recommended Live Loads, Pounds per Square Foot
<b>Building Materials</b>				
Cement, Natural.....	59	6	354	300 to 400
“ Portland.....	73	6	438	
Lime and Plaster.....	53	5	265	
<b>Hardware, Etc.</b>				
Door Checks.....	45			300 to 400
Hinges.....	64			
Locks, in cases, packed.....	31			
Sash Fasteners.....	48			
Screws.....	101			
Sheet Tin, in boxes.....	278	2	556	
Wire Cables, on reels.....			425	
Wire, Insulated Copper, in coils.....	63	5	315	
Wire, Galvanized Iron, in coils.....	74	4½	333	
Wire, Magnet, on spools.....	75	6	450	
<b>Drugs, Paints, Oil, Etc.</b>				
Alum, Pearl, in barrels.....	33	6	198	200 to 300
Bleaching Powder, in hogsheads.....	31	3½	102	
Blue Vitriol, in barrels.....	45	5	226	
Glycerine, in cases.....	52	6	312	
Linseed Oil, in barrels.....	36	6	216	
Linseed Oil, in iron drums.....	45	4	180	
Logwood Extract, in boxes.....	70	5	350	
Rosin, in barrels.....	48	6	288	
Shellac, Gum.....	38	6	228	
Soda Ash, in hogsheads.....	62	2¾	167	
Soda, Caustic, in iron drums.....	88	3¼	294	
Soda, Silicate, in barrels.....	53	6	318	
Sulphuric Acid.....	60	1½	100	
White Lead Paste, in cans.....	174	3½	610	
White Lead, dry.....	86	4¾	408	
Red Lead and Litharge, dry.....	132	3¾	495	
<b>Miscellaneous</b>				
Glass and Chinaware, in crates.....	40	8	320	300
Hides and Leather, in bales.....	20	8	160	
Hides, Buffalo, in bundles.....	37	8	296	
Paper, Newspaper, and Strawboards.....	35	6	210	
Paper, Writing and Calendered.....	60	6	360	
Rope, in coils.....	32	6	192	

## CARNEGIE STEEL COMPANY

## STRENGTH OF MATERIALS

## STRESSES PER SQUARE INCH

Metals and Alloys	Stresses in Thousands of Pounds					Modulus of Elasticity, Pounds	Elongation, %
	Tension, Ultimate	Elastic Limit	Compression, Ultimate	Bending, Ultimate	Shearing, Ultimate		
Aluminum, cast.....	15	6.5	12		12	11,000,000	
" bars, sheets.....	24-28	12-14					
" wire, hard.....	30-65	16-30					
" annealed.....	20-35	14					
" 2-7% Ni, Cu, Fe, etc.....	40-50	25					
Aluminum Bronze, 8% to 11% Al.....	75	40	120				
" 10% Al.....	85-100	60					
Copper, cast.....	25	6	40	22	30	10,000,000	
" plates, rods, bolts.....	32-35	10	32				
" wire, hard.....	55-65					18,000,000	
" wire, annealed.....	36	10				15,000,000	
Brass, 17% Zn.....	32.6	8.2		23.2			26.7
" 23% Zn.....		7.6	42	22.3			35.8
" 30% Zn.....	28.1	8.6		26.9			20.7
" 39% Zn.....	41.1	17.4	75	39			20.7
" 50% Zn.....	31	17.9	117	33.5			5.0
" cast, common.....	18-24	6	30	20	36	9,000,000	
" wire, hard.....	80						
" annealed.....	50	16				14,000,000	
Bronze 8% Sn.....	28.5	19	42	43.7		10,000,000	5.5
" 13% Sn.....	29.4	20	53	34.5			3.3
" 20% Sn.....	33	33	78	56.7			0.04
" 24% Sn.....	22	22	114	32			0
" 30% Sn.....	5.6	5.6	147	12.1			0
" gun metal, 9 Cu, 1 Sn.....	25-55	10		52		10,000,000	
" Manganese, cast 10% Sn.....	60	30	125				
" rolled 2% Mn.....	100	80					
" Phosphorus, cast 19% Sn.....	50	24					
" wire 11% P.....	100						
Silicon, cast, 3% Si.....	55						
" wire 5% Si.....	75						
" wire.....	108						
Tobin, cast.....	66						
" rolled 38% Zn.....	80						
" cold rolled 11% Sn.....	100	40				4,500,000	
" cold rolled 1% Pb.....	100						
Delta Metal, cast 55-60% Cu.....	45						
" plates 38-40% Zn.....	68						
" bars 2-4% Fe.....	85						
" wire 1-2% Sn.....	100						
German Silver, 25% Zn, 20% Ni.....							
Iron, see next page.....							
Gold, cast.....	20	4				8,000,000	
" wire.....	30						
" copper, 5 Au, 1 Cu.....	50						
Lead, cast.....	1.8					1,000,000	
" pipe, wire.....	2.2-2.5					1,000,000	
" rolled sheets.....	3.3					720,000	
Platinum, wire, unannealed.....	53						
" annealed.....	32						
Silver, cast.....	40						
Steel, see next page.....							
Tin, cast.....	3.5-4.6	1.5-1.8	6	4		4,000,000	
" antimony, 10 Sn, 1 Sb.....	11						
Zinc, cast.....	4-6	4	18	7		13,000,000	
" rolled sheets.....	7-16						

**PHYSICAL PROPERTIES OF SUBSTANCES**

**STRENGTH OF MATERIALS**

**STRESSES PER SQUARE INCH**

Metal and Alloys	Stresses in Thousands of Pounds					Modulus of Elasticity, Pounds	Elongation, %
	Tension, Ultimate	Elastic Limit	Compression, Ultimate	Bending, Ultimate	Shearing, Ultimate		
<b>Steel</b>							
Shapes, Plates, Bars*							
" bridges	55-65	½ tens.	tensile	tensile	¾ tens.	29,000,000	27.3-23.0
" buildings	55-65	"	"	"	"	29,000,000	25.4-21.5
" cars	50-65	"	"	"	"	29,000,000	30.0-23.0
" locomotives	55-65	"	"	"	"	29,000,000	27.3-23.0
" ships	58-68	"	"	"	"	29,000,000	25.0-22.1
Boiler Plates*							
" fire box	55-65	½ tens.	tensile	tensile	¾ tens.	29,000,000	27.3-23.0
" flange plates	52-62	"	"	"	"	29,000,000	28.8-24.2
Rivets*							
" boilers	45-55	½ tens.	tensile	tensile	¾ tens.	29,000,000	33.3-27.3
" bridges	46-56	"	"	"	"	29,000,000	32.6-26.8
" buildings	46-56	"	"	"	"	29,000,000	30.4-25.0
" cars	48-58	"	"	"	"	29,000,000	31.3-25.9
" ships	55-65	"	"	"	"	29,000,000	27.3-23.0
Concrete Bars*							
" plain, structural grade	55-70	33	tensile	tensile	¾ tens.	29,000,000	25.4-20.0
" intermediate	70-85	40	"	"	"	29,000,000	18.6-15.3
" hard	80	50	"	"	"	29,000,000	15.0
" deformed, structural grade	55-70	33	"	"	"	29,000,000	22.7-17.9
" intermediate	70-85	40	"	"	"	29,000,000	16.1-13.2
" hard	80	50	"	"	"	29,000,000	12.5
" cold twisted		55	"	"	"	29,000,000	5.0
Castings*							
" soft	60	27	tensile	tensile	¾ tens.	29,000,000	22.0
" medium	70	31.5	"	"	"	29,000,000	18.0
" hard	80	36	"	"	"	29,000,000	15.0
Forgings*							
<b>Steel Alloys</b>							
Nickel Steel,* 3.25% N.							
" shapes, plates, bars	85-100	50	tensile	tensile	¾ tens.	29,000,000	17.6-15.0
" rivets	70-80	45	"	"	"	29,000,000	21.4-18.8
" eye bars, unannealed	95-110	55	"	"	"	29,000,000	15.4-13.6
" annealed	90-105	52	"	"	"	29,000,000	20.0
Copper Steel, 0.50% Cu.	60-68	37-38	"	"	"	29,000,000	29.0-23.0
<b>Steel Springs and Wire</b>							
" Springs, untempered	65-110	40-70					
" Wire, unannealed	120	60					
" annealed	80	40					
" bridge cable	200	95					
<b>Wrought Iron</b>							
" Shapes	48	26	tensile	tensile	¾ tens.	28,000,000	
" Bars	50	27	"	"	"	28,000,000	
" Wire, unannealed	80					15,000,000	
" annealed	60	27				25,000,000	
<b>Cast Iron</b>							
" Common	15-18	6	80	30	18-20	12,000,000	
" Gray	18-24			25-33			
" Malleable	27-35	15-20	46	30	40		

\* See Specifications of the Society of Testing Materials.

**CARNEGIE STEEL COMPANY**

**STRENGTH OF MATERIALS**  
**STRESSES IN POUNDS PER SQUARE INCH**

Building Materials	Ultimate Average Stresses			Modulus of Elasticity	Safe Working Stresses		
	Compress.	Tension	Bending		Compress.	Bearing	Shearing
<b>Stone</b>							
Bluestone.....	12,000	1,200	2,500	7,000,000	1,200	1,200	200
Granite, gneiss.....	12,000	1,200	1,600	7,000,000	1,200	1,200	200
Limestone, marble.....	8,000	800	1,500	7,000,000	800	800	150
Sandstone.....	5,000	150	1,200	3,000,000	500	500	150
Slate.....	10,000	3,000	5,000	14,000,000	1,000	1,000	175
<b>Brick</b>							
Common, good.....	10,000	200	600				
" medium burned.....	11,000						
" hard burned.....	15,000						
Pressed and paving.....	6,000						
<b>Cement, Portland</b>							
Neat, 28 days.....	7,040	740					
" 90 days.....	7,350	740					
1:3 sand, 28 days.....	1,290	320					
" 90 days.....	1,490	340					
<b>Concrete, P. C.</b>							
1:1½:3, hard stone.....	2,650				Reinforced Concrete—Safe Working Stresses *		
soft stone.....	1,800						
" cinders.....	700				Elastic Modulus.....	2,000,000 if ult. compression is up to 2,200. 2,500,000 if ult. compression is over 2,200. 3,000,000 if ult. compression is over 2,900.	
1: 2 :4, hard stone.....	2,100				Compression.....	22.5% of ult. compression on piers or columns of lengths not exceeding 12 dia.	
soft stone.....	1,500				Bearing.....	32.5% of ult. compression on surfaces of at least twice the loaded area.	
" cinders.....	600				Shearing.....	2.0% of ult. compression, horizontal bars. 3.0% for reinforcement with bent-up bars. 6.0% for thoroughly reinforced webs.	
1:2½:5, hard stone.....	1,700				Bond.....	4% of ult. compression for plain bars. 2% for drawn wire.	
soft stone.....	1,200						
" cinders.....	500						
1: 3 :6, hard stone.....	1,350						
soft stone.....	1,000						
" cinders.....	400						
<b>Masonry</b>							
Granite.....						420	600
Limestone, bluestone.....						350	500
Sandstone.....						280	400
Rubble.....						140	250
" coursed.....						168	250
Concrete, P. C., 1: 2 :4.....						350	600
" 1:2½:5.....						280	500
Brick, common.....						168	300
" hard burned.....						210	300
<b>Miscellaneous</b>							
Glass, common.....	30,000	3,000	3,000	8,000,000			
" flooring.....	10,000	3,000	3,000				
Plaster.....	700	70					
Terra cotta.....	5,000						
Ropes, cast steel hoisting.....		80,000					
" standing, derrick.....		70,000					
" manila.....		8,000					
Belts, solid woven, cotton.....		7,200					
" flax.....		9,900					

For ultimate and working stresses of Structural Timber, see page 353.

\*For complete data, see Proceedings of the American Society of Civil Engineers, Vol. XXXIX, No. 2, February, 1913.

# PHYSICAL PROPERTIES OF SUBSTANCES

## EXPANSION OF BODIES BY HEAT

The linear coefficient of expansion of a body is the rate at which the unit of length changes, under constant pressure, with an increase of unit or one degree of temperature; the square surface coefficient of expansion is, approximately, two times, and the cubical or volumetric coefficient three times the linear coefficient of expansion. A bar, if not fixed, undergoes a change in length= $ltn$ , where  $l$  is the length of the bar in inches,  $t$  the number of degrees,  $n$  the corresponding linear coefficient; if fixed at both ends, the internal stress per unit of area= $tnE$ , pounds per square inch, where  $E$  is the modulus of elasticity, and the total temperature stress= $AtnE$ , pounds, where  $A$  is the cross section of the bar in square inches.

To find the increase of a bar due to an increase in temperature, from the table, multiply the length of the bar by the increase in degrees and by the coefficient for 100 degrees, and divide by 100.

### COEFFICIENTS OF EXPANSION FOR 100 DEGREES=100n

Substance	Linear Expansion		Substance	Linear Expansion	
	Centigrade	Fahrenheit		Centigrade	Fahrenheit
<b>Metals and Alloys</b>					
Aluminum, wrought...	.00231	.00128	Ashlar masonry.....	.00063	.00035
Brass.....	.00188	.00104	Brick masonry.....	.00055	.00031
" wire.....	.00193	.00107	Cement, portland.....	.00107	.00059
Bronze.....	.00181	.00101	Concrete.....	.00143	.00079
Copper.....	.00168	.00093	" masonry.....	.00120	.00067
German Silver.....	.00183	.00102	Granite.....	.00084	.00047
Gold.....	.00150	.00083	Limestone.....	.00080	.00044
Iron, cast, gray.....	.00108	.00059	Marble.....	.00100	.00058
" wrought.....	.00120	.00067	Plaster.....	.00166	.00092
" wire.....	.00124	.00069	Rubble masonry.....	.00063	.00035
Lead.....	.00286	.00159	Sandstone.....	.00110	.00061
Nickel.....	.00126	.00070	Slate.....	.00104	.00058
Platinum.....	.00090	.00050	<b>Timber</b>		
Platinum-Iridium, 15%Ir	.00081	.00045	Fir.....	.00037	.00021
Silver.....	.00102	.00107	Maple.....	.00064	.00036
Steel, cast.....	.00110	.00061	Oak.....	.00049	.00027
" hard.....	.00132	.00073	Pine.....	.00054	.00030
" medium.....	.00120	.00067	Fir.....	.00058	.00032
" soft.....	.00110	.00061	Maple.....	.00048	.00027
Tin.....	.00210	.00117	Oak.....	.00054	.00030
Zinc, rolled.....	.00311	.00173	Pine.....	.00034	.00019
<b>Miscellaneous Solids</b>					
Glass.....	.00085	.00047	<b>Liquid Substances</b>		
Graphite.....	.00079	.00044	Alcohol.....	.104	.058
Gutta-percha.....	.05980	.03322	Acid, nitric.....	.110	.061
Paraffin.....	.02785	.01547	" sulphuric.....	.063	.035
Porcelain.....	.00036	.00020	Mercury.....	.018	.010
			Oil, turpentine.....	.090	.050

### EXPANSION OF WATER, MAXIMUM DENSITY=1

C°	Volume	C°	Volume	C°	Volume	C°	Volume	C°	Volume	C°	Volume
0	1.000126	10	1.000267	30	1.004234	50	1.011877	70	1.023384	90	1.035829
4	1.000000	20	1.001732	40	1.007627	60	1.016954	80	1.029008	100	1.043116



# CARNEGIE STEEL COMPANY

## EQUIVALENTS OF MEASURE

### LENGTHS

1 meter, m = 10 decimeters, dm = 100 centimeters, cm = 1000 millimeters, mm.  
 1 meter, m = 0.1 decameter, dkm = 0.01 hectometer, hm = 0.001 kilometer, km.  
 1 meter, m = 39.37 inches, U. S. Standard = 39.370113 inches, British Standard.  
 1 millimeter, mm = 1000 microns,  $\mu$  = 0.03937 inch = 39.37 mils.

Meters, m	Inches, in.	Feet, ft.	Yard, yd.	Rods, r.	Chains, ch.	Miles, U. S.		Kilo- meters, km.
						Statute	Nautical	
1	39.37	3.28083	1.09361	0.19884	0.04971	0. <sup>000</sup> 6214	0. <sup>539</sup> 96	0.001
0.02540	1	0.08333	0.02778	0. <sup>5</sup> 5051	0. <sup>5</sup> 1263	0. <sup>5</sup> 1578	0. <sup>5</sup> 1371	0. <sup>5</sup> 2540
0.30480	12	1	0.33333	0.06061	0.01515	0. <sup>5</sup> 1894	0. <sup>5</sup> 1645	0. <sup>3</sup> 3048
0.91440	36	3	1	0.18182	0.04545	0. <sup>5</sup> 5682	0. <sup>5</sup> 4934	0. <sup>9</sup> 144
5.02921	198	16.5	5.5	1	0.25	0. <sup>5</sup> 3125	0. <sup>5</sup> 2714	0. <sup>5</sup> 5029
20.1168	792	66	22	4	1	0.01250	0.01085	0.02012
1609.35	63360	5280	1760	320	80	1	0.80839	1.60935
1853.25	72962.5	6080.20	2026.73	368.497	92.1243	1.15155	1	1.85325
1000	39370	3280.83	1093.61	198.838	49.7006	0.62137	0.53959	1

1 yard, U. S. = 1.0000029 yards British 1 yard British = 0.9999971 yard U. S.

1 chain, Gunter's = 100 links 1 link = 7.92 inches.

1 cable length, U. S. = 120 fathoms = 960 spans = 720 feet = 219.457 meters.

1 league, U. S. = 3 statute miles = 24 furlongs.

1 international geographical mile =  $\frac{1}{40}$ ° at equator = 7422 m

= 4.611808 U. S. statute miles.

1 international nautical mile =  $\frac{1}{40}$ ° at meridian = 1852 m

= 0.999326 U. S. nautical miles.

1 U. S. nautical mile =  $\frac{1}{40}$ ° of circumference of sphere whose surface equals

that of the earth = 6080.27 feet = 1.15155 statute miles = 1853.27 meters.

1 British nautical mile = 6080.00 feet = 1.15152 statute miles = 1853.19 meters.

### SURFACES AND AREAS

1 sq. meter, m<sup>2</sup> = 100 sq. decimeters, dm<sup>2</sup> = 10000 sq. centimeters, cm<sup>2</sup>.

1 sq. meter, m<sup>2</sup> = 0.01 are, a = 0.0001 hectare, ha.

1 sq. millimeter, mm<sup>2</sup> = 0.01 cm<sup>2</sup> = 0.00153 sq. inch = 1217.36 circ. mils.

1 are, a = 1 sq. decameter, dkm = 0.0247104 acre.

Sq. Meters, m <sup>2</sup>	Sq. Inches, sq. in.	Sq. Feet, sq. ft.	Sq. Yards, sq. yd.	Sq. Rods, sq. r.	Acres, A	Hectares, ha.	Sq. Miles, Statute	Sq. Kilo- meters, km <sup>2</sup>
1	1550.00	10.7639	1.19590	0.03954	0. <sup>5</sup> 2471	0.0001	0.3861	0.1
0. <sup>5</sup> 6452	1	0. <sup>5</sup> 6944	0. <sup>5</sup> 7716	0. <sup>5</sup> 2551	0. <sup>5</sup> 1594	0. <sup>5</sup> 6452	0. <sup>5</sup> 2491	0. <sup>5</sup> 6452
0.00290	144	1	0.11111	0. <sup>5</sup> 3673	0. <sup>5</sup> 2296	0.00290	0.13587	0.00290
0.83613	1296	9	1	0.03306	0. <sup>5</sup> 2066	0. <sup>5</sup> 8361	0. <sup>5</sup> 3228	0.83613
25.2930	39204	272.25	30.25	1	0.00625	0. <sup>5</sup> 2529	0. <sup>5</sup> 0766	0. <sup>5</sup> 2529
4046.87	6272840	43560	4840	160	1	0.40469	0. <sup>5</sup> 1563	0. <sup>5</sup> 4047
10000	15499060	107639	11959.9	395.366	2.47104	1	0.3861	0.01
2589999	27878400	3097600	102400	640	259.000	1	2.59000	
1000000	10763867	1195985	39536.6	247.104	100	0.38610	1	

1 sq. rod, sq. pole, or sq. perch = 625 sq. links =  $\frac{1}{160}$  acre.

1 sq. chain, Gunter's = 16 sq. rods =  $\frac{1}{10}$  acre.

1 acre = 4 sq. rods = 160 sq. rods. Square of 1 acre = 208.7103 feet square.

Notations  $\frac{5}{10}$ ,  $\frac{5}{100}$ , etc., indicate that the  $\frac{5}{10}$ ,  $\frac{5}{100}$ , etc., are to be replaced by 2, 3, 4, etc., ciphers.

EXAMPLE—1 sq. rod = 0.<sup>5</sup>9766 = 0.00009766 sq. miles.

# MEASURES AND WEIGHTS

## EQUIVALENTS OF MEASURE

### VOLUME AND CAPACITY

1 cu. meter, m<sup>3</sup> = 1000 cu. decimeter, dm<sup>3</sup> = 1000000 cu. centimeters, cm<sup>3</sup>.  
 1 liter, l = 10 deciliters, dl = 100 centiliters, cl = 1000 milliliters, ml  
 = 1000 cu. centimeters, cm<sup>3</sup>, or cc.  
 1 liter, l = 0.1 decaliter, dcl = 0.01 hectoliter, hl = 1 cu. decimeter, dm<sup>3</sup>.

Cubic Decimeter, dm <sup>3</sup> , l	Cubic Inches, cu. in.	Cubic Feet, cu. ft.	Cubic Yards, cu. yd.	U. S. Quarts		U. S. Gallons		U. S. Bushels, bu.
				Liquid, l. qt.	Dry, d. qt.	Liquid, l. gal.	Dry, d. gal.	
1	61.0234	0.03531	0.1308	1.05668	0.90808	0.26417	0.22702	0.02838
0.01639	1	0.05787	0.02143	0.01732	0.01488	0.04329	0.03720	0.004650
28.3170	1728	1	0.03704	29.9221	25.7140	7.48055	6.42851	0.80356
764.559	46656	27	1	807.896	694.279	201.974	173.570	21.0962
0.94636	57.75	0.03342	0.1238	1	0.85937	0.25	0.21484	0.02686
1.10123	67.2006	0.03889	0.1440	1.16365	1	0.29091	0.25	0.03125
3.78543	231	0.13368	0.4951	4	3.43747	1	0.85937	0.10742
4.40492	268.803	0.15556	0.5761	4.65460	4	1.16365	1	0.125
35.2393	2150.42	1.24446	0.04609	37.2368	32	9.30920	8	1

U. S. Dry Measure: 1 bushel = 4 pecks = 8 gallons = 32 quarts = 64 pints.  
 U. S. Liquid Measure: 1 gallon = 4 quarts = 8 pints = 32 gills = 128 fluid ounces.  
 U. S. Apoth. Measure: 1 fl. ounce, f℥ = 8 fl. drams, f℥ = 480 minims, m℥  
 = 29.574 cu. cm.  
 British Imperial gallon dry and liquid measure = 1.03202 U. S. dry gal.  
 = 1.20091 U. S. liquid gal.  
 British Imperial gallon = 277.410 cu. in. = 4545.9631 cm<sup>3</sup>.  
 Weight of water at maximum density, 4°C, 45° Lat., and sea level.  
 1 cu. ft. = 62.4283 lbs. av. = 28.3170 kg 1 cu. in. = 0.57804 oz. av. = 16.3872 g.  
 1 gal., U. S. liquid = 8.34545 lbs. = 3.78543 kg.  
 1 gal., British Imperial = 10.0221 lbs. = 4.5459631 kg.

### MASS AND WEIGHTS

1 gram, g = 10 decigrams, dg = 100 centigrams, cg = 1000 milligrams, mg.  
 1 gram, g = 0.1 decagram, dkg = 0.01 hectogram, hg = 0.001 kilogram, kg.  
 1 kilogram, kg = 1 cu. decimeter of water or liter, 4°C, 45° Lat. and sea level  
 = 15432.35839 grains, U. S. and British Standard.

Kilo- grams, kg.	Grains, gr.	Ounces		Pounds		Tons		
		Troy, oz. t.	Avoir, oz. av.	Troy, lb. t.	Avoir, lb. av.	Net, Short, 2000 lbs.	Gross, Long, 2240 lbs.	Metric, 1000 kg.
1	15432.4	32.1507	35.2740	2.67923	2.20462	0.001102	0.009842	0.001
0.00480	1	0.02083	0.02286	0.01736	0.01429	0.00000045	0.00000393	0.00000480
0.03110	480	1	1.09714	0.08333	0.06857	0.0000045	0.0000393	0.0003110
0.02835	437.5	0.91146	1	0.07505	0.06250	0.0000041	0.0000370	0.0002835
0.37324	5760	12	13.1657	1	0.82286	0.0000411	0.0003674	0.0037324
0.45359	7000	14.5833	16	1.21528	1	0.000050	0.0004464	0.0045359
907.185	14000000	29166.7	32000	2430.56	2000	1	0.89286	0.90719
1016.05	15680000	32666.7	35840	2722.22	2240	1.12	1	1.01605
1000	15432356	32150.7	35274.0	2679.23	2204.62	1.10231	0.98421	1

1 ounce avoird. = 16 drams, avoird. 1 ounce troy = 20 pennyweight, dwt.  
 1 ounce apoth., ℥ = 8 drams, 3 = 24 scruples, ℥ = 480 grains, gr = 31.1035 g.  
 1 hundredweight = 120 long ton = 4 quarters = 8 stone = 112 lbs. = 50.8024 kg.

Notations  $\frac{1}{2}$ ,  $\frac{1}{4}$ , etc., indicate that the  $\frac{1}{2}$ ,  $\frac{1}{4}$ , etc., are to be replaced by  
 2, 3, 4, etc., ciphers.

EXAMPLE—1 grain = 0.02083 = 0.002083 oz. t. 1 grain = 0.06480 = 0.0006480 kg.

# CARNEGIE STEEL COMPANY

## EQUIVALENTS OF MEASURE

### FORCES OR WEIGHTS PER UNITS OF LENGTH, LINEAR WEIGHTS

1 dyne per centimeter = 0.00101979 g/cm = 0.000183719 poundal/in.  
 1 gram per centimeter = 980.5966 dynes/cm = 0.180154 poundal/in.  
 1 poundal per inch = 6443.11 dynes/cm = 5.55081 g/cm = 0.0310832 pound/in.

Grams per Centi- meter g/cm	Grains per Inch, gr./in.	Pounds per Inch, lb./in.	Pounds per Foot, lb./ft.	Pounds per Yard, lb./yd.	Kilograms per Meter, kg/m	Net Tons, 2000 lbs., per Mile	Gross Tons, 2240 lbs., per Mile	Metric Tons, 1000 kg, per Kilometer
1	39.1983	0.55600	0.06720	0.20159	0.10	0.17740	0.15839	0.10
0.02551	1	0.51429	0.51714	0.5143	0.52551	0.4526	0.4041	0.2551
178.579	7000	1	12	36	17.8579	31.6800	28.2857	17.8579
14.8816	583.333	0.08333	1	3	1.48816	2.64000	2.35714	1.48816
4.96054	194.444	0.02778	0.33333	1	0.49605	0.88000	0.78571	0.49605
10	391.983	0.05600	0.67197	2.01591	1	1.77400	1.58393	1
5.63698	220.960	0.03157	0.37879	1.13636	0.56370	1	0.80286	0.56370
6.31342	247.475	0.03535	0.42424	1.27273	0.63134	1.12	1	0.63134
10	391.983	0.05600	0.67197	2.01591	1	1.77400	1.58393	1

### FORCES OR WEIGHTS PER UNITS OF AREA, PRESSURE

1 dyne per sq. centimeter = 0.00101979 g/cm<sup>2</sup> = 0.000466846 pounds/in.<sup>2</sup>  
 1 gram per sq. centimeter = 980.5966 dynes/cm<sup>2</sup> = 0.457592 pounds/in.<sup>2</sup>  
 1 poundal per sq. inch = 2142.85 dynes/cm<sup>2</sup> = 2.18536 g/cm<sup>2</sup> = 0.0310832 pound/in.<sup>2</sup>

Kilograms per Sq. Centi- meter, kg/cm <sup>2</sup>	Pounds per Sq. Inch, lb./in. <sup>2</sup>	Pounds per Sq. Foot, lb./ft. <sup>2</sup>	Net Tons, 2000 lbs., per Sq. Foot	Atmos- pheres, Standard, 760 mm	Columns of Mercury, Hg. 13.5959 Sp. G.	Columns of Water, Max. Density 4° C.		
					Milli- meters	Inches Meters	Feet	
1	14.2234	2048.17	1.02408	0.90778	735.514	28.9572	10	32.8083
0.07031	1	144	0.07200	0.06804	51.7116	2.03588	0.70307	2.30665
0.54882	0.56944	1	0.00050	0.54725	0.35911	0.01414	0.54882	0.01602
0.97648	13.8889	2000	1	0.94502	718.216	28.2762	9.76482	32.0367
1.03329	14.6909	2116.35	1.06818	1	760	29.9212	10.3329	33.9006
0.51360	0.01934	2.78468	1.51392	0.51316	1	0.03937	0.01360	0.04461
0.03453	0.49119	70.7310	0.03537	0.03342	25.4001	1	0.34534	1.13299
0.10	1.42234	204.817	0.10241	0.09678	73.5514	2.89572	1	3.28083
0.03048	0.43353	62.4283	0.03121	0.02950	22.4185	0.88262	0.30480	1

### FORCES OR WEIGHTS PER UNITS OF VOLUME, DENSITY

1 dyne per cu. centimeter = 0.00101979 gram/cm<sup>3</sup> = 0.00118528 pounds/in.<sup>3</sup>  
 1 gram per cu. centimeter = 980.5966 dynes/cm<sup>3</sup> = 1.182283 pounds/in.<sup>3</sup>  
 1 poundal per cu. inch = 843.683 dynes/cm<sup>3</sup> = 0.860378 g/cm<sup>3</sup> = 0.0310832 pound/in.<sup>3</sup>

Grams per Cu. Centi- meter, g/cm <sup>3</sup>	Pounds per Cu. Inch, lb./in. <sup>3</sup>	Pounds per Cu. Foot, lb./ft. <sup>3</sup>	Pounds per Cu. Yard, lb./yd. <sup>3</sup>	Kilograms per Cu. Meter, kg/m <sup>3</sup>	Pounds per Bushel, U. S.	Pounds per Gallon, U. S.	Pounds per Gallon, Liquid, U. S.	Kilograms per Hectoliter, kg/hl
1	0.03613	62.4283	1685.56	1000	77.6893	9.71118	8.34545	100
27.6797	1	1728	46656	27679.7	2150.42	268.803	231	2767.97
0.01602	0.55787	1	27	16.0184	1.24446	0.15556	0.13368	1.60184
0.55933	0.52143	0.03704	1	0.59327	0.04609	0.55762	0.4951	0.05933
0.001	0.53613	0.06243	1.68556	1	0.07769	0.97111	0.8345	0.10
0.01287	0.46650	0.80356	21.6962	12.8718	1	0.125	0.10742	1.28718
0.10297	0.3720	0.42851	173.570	102.974	8	1	0.85937	10.2974
0.11983	0.4329	7.48052	201.974	119.826	9.30920	1.16365	1	11.9826
0.01	0.53613	0.62428	16.5557	10	0.77689	0.09711	0.08345	1

Notations  $\frac{1}{2}$ ,  $\frac{1}{4}$ ,  $\frac{3}{4}$ , etc., indicate that the  $\frac{1}{2}$ ,  $\frac{1}{4}$ ,  $\frac{3}{4}$ , etc., are to be replaced by 2, 3, 4, etc. ciphers. EXAMPLE—1 kg/m<sup>3</sup> = 0.53613 = 0.0003613 lb./in.<sup>3</sup>

# MEASURES AND WEIGHTS

## EQUIVALENTS OF MEASURE

### ENERGY, WORK, HEAT

1 dyne-centimeter = 1 erg = 0.00101979 gram-centimeter = 0.737612 foot-pound.

1 gram-centimeter = 980.5966 ergs = 0.7233 foot-pound.

1 foot-pound = 13557300 ergs = 13825.5 gram-centimeters.

Kilogram-meters, kg-m	Foot-Pounds, ft.-lbs.	Horsepower-hour		Poncelet-hours, 100 kg-m-h	Kilowatt-hours, kw-h	Joules, 10 <sup>7</sup> ergs, j-s	Thermal Units	
		U. S., H. P.-h	Metric, 75 kg-m-h				B. T. U., b. t. u.	Calorie, kg-cal
1	7.23300	0.53653	0.53704	0.52778	0.52724	9.80597	0.92996	0.2342
0.13826	1	0.55051	0.55121	0.53840	0.53766	1.35573	0.1285	0.3239
273745	1980000	1*	1.01387	0.76040	0.74565	2684340	2544.65	641.240
270000	1952910	0.98632	1	0.75	0.73545	2647610	2509.83	632.467
360000	2603880	1.31509	1.33333	1	0.98060	3530147	3346.44	843.289
367123	2655403	1.34111	1.35972	1.01979	1	3600000	3412.66	859.975
0.10198	0.73761	0.53725	0.53777	0.52833	0.52778	1	0.9480	0.2389
107.577	778.104	0.53930	0.53984	0.52988	0.52930	1054.90	1	0.25200
426.900	3087.77	0.51569	0.51581	0.51180	0.51163	4186.17	3.96832	1

### POWER, RATE OF ENERGY AND HEAT

1 erg per sec. = 1 dyne-cm/sec. = 0.00101979 gram-cm/sec. = 0.737612 foot-pounds/sec.

1 gram-centimeter per second = 980.5966 ergs/sec. = 0.7238 foot-pounds/sec.

1 foot-pound per second = 13557300 ergs/sec = 13825.5 gram-cm/sec.

Kilogram-meters per Second, kg-m/s	Foot-pounds per Second, ft.-lbs./s	Horsepower		Poncelet, 100 kg-m/s	Kilowatt, kw.	Watts, 10 <sup>7</sup> ergs/s	Thermal Units per Sec.	
		U. S., 550 ft.-lbs./s	Metric, 75 kg-m/s				B. T. U., btu/s	Calorie kg-cal/s
1	7.23300	0.01315	0.01333	0.01	0.9806	9.80597	0.92996	0.2342
0.13826	1	0.51818	0.51843	0.51383	0.51356	1.35573	0.1285	0.3237
78.0404	550	1	1.01387	0.76040	0.74565	745.660	0.70685	0.17812
75	542.475	0.98632	1	0.75	0.73545	735.448	0.69718	0.17569
100	723.300	1.31509	1.33333	1	0.98060	980.597	0.92957	0.23425
101.979	737.612	1.34111	1.35972	1.01979	1	1000	0.94796	0.23888
0.10198	0.73761	0.51341	0.51360	0.51020	0.001	1	0.9480	0.2389
107.577	778.104	1.41474	1.43436	1.07577	1.05490	1054.90	1	0.25200
426.900	3087.77	5.61412	5.69200	4.26900	4.18617	4186.17	3.96832	1

### VELOCITIES AND ACCELERATIONS

1 kine = 1 centimeter per second = 0.0328083 foot per second.

1 radian per second = 57.2958 degrees per sec. = 0.159155 revolutions per sec.

1 gravity = 980.5966 centimeters per sec. per sec. = 32.1717 feet per sec. per sec.

Meters per Second, m/s	Feet per Second, ft./s	Miles per Hour, M/h	Knots per Hour, U. S.	Kilometers per Hour, km/h	Meter per sec/sec, m/s²	Feet per sec/sec, ft./s²	Miles per hour/sec, M/h-s	Kilometer per hour/sec, km/h-s
1	3.28083	2.23693	1.94254	3.6				
0.30480	1	0.68182	0.59209	1.09728				
0.44704	1.46667	1	0.86839	1.60935				
0.51479	1.68894	1.15155	1	1.85325				
0.27778	0.91134	0.62137	0.53959	1				
					1	3.28083	2.23693	3.6
					0.30480	1	0.68182	1.09728
					0.44704	1.46667	1	1.60935
					0.27778	0.91134	0.62137	1

Notations 2, 3, 4, etc., indicate that the 9, 8, 6, etc., are to be replaced by 2, 3, 4, etc., ciphers. EXAMPLE—1 Calorie = 0.21163 = 0.01163 kilowatt-hours.

# CARNEGIE STEEL COMPANY

## METRIC CONVERSION TABLES

INCHES TO CENTIMETERS—1 in.=2.540005 cm

Units Tons	0	1	2	3	4	5	6	7	8	9
0		2.540	5.080	7.620	10.160	12.700	15.240	17.780	20.320	22.860
1	25.400	27.940	30.480	33.020	35.560	38.100	40.640	43.180	45.720	48.260
2	50.800	53.340	55.880	58.420	60.960	63.500	66.040	68.580	71.120	73.660
3	76.200	78.740	81.280	83.820	86.360	88.900	91.440	93.980	96.520	99.060
4	101.600	104.140	106.680	109.220	111.760	114.300	116.840	119.380	121.920	124.460
5	127.000	129.540	132.080	134.620	137.160	139.700	142.240	144.780	147.320	149.860
6	152.400	154.940	157.480	160.020	162.560	165.100	167.640	170.180	172.720	175.260
7	177.800	180.340	182.880	185.420	187.960	190.500	193.040	195.580	198.120	200.660
8	203.200	205.740	208.280	210.820	213.360	215.900	218.440	220.980	223.520	226.060
9	228.600	231.140	233.680	236.220	238.760	241.300	243.840	246.380	248.920	251.460

INCHES<sup>2</sup> TO CENTIMETERS<sup>2</sup>—1 in.<sup>2</sup>=6.451625 cm<sup>2</sup>

Units Tons	0	1	2	3	4	5	6	7	8	9
0		6.452	12.903	19.355	25.807	32.258	38.710	45.161	51.613	58.065
1	64.516	70.968	77.420	83.871	90.323	96.774	103.226	109.678	116.129	122.581
2	129.033	135.484	141.936	148.387	154.839	161.291	167.742	174.194	180.646	187.097
3	193.649	200.000	206.452	212.904	219.355	225.807	232.259	238.710	245.162	251.613
4	258.065	264.517	270.968	277.420	283.872	290.323	296.775	303.226	309.678	316.130
5	322.581	329.033	335.485	341.936	348.388	354.839	361.291	367.743	374.194	380.646
6	387.098	393.549	400.001	406.452	412.904	419.356	425.807	432.259	438.711	445.162
7	451.614	458.065	464.517	470.969	477.420	483.872	490.324	496.775	503.227	509.678
8	516.130	522.582	529.033	535.485	541.937	548.388	554.840	561.291	567.743	574.195
9	588.648	595.099	601.550	608.001	614.453	620.904	627.356	633.808	640.259	646.711

INCHES<sup>3</sup> TO CENTIMETERS<sup>3</sup>—1 in.<sup>3</sup>=16.38716 cm<sup>3</sup>

Units Tons	0	1	2	3	4	5	6	7	8	9
0		16.39	32.77	49.16	65.55	81.94	98.32	114.71	131.10	147.48
1	163.87	180.26	196.65	213.03	229.42	245.81	262.19	278.58	294.97	311.36
2	327.74	344.13	360.52	376.90	393.29	409.68	426.07	442.46	458.84	475.23
3	491.61	508.00	524.39	540.78	557.16	573.55	589.94	606.32	622.71	639.10
4	655.49	671.87	688.26	704.65	721.04	737.42	753.81	770.20	786.58	802.97
5	819.36	835.75	852.13	868.52	884.91	901.29	917.68	934.07	950.45	966.84
6	983.23	999.62	1016.00	1032.39	1048.78	1065.17	1081.55	1097.94	1114.33	1130.71
7	1147.10	1163.49	1179.88	1196.26	1212.65	1229.04	1245.42	1261.81	1278.20	1294.59
8	1310.97	1327.36	1343.75	1360.13	1376.52	1392.91	1409.30	1425.68	1442.07	1458.46
9	1474.84	1491.23	1507.62	1524.01	1540.39	1556.78	1573.17	1589.55	1605.94	1622.33

INCHES<sup>4</sup> TO CENTIMETERS<sup>4</sup>—1 in.<sup>4</sup>=41.02347 cm<sup>4</sup>

Units Tons	0	1	2	3	4	5	6	7	8	9
0		41.62	83.25	124.87	166.49	208.12	249.74	291.36	332.99	374.61
1	416.23	457.86	499.48	541.11	582.73	624.35	665.98	707.60	749.22	790.85
2	832.47	874.09	915.72	957.34	998.96	1040.59	1082.21	1123.83	1165.45	1207.08
3	1248.70	1290.33	1331.95	1373.57	1415.20	1456.82	1498.44	1540.07	1581.69	1623.32
4	1664.94	1706.56	1748.19	1789.81	1831.43	1873.06	1914.68	1956.30	1997.93	2039.55
5	2081.17	2122.80	2164.42	2206.04	2247.67	2289.29	2330.91	2372.54	2414.16	2455.79
6	2497.41	2539.03	2580.66	2622.28	2663.90	2705.53	2747.15	2788.77	2830.40	2872.02
7	2913.64	2955.27	2996.89	3038.51	3080.14	3121.76	3163.38	3205.01	3246.63	3288.25
8	3329.88	3371.50	3413.12	3454.75	3496.37	3537.99	3579.62	3621.24	3662.87	3704.49
9	3746.11	3787.74	3829.36	3870.98	3912.61	3954.23	3995.85	4037.48	4079.10	4120.72

# MEASURES AND WEIGHTS

## METRIC CONVERSION TABLES

### CENTIMETERS TO INCHES—1 cm=0.3937 in.

Units Tens	0	1	2	3	4	5	6	7	8	9
0		0.3937	0.7874	1.1811	1.5748	1.9685	2.3622	2.7559	3.1496	3.5433
1	3.9370	4.3307	4.7244	5.1181	5.5118	5.9055	6.2992	6.6929	7.0866	7.4803
2	7.8740	8.2677	8.6614	9.0551	9.4488	9.8425	10.2362	10.6299	11.0236	11.4173
3	11.8110	12.2047	12.5984	12.9921	13.3858	13.7795	14.1732	14.5669	14.9606	15.3543
4	15.7480	16.1417	16.5354	16.9291	17.3228	17.7165	18.1102	18.5039	18.8976	19.2913
5	19.6850	20.0787	20.4724	20.8661	21.2598	21.6535	22.0472	22.4409	22.8346	23.2283
6	23.6220	24.0157	24.4094	24.8031	25.1968	25.5905	25.9842	26.3779	26.7716	27.1653
7	27.5590	27.9527	28.3464	28.7401	29.1338	29.5275	29.9212	30.3149	30.7086	31.1023
8	31.4960	31.8897	32.2834	32.6771	33.0708	33.4645	33.8582	34.2519	34.6456	35.0393
9	35.4330	35.8267	36.2204	36.6141	37.0078	37.4015	37.7952	38.1889	38.5826	38.9763

### CENTIMETERS<sup>2</sup> TO INCHES<sup>2</sup>—1 cm<sup>2</sup>=0.15499069 in.<sup>2</sup>.

Units Tens	0	1	2	3	4	5	6	7	8	9
0		0.1550	0.3100	0.4650	0.6200	0.7750	0.9300	1.0850	1.2400	1.3950
1	1.5500	1.7050	1.8600	2.0150	2.1700	2.3250	2.4800	2.6350	2.7900	2.9450
2	3.1000	3.2550	3.4100	3.5650	3.7200	3.8750	4.0300	4.1850	4.3400	4.4950
3	4.6500	4.8050	4.9600	5.1150	5.2700	5.4250	5.5800	5.7350	5.8900	6.0450
4	6.2000	6.3550	6.5100	6.6650	6.8200	6.9750	7.1300	7.2850	7.4400	7.5950
5	7.7500	7.9050	8.0600	8.2150	8.3700	8.5250	8.6800	8.8350	8.9900	9.1450
6	9.3000	9.4550	9.6100	9.7650	9.9200	10.0750	10.2300	10.3850	10.5400	10.6950
7	10.8500	11.0050	11.1600	11.3150	11.4700	11.6250	11.7800	11.9350	12.0900	12.2450
8	12.4000	12.5550	12.7100	12.8650	13.0200	13.1750	13.3300	13.4850	13.6400	13.7950
9	13.9500	14.1050	14.2600	14.4150	14.5700	14.7250	14.8800	15.0350	15.1900	15.3450

### CENTIMETERS<sup>3</sup> TO INCHES<sup>3</sup>—1 cm<sup>3</sup>=0.0610234 in.<sup>3</sup>.

Units Tens	0	1	2	3	4	5	6	7	8	9
0		0.06102	0.12205	0.18307	0.24409	0.30512	0.36614	0.42716	0.48819	0.54921
1	0.61023	0.67126	0.73228	0.79330	0.85433	0.91535	0.97637	1.03740	1.09842	1.15944
2	1.22047	1.28149	1.34251	1.40354	1.46456	1.52559	1.58661	1.64763	1.70866	1.76968
3	1.83070	1.89173	1.95275	2.01377	2.07480	2.13582	2.19684	2.25787	2.31889	2.37991
4	2.44094	2.50196	2.56298	2.62401	2.68503	2.74605	2.80708	2.86810	2.92912	2.99015
5	3.05117	3.11219	3.17322	3.23424	3.29526	3.35629	3.41731	3.47833	3.53936	3.60038
6	3.66140	3.72243	3.78345	3.84447	3.90550	3.96652	4.02754	4.08857	4.14959	4.21061
7	4.27164	4.33266	4.39368	4.45471	4.51573	4.57675	4.63778	4.69880	4.75983	4.82085
8	4.88187	4.94290	5.00392	5.06494	5.12597	5.18699	5.24801	5.30904	5.37006	5.43108
9	5.49211	5.55313	5.61415	5.67518	5.73620	5.79722	5.85825	5.91927	5.98029	6.04132

### CENTIMETERS<sup>4</sup> TO INCHES<sup>4</sup>—1 cm<sup>4</sup>=0.0240249 in.<sup>4</sup>.

Units Tens	0	1	2	3	4	5	6	7	8	9
0		0.02402	0.04805	0.07207	0.09610	0.12012	0.14415	0.16817	0.19220	0.21622
1	0.24025	0.26427	0.28830	0.31232	0.33635	0.36037	0.38440	0.40842	0.43245	0.45647
2	0.48050	0.50452	0.52855	0.55257	0.57660	0.60062	0.62465	0.64867	0.67270	0.69672
3	0.72075	0.74477	0.76880	0.79282	0.81685	0.84087	0.86490	0.88892	0.91295	0.93697
4	0.96100	0.98502	1.00905	1.03307	1.05710	1.08112	1.10515	1.12917	1.15320	1.17722
5	1.20125	1.22527	1.24930	1.27332	1.29734	1.32137	1.34539	1.36942	1.39344	1.41747
6	1.44149	1.46552	1.48954	1.51357	1.53759	1.56162	1.58565	1.60967	1.63369	1.65772
7	1.68174	1.70577	1.72979	1.75382	1.77784	1.80187	1.82589	1.84992	1.87394	1.89797
8	1.92199	1.94602	1.97004	1.99407	2.01809	2.04212	2.06614	2.09017	2.11419	2.13822
9	2.16224	2.18627	2.21029	2.23432	2.25834	2.28237	2.30639	2.33042	2.35444	2.37847

# CARNEGIE STEEL COMPANY

## METRIC CONVERSION TABLES FEET TO METERS—1 ft.=0.3048006 m

Units Feet	0	1	2	3	4	5	6	7	8	9
0		0.3048	0.6096	0.9144	1.2192	1.5240	1.8288	2.1336	2.4384	2.7432
1	3.0480	3.3528	3.6576	3.9624	4.2672	4.5720	4.8768	5.1816	5.4864	5.7912
2	6.0960	6.4008	6.7056	7.0104	7.3152	7.6200	7.9248	8.2296	8.5344	8.8392
3	9.1440	9.4488	9.7536	10.0584	10.3632	10.6680	10.9728	11.2776	11.5824	11.8872
4	12.1920	12.4968	12.8016	13.1064	13.4112	13.7160	14.0208	14.3256	14.6304	14.9352
5	15.2400	15.5448	15.8496	16.1544	16.4592	16.7640	17.0688	17.3736	17.6784	17.9832
6	18.2880	18.5928	18.8976	19.2024	19.5072	19.8120	20.1168	20.4216	20.7264	21.0312
7	21.3360	21.6408	21.9456	22.2504	22.5552	22.8600	23.1648	23.4696	23.7744	24.0792
8	24.3840	24.6888	24.9936	25.2984	25.6032	25.9080	26.2128	26.5176	26.8224	27.1272
9	27.4320	27.7368	28.0416	28.3464	28.6512	28.9560	29.2608	29.5656	29.8704	30.1752

## POUNDS PER FOOT TO KILOGRAMS PER METER—1 lb./ft.=1.488161 kg/m

Units Feet	0	1	2	3	4	5	6	7	8	9
0		1.488	2.976	4.464	5.953	7.441	8.929	10.417	11.905	13.393
1	14.882	16.370	17.858	19.346	20.834	22.322	23.811	25.299	26.787	28.275
2	29.763	31.251	32.740	34.228	35.716	37.204	38.692	40.180	41.669	43.157
3	44.645	46.133	47.621	49.109	50.597	52.086	53.574	55.062	56.550	58.038
4	59.526	61.015	62.503	63.991	65.479	66.967	68.455	69.944	71.432	72.920
5	74.408	75.896	77.384	78.873	80.361	81.849	83.337	84.825	86.313	87.802
6	89.290	90.778	92.266	93.754	95.242	96.730	98.219	99.707	101.195	102.683
7	104.171	105.659	107.148	108.636	110.124	111.612	113.100	114.588	116.077	117.565
8	119.053	120.541	122.029	123.517	125.006	126.494	127.982	129.470	130.958	132.446
9	133.934	135.423	136.911	138.399	139.887	141.375	142.863	144.352	145.840	147.328

## POUNDS PER SQ. INCH TO KG. PER SQ. CM.—1 lb./in.<sup>2</sup>=0.0703067 kg/cm<sup>2</sup>

Units Feet	0	1	2	3	4	5	6	7	8	9
0		0.07031	0.14061	0.21092	0.28123	0.35153	0.42184	0.49215	0.56245	0.63276
1	0.70307	0.77337	0.84368	0.91399	0.98429	1.05460	1.12491	1.19521	1.26552	1.33583
2	1.40613	1.47644	1.54675	1.61705	1.68736	1.75767	1.82797	1.89828	1.96859	2.03889
3	2.10020	2.17051	2.24081	2.31012	2.38043	2.45073	2.52104	2.59135	2.66165	2.73196
4	2.81227	2.88257	2.95288	3.02319	3.09349	3.16380	3.23411	3.30441	3.37472	3.44503
5	3.51534	3.58564	3.65595	3.72626	3.79656	3.86687	3.93718	4.00748	4.07779	4.14810
6	4.21840	4.28871	4.35902	4.42932	4.49963	4.56994	4.64024	4.71055	4.78086	4.85116
7	4.92147	4.99178	5.06208	5.13239	5.20270	5.27300	5.34331	5.41362	5.48392	5.55423
8	5.62454	5.69484	5.76515	5.83546	5.90576	5.97607	6.04638	6.11668	6.18699	6.25730
9	6.32760	6.39791	6.46822	6.53852	6.60883	6.67914	6.74944	6.81975	6.89006	6.96036

## INCH-POUNDS TO KILOGRAM-CENTIMETERS—1 in.-lb.=1.152127 kg-cm

Units Feet	0	1	2	3	4	5	6	7	8	9
0		1.152	2.304	3.456	4.609	5.761	6.913	8.065	9.217	10.369
1	11.521	12.673	13.826	14.978	16.130	17.282	18.434	19.586	20.738	21.890
2	23.043	24.195	25.347	26.499	27.651	28.803	29.955	31.107	32.260	33.412
3	34.564	35.716	36.868	38.020	39.172	40.324	41.477	42.629	43.781	44.933
4	46.085	47.237	48.389	49.541	50.694	51.846	52.998	54.150	55.302	56.454
5	57.806	58.958	59.911	61.063	62.215	63.367	64.519	65.671	66.823	67.975
6	69.128	70.280	71.432	72.584	73.736	74.888	76.040	77.192	78.344	79.497
7	80.649	81.801	82.953	84.105	85.257	86.410	87.562	88.714	89.866	91.018
8	92.170	93.322	94.474	95.627	96.779	97.931	99.083	100.235	101.387	102.539
9	103.691	104.844	105.996	107.148	108.300	109.452	110.604	111.756	112.908	114.061

# MEASURES AND WEIGHTS

## METRIC CONVERSION TABLES

METERS TO FEET—1 m=3.2808333 ft.

Units Feet	0	1	2	3	4	5	6	7	8	9
0		3.281	6.562	9.843	13.123	16.404	19.685	22.966	26.247	29.528
1	32.808	36.089	39.370	42.651	45.932	49.213	52.493	55.774	59.055	62.336
2	65.617	68.898	72.178	75.459	78.740	82.021	85.302	88.583	91.863	95.144
3	98.425	101.706	104.987	108.268	111.548	114.829	118.110	121.391	124.672	127.953
4	131.233	134.514	137.795	141.076	144.357	147.638	150.918	154.199	157.480	160.761
5	164.042	167.323	170.603	173.884	177.165	180.446	183.727	187.008	190.288	193.569
6	196.850	200.131	203.412	206.693	209.974	213.254	216.535	219.816	223.097	226.378
7	229.658	232.939	236.220	239.501	242.782	246.063	249.343	252.624	255.905	259.186
8	262.467	265.748	269.028	272.309	275.590	278.871	282.152	285.433	288.713	291.994
9	295.275	298.556	301.837	305.118	308.398	311.679	314.960	318.241	321.522	324.803

KILOGRAMS PER METER TO POUNDS PER FOOT—1 kg/m=0.67197 lb./ft.

Units Feet	0	1	2	3	4	5	6	7	8	9
0		0.6720	1.3439	2.0159	2.6879	3.3599	4.0318	4.7038	5.3758	6.0477
1	6.7197	7.3917	8.0636	8.7356	9.4076	10.0796	10.7515	11.4235	12.0955	12.7674
2	13.4394	14.1114	14.7833	15.4553	16.1273	16.7993	17.4712	18.1432	18.8152	19.4871
3	20.1591	20.8311	21.5030	22.1750	22.8470	23.5190	24.1909	24.8629	25.5349	26.2068
4	26.8788	27.5508	28.2227	28.8947	29.5667	30.2387	30.9106	31.5826	32.2546	32.9265
5	33.5985	34.2705	34.9424	35.6144	36.2864	36.9584	37.6303	38.3023	38.9743	39.6462
6	40.3182	40.9902	41.6621	42.3341	43.0061	43.6781	44.3500	45.0220	45.6940	46.3659
7	47.0379	47.7099	48.3818	49.0538	49.7258	50.3978	51.0697	51.7417	52.4137	53.0856
8	53.7578	54.4298	55.1015	55.7735	56.4455	57.1175	57.7894	58.4614	59.1334	59.8053
9	60.4773	61.1493	61.8212	62.4932	63.1652	63.8372	64.5091	65.1811	65.8531	66.5250

Kg. PER SQ. CM. TO POUNDS PER SQ. INCH—1 kg/cm<sup>2</sup>=14.2234 lbs./in.<sup>2</sup>

Units Feet	0	1	2	3	4	5	6	7	8	9
0		14.22	28.45	42.67	56.89	71.12	85.34	99.56	113.79	128.01
1	142.23	156.46	170.68	184.90	199.13	213.35	227.57	241.80	256.02	270.24
2	284.47	298.69	312.91	327.14	341.36	355.59	369.81	384.03	398.26	412.48
3	426.70	440.93	455.15	469.37	483.60	497.82	512.04	526.27	540.49	554.71
4	568.94	583.16	597.38	611.61	625.83	640.05	654.28	668.50	682.72	696.95
5	711.17	725.39	739.62	753.84	768.06	782.29	796.51	810.73	824.96	839.18
6	853.40	867.63	881.85	896.07	910.30	924.52	938.74	952.97	967.19	981.41
7	995.64	1009.86	1024.08	1038.31	1052.53	1066.76	1080.98	1095.20	1109.43	1123.65
8	1137.87	1152.10	1166.32	1180.54	1194.77	1208.99	1223.21	1237.44	1251.66	1265.88
9	1280.11	1294.33	1308.55	1322.78	1337.00	1351.22	1365.45	1379.67	1393.89	1408.12

KILOGRAM-CENTIMETERS TO INCH-POUNDS—1 kg/cm=0.86796 in./lb.

Units Feet	0	1	2	3	4	5	6	7	8	9
0		0.8680	1.7359	2.6039	3.4718	4.3398	5.2078	6.0757	6.9437	7.8116
1	8.6796	9.5476	10.4155	11.2835	12.1514	13.0194	13.8874	14.7553	15.6233	16.4912
2	17.3592	18.2272	19.0951	19.9631	20.8310	21.6990	22.5670	23.4349	24.3029	25.1708
3	26.0388	26.9068	27.7747	28.6427	29.5106	30.3786	31.2466	32.1145	32.9825	33.8504
4	34.7184	35.5864	36.4543	37.3223	38.1902	39.0582	39.9262	40.7941	41.6621	42.5300
5	43.3980	44.2660	45.1339	46.0019	46.8698	47.7378	48.6058	49.4737	50.3417	51.2096
6	52.0776	52.9456	53.8135	54.6815	55.5494	56.4174	57.2854	58.1533	59.0213	59.8892
7	60.7572	61.6252	62.4931	63.3611	64.2290	65.0970	65.9650	66.8329	67.7009	68.5688
8	69.4368	70.3048	71.1727	72.0407	72.9086	73.7766	74.6446	75.5125	76.3805	77.2484
9	78.1164	78.9844	79.8523	80.7203	81.5882	82.4562	83.3242	84.1921	85.0601	85.9280



**CARNEGIE STEEL COMPANY**

**METRIC CONVERSION TABLE**

**INCHES TO MILLIMETERS**

30.37 inches, U. S. Standard=1 meter=100 centimeters=1000 millimeters.

Inches	0	$\frac{1}{16}$	$\frac{1}{8}$	$\frac{3}{16}$	$\frac{1}{2}$	$\frac{5}{8}$	$\frac{3}{4}$	$\frac{7}{8}$
0	0.00	1.59	3.18	4.76	6.35	7.94	9.53	11.11
1	25.40	26.99	28.58	30.16	31.75	33.34	34.93	36.51
2	50.80	53.98	57.16	60.34	63.52	66.70	69.88	73.06
3	76.20	77.79	79.38	80.97	82.55	84.14	85.73	87.31
4	101.60	103.19	104.78	106.36	107.95	109.54	111.13	112.71
5	127.00	128.59	130.18	131.77	133.35	134.94	136.53	138.11
6	152.40	153.99	155.58	157.16	158.75	160.34	161.93	163.51
7	177.80	179.39	180.98	182.56	184.15	185.74	187.33	188.91
8	203.20	204.79	206.38	207.96	209.55	211.14	212.73	214.31
9	228.60	230.19	231.78	233.36	234.95	236.54	238.13	239.71
10	254.00	255.59	257.18	258.76	260.35	261.94	263.53	265.11
11	279.40	280.99	282.58	284.16	285.75	287.34	288.93	290.51
12	304.80	306.39	307.98	309.56	311.15	312.74	314.33	315.91
13	330.20	331.79	333.38	334.96	336.55	338.14	339.73	341.31
14	355.60	357.19	358.78	360.36	361.95	363.54	365.13	366.71
15	381.00	382.59	384.18	385.76	387.35	388.94	390.53	392.11
16	406.40	407.99	409.58	411.16	412.75	414.34	415.93	417.51
17	431.80	433.39	434.98	436.56	438.15	439.74	441.33	442.91
18	457.20	458.79	460.38	461.96	463.55	465.14	466.73	468.31
19	482.60	484.19	485.78	487.36	488.95	490.54	492.13	493.71
20	508.00	509.59	511.18	512.76	514.35	515.94	517.53	519.11
21	533.40	534.99	536.58	538.16	539.75	541.34	542.93	544.51
22	558.80	560.39	561.98	563.56	565.15	566.74	568.33	569.91
23	584.20	585.79	587.38	588.96	590.55	592.14	593.73	595.31
24	609.60	611.19	612.78	614.36	615.95	617.54	619.13	620.71
25	635.00	636.59	638.18	639.76	641.35	642.94	644.53	646.11
26	660.40	661.99	663.58	665.16	666.75	668.34	669.93	671.51
27	685.80	687.39	688.98	690.56	692.15	693.74	695.33	696.91
28	711.20	712.79	714.38	715.96	717.55	719.14	720.73	722.31
29	736.60	738.19	739.78	741.36	742.95	744.54	746.13	747.71
30	762.00	763.59	765.18	766.76	768.35	769.94	771.53	773.11
31	787.40	788.99	790.58	792.16	793.75	795.34	796.93	798.51
32	812.80	814.39	815.98	817.56	819.15	820.74	822.33	823.91
33	838.20	839.79	841.38	842.96	844.55	846.14	847.73	849.31
34	863.60	865.19	866.78	868.36	869.95	871.54	873.13	874.71
35	889.00	890.59	892.18	893.76	895.35	896.94	898.53	900.11
36	914.40	915.99	917.58	919.16	920.75	922.34	923.93	925.51
37	939.80	941.39	942.98	944.56	946.15	947.74	949.33	950.91
38	965.20	966.79	968.38	969.96	971.55	973.14	974.73	976.31
39	990.60	992.19	993.78	995.36	996.95	998.54	1000.13	1001.71
40	1016.00	1017.59	1019.18	1020.76	1022.35	1023.94	1025.53	1027.11
41	1041.40	1042.99	1044.58	1046.16	1047.75	1049.34	1050.93	1052.51
42	1066.80	1068.39	1069.98	1071.56	1073.15	1074.74	1076.33	1077.91
43	1092.20	1093.79	1095.38	1096.96	1098.55	1100.14	1101.73	1103.31
44	1117.60	1119.19	1120.78	1122.36	1123.95	1125.54	1127.13	1128.71
45	1143.00	1144.59	1146.18	1147.76	1149.35	1150.94	1152.53	1154.11
46	1168.40	1169.99	1171.58	1173.16	1174.75	1176.34	1177.93	1179.51
47	1193.80	1195.39	1196.98	1198.56	1200.15	1201.74	1203.33	1204.91
48	1219.20	1220.79	1222.38	1223.96	1225.55	1227.14	1228.73	1230.31
49	1244.60	1246.19	1247.78	1249.36	1250.95	1252.54	1254.13	1255.71
50	1270.00	1271.59	1273.18	1274.76	1276.35	1277.94	1279.53	1281.11

# MEASURES AND WEIGHTS

## METRIC CONVERSION TABLE

### INCHES TO MILLIMETERS

39.37 inches, U. S. Standard=1 meter=100 centimeters=1000 millimeters

Inches	$\frac{1}{8}$	$\frac{3}{16}$	$\frac{1}{4}$	$\frac{5}{16}$	$\frac{3}{8}$	$\frac{7}{16}$	$\frac{1}{2}$	$\frac{9}{16}$
0	12.70	14.29	15.88	17.46	19.05	20.64	22.23	23.81
1	38.10	39.69	41.28	42.86	44.45	46.04	47.63	49.21
2	63.50	65.09	66.68	68.26	69.85	71.44	73.03	74.61
3	88.90	90.49	92.08	93.66	95.25	96.84	98.43	100.01
4	114.30	115.89	117.48	119.06	120.65	122.24	123.83	125.41
5	139.70	141.29	142.88	144.46	146.05	147.64	149.23	150.81
6	165.10	166.69	168.28	169.86	171.45	173.04	174.63	176.21
7	190.50	192.09	193.68	195.26	196.85	198.44	200.03	201.61
8	215.90	217.49	219.08	220.66	222.25	223.84	225.43	227.01
9	241.30	242.89	244.48	246.06	247.65	249.24	250.83	252.41
10	266.70	268.29	269.88	271.46	273.05	274.64	276.23	277.81
11	292.10	293.69	295.28	296.86	298.45	300.04	301.63	303.21
12	317.50	319.09	320.68	322.26	323.85	325.44	327.03	328.61
13	342.90	344.49	346.08	347.66	349.25	350.84	352.43	354.01
14	368.30	369.89	371.48	373.06	374.65	376.24	377.83	379.41
15	393.70	395.29	396.88	398.46	400.05	401.64	403.23	404.81
16	419.10	420.69	422.28	423.86	425.45	427.04	428.63	430.21
17	444.50	446.09	447.68	449.26	450.85	452.44	454.03	455.61
18	469.90	471.49	473.08	474.66	476.25	477.84	479.43	481.01
19	495.30	496.89	498.48	500.06	501.65	503.24	504.83	506.41
20	520.70	522.29	523.88	525.46	527.05	528.64	530.23	531.81
21	546.10	547.69	549.28	550.86	552.45	554.04	555.63	557.21
22	571.50	573.09	574.68	576.26	577.85	579.44	581.03	582.61
23	596.90	598.49	600.08	601.66	603.25	604.84	606.43	608.01
24	622.30	623.89	625.48	627.06	628.65	630.24	631.83	633.41
25	647.70	649.29	650.88	652.46	654.05	655.64	657.23	658.81
26	673.10	674.69	676.28	677.86	679.45	681.04	682.63	684.21
27	698.50	700.09	701.68	703.26	704.85	706.44	708.03	709.61
28	723.90	725.49	727.08	728.66	730.25	731.84	733.43	735.01
29	749.30	750.89	752.48	754.06	755.65	757.24	758.83	760.41
30	774.70	776.29	777.88	779.46	781.05	782.64	784.23	785.81
31	800.10	801.69	803.28	804.86	806.45	808.04	809.63	811.21
32	825.50	827.09	828.68	830.26	831.85	833.44	835.03	836.61
33	850.90	852.49	854.08	855.66	857.25	858.84	860.43	862.01
34	876.30	877.89	879.48	881.06	882.65	884.24	885.83	887.41
35	901.70	903.29	904.88	906.46	908.05	909.64	911.23	912.81
36	927.10	928.69	930.28	931.86	933.45	935.04	936.63	938.21
37	952.50	954.09	955.68	957.26	958.85	960.44	962.03	963.61
38	977.90	979.49	981.08	982.66	984.25	985.84	987.43	989.01
39	1003.30	1004.89	1006.48	1008.06	1009.65	1011.24	1012.83	1014.41
40	1028.70	1030.29	1031.88	1033.46	1035.05	1036.64	1038.23	1039.81
41	1054.10	1055.69	1057.28	1058.86	1060.45	1062.04	1063.63	1065.21
42	1079.50	1081.09	1082.68	1084.26	1085.85	1087.44	1089.03	1090.61
43	1104.90	1106.49	1108.08	1109.66	1111.25	1112.84	1114.43	1116.01
44	1130.30	1131.89	1133.48	1135.06	1136.65	1138.24	1139.83	1141.41
45	1155.70	1157.29	1158.88	1160.46	1162.05	1163.64	1165.23	1166.81
46	1181.10	1182.69	1184.28	1185.86	1187.45	1189.04	1190.63	1192.21
47	1206.50	1208.09	1209.68	1211.26	1212.85	1214.44	1216.03	1217.61
48	1231.90	1233.49	1235.08	1236.66	1238.25	1239.84	1241.43	1243.01
49	1257.30	1258.89	1260.48	1262.06	1263.65	1265.24	1266.83	1268.41
50	1282.70	1284.29	1285.88	1287.46	1289.05	1290.64	1292.23	1293.81

## CARNEGIE STEEL COMPANY

# METRIC CONVERSION TABLE

## POUNDS AVOIRDUPOIS TO KILOGRAMS

1 Pound=0.45359 Kilograms

Pounds	0	1	2	3	4	5	6	7	8	9
0		0.45	0.91	1.36	1.81	2.27	2.72	3.18	3.63	4.08
1	4.54	4.99	5.44	5.90	6.35	6.80	7.26	7.71	8.16	8.62
2	9.07	9.53	9.98	10.43	10.89	11.34	11.79	12.25	12.70	13.15
3	13.61	14.06	14.51	14.97	15.42	15.88	16.33	16.78	17.24	17.69
4	18.14	18.60	19.05	19.50	19.96	20.41	20.87	21.32	21.77	22.23
5	22.68	23.13	23.59	24.04	24.49	24.95	25.40	25.85	26.31	26.76
6	27.22	27.67	28.12	28.58	29.03	29.48	29.94	30.39	30.84	31.30
7	31.75	32.21	32.66	33.11	33.57	34.02	34.47	34.93	35.38	35.83
8	36.29	36.74	37.19	37.65	38.10	38.56	39.01	39.46	39.92	40.37
9	40.82	41.28	41.73	42.18	42.64	43.09	43.54	44.00	44.45	44.91
10	45.36	45.81	46.27	46.72	47.17	47.63	48.08	48.53	48.99	49.44
11	49.96	50.35	50.80	51.26	51.71	52.16	52.62	53.07	53.52	53.98
12	54.43	54.88	55.34	55.79	56.25	56.70	57.15	57.61	58.06	58.51
13	58.97	59.42	59.87	60.33	60.78	61.23	61.69	62.14	62.60	63.05
14	63.50	63.96	64.41	64.86	65.32	65.77	66.22	66.68	67.13	67.59
15	68.04	68.49	68.95	69.40	69.85	70.31	70.76	71.21	71.67	72.12
16	72.57	73.03	73.48	73.94	74.39	74.84	75.30	75.75	76.20	76.66
17	77.11	77.56	78.02	78.47	78.93	79.38	79.83	80.29	80.74	81.19
18	81.65	82.10	82.55	83.01	83.46	83.91	84.37	84.82	85.28	85.73
19	86.18	86.64	87.09	87.54	88.00	88.45	88.90	89.36	89.81	90.26
20	90.72	91.17	91.63	92.08	92.53	92.99	93.44	93.89	94.35	94.80
21	95.25	95.71	96.16	96.62	97.07	97.52	97.98	98.43	98.88	99.34
22	99.79	100.24	100.70	101.15	101.60	102.06	102.51	102.97	103.42	103.87
23	104.33	104.78	105.23	105.69	106.14	106.59	107.05	107.50	107.96	108.41
24	108.86	109.32	109.77	110.22	110.68	111.13	111.58	112.04	112.49	112.94
25	113.40	113.85	114.31	114.76	115.21	115.67	116.12	116.57	117.03	117.48
26	117.93	118.39	118.84	119.29	119.75	120.20	120.66	121.11	121.56	122.02
27	122.47	122.92	123.38	123.83	124.28	124.74	125.19	125.65	126.10	126.55
28	127.01	127.46	127.91	128.37	128.82	129.27	129.73	130.18	130.63	131.09
29	131.54	132.00	132.45	132.90	133.36	133.81	134.26	134.72	135.17	135.62
30	136.08	136.53	136.98	137.44	137.89	138.35	138.80	139.25	139.71	140.16
31	140.61	141.07	141.52	141.97	142.43	142.88	143.34	143.79	144.24	144.70
32	145.15	145.60	146.06	146.51	146.96	147.42	147.87	148.32	148.78	149.23
33	149.69	150.14	150.59	151.05	151.50	151.95	152.41	152.86	153.31	153.77
34	154.22	154.68	155.13	155.58	156.04	156.49	156.94	157.40	157.85	158.30
35	158.76	159.21	159.66	160.12	160.57	161.03	161.48	161.93	162.39	162.84
36	163.29	163.75	164.20	164.65	165.11	165.56	166.01	166.47	166.92	167.38
37	167.83	168.28	168.74	169.19	169.64	170.10	170.55	171.00	171.46	171.91
38	172.37	172.82	173.27	173.73	174.18	174.63	175.09	175.54	175.99	176.45
39	176.90	177.35	177.81	178.26	178.72	179.17	179.62	180.08	180.53	180.98
40	181.44	181.89	182.34	182.80	183.25	183.70	184.16	184.61	185.07	185.52
41	185.97	186.43	186.88	187.33	187.79	188.24	188.69	189.15	189.60	190.06
42	190.51	190.96	191.42	191.87	192.32	192.78	193.23	193.68	194.14	194.59
43	195.04	195.50	195.95	196.41	196.86	197.31	197.77	198.22	198.67	199.13
44	199.58	200.03	200.49	200.94	201.40	201.85	202.30	202.76	203.21	203.66
45	204.12	204.57	205.02	205.48	205.93	206.38	206.84	207.29	207.75	208.20
46	208.65	209.11	209.56	210.01	210.47	210.92	211.37	211.83	212.28	212.73
47	213.19	213.64	214.10	214.55	215.00	215.46	215.91	216.36	216.82	217.27
48	217.72	218.18	218.63	219.09	219.54	219.99	220.45	220.90	221.35	221.81
49	222.26	222.71	223.17	223.62	224.07	224.53	224.98	225.44	225.89	226.34

# MEASURES AND WEIGHTS

## METRIC CONVERSION TABLE

### POUNDS AVOIRDUPOIS TO KILOGRAMS

1 Pound=0.45359 Kilograms

Pounds	0	1	2	3	4	5	6	7	8	9
50	226.80	227.25	227.70	228.16	228.61	229.06	229.52	229.97	230.42	230.88
51	231.33	231.79	232.24	232.69	233.15	233.60	234.05	234.51	234.96	235.41
52	235.87	236.32	236.78	237.23	237.68	238.14	238.59	239.04	239.50	239.95
53	240.40	240.86	241.31	241.76	242.22	242.67	243.13	243.58	244.03	244.49
54	244.94	245.39	245.85	246.30	246.75	247.21	247.66	248.12	248.57	249.02
55	249.48	249.93	250.38	250.84	251.29	251.74	252.20	252.65	253.10	253.56
56	254.01	254.47	254.92	255.37	255.83	256.28	256.73	257.19	257.64	258.09
57	258.55	259.00	259.45	259.91	260.36	260.82	261.27	261.72	262.18	262.63
58	263.08	263.54	263.99	264.44	264.90	265.35	265.81	266.26	266.71	267.17
59	267.62	268.07	268.53	268.98	269.43	269.89	270.34	270.79	271.25	271.70
60	272.16	272.61	273.06	273.52	273.97	274.42	274.88	275.33	275.78	276.24
61	276.69	277.14	277.60	278.05	278.51	278.96	279.41	279.87	280.32	280.77
62	281.23	281.68	282.13	282.59	283.04	283.50	283.95	284.40	284.86	285.31
63	285.76	286.22	286.67	287.12	287.58	288.03	288.48	288.94	289.39	289.85
64	290.30	290.75	291.21	291.66	292.11	292.57	293.02	293.47	293.93	294.38
65	294.84	295.29	295.74	296.20	296.65	297.10	297.56	298.01	298.46	298.92
66	299.37	299.82	300.28	300.73	301.19	301.64	302.09	302.55	303.00	303.45
67	303.91	304.36	304.81	305.27	305.72	306.17	306.63	307.08	307.54	307.99
68	308.44	308.90	309.35	309.80	310.26	310.71	311.16	311.62	312.07	312.53
69	312.98	313.43	313.89	314.34	314.79	315.25	315.70	316.15	316.61	317.06
70	317.51	317.97	318.42	318.88	319.33	319.78	320.24	320.69	321.14	321.60
71	322.05	322.50	322.96	323.41	323.86	324.32	324.77	325.23	325.68	326.13
72	326.59	327.04	327.49	327.95	328.40	328.85	329.31	329.76	330.22	330.67
73	331.12	331.58	332.03	332.48	332.94	333.39	333.84	334.30	334.75	335.20
74	335.66	336.11	336.57	337.02	337.47	337.93	338.38	338.83	339.29	339.74
75	340.19	340.65	341.10	341.56	342.01	342.46	342.92	343.37	343.82	344.28
76	344.73	345.18	345.64	346.09	346.54	347.00	347.45	347.91	348.36	348.81
77	349.27	349.72	350.17	350.63	351.08	351.53	351.99	352.44	352.89	353.35
78	353.80	354.26	354.71	355.16	355.62	356.07	356.52	356.98	357.43	357.88
79	358.34	358.79	359.25	359.70	360.15	360.61	361.06	361.51	361.97	362.42
80	362.87	363.33	363.78	364.23	364.69	365.14	365.60	366.05	366.50	366.96
81	367.41	367.86	368.32	368.77	369.22	369.68	370.13	370.59	371.04	371.49
82	371.95	372.40	372.85	373.31	373.76	374.21	374.67	375.12	375.57	376.03
83	376.48	376.94	377.39	377.84	378.30	378.75	379.20	379.66	380.11	380.56
84	381.02	381.47	381.92	382.38	382.83	383.29	383.74	384.19	384.65	385.10
85	385.55	386.01	386.46	386.91	387.37	387.82	388.28	388.73	389.18	389.64
86	390.09	390.54	391.00	391.45	391.90	392.36	392.81	393.26	393.72	394.17
87	394.63	395.08	395.53	395.99	396.44	396.89	397.35	397.80	398.25	398.71
88	399.16	399.61	400.07	400.52	400.98	401.43	401.88	402.34	402.79	403.24
89	403.78	404.15	404.60	405.06	405.51	405.97	406.42	406.87	407.33	407.78
90	408.23	408.69	409.14	409.59	410.05	410.50	410.95	411.41	411.86	412.32
91	412.77	413.22	413.68	414.13	414.58	415.04	415.49	415.94	416.40	416.85
92	417.31	417.76	418.21	418.67	419.12	419.57	420.03	420.48	420.93	421.39
93	421.84	422.29	422.75	423.20	423.65	424.11	424.56	425.02	425.47	425.92
94	426.38	426.83	427.28	427.74	428.19	428.64	429.10	429.55	430.01	430.46
95	430.91	431.37	431.82	432.27	432.73	433.18	433.63	434.09	434.54	435.00
96	435.45	435.90	436.36	436.81	437.26	437.72	438.17	438.62	439.08	439.53
97	439.98	440.44	440.89	441.35	441.80	442.25	442.71	443.16	443.61	444.07
98	444.52	444.97	445.43	445.88	446.33	446.79	447.24	447.70	448.15	448.60
99	449.06	449.51	449.96	450.42	450.87	451.32	451.78	452.23	452.69	453.14

# CARNEGIE STEEL COMPANY

## PROPERTIES OF THE CIRCLE

Circumference of Circle of Dia. 1 =  $\pi = 3.14159265$

Circumference of Circle =  $2\pi r$


Dia. of Circle = Circumference  $\times 0.31831$

Diameter of Circle of equal periphery as square = side  $\times 1.27324$

Side of Square of equal periphery as circle = diameter  $\times 0.78540$

Diameter of Circle circumscribed about square = side  $\times 1.41421$

Side of Square inscribed in Circle = diameter  $\times 0.70711$

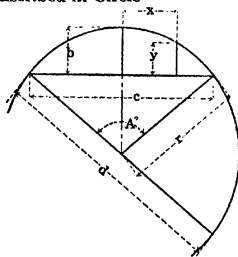

$$\text{Arc, } a = \frac{\pi r A^\circ}{180} = 0.017453 r A^\circ$$

$$\text{Angle, } A = \frac{180^\circ a}{\pi r} = 57.29578 \frac{a}{r}$$

$$\text{Radius, } r = \frac{4b^2 + c^2}{8b} \quad \text{Diameter, } d = \frac{4b^2 + c^2}{4b}$$

$$\text{Chord, } c = 2\sqrt{2br - b^2} = 2r \sin \frac{A^\circ}{2}$$

$$\text{Rise, } b = r - \frac{1}{2}\sqrt{4r^2 - c^2} = \frac{c}{2} \tan \frac{A^\circ}{4} = 2r \sin^2 \frac{A^\circ}{4}$$

$$\text{Rise, } b = r + y - \sqrt{r^2 - x^2}, \quad y = b - r + \sqrt{r^2 - x^2}, \quad x = \sqrt{r^2 - (r + y - b)^2}$$

$$\pi = 3.14159265, \log = 0.4971499$$

$$\frac{1}{\pi} = 0.3183099, \log = 1.5028501$$

$$\pi^2 = 9.8696044, \log = 0.9942997$$

$$\frac{1}{\pi^2} = 0.1013212, \log = 1.0057003$$

$$\sqrt{\pi} = 1.7724539, \log = 0.2485749$$

$$\sqrt{\frac{1}{\pi}} = 0.5641896, \log = 1.7514251$$

$$\frac{\pi}{180} = 0.0174533, \log = 2.2418774$$


$$\frac{180}{\pi} = 57.2957795, \log = 1.7581226$$

## MENSURATION TABLES

### AREA OF PLANE FIGURES

<b>Triangle:</b>	Base x $\frac{1}{2}$ perpendicular height. $\sqrt{s(s-a)(s-b)(s-c)}$ , $s = \frac{1}{2}$ sum of the three sides a, b and c.
<b>Trapezium:</b>	Sum of area of the two triangles.
<b>Trapezoid:</b>	$\frac{1}{2}$ sum of parallel sides x perpendicular height.
<b>Parallelogram:</b>	Base x perpendicular height.
<b>Regular Polygon:</b>	$\frac{1}{2}$ sum of sides x inside radius.
<b>Circle:</b>	$\pi r^2 = 0.78540 \times \text{dia.}^2 = 0.07958 \times \text{circumference}^2$ .
<b>Sector of Circle:</b>	$\frac{\pi r^2 A^\circ}{360} = 0.0087266 r^2 A^\circ = \text{arc} \times \frac{1}{2} \text{ radius}$ .
<b>Segment of Circle:</b>	$\frac{r^2}{2} \left( \frac{\pi A^\circ}{180} - \sin A^\circ \right)$
<b>Circle of same area as square:</b>	diameter = side $\times 1.12838$
<b>Square of same area as circle:</b>	side = diameter $\times 0.88623$
<b>Ellipse:</b>	Long diameter x short diameter $\times 0.78540$
<b>Parabola:</b>	Base x $\frac{2}{3}$ perpendicular height.

#### Irregular plane surface.

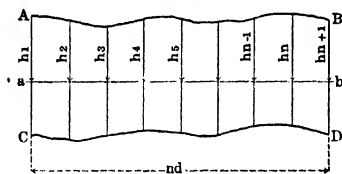


Divide any plane surface A, B, C, D, along a line a-b into an even number, n, of parallel and sufficiently small strips, d, whose ordinates are  $h_1, h_2, h_3, h_4, h_5, \dots, h_{n-1}, h_n, h_{n+1}$ , and considering contours between three ordinates as parabolic curves, then for section ABCD,

$$\text{Area} = \frac{d}{3} [h_1 + h_{n+1} + 4(h_2 + h_4 + h_6 \dots + h_n) + 2(h_3 + h_5 + h_7 \dots + h_{n-1})]$$

or, approximately, Area = Sum of ordinates x width, d.

# TRIGONOMETRIC FORMULAS



Radius,  $1 = \sin^2 A + \cos^2 A$

$$\sin A \csc A = \cos A \sec A = \tan A \cot A = 1$$

Sine  $A = \frac{\text{opp}}{\text{hyp}} = \frac{1}{\csc A} = \cos A \tan A = \sqrt{1 - \cos^2 A}$

Cosine  $A = \frac{\text{adj}}{\text{hyp}} = \frac{1}{\sec A} = \sin A \cot A = \sqrt{1 - \sin^2 A}$

Tangent  $A = \frac{\text{opp}}{\text{adj}} = \frac{1}{\cot A} = \cos A \sec A$

Cotangent  $A = \frac{\text{adj}}{\text{opp}} = \frac{1}{\tan A} = \cos A \csc A$

Secant  $A = \frac{\text{hyp}}{\text{adj}} = \frac{1}{\cos A}$

Cosecant  $A = \frac{\text{hyp}}{\text{opp}} = \frac{1}{\sin A}$

$$\sin(A \pm B) = \sin A \cos B \pm \cos A \sin B$$

$$\cos(A \pm B) = \cos A \cos B \mp \sin A \sin B$$

$$\sin A + \sin B = 2 \sin \frac{1}{2}(A+B) \cos \frac{1}{2}(A-B)$$

$$\sin A - \sin B = 2 \cos \frac{1}{2}(A+B) \sin \frac{1}{2}(A-B)$$

$$\cos A + \cos B = 2 \cos \frac{1}{2}(A+B) \cos \frac{1}{2}(A-B)$$

$$\cos B - \cos A = 2 \sin \frac{1}{2}(A+B) \sin \frac{1}{2}(A-B)$$

$$\sin 2A = 2 \sin A \cos A$$

$$\cos 2A = \cos^2 A - \sin^2 A$$

$$\sin \frac{1}{2} A = \sqrt{\frac{1 - \cos A}{2}} \quad \cos \frac{1}{2} A = \sqrt{\frac{1 + \cos A}{2}}$$

$$\sin^2 A = \frac{1 - \cos 2A}{2} \quad \cos^2 A = \frac{1 + \cos 2A}{2}$$

$$\sin^2 A - \sin^2 B = \sin(A+B) \sin(A-B)$$

$$\frac{\sin A + \sin B}{\cos A + \cos B} = \tan \frac{1}{2}(A+B)$$

$$\tan(A \pm B) = \frac{\tan A \pm \tan B}{1 \mp \tan A \tan B}$$

$$\cot(A \pm B) = \frac{\cot A \cot B \mp 1}{\cot B \pm \cot A}$$

$$\tan A + \tan B = \frac{\sin(A+B)}{\cos A \cos B}$$

$$\tan A - \tan B = \frac{\sin(A-B)}{\cos A \cos B}$$

$$\cot A + \cot B = \frac{\sin(B+A)}{\sin A \sin B}$$

$$\cot A - \cot B = \frac{\sin(B-A)}{\sin A \sin B}$$

$$\tan 2A = \frac{2 \tan A}{1 - \tan^2 A}$$

$$\cot 2A = \frac{\cot^2 A - 1}{2 \cot A}$$

$$\tan \frac{1}{2} A = \frac{\sin A}{1 + \cos A} \quad \cot \frac{1}{2} A = \frac{\sin A}{1 - \cos A}$$

$$\tan^2 A = \frac{1 - \cos 2A}{1 + \cos 2A} \quad \cot^2 A = \frac{1 + \cos 2A}{1 - \cos 2A}$$

$$\cos^2 A - \sin^2 B = \cos(A+B) \cos(A-B)$$



$$\frac{\cos A + \cos B}{\cos A - \cos B} = \cot \frac{1}{2}(A \mp B)$$

Quadrant	I	II	III	IV	Angle		
Angle	0° to 90°	90° to 180°	180° to 270°	270° to 360°	30°	45°	60°
Functions	Values vary from				Equivalent values		
sin	+0 to +1	+1 to +0	-0 to -1	-1 to -0	$\frac{1}{2}$	$\frac{1}{2}\sqrt{2}$	$\frac{\sqrt{3}}{2}$
cos	+1 to +0	+0 to -1	-1 to -0	+0 to +1	$\frac{1}{2}\sqrt{3}$	$\frac{1}{2}\sqrt{2}$	$\frac{1}{2}$
tan	+0 to +∞	-∞ to -0	+0 to +∞	-∞ to -0	$\frac{1}{2}\sqrt{3}$	1	$\sqrt{3}$
cot	+∞ to +0	-0 to -∞	+∞ to +0	-0 to -∞	$\sqrt{3}$	1	$\frac{1}{2}\sqrt{3}$

Angle a < 90°				
Angle	sin	cos	tan	cot
0° ± a	±sin a	+cos a	±tan a	±cot a
90° ± a	+cos a	∓sin a	∓cot a	±tan a
180° ± a	∓sin a	-cos a	±tan a	±cot a
270° ± a	-cos a	±sin a	∓cot a	±tan a

# MENSURATION TABLES

## TRIGONOMETRIC SOLUTION OF TRIANGLES




Given	Sought	Formulae		
RIGHT-ANGLED TRIANGLES				
a, c	A, B, b	$\sin A = \frac{a}{c}, \cos B = \frac{a}{c}, b = \sqrt{c^2 - a^2}$		
	Area	$\text{Area} = \frac{a}{2} \sqrt{c^2 - a^2}$		
a, b	A, B, c	$\tan A = \frac{a}{b}, \tan B = \frac{b}{a}, c = \sqrt{a^2 + b^2}$		
	Area	$\text{Area} = \frac{a b}{2}$		
A, a	B, b, c	$B = 90^\circ - A, b = a \cot A, c = \frac{a}{\sin A}$		
	Area	$\text{Area} = \frac{a^2 \cot A}{2}$		
A, b	B, a, c	$B = 90^\circ - A, a = b \tan A, c = \frac{b}{\cos A}$		
	Area	$\text{Area} = \frac{b^2 \tan A}{2}$		
A, c	B, a, b	$B = 90^\circ - A, a = c \sin A, b = c \cos A$		
	Area	$\text{Area} = \frac{c^2 \sin A \cos A}{2} \text{ or } \frac{c^2 \sin 2 A}{4}$		
OBLIQUE-ANGLED TRIANGLES				
a, b, c	A	$\sin \frac{1}{2} A = \sqrt{\frac{(s-b)(s-c)}{b c}}, \cos \frac{1}{2} A = \sqrt{\frac{s(s-a)}{b c}}, \tan \frac{1}{2} A = \sqrt{\frac{(s-b)(s-c)}{s(s-a)}}$		
	B	$\sin \frac{1}{2} B = \sqrt{\frac{(s-a)(s-c)}{a c}}, \cos \frac{1}{2} B = \sqrt{\frac{s(s-b)}{a c}}, \tan \frac{1}{2} B = \sqrt{\frac{(s-a)(s-c)}{s(s-b)}}$		
	C	$\sin \frac{1}{2} C = \sqrt{\frac{(s-a)(s-b)}{a b}}, \cos \frac{1}{2} C = \sqrt{\frac{s(s-c)}{a b}}, \tan \frac{1}{2} C = \sqrt{\frac{(s-a)(s-b)}{s(s-c)}}$		
	Area	$\text{Area} = \sqrt{s(s-a)(s-b)(s-c)}$		
a, A, B	b, c	$b = \frac{a \sin B}{\sin A}, c = \frac{a \sin C}{\sin A} = \frac{a \sin (A+B)}{\sin A}$		
	Area	$\text{Area} = \frac{1}{2} a b \sin C = \frac{a^2 \sin B \sin C}{2 \sin A}$		
a, b, A	B	$\sin B = \frac{b \sin A}{a}$		
	c	$c = \frac{a \sin C}{\sin A} = \frac{b \sin C}{\sin B} = \sqrt{a^2 + b^2 - 2 a b \cos C}$		
	Area	$\text{Area} = \frac{1}{2} a b \sin C$		
a, b, C	A	$\tan A = \frac{a \sin C}{b - a \cos C}, \tan \frac{1}{2}(A-B) = \frac{a-b}{a+b} \cot \frac{1}{2} C$		
	c	$c = \sqrt{a^2 + b^2 - 2 a b \cos C} = \frac{a \sin C}{\sin A}$		
	Area	$\text{Area} = \frac{1}{2} a b \sin C$		
$a^2 = b^2 + c^2 - 2 b c \cos A, b^2 = a^2 + c^2 - 2 a c \cos B, c^2 = a^2 + b^2 - 2 a b \cos C$				




# CARNEGIE STEEL COMPANY

## AREA OF CIRCULAR SECTIONS



### Circular Sector, m o n p

Area =  $\frac{1}{2}$  (length of arc, m p n x radius, r)  
 = area of circle x  $\frac{\text{arc, m p n, in degrees}}{360}$   
 =  $0.0087266 \times \text{square of radius, } r^2, \times \text{angle of arc, m p n, in degrees.}$



### Circular Segment, m p n, less than half circle,

Area = area of sector, m o n p - area of triangle, m o n  
 =  $\frac{(\text{length of arc, m p n, x radius, r}) - (\text{radius, r, - rise, b}) \times \text{chord, c}}{2}$

### Circular Segment, m q n, greater than half circle.

Area = area of circle - area of segment, m n p

### Circular Segment, from Table I, page 389.

Given: rise, b, and chord, c.

Area = product of rise and chord, b x c, multiplied by the coefficient given opposite the quotient of  $\frac{b}{c}$ :


Intermediate coefficients for values of  $\frac{b}{c}$  not given

in tables are obtained by interpolation.

Example - Given: rise = 1.49 and chord = 3.52,

$$\frac{b}{c} = \frac{1.49}{3.52} = 0.4233. \quad \text{Coefficient} = 0.7542.$$

$$\text{Area} = b \times c \times \text{coeff.} = 1.49 \times 3.52 \times 0.7542 = 3.9556.$$



### Circular Segment, from Table II, pages 390 and 391.

Given: rise, b, and diameter, d = 2r.

Area = square of diameter, d<sup>2</sup>, multiplied by the coefficient given opposite the quotient of  $\frac{b}{d}$ .

Intermediate coefficients for values of  $\frac{b}{d}$  not given



in tables are obtained by interpolation.

Example - Given: rise =  $2\frac{1}{10}$  and diameter =  $5\frac{1}{2}$ .

$$\frac{b}{d} = 2\frac{1}{10} \div 5\frac{1}{2} = 0.478528.$$

Coefficient by interpolation = 0.371233.

$$\text{Area} = d^2 \times \text{coeff.} = 25.94020 \times 0.371233 = 9.6321.$$



### Circular Zone, t u v w

Area = area of circle - (area of segment, t p u + area of segment, v q w).


### Circular Lune, m p n s

Area = segment, m p n - segment, m s n.

# MENSURATION TABLES

## AREAS OF CIRCULAR SEGMENTS

TABLE 1—FOR RATIOS OF RISE AND CHORD




Area =  $C \times b \times \text{coefficient}$

A°	Coefficient	$\frac{b}{C}$	A°	Coefficient	$\frac{b}{C}$	A°	Coefficient	$\frac{b}{C}$	A°	Coefficient	$\frac{b}{C}$	A°	Coefficient	$\frac{b}{C}$
1	.6667	.0022	46	.6722	.1017	91	.6895	.2097	136	.7239	.3373			
2	.6667	.0044	47	.6724	.1040	92	.6901	.2122	137	.7249	.3404			
3	.6667	.0066	48	.6727	.1063	93	.6906	.2148	138	.7260	.3436			
4	.6667	.0087	49	.6729	.1086	94	.6912	.2174	139	.7270	.3469			
5	.6667	.0109	50	.6732	.1109	95	.6918	.2200	140	.7281	.3501			
6	.6667	.0131	51	.6734	.1131	96	.6924	.2226	141	.7292	.3534			
7	.6668	.0153	52	.6737	.1154	97	.6930	.2252	142	.7303	.3567			
8	.6668	.0175	53	.6740	.1177	98	.6936	.2279	143	.7314	.3600			
9	.6669	.0197	54	.6743	.1200	99	.6942	.2305	144	.7325	.3633			
10	.6670	.0218	55	.6746	.1224	100	.6948	.2332	145	.7336	.3666			
11	.6670	.0240	56	.6749	.1247	101	.6954	.2358	146	.7348	.3700			
12	.6671	.0262	57	.6752	.1270	102	.6961	.2385	147	.7360	.3734			
13	.6672	.0284	58	.6755	.1293	103	.6967	.2412	148	.7372	.3768			
14	.6672	.0306	59	.6758	.1316	104	.6974	.2439	149	.7384	.3802			
15	.6673	.0328	60	.6761	.1340	105	.6980	.2466	150	.7396	.3837			
16	.6674	.0350	61	.6764	.1363	106	.6987	.2493	151	.7408	.3871			
17	.6674	.0372	62	.6768	.1387	107	.6994	.2520	152	.7421	.3906			
18	.6675	.0394	63	.6771	.1410	108	.7001	.2548	153	.7434	.3942			
19	.6676	.0416	64	.6775	.1434	109	.7008	.2575	154	.7447	.3977			
20	.6677	.0437	65	.6779	.1457	110	.7015	.2603	155	.7460	.4013			
21	.6678	.0459	66	.6782	.1481	111	.7022	.2631	156	.7473	.4049			
22	.6679	.0481	67	.6786	.1505	112	.7030	.2659	157	.7486	.4085			
23	.6680	.0504	68	.6790	.1529	113	.7037	.2687	158	.7500	.4122			
24	.6681	.0526	69	.6794	.1553	114	.7045	.2715	159	.7514	.4159			
25	.6682	.0548	70	.6797	.1577	115	.7052	.2743	160	.7528	.4196			
26	.6684	.0570	71	.6801	.1601	116	.7060	.2772	161	.7542	.4233			
27	.6685	.0592	72	.6805	.1625	117	.7068	.2800	162	.7557	.4270			
28	.6687	.0614	73	.6809	.1649	118	.7076	.2829	163	.7571	.4308			
29	.6688	.0636	74	.6814	.1673	119	.7084	.2858	164	.7586	.4346			
30	.6690	.0658	75	.6818	.1697	120	.7092	.2887	165	.7601	.4385			
31	.6691	.0681	76	.6823	.1722	121	.7100	.2916	166	.7616	.4424			
32	.6693	.0703	77	.6826	.1746	122	.7109	.2946	167	.7632	.4463			
33	.6694	.0725	78	.6831	.1771	123	.7117	.2975	168	.7648	.4502			
34	.6696	.0747	79	.6835	.1795	124	.7126	.3004	169	.7664	.4542			
35	.6698	.0770	80	.6840	.1820	125	.7134	.3034	170	.7680	.4582			
36	.6700	.0792	81	.6844	.1845	126	.7143	.3064	171	.7696	.4622			
37	.6702	.0814	82	.6849	.1869	127	.7152	.3094	172	.7712	.4663			
38	.6704	.0837	83	.6854	.1894	128	.7161	.3124	173	.7729	.4704			
39	.6706	.0859	84	.6859	.1919	129	.7170	.3155	174	.7746	.4745			
40	.6708	.0882	85	.6864	.1944	130	.7180	.3185	175	.7763	.4787			
41	.6710	.0904	86	.6869	.1970	131	.7189	.3216	176	.7781	.4828			
42	.6712	.0927	87	.6874	.1995	132	.7199	.3247	177	.7799	.4871			
43	.6714	.0949	88	.6879	.2020	133	.7209	.3278	178	.7817	.4914			
44	.6717	.0972	89	.6884	.2046	134	.7219	.3309	179	.7835	.4957			
45	.6719	.0995	90	.6890	.2071	135	.7229	.3341	180	.7854	.5000			

CARNEGIE STEEL COMPANY

AREAS OF CIRCULAR SEGMENTS  
TABLE II, FOR RATIOS OF RISE AND DIAMETER




$$\text{Area} = d^2 \times \text{Coefficient}$$

$\frac{b}{d}$	Coefficient	$\frac{b}{d}$	Coefficient	$\frac{b}{d}$	Coefficient	$\frac{b}{d}$	Coefficient	$\frac{b}{d}$	Coefficient
.001	.000042	.051	.015119	.101	.041477	.151	.074590	.201	.112625
.002	.000119	.052	.015561	.102	.042081	.152	.075307	.202	.113427
.003	.000219	.053	.016008	.103	.042687	.153	.076026	.203	.114231
.004	.000337	.054	.016458	.104	.043296	.154	.076747	.204	.115036
.005	.000471	.055	.016912	.105	.043908	.155	.077470	.205	.115842
.006	.000619	.056	.017369	.106	.044523	.156	.078194	.206	.116651
.007	.000779	.057	.017831	.107	.045140	.157	.078921	.207	.117460
.008	.000952	.058	.018297	.108	.045759	.158	.079650	.208	.118271
.009	.001135	.059	.018766	.109	.046381	.159	.080380	.209	.119084
.010	.001329	.060	.019239	.110	.047006	.160	.081112	.210	.119898
.011	.001533	.061	.019716	.111	.047633	.161	.081847	.211	.120713
.012	.001746	.062	.020197	.112	.048262	.162	.082582	.212	.121530
.013	.001969	.063	.020681	.113	.048894	.163	.083320	.213	.122348
.014	.002199	.064	.021168	.114	.049529	.164	.084060	.214	.123167
.015	.002438	.065	.021660	.115	.050165	.165	.084801	.215	.123988
.016	.002685	.066	.022155	.116	.050805	.166	.085545	.216	.124811
.017	.002940	.067	.022653	.117	.051446	.167	.086290	.217	.125634
.018	.003202	.068	.023155	.118	.052090	.168	.087037	.218	.126459
.019	.003472	.069	.023660	.119	.052737	.169	.087785	.219	.127286
.020	.003749	.070	.024168	.120	.053385	.170	.088536	.220	.128114
.021	.004032	.071	.024680	.121	.054037	.171	.089288	.221	.128943
.022	.004322	.072	.025190	.122	.054690	.172	.090042	.222	.129773
.023	.004619	.073	.025714	.123	.055346	.173	.090797	.223	.130605
.024	.004922	.074	.026236	.124	.056004	.174	.091555	.224	.131438
.025	.005231	.075	.026761	.125	.056664	.175	.092314	.225	.132273
.026	.005546	.076	.027290	.126	.057327	.176	.093074	.226	.133109
.027	.005867	.077	.027821	.127	.057991	.177	.093837	.227	.133946
.028	.006194	.078	.028356	.128	.058658	.178	.094601	.228	.134784
.029	.006527	.079	.028894	.129	.059328	.179	.095367	.229	.135624
.030	.006866	.080	.029435	.130	.059999	.180	.096135	.230	.136465
.031	.007209	.081	.029979	.131	.060673	.181	.096904	.231	.137307
.032	.007559	.082	.030526	.132	.061349	.182	.097675	.232	.138151
.033	.007913	.083	.031077	.133	.062027	.183	.098447	.233	.138996
.034	.008273	.084	.031630	.134	.062707	.184	.099221	.234	.139842
.035	.008638	.085	.032186	.135	.063389	.185	.099997	.235	.140689
.036	.009008	.086	.032746	.136	.064074	.186	.100774	.236	.141538
.037	.009383	.087	.033308	.137	.064761	.187	.101553	.237	.142388
.038	.009764	.088	.033873	.138	.065449	.188	.102334	.238	.143239
.039	.010148	.089	.034441	.139	.066140	.189	.103116	.239	.144091
.040	.010538	.090	.035012	.140	.066833	.190	.103900	.240	.144945
.041	.010932	.091	.035586	.141	.067528	.191	.104686	.241	.145800
.042	.011331	.092	.036162	.142	.068225	.192	.105472	.242	.146656
.043	.011734	.093	.036742	.143	.068924	.193	.106261	.243	.147513
.044	.012142	.094	.037324	.144	.069626	.194	.107051	.244	.148371
.045	.012555	.095	.037909	.145	.070329	.195	.107843	.245	.149231
.046	.012971	.096	.038497	.146	.071034	.196	.108636	.246	.150091
.047	.013393	.097	.039087	.147	.071741	.197	.109431	.247	.150953
.048	.013818	.098	.039681	.148	.072450	.198	.110227	.248	.151816
.049	.014248	.099	.040277	.149	.073162	.199	.111025	.249	.152681
.050	.014681	.100	.040875	.150	.073875	.200	.111824	.250	.153546

# MENSURATION TABLES

## AREAS OF CIRCULAR SEGMENTS

TABLE II, FOR RATIOS OF RISE AND DIAMETER—Concluded




$$\text{Area} = d^2 \times \text{coefficient}$$

$\frac{h}{d}$	Coefficient	$\frac{h}{d}$	Coefficient	$\frac{h}{d}$	Coefficient	$\frac{h}{d}$	Coefficient	$\frac{h}{d}$	Coefficient
.251	.154413	.301	.199085	.351	.245935	.401	.294350	.451	.343778
.252	.155281	.302	.200003	.352	.246890	.402	.295330	.452	.344773
.253	.156149	.303	.200922	.353	.247845	.403	.296311	.453	.345768
.254	.157019	.304	.201841	.354	.248801	.404	.297292	.454	.346764
.255	.157891	.305	.202762	.355	.249758	.405	.298274	.455	.347760
.256	.158763	.306	.203683	.356	.250715	.406	.299256	.456	.348756
.257	.159636	.307	.204605	.357	.251673	.407	.300238	.457	.349752
.258	.160511	.308	.205528	.358	.252632	.408	.301221	.458	.350749
.259	.161386	.309	.206452	.359	.253591	.409	.302204	.459	.351745
.260	.162263	.310	.207376	.360	.254551	.410	.303187	.460	.352742
.261	.163141	.311	.208302	.361	.255511	.411	.304171	.461	.353739
.262	.164020	.312	.209228	.362	.256472	.412	.305156	.462	.354736
.263	.164900	.313	.210155	.363	.257433	.413	.306140	.463	.355733
.264	.165781	.314	.211083	.364	.258395	.414	.307125	.464	.356730
.265	.166663	.315	.212011	.365	.259358	.415	.308110	.465	.357728
.266	.167546	.316	.212941	.366	.260321	.416	.309096	.466	.358725
.267	.168431	.317	.213871	.367	.261285	.417	.310082	.467	.359723
.268	.169316	.318	.214802	.368	.262249	.418	.311068	.468	.360721
.269	.170202	.319	.215734	.369	.263214	.419	.312065	.469	.361719
.270	.171090	.320	.216666	.370	.264179	.420	.313042	.470	.362717
.271	.171978	.321	.217600	.371	.265145	.421	.314029	.471	.363715
.272	.172868	.322	.218534	.372	.266111	.422	.315017	.472	.364714
.273	.173758	.323	.219469	.373	.267078	.423	.316005	.473	.365712
.274	.174650	.324	.220404	.374	.268046	.424	.316993	.474	.366711
.275	.175542	.325	.221341	.375	.269014	.425	.317981	.475	.367710
.276	.176436	.326	.222278	.376	.269982	.426	.318970	.476	.368708
.277	.177330	.327	.223216	.377	.270951	.427	.319959	.477	.369707
.278	.178226	.328	.224154	.378	.271921	.428	.320949	.478	.370706
.279	.179122	.329	.225094	.379	.272891	.429	.321938	.479	.371705
.280	.180020	.330	.226034	.380	.273861	.430	.322928	.480	.372704
.281	.180918	.331	.226974	.381	.274832	.431	.323919	.481	.373704
.282	.181818	.332	.227916	.382	.275804	.432	.324909	.482	.374703
.283	.182718	.333	.228858	.383	.276776	.433	.325900	.483	.375702
.284	.183619	.334	.229801	.384	.277748	.434	.326891	.484	.376702
.285	.184522	.335	.230745	.385	.278721	.435	.327883	.485	.377701
.286	.185425	.336	.231689	.386	.279695	.436	.328874	.486	.378701
.287	.186329	.337	.232634	.387	.280669	.437	.329866	.487	.379701
.288	.187235	.338	.233580	.388	.281643	.438	.330858	.488	.380700
.289	.188141	.339	.234526	.389	.282618	.439	.331851	.489	.381700
.290	.189048	.340	.235473	.390	.283593	.440	.332843	.490	.382700
.291	.189956	.341	.236421	.391	.284569	.441	.333836	.491	.383700
.292	.190905	.342	.237369	.392	.285545	.442	.334829	.492	.384699
.293	.191774	.343	.238319	.393	.286521	.443	.335823	.493	.385699
.294	.192655	.344	.239268	.394	.287499	.444	.336816	.494	.386699
.295	.193557	.345	.240219	.395	.288476	.445	.337810	.495	.387699
.296	.194509	.346	.241170	.396	.289454	.446	.338804	.496	.388699
.297	.195423	.347	.242122	.397	.290432	.447	.339799	.497	.389699
.298	.196337	.348	.243074	.398	.291411	.448	.340793	.498	.390699
.299	.197252	.349	.244027	.399	.292390	.449	.341788	.499	.391699
.300	.198168	.350	.244980	.400	.293370	.450	.342783	.500	.392699

# CARNEGIE STEEL COMPANY

## SURFACE AND VOLUME OF SOLIDS

**S=LATERAL OR CONVEX SURFACE. V=VOLUME**




### Parallelepiped

$S$ =perimeter,  $P$ , perp. to sides  $\times$  lat. length,  $l$ :  $Pl$   
 $V$ =area of base,  $B \times$  perpendicular height,  $h$ :  $Bh$   
 $V$ =area of section,  $A$ , perp. to sides  $\times$  lat. length,  $l$ :  $Al$



### Prism, Right or Oblique, Regular or Irregular

$S$ =perimeter,  $P$ , perp. to sides  $\times$  lat. length,  $l$ :  $Pl$   
 $V$ =area of base,  $B \times$  perpendicular height,  $h$ :  $Bh$   
 $V$ =area of section,  $A$ , perp. to sides  $\times$  lat. length,  $l$ :  $Al$



### Cylinder, Right or Oblique, Circular or Elliptic, etc.

$S$ =perimeter of base,  $C \times$  perp. height,  $h$ :  $Ch$   
 $S$ =perimeter,  $P$ , perp. to sides  $\times$  lat. length,  $l$ :  $Pl$   
 $V$ =area of base,  $B \times$  perpendicular height,  $h$ :  $Bh$   
 $V$ =area of section,  $A$ , perp. to sides  $\times$  lat. length,  $l$ :  $Al$



### Frustum of any Prism or Cylinder

$V$ =area of base,  $B \times$  perp. distance,  $h$ , from base to center of gravity of opposite face:  $Bh$   
 For cylinder:  $\frac{1}{2} A (A_1 + A_2)$



### Pyramid or Cone, Right and Regular

$S$ =perimeter of base,  $B \times \frac{1}{2}$  slant height,  $l$ :  $\frac{1}{2} Bl$   
 $V$ =area of base,  $B \times \frac{1}{3}$  perp. height,  $h$ :  $\frac{1}{3} Bh$




### Pyramid or Cone, Right or Oblique, Regular or Irregular

$V$ =area of base,  $B \times \frac{1}{3}$  perp. height,  $h$ :  $\frac{1}{3} Bh$   
 $V=\frac{1}{3}$  volume of prism or cylinder of same base and perpendicular height  
 $V=\frac{1}{3}$  volume of hemisphere of same base and perpendicular height

### Frustum of Pyramid or Cone, Right and Regular, Parallel Ends

$S$ =(sum of perimeter of base,  $B$ , and top,  $b$ )  $\times \frac{1}{2}$  slant height,  $l$ :  $\frac{1}{2} l (B + b)$   
 $V$ =(sum of areas of base,  $B$ , and top,  $b$  + square root of their products)  $\times \frac{1}{3}$  perp. height,  $h$ :  $\frac{1}{3} h (B + b + \sqrt{Bb})$



### Frustum of any Pyramid or Cone, Parallel Ends

$V$ =(sum of areas of base,  $B$ , and top,  $b$  + square root of their products)  $\times \frac{1}{3}$  perp. height,  $h$ :  $\frac{1}{3} h (B + b + \sqrt{Bb})$



### Wedge, Parallelogram Face

$V=\frac{1}{6}$  (sum of three edges,  $a, b, c \times$  perpendicular height,  $h \times$  perpendicular width,  $d$ ):  $\frac{1}{6} d h (2a + b)$



### Prismatoid

$V=\frac{1}{6}$  perp. height,  $h$  (sum of areas of base,  $B$ , and top  $b$ , + 4  $\times$  area of section,  $M$ , parallel to bases and midway between them):  $\frac{1}{6} h (B + b + 4M)$

The Prismatoid formula applies also to any of the foregoing solids with parallel bases, to pyramids, cones, spherical sections, and to many solids with irregular surfaces.

# MENSURATION TABLES

## SURFACE AND VOLUME OF SOLIDS—Concluded

S=LATERAL OR CONVEX SURFACE. V=VOLUME



### Sphere

$$S = 4 \pi r^2 = \pi d^2 = 3.14159265 d^2$$


$$V = \frac{4}{3} \pi r^3 = \frac{1}{6} \pi d^3 = 0.52359878 d^3$$



### Spherical Sector

$$S = \frac{1}{2} \pi r (4b + c)$$


$$V = \frac{2}{3} \pi r^2 b$$



### Spherical Segment

$$S = 2 \pi r b = \frac{1}{4} \pi (4b^2 + c^2)$$

$$V = \frac{1}{4} \pi b^2 (3r - b) = \frac{1}{24} \pi b (3c^2 + 4b^2)$$



### Spherical Zone

$$S = 2 \pi r b$$

$$V = \frac{1}{24} \pi b (3a^2 + 3c^2 + 4b^2)$$




### Circular Ring

$$S = 4 \pi^2 R r$$

$$V = 2 \pi^2 R r^2$$

### Ungula of Right, Regular Cylinder



Base=Segment, b a b

Base=Half Circle

$$S = (2 r m - o \times \text{arc, } b a b) \frac{h}{r - o}$$

$$S = 2 r h$$

$$V = (\frac{3}{4} m^2 - o \times \text{area, } b a b) \frac{h}{r - o}$$

$$V = \frac{3}{2} r^2 h$$



Base=Segment, c a c


Base=Circle

$$S = (2 r n + p \times \text{arc, } c a c) \frac{h}{r + p}$$

$$S = r \pi h$$

$$V = (\frac{3}{4} n^2 + p \times \text{area, } c a c) \frac{h}{r + p}$$

$$V = \frac{1}{4} r^2 \pi h$$




### Ellipsoid

$$V = \frac{4}{3} \pi r a b$$

### Paraboloid

$$V = \frac{1}{2} \pi r^2 h$$



Ratio of corresponding volumes of a Cone, Paraboloid, Sphere, and Cylinder of equal height:  $\frac{1}{6} : \frac{1}{2} : \frac{2}{3} : 1$

### Bodies Generated by Partial or Complete Revolution

l=length of a curve } rotating about an axis 1-1  
A=area of a plane } on one side and in plane of axis  
r=distance of center of gravity of line or plane from axis 1-1 and for any angle of revolution,  $a^\circ$ .



$$\frac{2 r \pi a^\circ}{360} = \text{length of arc described by center of gravity.}$$

S=length of curve x length of arc about axis

$$= l \frac{2 r \pi a^\circ}{360} \text{ For complete revolution } S = 2 r \pi l$$

V=area of plane x length of arc about axis

$$= A \frac{2 r \pi a^\circ}{360} \text{ For complete revolution } V = 2 r \pi A$$



# CARNEGIE STEEL COMPANY

## FUNCTIONS OF NUMBERS, 1 TO 49

No.	Square	Cube	Square Root	Cubic Root	Logarithm	1000 x Reciprocal	No. = Diameter	
							Circum.	Area
1	1	1	1.0000	1.0000	0.00000	1000.000	3.142	0.7854
2	4	8	1.4142	1.2599	0.30103	500.000	6.283	3.1416
3	9	27	1.7321	1.4422	0.47712	333.333	9.425	7.0686
4	16	64	2.0000	1.5874	0.60206	250.000	12.566	12.5664
5	25	125	2.2361	1.7100	0.69897	200.000	15.708	19.6350
6	36	216	2.4495	1.8171	0.77815	166.667	18.850	28.2743
7	49	343	2.6458	1.9129	0.84510	142.857	21.991	38.4845
8	64	512	2.8284	2.0000	0.90309	125.000	25.133	50.2655
9	81	729	3.0000	2.0801	0.95424	111.111	28.274	63.6173
10	100	1000	3.1623	2.1544	1.00000	100.000	31.416	78.5398
11	121	1331	3.3166	2.2240	1.04139	90.9091	34.558	95.0332
12	144	1728	3.4641	2.2894	1.07918	83.3333	37.699	113.097
13	169	2197	3.6056	2.3513	1.11394	76.9231	40.841	132.732
14	196	2744	3.7417	2.4101	1.14613	71.4286	43.982	153.938
15	225	3375	3.8730	2.4662	1.17609	66.6667	47.124	176.715
16	256	4096	4.0000	2.5198	1.20412	62.5000	50.265	201.062
17	289	4913	4.1231	2.5713	1.23045	58.8235	53.407	226.980
18	324	5832	4.2426	2.6207	1.25527	55.5556	56.549	254.469
19	361	6859	4.3589	2.6684	1.27875	52.6316	59.690	283.529
20	400	8000	4.4721	2.7144	1.30103	50.0000	62.832	314.159
21	441	9261	4.5826	2.7589	1.32222	47.6190	65.973	346.361
22	484	10648	4.6904	2.8020	1.34242	45.4545	69.115	380.133
23	529	12167	4.7958	2.8439	1.36173	43.4783	72.257	415.476
24	576	13824	4.8990	2.8845	1.38021	41.6667	75.398	452.389
25	625	15625	5.0000	2.9240	1.39794	40.0000	78.540	490.874
26	676	17576	5.0990	2.9625	1.41497	38.4615	81.681	530.929
27	729	19683	5.1962	3.0000	1.43136	37.0370	84.823	572.555
28	784	21952	5.2915	3.0366	1.44716	35.7143	87.965	615.752
29	841	24389	5.3852	3.0723	1.46240	34.4828	91.106	660.520
30	900	27000	5.4772	3.1072	1.47712	33.3333	94.248	706.858
31	961	29791	5.5678	3.1414	1.49136	32.2581	97.389	754.768
32	1024	32768	5.6569	3.1748	1.50515	31.2500	100.531	804.248
33	1089	35937	5.7446	3.2075	1.51851	30.3030	103.673	855.299
34	1156	39304	5.8310	3.2396	1.53148	29.4118	106.814	907.920
35	1225	42875	5.9161	3.2711	1.54407	28.5714	109.956	962.113
36	1296	46656	6.0000	3.3019	1.55630	27.7778	113.007	1017.88
37	1369	50653	6.0828	3.3322	1.56820	27.0270	116.239	1075.21
38	1444	54872	6.1644	3.3620	1.57978	26.3158	119.381	1134.11
39	1521	59319	6.2450	3.3912	1.59106	25.6410	122.522	1194.59
40	1600	64000	6.3246	3.4200	1.60206	25.0000	125.66	1256.64
41	1681	68921	6.4031	3.4482	1.61278	24.3902	128.81	1320.25
42	1764	74088	6.4807	3.4760	1.62325	23.8095	131.95	1385.44
43	1849	79507	6.5574	3.5034	1.63347	23.2558	135.09	1452.20
44	1936	85184	6.6332	3.5303	1.64345	22.7273	138.23	1520.53
45	2025	91125	6.7082	3.5569	1.65321	22.2222	141.37	1590.43
46	2116	97336	6.7823	3.5830	1.66276	21.7391	144.51	1661.90
47	2209	103823	6.8557	3.6088	1.67210	21.2766	147.65	1734.94
48	2304	110592	6.9282	3.6342	1.68124	20.8333	150.80	1809.56
49	2401	117649	7.0000	3.6593	1.69020	20.4082	153.94	1885.74

# MATHEMATICAL TABLES

## FUNCTIONS OF NUMBERS 50 TO 99

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No. = Diameter	
							Circum.	Area
50	2500	125000	7.0711	3.6840	1.69897	20.0000	157.08	1963.50
51	2601	132651	7.1414	3.7084	1.70757	19.6078	160.22	2042.82
52	2704	140608	7.2111	3.7325	1.71600	19.2308	163.36	2123.72
53	2809	148877	7.2801	3.7563	1.72428	18.8679	166.50	2206.18
54	2916	157464	7.3485	3.7798	1.73239	18.5185	169.65	2290.22
55	3025	166375	7.4162	3.8030	1.74036	18.1818	172.79	2375.83
56	3136	175616	7.4833	3.8259	1.74819	17.8571	175.93	2463.01
57	3249	185193	7.5498	3.8485	1.75587	17.5439	179.07	2551.76
58	3364	195112	7.6158	3.8709	1.76343	17.2414	182.21	2642.08
59	3481	205379	7.6811	3.8930	1.77085	16.9492	185.35	2733.97
60	3600	216000	7.7460	3.9149	1.77815	16.6667	188.50	2827.43
61	3721	226981	7.8102	3.9365	1.78533	16.3934	191.64	2922.47
62	3844	238328	7.8740	3.9579	1.79239	16.1290	194.78	3019.07
63	3969	250047	7.9373	3.9791	1.79934	15.8730	197.92	3117.25
64	4096	262144	8.0000	4.0000	1.80618	15.6250	201.06	3216.99
65	4225	274625	8.0623	4.0207	1.81291	15.3846	204.20	3318.31
66	4356	287496	8.1240	4.0412	1.81951	15.1515	207.35	3421.19
67	4489	300763	8.1854	4.0615	1.82607	14.9254	210.49	3525.65
68	4624	314432	8.2462	4.0817	1.83251	14.7059	213.63	3631.68
69	4761	328509	8.3066	4.1016	1.83885	14.4928	216.77	3739.28
70	4900	343000	8.3666	4.1213	1.84510	14.2857	219.91	3848.45
71	5041	357911	8.4261	4.1408	1.85126	14.0845	223.05	3959.19
72	5184	373248	8.4853	4.1602	1.85733	13.8889	226.19	4071.50
73	5329	389017	8.5440	4.1793	1.86332	13.6986	229.34	4185.39
74	5476	405224	8.6023	4.1983	1.86923	13.5135	232.48	4300.84
75	5625	421875	8.6603	4.2172	1.87506	13.3333	235.62	4417.86
76	5776	438976	8.7178	4.2358	1.88081	13.1579	238.76	4536.46
77	5929	456533	8.7750	4.2543	1.88649	12.9870	241.90	4656.63
78	6084	474552	8.8318	4.2727	1.89209	12.8205	245.04	4778.36
79	6241	493030	8.8882	4.2908	1.89763	12.6582	248.19	4901.67
80	6400	512000	8.9443	4.3089	1.90309	12.5000	251.33	5026.55
81	6561	531441	9.0000	4.3267	1.90849	12.3457	254.47	5153.00
82	6724	551368	9.0554	4.3445	1.91381	12.1951	257.61	5281.02
83	6889	571787	9.1104	4.3621	1.91908	12.0482	260.75	5410.61
84	7056	592704	9.1652	4.3795	1.92428	11.9048	263.89	5541.77
85	7225	614125	9.2195	4.3968	1.92942	11.7647	267.04	5674.50
86	7396	636056	9.2736	4.4140	1.93450	11.6279	270.18	5808.80
87	7569	658503	9.3274	4.4310	1.93952	11.4943	273.32	5944.68
88	7744	681472	9.3808	4.4480	1.94448	11.3636	276.46	6082.12
89	7921	704969	9.4340	4.4647	1.94939	11.2360	279.60	6221.14
90	8100	729000	9.4868	4.4814	1.95424	11.1111	282.74	6361.73
91	8281	753571	9.5394	4.4979	1.95904	10.9890	285.88	6503.88
92	8464	778688	9.5917	4.5144	1.96379	10.8696	289.03	6647.61
93	8649	804357	9.6437	4.5307	1.96848	10.7527	292.17	6792.91
94	8836	830584	9.6954	4.5468	1.97313	10.6383	295.31	6939.78
95	9025	857375	9.7468	4.5629	1.97772	10.5263	298.45	7088.22
96	9216	884736	9.7980	4.5789	1.98227	10.4167	301.59	7238.23
97	9409	912673	9.8489	4.5947	1.98677	10.3093	304.73	7389.81
98	9604	941192	9.8995	4.6104	1.99123	10.2041	307.88	7542.96
99	9801	970299	9.9499	4.6261	1.99564	10.1010	311.02	7697.69



# CARNEGIE STEEL COMPANY

## FUNCTIONS OF NUMBERS, 100 TO 149

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No. = Diameter	
							Circum.	Area
100	10000	1000000	10.0000	4.6416	2.00000	10.0000	314.16	7853.98
101	10201	1030301	10.0499	4.6570	2.00432	9.90099	317.30	8011.85
102	10404	1061208	10.0995	4.6723	2.00860	9.80392	320.44	8171.28
103	10609	1092727	10.1489	4.6875	2.01284	9.70874	323.58	8332.29
104	10816	1124864	10.1980	4.7027	2.01703	9.61538	326.73	8494.87
105	11025	1157625	10.2470	4.7177	2.02119	9.52381	329.87	8659.01
106	11236	1191016	10.2956	4.7326	2.02531	9.43396	333.01	8824.73
107	11449	1225043	10.3441	4.7475	2.02938	9.34579	336.15	8992.02
108	11664	1259712	10.3923	4.7622	2.03342	9.25926	339.29	9160.88
109	11881	1295029	10.4403	4.7769	2.03743	9.17431	342.43	9331.32
110	12100	1331000	10.4881	4.7914	2.04139	9.09091	345.58	9503.32
111	12321	1367631	10.5357	4.8059	2.04532	9.00001	348.72	9676.89
112	12544	1404928	10.5830	4.8203	2.04922	8.92857	351.86	9852.03
113	12769	1442897	10.6301	4.8346	2.05308	8.84956	355.00	10028.7
114	12996	1481544	10.6771	4.8488	2.05690	8.77193	358.14	10207.0
115	13225	1520875	10.7238	4.8629	2.06070	8.69565	361.28	10386.9
116	13456	1560896	10.7703	4.8770	2.06446	8.62069	364.42	10568.3
117	13689	1601613	10.8167	4.8910	2.06819	8.54701	367.57	10751.3
118	13924	1643032	10.8628	4.9049	2.07188	8.47458	370.71	10935.9
119	14161	1685159	10.9087	4.9187	2.07555	8.40336	373.85	11122.0
120	14400	1728000	10.9545	4.9324	2.07918	8.33333	376.99	11309.7
121	14641	1771561	11.0000	4.9461	2.08270	8.26446	380.13	11499.0
122	14884	1815848	11.0454	4.9597	2.08636	8.19672	383.27	11689.9
123	15129	1860867	11.0905	4.9732	2.08991	8.13008	386.42	11882.3
124	15376	1906624	11.1355	4.9866	2.09342	8.06452	389.56	12076.3
125	15625	1953125	11.1803	5.0000	2.09691	8.00000	392.70	12271.8
126	15876	2000376	11.2250	5.0133	2.10037	7.93651	395.84	12469.0
127	16129	2048383	11.2694	5.0265	2.10380	7.87402	398.98	12667.7
128	16384	2097152	11.3137	5.0397	2.10721	7.81250	402.12	12868.0
129	16641	2146689	11.3578	5.0528	2.11059	7.75194	405.27	13069.8
130	16900	2197000	11.4018	5.0658	2.11394	7.69231	408.41	13273.2
131	17161	2248091	11.4455	5.0788	2.11727	7.63359	411.55	13478.2
132	17424	2299968	11.4891	5.0916	2.12057	7.57576	414.69	13684.8
133	17689	2352637	11.5326	5.1045	2.12385	7.51880	417.83	13892.9
134	17956	2406104	11.5758	5.1172	2.12710	7.46269	420.97	14102.6
135	18225	2460375	11.6190	5.1299	2.13033	7.40741	424.12	14313.9
136	18496	2515456	11.6619	5.1426	2.13354	7.35294	427.26	14526.7
137	18769	2571353	11.7047	5.1551	2.13672	7.29927	430.40	14741.1
138	19044	2628072	11.7473	5.1676	2.13988	7.24638	433.54	14957.1
139	19321	2685619	11.7898	5.1801	2.14301	7.19424	436.68	15174.7
140	19600	2744000	11.8322	5.1925	2.14613	7.14286	439.82	15393.8
141	19881	2803221	11.8743	5.2048	2.14922	7.09220	442.96	15614.5
142	20164	2863288	11.9164	5.2171	2.15229	7.04225	446.11	15836.8
143	20449	2924207	11.9583	5.2293	2.15534	6.99301	449.25	16060.6
144	20736	2985984	12.0000	5.2415	2.15836	6.94444	452.39	16286.0
145	21025	3048625	12.0416	5.2536	2.16137	6.89655	455.53	16513.0
146	21316	3112136	12.0830	5.2656	2.16435	6.84932	458.67	16741.5
147	21609	3176523	12.1244	5.2776	2.16732	6.80272	461.81	16971.7
148	21904	3241792	12.1655	5.2896	2.17026	6.75676	464.96	17203.4
149	22201	3307949	12.2066	5.3015	2.17319	6.71141	468.10	17436.6

# MATHEMATICAL TABLES

## FUNCTIONS OF NUMBERS, 150 TO 199

No.	Square	Cube	Square Root	Cubic Root	Logarithm	1000 x Reciprocal	No. = Diameter	
							Circum.	Area
150	22500	3375000	12.2474	5.3133	2.17609	6.66667	471.24	17671.5
151	22801	3442951	12.2882	5.3251	2.17898	6.62252	474.38	17907.9
152	23104	3511808	12.3288	5.3368	2.18184	6.57805	477.52	18145.8
153	23409	3581577	12.3693	5.3485	2.18469	6.53505	480.66	18385.4
154	23716	3652264	12.4097	5.3601	2.18752	6.49351	483.81	18626.5
155	24025	3723875	12.4499	5.3717	2.19033	6.45161	486.95	18869.2
156	24336	3796416	12.4900	5.3832	2.19312	6.41026	490.09	19113.4
157	24649	3869893	12.5300	5.3947	2.19590	6.36943	493.23	19359.3
158	24964	3944312	12.5698	5.4061	2.19866	6.32911	496.37	19606.7
159	25281	4019679	12.6095	5.4175	2.20140	6.28931	499.51	19855.7
160	25600	4096000	12.6491	5.4288	2.20412	6.25000	502.65	20106.2
161	25921	4173281	12.6886	5.4401	2.20683	6.21118	505.80	20358.3
162	26244	4251528	12.7279	5.4514	2.20952	6.17284	508.94	20612.0
163	26569	4330747	12.7671	5.4626	2.21219	6.13497	512.08	20867.2
164	26896	4410944	12.8062	5.4737	2.21484	6.09756	515.22	21124.1
165	27225	4492125	12.8452	5.4848	2.21748	6.06061	518.36	21382.5
166	27556	4574296	12.8841	5.4959	2.22011	6.02410	521.50	21642.4
167	27889	4657463	12.9228	5.5069	2.22272	5.98802	524.65	21904.0
168	28224	4741632	12.9615	5.5178	2.22531	5.95238	527.79	22167.1
169	28561	4826809	13.0000	5.5288	2.22789	5.91716	530.93	22431.8
170	28900	4913000	13.0384	5.5397	2.23045	5.88235	534.07	22698.0
171	29241	5000211	13.0767	5.5505	2.23300	5.84705	537.21	22965.8
172	29584	5088448	13.1149	5.5613	2.23553	5.81195	540.35	23235.2
173	29929	5177717	13.1529	5.5721	2.23805	5.77805	543.50	23506.2
174	30276	5268024	13.1909	5.5828	2.24055	5.74713	546.64	23778.7
175	30625	5359375	13.2288	5.5934	2.24304	5.71429	549.78	24052.8
176	30976	5451776	13.2665	5.6041	2.24551	5.68182	552.92	24328.5
177	31329	5545233	13.3041	5.6147	2.24797	5.64972	556.06	24605.7
178	31684	5639752	13.3417	5.6252	2.25042	5.61798	559.20	24884.6
179	32041	5735339	13.3791	5.6357	2.25285	5.58659	562.35	25164.9
180	32400	5832000	13.4164	5.6462	2.25527	5.55556	565.49	25446.9
181	32761	5929741	13.4536	5.6567	2.25768	5.52486	568.63	25730.4
182	33124	6028568	13.4907	5.6671	2.26007	5.49451	571.77	26015.5
183	33489	6128487	13.5277	5.6774	2.26245	5.46448	574.91	26302.2
184	33856	6229504	13.5647	5.6877	2.26482	5.43478	578.05	26590.4
185	34225	6331625	13.6015	5.6980	2.26717	5.40541	581.19	26880.3
186	34596	6434856	13.6382	5.7083	2.26951	5.37634	584.34	27171.6
187	34969	6539203	13.6748	5.7185	2.27184	5.34759	587.48	27464.6
188	35344	6644672	13.7113	5.7287	2.27416	5.31915	590.62	27759.1
189	35721	6751269	13.7477	5.7388	2.27646	5.29101	593.76	28055.2
190	36100	6859000	13.7840	5.7489	2.27875	5.26310	596.90	28352.9
191	36481	6967871	13.8203	5.7590	2.28103	5.23550	600.04	28652.1
192	36864	7077888	13.8564	5.7690	2.28330	5.20833	603.19	28952.9
193	37249	7189057	13.8924	5.7790	2.28556	5.18135	606.33	29255.3
194	37636	7301384	13.9284	5.7890	2.28780	5.15464	609.47	29559.2
195	38025	7414875	13.9642	5.7989	2.29003	5.12821	612.61	29864.8
196	38416	7529536	14.0000	5.8088	2.29226	5.10204	615.75	30171.9
197	38809	7645373	14.0357	5.8186	2.29447	5.07614	618.89	30480.5
198	39204	7762392	14.0712	5.8285	2.29667	5.05051	622.04	30790.7
199	39601	7880599	14.1067	5.8383	2.29885	5.02513	625.18	31102.6

# CARNEGIE STEEL COMPANY

## FUNCTIONS OF NUMBERS, 200 TO 249

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No. — Diameter	
							Circum.	Area
200	40000	8000000	14.1421	5.8480	2.30103	5.00000	628.32	31415.9
201	40401	8120601	14.1774	5.8578	2.30320	4.97512	631.46	31730.9
202	40804	8242408	14.2127	5.8675	2.30535	4.95050	634.60	32047.4
203	41209	8365427	14.2478	5.8771	2.30750	4.92611	637.74	32365.5
204	41616	8489664	14.2820	5.8868	2.30963	4.90196	640.88	32685.1
205	42025	8615125	14.3178	5.8964	2.31175	4.87805	644.03	33006.4
206	42436	8741816	14.3527	5.9059	2.31387	4.85437	647.17	33329.2
207	42849	8869743	14.3875	5.9155	2.31597	4.83092	650.31	33653.5
208	43264	8998912	14.4222	5.9250	2.31806	4.80769	653.45	33979.5
209	43681	9129329	14.4568	5.9345	2.32015	4.78469	656.59	34307.0
210	44100	9261000	14.4914	5.9439	2.32222	4.76190	659.73	34636.1
211	44521	9393931	14.5258	5.9533	2.32428	4.73934	662.88	34966.7
212	44944	9528128	14.5602	5.9627	2.32634	4.71698	666.02	35298.9
213	45369	9663597	14.5945	5.9721	2.32838	4.69484	669.16	35632.7
214	45796	9800344	14.6287	5.9814	2.33041	4.67290	672.30	35968.1
215	46225	9938375	14.6629	5.9907	2.33244	4.65116	675.44	36305.0
216	46656	10077696	14.6969	6.0000	2.33445	4.62963	678.58	36643.5
217	47089	10218313	14.7309	6.0092	2.33646	4.60829	681.73	36983.6
218	47524	10360232	14.7648	6.0185	2.33846	4.58716	684.87	37325.3
219	47961	10503459	14.7986	6.0277	2.34044	4.56621	688.01	37668.5
220	48400	10648000	14.8324	6.0368	2.34242	4.54545	691.15	38013.3
221	48841	10793861	14.8661	6.0459	2.34439	4.52489	694.29	38359.6
222	49284	10941048	14.8997	6.0550	2.34635	4.50450	697.43	38707.6
223	49729	11089567	14.9332	6.0641	2.34830	4.48430	700.58	39057.1
224	50176	11239424	14.9666	6.0732	2.35025	4.46429	703.72	39408.1
225	50625	11390625	15.0000	6.0822	2.35218	4.44444	706.86	39760.8
226	51076	11543176	15.0333	6.0912	2.35411	4.42478	710.00	40115.0
227	51529	11697083	15.0665	6.1002	2.35603	4.40529	713.14	40470.8
228	51984	11852352	15.0997	6.1091	2.35793	4.38596	716.28	40828.1
229	52441	12008989	15.1327	6.1180	2.35984	4.36681	719.42	41187.1
230	52900	12167000	15.1658	6.1269	2.36173	4.34783	722.57	41547.6
231	53361	12326391	15.1987	6.1358	2.36361	4.32900	725.71	41909.6
232	53824	12487168	15.2315	6.1446	2.36549	4.31034	728.85	42273.3
233	54289	12649337	15.2643	6.1534	2.36736	4.29185	731.99	42638.5
234	54756	12812904	15.2971	6.1622	2.36922	4.27350	735.13	43005.3
235	55225	12977875	15.3297	6.1710	2.37107	4.25532	738.27	43373.6
236	55696	13144256	15.3623	6.1797	2.37291	4.23729	741.42	43743.5
237	56169	13312053	15.3948	6.1885	2.37475	4.21941	744.56	44115.0
238	56644	13481272	15.4272	6.1972	2.37658	4.20168	747.70	44488.1
239	57121	13651919	15.4596	6.2058	2.37840	4.18410	750.84	44862.7
240	57600	13824000	15.4919	6.2145	2.38021	4.16667	753.98	45238.9
241	58081	13997521	15.5242	6.2231	2.38202	4.14933	757.12	45616.7
242	58564	14172488	15.5563	6.2317	2.38382	4.13223	760.27	45996.1
243	59049	14348907	15.5885	6.2403	2.38561	4.11523	763.41	46377.0
244	59536	14526784	15.6205	6.2488	2.38739	4.09830	766.55	46759.5
245	60025	14706125	15.6525	6.2573	2.38917	4.08163	769.69	47143.5
246	60516	14886936	15.6844	6.2658	2.39094	4.06504	772.83	47529.2
247	61009	15069223	15.7162	6.2743	2.39270	4.04855	775.97	47916.4
248	61504	15252992	15.7480	6.2828	2.39445	4.03226	779.12	48305.1
249	62001	15438249	15.7797	6.2912	2.39620	4.01606	782.26	48695.5

# MATHEMATICAL TABLES

## FUNCTIONS OF NUMBERS, 250 TO 299

No.	Square	Cube	Square Root	Cubic Root	Logarithm	1000 x Reciprocal	No. = Diameter	
							Circum.	Area
250	62500	15625000	15.8114	6.2096	2.39794	4.00000	785.40	49087.4
251	63001	15813251	15.8430	6.3080	2.39967	3.98406	788.54	49480.9
252	63504	16003008	15.8745	6.3184	2.40140	3.96825	791.68	49875.9
253	64009	16194277	15.9060	6.3247	2.40312	3.95257	794.82	50272.6
254	64516	16387064	15.9374	6.3330	2.40483	3.93701	797.96	50670.7
255	65025	16581375	15.9687	6.3413	2.40654	3.92157	801.11	51070.5
256	65536	16777216	16.0000	6.3496	2.40824	3.90625	804.25	51471.9
257	66049	16974593	16.0312	6.3579	2.40993	3.89105	807.39	51874.8
258	66564	17173512	16.0624	6.3661	2.41162	3.87597	810.53	52279.2
259	67081	17373979	16.0935	6.3743	2.41330	3.86100	813.67	52685.3
260	67600	17576000	16.1245	6.3825	2.41497	3.84615	816.81	53092.9
261	68121	17779581	16.1555	6.3907	2.41664	3.83142	819.96	53502.1
262	68644	17984728	16.1864	6.3988	2.41830	3.81679	823.10	53912.9
263	69169	18191447	16.2173	6.4070	2.41996	3.80228	826.24	54325.2
264	69696	18399744	16.2481	6.4151	2.42160	3.78788	829.38	54739.1
265	70225	18609625	16.2788	6.4232	2.42325	3.77358	832.52	55154.6
266	70756	18821096	16.3095	6.4312	2.42488	3.75940	835.66	55571.0
267	71289	19034163	16.3401	6.4393	2.42651	3.74532	838.81	55990.2
268	71824	19248832	16.3707	6.4473	2.42813	3.73134	841.95	56410.4
269	72361	19465109	16.4012	6.4553	2.42975	3.71747	845.09	56832.2
270	72900	19683000	16.4317	6.4633	2.43136	3.70370	848.23	57255.5
271	73441	19902511	16.4621	6.4713	2.43297	3.69004	851.37	57680.4
272	73984	20123648	16.4924	6.4792	2.43457	3.67647	854.51	58106.9
273	74529	20346417	16.5227	6.4872	2.43616	3.66300	857.65	58534.9
274	75076	20570824	16.5529	6.4951	2.43775	3.64964	860.80	58964.6
275	75625	20796875	16.5831	6.5030	2.43933	3.63636	863.94	59395.7
276	76176	21024576	16.6132	6.5108	2.44091	3.62310	867.08	59828.5
277	76729	21253933	16.6433	6.5187	2.44248	3.61011	870.22	60262.8
278	77284	21484952	16.6733	6.5265	2.44404	3.59712	873.36	60698.7
279	77841	21717639	16.7033	6.5343	2.44560	3.58423	876.50	61136.2
280	78400	21952000	16.7332	6.5421	2.44716	3.57143	879.65	61575.2
281	78961	22188041	16.7631	6.5499	2.44871	3.55872	882.79	62015.8
282	79524	22425768	16.7929	6.5577	2.45025	3.54610	885.93	62458.0
283	80089	22665187	16.8226	6.5654	2.45179	3.53357	889.07	62901.8
284	80656	22906304	16.8523	6.5731	2.45332	3.52113	892.21	63347.1
285	81225	23149125	16.8819	6.5808	2.45484	3.50877	895.35	63794.0
286	81796	23393656	16.9115	6.5885	2.45637	3.49650	898.50	64242.4
287	82369	23639903	16.9411	6.5962	2.45788	3.48432	901.64	64692.5
288	82944	23887872	16.9706	6.6039	2.45939	3.47222	904.78	65144.1
289	83521	24137569	17.0000	6.6115	2.46090	3.46021	907.92	65597.2
290	84100	24389000	17.0294	6.6191	2.46240	3.44823	911.06	66052.0
291	84681	24642171	17.0587	6.6267	2.46389	3.43643	914.20	66508.3
292	85264	24897088	17.0880	6.6343	2.46538	3.42466	917.35	66966.2
293	85849	25153757	17.1172	6.6419	2.46687	3.41297	920.49	67425.6
294	86436	25412184	17.1464	6.6494	2.46835	3.40136	923.63	67886.7
295	87025	25672375	17.1756	6.6569	2.46982	3.38983	926.77	68349.3
296	87616	25934336	17.2047	6.6644	2.47129	3.37838	929.91	68813.4
297	88209	26198073	17.2337	6.6719	2.47276	3.36700	933.05	69279.2
298	88804	26463592	17.2627	6.6794	2.47422	3.35570	936.19	69746.5
299	89401	26730899	17.2916	6.6869	2.47567	3.34448	939.34	70215.4

# CARNEGIE STEEL COMPANY

## FUNCTIONS OF NUMBERS, 300 TO 349

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No. = Diameter	
							Circum.	Area
300	90000	27000000	17.3205	6.6943	2.47712	3.33333	942.48	70685.8
301	90601	27270901	17.3494	6.7018	2.47857	3.32226	945.62	71157.9
302	91204	27543608	17.3781	6.7092	2.48001	3.31126	948.76	71631.5
303	91809	27818127	17.4069	6.7166	2.48144	3.30033	951.90	72106.6
304	92410	28094464	17.4356	6.7240	2.48287	3.28947	955.04	72583.4
305	93025	28372825	17.4642	6.7313	2.48430	3.27869	958.19	73061.7
306	93636	28652616	17.4929	6.7387	2.48572	3.26797	961.33	73541.5
307	94249	28934443	17.5214	6.7460	2.48714	3.25733	964.47	74023.0
308	94864	29218112	17.5499	6.7533	2.48855	3.24675	967.61	74506.0
309	95481	29503629	17.5784	6.7606	2.48996	3.23625	970.75	74990.6
310	96100	29791000	17.6068	6.7679	2.49136	3.22581	973.89	75476.8
311	96721	30080231	17.6352	6.7752	2.49276	3.21543	977.04	75964.5
312	97344	30371328	17.6635	6.7824	2.49415	3.20513	980.18	76453.8
313	97969	30664297	17.6918	6.7897	2.49554	3.19489	983.32	76944.7
314	98596	30959144	17.7200	6.7969	2.49693	3.18471	986.46	77437.1
315	99225	31255875	17.7482	6.8041	2.49831	3.17460	989.60	77931.1
316	99856	31554496	17.7764	6.8113	2.49969	3.16456	992.74	78426.7
317	100489	31855013	17.8045	6.8185	2.50106	3.15457	995.88	78923.9
318	101124	32157432	17.8326	6.8256	2.50243	3.14465	999.03	79422.6
319	101761	32461759	17.8606	6.8328	2.50379	3.13480	1002.2	79922.9
320	102400	32768000	17.8885	6.8399	2.50515	3.12500	1005.3	80424.8
321	103041	33076101	17.9165	6.8470	2.50651	3.11526	1008.5	80928.2
322	103684	33386248	17.9444	6.8541	2.50786	3.10559	1011.6	81433.2
323	104329	33698267	17.9722	6.8612	2.50920	3.09598	1014.7	81939.8
324	104976	34012224	18.0000	6.8683	2.51055	3.08642	1017.9	82448.0
325	105625	34328125	18.0278	6.8753	2.51188	3.07692	1021.0	82957.7
326	106276	34645076	18.0555	6.8824	2.51322	3.06749	1024.2	83469.0
327	106929	34965783	18.0831	6.8894	2.51455	3.05810	1027.3	83981.8
328	107584	35287552	18.1108	6.8964	2.51587	3.04878	1030.4	84496.3
329	108241	35611289	18.1384	6.9034	2.51720	3.03951	1033.6	85012.3
330	108900	35937000	18.1659	6.9104	2.51851	3.03030	1036.7	85529.9
331	109561	36264691	18.1934	6.9174	2.51983	3.02115	1039.9	86049.0
332	110224	36594368	18.2209	6.9244	2.52114	3.01205	1043.0	86569.7
333	110889	36926037	18.2483	6.9313	2.52244	3.00300	1046.2	87092.0
334	111556	37259704	18.2757	6.9382	2.52375	2.99401	1049.3	87615.9
335	112225	37595375	18.3030	6.9451	2.52504	2.98507	1052.4	88141.3
336	112896	37933056	18.3303	6.9521	2.52634	2.97619	1055.6	88668.3
337	113569	38272753	18.3576	6.9589	2.52763	2.96736	1058.7	89196.9
338	114244	38614472	18.3848	6.9658	2.52892	2.95858	1061.9	89727.0
339	114921	38958219	18.4120	6.9727	2.53020	2.94985	1065.0	90258.7
340	115600	39304000	18.4391	6.9795	2.53148	2.94118	1068.1	90792.0
341	116281	39651821	18.4662	6.9864	2.53275	2.93255	1071.3	91326.9
342	116964	40001688	18.4932	6.9932	2.53403	2.92398	1074.4	91863.3
343	117649	40353607	18.5203	7.0000	2.53529	2.91545	1077.6	92401.3
344	118336	40707584	18.5472	7.0068	2.53656	2.90698	1080.7	92940.9
345	119025	41063625	18.5742	7.0136	2.53782	2.89855	1083.8	93482.0
346	119716	41421736	18.6011	7.0203	2.53908	2.89017	1087.0	94024.7
347	120409	41781923	18.6279	7.0271	2.54033	2.88184	1090.1	94569.0
348	121104	42144192	18.6548	7.0338	2.54158	2.87356	1093.3	95114.9
349	121801	42508549	18.6815	7.0406	2.54283	2.86533	1096.4	95662.3

# MATHEMATICAL TABLES

## FUNCTIONS OF NUMBERS, 350 TO 399

No.	Square	Cube	Square Root	Cubic Root	Logarithm	1000 x Reciprocal	No. = Diameter	
							Circum.	Area
350	122500	42875000	18.7083	7.0473	2.54407	2.85714	1099.6	06211.3
351	123201	43243551	18.7350	7.0540	2.54531	2.84900	1102.7	06761.8
352	123904	43614208	18.7617	7.0607	2.54654	2.84091	1105.8	07314.0
353	124609	43986977	18.7883	7.0674	2.54777	2.83288	1109.0	07867.7
354	125316	44361864	18.8149	7.0740	2.54900	2.82486	1112.1	08423.0
355	126025	44738875	18.8414	7.0807	2.55023	2.81690	1115.3	08979.8
356	126736	45118016	18.8680	7.0873	2.55145	2.80899	1118.4	09538.2
357	127449	45499293	18.8944	7.0940	2.55267	2.80112	1121.5	10099.8
358	128164	45882712	18.9209	7.1006	2.55388	2.79330	1124.7	10660.6
359	128881	46268279	18.9473	7.1072	2.55509	2.78552	1127.8	101223
360	129600	46656000	18.9737	7.1138	2.55630	2.77778	1131.0	101788
361	130321	47045881	19.0000	7.1204	2.55751	2.77008	1134.1	102354
362	131044	47437928	19.0263	7.1269	2.55871	2.76243	1137.3	102922
363	131769	47832147	19.0526	7.1335	2.55991	2.75482	1140.4	103491
364	132496	48228544	19.0788	7.1400	2.56110	2.74725	1143.5	104062
365	133225	48627125	19.1050	7.1466	2.56229	2.73973	1146.7	104635
366	133956	49027896	19.1311	7.1531	2.56348	2.73224	1149.8	105209
367	134689	49430863	19.1572	7.1596	2.56467	2.72480	1153.0	105785
368	135424	49836032	19.1833	7.1661	2.56585	2.71739	1156.1	106362
369	136161	50243409	19.2094	7.1726	2.56703	2.71003	1159.2	106941
370	136900	50653000	19.2354	7.1791	2.56820	2.70270	1162.4	107521
371	137641	51064811	19.2614	7.1855	2.56937	2.69542	1165.5	108103
372	138384	51478848	19.2873	7.1920	2.57054	2.68817	1168.7	108687
373	139129	51895117	19.3132	7.1984	2.57171	2.68097	1171.8	109272
374	139876	52313624	19.3391	7.2048	2.57287	2.67380	1175.0	109858
375	140625	52734375	19.3649	7.2112	2.57403	2.66667	1178.1	110447
376	141376	53157376	19.3907	7.2177	2.57519	2.65957	1181.2	111036
377	142129	53582633	19.4165	7.2240	2.57634	2.65252	1184.4	111628
378	142884	54010152	19.4422	7.2304	2.57749	2.64550	1187.5	112221
379	143641	54439939	19.4679	7.2368	2.57864	2.63852	1190.7	112815
380	144400	54872000	19.4936	7.2432	2.57978	2.63158	1193.8	113411
381	145161	55306341	19.5192	7.2495	2.58093	2.62467	1196.9	114009
382	145924	55742968	19.5448	7.2558	2.58206	2.61780	1200.1	114608
383	146689	56181887	19.5704	7.2622	2.58320	2.61097	1203.2	115209
384	147456	56623104	19.5959	7.2685	2.58433	2.60417	1206.4	115812
385	148225	57066625	19.6214	7.2748	2.58546	2.59740	1209.5	116416
386	148996	57512450	19.6469	7.2811	2.58659	2.59067	1212.7	117021
387	149769	57960603	19.6723	7.2874	2.58771	2.58398	1215.8	117628
388	150544	58411072	19.6977	7.2936	2.58883	2.57732	1218.9	118237
389	151321	58863869	19.7231	7.2999	2.58995	2.57069	1222.1	118847
390	152100	59319000	19.7484	7.3061	2.59106	2.56410	1225.2	119459
391	152881	59776471	19.7737	7.3124	2.59218	2.55754	1228.4	120072
392	153664	60236288	19.7990	7.3186	2.59329	2.55102	1231.5	120687
393	154449	60698457	19.8242	7.3248	2.59439	2.54453	1234.6	121304
394	155236	61162984	19.8494	7.3310	2.59550	2.53807	1237.8	121922
395	156025	61629875	19.8746	7.3372	2.59660	2.53165	1240.9	122542
396	156816	62099136	19.8997	7.3434	2.59770	2.52525	1244.1	123163
397	157609	62570773	19.9249	7.3496	2.59879	2.51889	1247.2	123786
398	158404	63044792	19.9499	7.3558	2.59988	2.51256	1250.4	124410
399	159201	63521199	19.9750	7.3619	2.60097	2.50627	1253.5	125036

# CARNEGIE STEEL COMPANY

## FUNCTIONS OF NUMBERS 400 TO 449

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No.—Diameter	
							Circum.	Area
400	160000	64000000	20.0000	7.3681	2.60206	2.50000	1256.6	125664
401	160801	64481201	20.0250	7.3742	2.60314	2.49377	1259.8	126293
402	161604	64964808	20.0499	7.3803	2.60423	2.48756	1262.9	126923
403	162409	65450827	20.0749	7.3864	2.60531	2.48139	1266.1	127556
404	163216	65939264	20.0998	7.3925	2.60638	2.47525	1269.2	128190
405	164025	66430125	20.1246	7.3986	2.60746	2.46914	1272.3	128825
406	164836	66923416	20.1494	7.4047	2.60853	2.46305	1275.5	129462
407	165649	67419143	20.1742	7.4108	2.60959	2.45700	1278.6	130100
408	166464	67917312	20.1990	7.4169	2.61066	2.45098	1281.8	130741
409	167281	68417929	20.2237	7.4229	2.61172	2.44499	1284.9	131382
410	168100	68921000	20.2485	7.4290	2.61278	2.43902	1288.1	132025
411	168921	69426531	20.2731	7.4350	2.61384	2.43309	1291.2	132670
412	169744	69934528	20.2978	7.4410	2.61490	2.42718	1294.3	133317
413	170569	70444997	20.3224	7.4470	2.61595	2.42131	1297.5	133965
414	171396	70957944	20.3470	7.4530	2.61700	2.41546	1300.6	134614
415	172225	71473375	20.3715	7.4590	2.61805	2.40964	1303.8	135265
416	173056	71991296	20.3961	7.4650	2.61909	2.40385	1306.9	135918
417	173889	72511713	20.4206	7.4710	2.62014	2.39808	1310.0	136572
418	174724	73034632	20.4450	7.4770	2.62118	2.39234	1313.2	137228
419	175561	73560059	20.4695	7.4829	2.62221	2.38663	1316.3	137885
420	176400	74088000	20.4939	7.4889	2.62325	2.38095	1319.5	138544
421	177241	74618461	20.5183	7.4948	2.62428	2.37530	1322.6	139205
422	178084	75151448	20.5426	7.5007	2.62531	2.36967	1325.8	139867
423	178929	75686967	20.5670	7.5067	2.62634	2.36407	1328.9	140531
424	179776	76225024	20.5913	7.5126	2.62737	2.35849	1332.0	141196
425	180625	76765625	20.6155	7.5185	2.62839	2.35294	1335.2	141863
426	181476	77308776	20.6398	7.5244	2.62941	2.34742	1338.3	142531
427	182329	77854483	20.6640	7.5302	2.63043	2.34192	1341.5	143201
428	183184	78402752	20.6882	7.5361	2.63144	2.33645	1344.6	143872
429	184041	78953589	20.7123	7.5420	2.63246	2.33100	1347.7	144545
430	184900	79507000	20.7364	7.5478	2.63347	2.32558	1350.9	145220
431	185761	80062991	20.7605	7.5537	2.63448	2.32019	1354.0	145896
432	186624	80621568	20.7846	7.5595	2.63548	2.31481	1357.2	146574
433	187489	81182737	20.8087	7.5654	2.63649	2.30947	1360.3	147254
434	188356	81746504	20.8327	7.5712	2.63749	2.30415	1363.5	147934
435	189225	82312875	20.8567	7.5770	2.63849	2.29885	1366.6	148617
436	190096	82881856	20.8806	7.5828	2.63949	2.29358	1369.7	149301
437	190969	83453453	20.9045	7.5886	2.64048	2.28833	1372.9	149987
438	191844	84027672	20.9284	7.5944	2.64147	2.28311	1376.0	150674
439	192721	84604519	20.9523	7.6001	2.64246	2.27790	1379.2	151363
440	193600	85184000	20.9762	7.6059	2.64345	2.27273	1382.3	152053
441	194481	85766121	21.0000	7.6117	2.64444	2.26757	1385.4	152745
442	195364	86350888	21.0238	7.6174	2.64542	2.26244	1388.6	153439
443	196249	86938307	21.0476	7.6232	2.64640	2.25734	1391.7	154134
444	197136	87528384	21.0713	7.6289	2.64738	2.25225	1394.9	154830
445	198025	88121125	21.0950	7.6346	2.64836	2.24719	1398.0	155528
446	198916	88716536	21.1187	7.6403	2.64933	2.24215	1401.2	156228
447	199809	89314623	21.1424	7.6460	2.65031	2.23714	1404.3	156930
448	200704	89915392	21.1660	7.6517	2.65128	2.23214	1407.4	157633
449	201601	90518849	21.1896	7.6574	2.65225	2.22717	1410.6	158337

# MATHEMATICAL TABLES

## FUNCTIONS OF NUMBERS, 450 TO 499

No.	Square	Cube	Square Root	Cubic Root	Logarithm	1000 x Reciprocal	No. = Diameter	
							Circum.	Area
450	202500	91125000	21.2132	7.6631	2.65321	2.22222	1413.7	150043
451	203401	91733851	21.2368	7.6688	2.65418	2.21729	1416.9	150751
452	204304	92345408	21.2603	7.6744	2.65514	2.21239	1420.0	150460
453	205209	92959677	21.2838	7.6801	2.65610	2.20751	1423.1	151171
454	206116	93576664	21.3073	7.6857	2.65706	2.20264	1426.3	151883
455	207025	94196375	21.3307	7.6914	2.65801	2.19780	1429.4	152597
456	207936	94818816	21.3542	7.6970	2.65896	2.19298	1432.6	153313
457	208849	95443993	21.3776	7.7026	2.65992	2.18818	1435.7	154030
458	209764	96071912	21.4009	7.7082	2.66087	2.18341	1438.8	154748
459	210681	96702579	21.4243	7.7138	2.66181	2.17865	1442.0	155468
460	211600	97336000	21.4476	7.7194	2.66276	2.17391	1445.1	156190
461	212521	97972181	21.4709	7.7250	2.66370	2.16920	1448.3	156914
462	213444	98611128	21.4942	7.7306	2.66464	2.16450	1451.4	157639
463	214369	99252847	21.5174	7.7362	2.66558	2.15983	1454.6	158365
464	215296	99897344	21.5407	7.7418	2.66652	2.15517	1457.7	159093
465	216225	100544625	21.5639	7.7473	2.66745	2.15054	1460.8	159823
466	217156	101194696	21.5870	7.7529	2.66839	2.14592	1464.0	160554
467	218089	101847563	21.6102	7.7584	2.66932	2.14133	1467.1	171287
468	219024	102503232	21.6333	7.7639	2.67025	2.13675	1470.3	172021
469	219961	103161709	21.6564	7.7695	2.67117	2.13220	1473.4	172757
470	220900	103823000	21.6795	7.7750	2.67210	2.12766	1476.5	173494
471	221841	104487111	21.7025	7.7805	2.67302	2.12314	1479.7	174234
472	222784	105154048	21.7256	7.7860	2.67394	2.11864	1482.8	174974
473	223729	105823817	21.7486	7.7915	2.67486	2.11416	1486.0	175716
474	224676	106496424	21.7715	7.7970	2.67578	2.10970	1489.1	176460
475	225625	107171875	21.7945	7.8025	2.67669	2.10526	1492.3	177205
476	226576	107850176	21.8174	7.8079	2.67761	2.10084	1495.4	177952
477	227529	108531333	21.8403	7.8134	2.67852	2.09644	1498.5	178701
478	228484	109215352	21.8632	7.8188	2.67943	2.09205	1501.7	179451
479	229441	109902239	21.8861	7.8243	2.68034	2.08768	1504.8	180203
480	230400	110592000	21.9089	7.8297	2.68124	2.08333	1508.0	180956
481	231361	111284641	21.9317	7.8352	2.68215	2.07900	1511.1	181711
482	232324	111980168	21.9545	7.8406	2.68305	2.07469	1514.2	182467
483	233289	112678587	21.9773	7.8460	2.68395	2.07039	1517.4	183225
484	234256	113379904	22.0000	7.8514	2.68485	2.06612	1520.5	183984
485	235225	114084125	22.0227	7.8568	2.68574	2.06186	1523.7	184745
486	236196	114791256	22.0454	7.8622	2.68664	2.05761	1526.8	185508
487	237169	115501303	22.0681	7.8676	2.68753	2.05339	1530.0	186272
488	238144	116214272	22.0907	7.8730	2.68842	2.04918	1533.1	187038
489	239121	116930169	22.1133	7.8784	2.68931	2.04499	1536.2	187805
490	240100	117649000	22.1359	7.8837	2.69020	2.04082	1539.4	188574
491	241081	118370771	22.1585	7.8891	2.69108	2.03666	1542.5	189345
492	242064	119095488	22.1811	7.8944	2.69197	2.03252	1545.7	190117
493	243049	119823157	22.2036	7.8998	2.69285	2.02840	1548.8	190890
494	244036	120553784	22.2261	7.9051	2.69373	2.02429	1551.9	191665
495	245025	121287375	22.2486	7.9105	2.69461	2.02020	1555.1	192442
496	246016	122023936	22.2711	7.9158	2.69548	2.01613	1558.2	193221
497	247009	122763473	22.2935	7.9211	2.69636	2.01207	1561.4	194000
498	248004	123505992	22.3159	7.9264	2.69723	2.00803	1564.5	194782
499	249001	124251499	22.3383	7.9317	2.69810	2.00401	1567.7	195565



# CARNEGIE STEEL COMPANY

## FUNCTIONS OF NUMBERS 600 TO 649

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No.—Diameter	
							Circum.	Area
600	360000	216000000	24.4940	8.4343	2.77815	1.66667	1885.0	282743
601	361201	217081801	24.5153	8.4390	2.77887	1.66389	1888.1	283087
602	362404	218167208	24.5357	8.4437	2.77960	1.66113	1891.2	284631
603	363609	219256227	24.5561	8.4484	2.78032	1.65837	1894.4	285578
604	364816	220348864	24.5764	8.4530	2.78104	1.65563	1897.5	286526
605	366025	221445125	24.5967	8.4577	2.78176	1.65289	1900.7	287475
606	367236	222545016	24.6171	8.4623	2.78247	1.65017	1903.8	288426
607	368449	223648543	24.6374	8.4670	2.78319	1.64745	1906.9	289379
608	369664	224755712	24.6577	8.4716	2.78390	1.64474	1910.1	290333
609	370881	225866529	24.6779	8.4763	2.78462	1.64204	1913.2	291289
610	372100	226981000	24.6982	8.4809	2.78533	1.63934	1916.4	292247
611	373321	228099131	24.7184	8.4856	2.78604	1.63666	1919.5	293206
612	374544	229220928	24.7386	8.4902	2.78675	1.63399	1922.7	294166
613	375769	230346397	24.7588	8.4948	2.78746	1.63132	1925.8	295128
614	376996	231475544	24.7790	8.4994	2.78817	1.62866	1928.9	296092
615	378225	232608375	24.7992	8.5040	2.78888	1.62602	1932.1	297057
616	379456	233744896	24.8193	8.5086	2.78958	1.62338	1935.2	298024
617	380689	234885113	24.8395	8.5132	2.79029	1.62075	1938.4	298992
618	381924	236029032	24.8596	8.5178	2.79099	1.61812	1941.5	299962
619	383161	237176659	24.8797	8.5224	2.79169	1.61551	1944.6	300934
620	384400	238328000	24.8998	8.5270	2.79239	1.61290	1947.8	301907
621	385641	239483061	24.9199	8.5316	2.79309	1.61031	1950.9	302882
622	386884	240641848	24.9399	8.5362	2.79379	1.60772	1954.1	303858
623	388129	241804367	24.9600	8.5408	2.79449	1.60514	1957.2	304836
624	389376	242970624	24.9800	8.5453	2.79518	1.60256	1960.4	305815
625	390625	244140625	25.0000	8.5499	2.79588	1.60000	1963.5	306796
626	391876	245314376	25.0200	8.5544	2.79657	1.59744	1966.6	307779
627	393129	246491883	25.0400	8.5590	2.79727	1.59490	1969.8	308763
628	394384	247673152	25.0599	8.5635	2.79796	1.59236	1972.9	309748
629	395641	248858189	25.0799	8.5681	2.79865	1.58983	1976.1	310736
630	396900	250047000	25.0998	8.5726	2.79934	1.58730	1979.2	311725
631	398161	251239591	25.1197	8.5772	2.80003	1.58479	1982.3	312715
632	399424	252435968	25.1396	8.5817	2.80072	1.58228	1985.5	313707
633	400689	253636137	25.1595	8.5862	2.80140	1.57978	1988.6	314700
634	401956	254840104	25.1794	8.5907	2.80209	1.57729	1991.8	315696
635	403225	256047875	25.1992	8.5952	2.80277	1.57480	1994.9	316692
636	404496	257259456	25.2190	8.5997	2.80346	1.57233	1998.1	317690
637	405769	258474853	25.2389	8.6043	2.80414	1.56986	2001.2	318690
638	407044	259694072	25.2587	8.6088	2.80482	1.56740	2004.3	319692
639	408321	260917119	25.2784	8.6132	2.80550	1.56495	2007.5	320695
640	409600	262144000	25.2982	8.6177	2.80618	1.56250	2010.6	321699
641	410881	263374721	25.3180	8.6222	2.80686	1.56006	2013.8	322705
642	412164	264609288	25.3377	8.6267	2.80754	1.55763	2016.9	323713
643	413449	265847707	25.3574	8.6312	2.80821	1.55521	2020.0	324722
644	414736	267089984	25.3772	8.6357	2.80889	1.55280	2023.2	325733
645	416025	268336125	25.3969	8.6401	2.80956	1.55039	2026.3	326745
646	417316	269586136	25.4165	8.6446	2.81023	1.54799	2029.5	327759
647	418609	270840023	25.4362	8.6490	2.81090	1.54560	2032.6	328775
648	419904	272097792	25.4558	8.6535	2.81158	1.54321	2035.8	329792
649	421201	273359449	25.4755	8.6579	2.81224	1.54083	2038.9	330810

# MATHEMATICAL TABLES

## FUNCTIONS OF NUMBERS, 650 TO 699

No.	Square	Cube	Square Root	Cubic Root	Logarithm	1000 x Reciprocal	No. as Diameter	
							Circum.	Area
650	422500	274625000	25.4951	8.6624	2.81291	1.53846	2042.0	331831
651	423801	275894451	25.5147	8.6668	2.81358	1.53610	2045.2	332853
652	425104	277167808	25.5343	8.6713	2.81425	1.53374	2048.3	333876
653	426409	278445077	25.5539	8.6757	2.81491	1.53139	2051.5	334901
654	427716	279726264	25.5734	8.6801	2.81558	1.52905	2054.6	335927
655	429025	281011375	25.5930	8.6845	2.81624	1.52672	2057.7	336955
656	430336	282300416	25.6125	8.6890	2.81690	1.52439	2060.9	337985
657	431649	283593393	25.6320	8.6934	2.81757	1.52207	2064.0	339016
658	432964	284890312	25.6515	8.6978	2.81823	1.51976	2067.2	340049
659	434281	286191179	25.6710	8.7022	2.81889	1.51745	2070.3	341084
660	435600	287496000	25.6905	8.7066	2.81954	1.51515	2073.5	342119
661	436921	288804781	25.7099	8.7110	2.82020	1.51286	2076.6	343157
662	438244	290117528	25.7294	8.7154	2.82086	1.51057	2079.7	344196
663	439569	291434247	25.7488	8.7198	2.82151	1.50830	2082.9	345237
664	440896	292754944	25.7682	8.7241	2.82217	1.50602	2086.0	346279
665	442225	294079625	25.7876	8.7285	2.82282	1.50376	2089.2	347323
666	443556	295408206	25.8070	8.7329	2.82347	1.50150	2092.3	348368
667	444889	296740963	25.8263	8.7373	2.82413	1.49925	2095.4	349415
668	446224	298077632	25.8457	8.7416	2.82478	1.49701	2098.6	350464
669	447561	299418309	25.8650	8.7460	2.82543	1.49477	2101.7	351514
670	448900	300763000	25.8844	8.7503	2.82607	1.49254	2104.9	352565
671	450241	302111711	25.9037	8.7547	2.82672	1.49031	2108.0	353618
672	451584	303464448	25.9230	8.7590	2.82737	1.48810	2111.2	354673
673	452929	304821217	25.9422	8.7634	2.82802	1.48588	2114.3	355730
674	454276	306182024	25.9615	8.7677	2.82866	1.48368	2117.4	356788
675	455625	307546875	25.9808	8.7721	2.82930	1.48148	2120.6	357847
676	456976	308915776	26.0000	8.7764	2.82995	1.47929	2123.7	358908
677	458329	310288733	26.0192	8.7807	2.83059	1.47710	2126.9	359971
678	459684	311665752	26.0384	8.7850	2.83123	1.47493	2130.0	361036
679	461041	313046839	26.0576	8.7893	2.83187	1.47275	2133.1	362101
680	462400	314432000	26.0768	8.7937	2.83251	1.47059	2136.3	363168
681	463761	315821241	26.0960	8.7980	2.83315	1.46843	2139.4	364237
682	465124	317214568	26.1151	8.8023	2.83378	1.46628	2142.6	365308
683	466489	318611987	26.1343	8.8066	2.83442	1.46413	2145.7	366380
684	467856	320013504	26.1534	8.8109	2.83506	1.46199	2148.8	367453
685	469225	321419125	26.1725	8.8152	2.83569	1.45985	2152.0	368528
686	470596	322828856	26.1916	8.8194	2.83632	1.45773	2155.1	369605
687	471969	324242703	26.2107	8.8237	2.83696	1.45560	2158.3	370684
688	473344	325660672	26.2298	8.8280	2.83759	1.45349	2161.4	371764
689	474721	327082769	26.2488	8.8323	2.83822	1.45138	2164.6	372845
690	476100	328509000	26.2679	8.8366	2.83885	1.44928	2167.7	373928
691	477481	329939371	26.2869	8.8408	2.83948	1.44718	2170.8	375013
692	478864	331373888	26.3059	8.8451	2.84011	1.44509	2174.0	376099
693	480249	332812557	26.3249	8.8493	2.84073	1.44300	2177.1	377187
694	481636	334255384	26.3439	8.8536	2.84136	1.44092	2180.3	378276
695	483025	335702375	26.3629	8.8578	2.84198	1.43885	2183.4	379367
696	484416	337153536	26.3818	8.8621	2.84261	1.43678	2186.5	380459
697	485809	338608873	26.4008	8.8663	2.84323	1.43472	2189.7	381553
698	487204	340068392	26.4197	8.8706	2.84386	1.43266	2192.8	382649
699	488601	341532099	26.4386	8.8748	2.84448	1.43062	2196.0	383746

# CARNEGIE STEEL COMPANY

## FUNCTIONS OF NUMBERS, 700 TO 749

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No.—Diameter	
							Circum.	Area
700	490000	343000000	26.4575	8.8790	2.84510	1.42857	2199.1	384845
701	491401	344472101	26.4764	8.8833	2.84572	1.42663	2202.3	385945
702	492804	345948408	26.4953	8.8875	2.84634	1.42450	2205.4	387047
703	494209	347428927	26.5141	8.8917	2.84696	1.42248	2208.5	388151
704	495616	348913664	26.5330	8.8959	2.84757	1.42045	2211.7	389256
705	497025	350402025	26.5518	8.9001	2.84819	1.41844	2214.8	390363
706	498436	351895816	26.5707	8.9043	2.84880	1.41643	2218.0	391471
707	499849	353393243	26.5895	8.9085	2.84942	1.41443	2221.1	392580
708	501264	354894912	26.6083	8.9127	2.85003	1.41243	2224.2	393692
709	502681	356400829	26.6271	8.9169	2.85065	1.41044	2227.4	394805
710	504100	357911000	26.6458	8.9211	2.85126	1.40845	2230.5	395919
711	505521	359425431	26.6646	8.9253	2.85187	1.40647	2233.7	397035
712	506944	360944128	26.6833	8.9295	2.85248	1.40449	2236.8	398153
713	508369	362467097	26.7021	8.9337	2.85309	1.40252	2240.0	399272
714	509796	363994344	26.7208	8.9378	2.85370	1.40056	2243.1	400393
715	511225	365525875	26.7395	8.9420	2.85431	1.39860	2246.2	401515
716	512656	367061696	26.7582	8.9462	2.85491	1.39665	2249.4	402639
717	514089	368601813	26.7769	8.9503	2.85552	1.39470	2252.5	403765
718	515524	370146232	26.7955	8.9545	2.85612	1.39276	2255.7	404892
719	516961	371694959	26.8142	8.9587	2.85673	1.39082	2258.8	406020
720	518400	373248000	26.8328	8.9628	2.85733	1.38889	2261.9	407150
721	519841	374805361	26.8514	8.9670	2.85794	1.38696	2265.1	408282
722	521284	376367048	26.8701	8.9711	2.85854	1.38504	2268.2	409415
723	522729	377933067	26.8887	8.9752	2.85914	1.38313	2271.4	410550
724	524176	379503424	26.9072	8.9794	2.85974	1.38122	2274.5	411687
725	525625	381078125	26.9258	8.9835	2.86034	1.37931	2277.7	412825
726	527076	382657176	26.9444	8.9876	2.86094	1.37741	2280.8	413965
727	528529	384240583	26.9629	8.9918	2.86153	1.37552	2283.9	415106
728	529984	385828352	26.9815	8.9959	2.86213	1.37363	2287.1	416248
729	531441	387420489	27.0000	9.0000	2.86273	1.37174	2290.2	417393
730	532900	389017000	27.0185	9.0041	2.86332	1.36986	2293.4	418539
731	534361	390617891	27.0370	9.0082	2.86392	1.36799	2296.5	419686
732	535824	392223108	27.0555	9.0123	2.86451	1.36612	2299.6	420835
733	537289	393832837	27.0740	9.0164	2.86510	1.36426	2302.8	421986
734	538756	395446904	27.0924	9.0205	2.86570	1.36240	2305.9	423138
735	540225	397065375	27.1109	9.0246	2.86629	1.36054	2309.1	424293
736	541696	398688256	27.1293	9.0287	2.86688	1.35870	2312.2	425447
737	543169	400315553	27.1477	9.0328	2.86747	1.35685	2315.4	426604
738	544644	401947272	27.1662	9.0369	2.86806	1.35501	2318.5	427762
739	546121	403583419	27.1846	9.0410	2.86864	1.35318	2321.6	428922
740	547600	405224000	27.2029	9.0450	2.86923	1.35135	2324.8	430084
741	549081	406869021	27.2213	9.0491	2.86982	1.34953	2327.9	431247
742	550564	408518488	27.2397	9.0532	2.87040	1.34771	2331.1	432412
743	552049	410172407	27.2580	9.0572	2.87099	1.34590	2334.2	433578
744	553536	411830784	27.2764	9.0613	2.87157	1.34409	2337.3	434746
745	555025	413493625	27.2947	9.0654	2.87216	1.34228	2340.5	435916
746	556516	415160936	27.3130	9.0694	2.87274	1.34048	2343.6	437087
747	558009	416832723	27.3313	9.0735	2.87332	1.33869	2346.8	438259
748	559504	418508992	27.3496	9.0775	2.87390	1.33690	2349.9	439433
749	561001	420189749	27.3679	9.0816	2.87448	1.33511	2353.1	440609

# MATHEMATICAL TABLES

## FUNCTIONS OF NUMBERS, 750 TO 799

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No.—Diameter	
							Circum.	Area
750	562500	421875000	27.3861	9.0856	2.87506	1.33333	2356.2	441786
751	564001	423504751	27.4044	9.0896	2.87564	1.33156	2350.3	442065
752	565504	425259008	27.4226	9.0937	2.87622	1.32979	2362.5	444146
753	567009	426957777	27.4408	9.0977	2.87680	1.32802	2365.6	445328
754	568516	428661004	27.4591	9.1017	2.87737	1.32626	2368.8	446511
755	570025	430368875	27.4773	9.1057	2.87795	1.32450	2371.9	447697
756	571536	432081216	27.4955	9.1098	2.87852	1.32275	2375.0	448883
757	573049	433798003	27.5136	9.1138	2.87910	1.32100	2378.2	450072
758	574564	435519512	27.5318	9.1178	2.87967	1.31926	2381.3	451262
759	576081	437245479	27.5500	9.1218	2.88024	1.31752	2384.5	452453
760	577600	438976000	27.5681	9.1258	2.88081	1.31579	2387.6	453646
761	579121	440711081	27.5862	9.1298	2.88138	1.31406	2390.8	454841
762	580644	442456072	27.6043	9.1338	2.88196	1.31234	2393.9	456037
763	582169	444194947	27.6225	9.1378	2.88252	1.31062	2397.0	457234
764	583696	445943744	27.6405	9.1418	2.88309	1.30890	2400.2	458434
765	585225	447697125	27.6586	9.1458	2.88366	1.30719	2403.3	459635
766	586756	449455096	27.6767	9.1498	2.88423	1.30548	2406.5	460837
767	588289	451217663	27.6948	9.1537	2.88480	1.30378	2409.6	462041
768	589824	452984832	27.7128	9.1577	2.88536	1.30208	2412.7	463247
769	591361	454756609	27.7308	9.1617	2.88593	1.30039	2415.9	464454
770	592900	456533000	27.7489	9.1657	2.88649	1.29870	2419.0	465663
771	594441	458314011	27.7669	9.1696	2.88705	1.29702	2422.2	466873
772	595984	460099048	27.7849	9.1736	2.88762	1.29534	2425.3	468085
773	597529	461889917	27.8029	9.1776	2.88818	1.29366	2428.5	469298
774	599076	463684824	27.8209	9.1816	2.88874	1.29199	2431.6	470513
775	600625	465484375	27.8388	9.1855	2.88930	1.29032	2434.7	471730
776	602176	467288576	27.8568	9.1894	2.88986	1.28866	2437.9	472948
777	603729	469097433	27.8747	9.1933	2.89042	1.28700	2441.0	474168
778	605284	470910952	27.8927	9.1973	2.89098	1.28535	2444.2	475389
779	606841	472729139	27.9106	9.2012	2.89154	1.28370	2447.3	476612
780	608400	474552000	27.9285	9.2052	2.89209	1.28205	2450.4	477836
781	609961	476379541	27.9464	9.2091	2.89265	1.28041	2453.6	479062
782	611524	478211768	27.9643	9.2130	2.89321	1.27877	2456.7	480290
783	613089	480048687	27.9821	9.2170	2.89376	1.27714	2459.9	481519
784	614656	481890304	28.0000	9.2209	2.89432	1.27551	2463.0	482750
785	616225	483736625	28.0179	9.2248	2.89487	1.27389	2466.2	483982
786	617796	485587656	28.0357	9.2287	2.89542	1.27226	2469.3	485216
787	619369	487443403	28.0535	9.2326	2.89597	1.27065	2472.4	486451
788	620944	489303872	28.0713	9.2365	2.89653	1.26904	2475.6	487688
789	622521	491169069	28.0891	9.2404	2.89708	1.26743	2478.7	488927
790	624100	493039000	28.1069	9.2443	2.89763	1.26582	2481.9	490167
791	625681	494913671	28.1247	9.2482	2.89818	1.26422	2485.0	491409
792	627264	496793088	28.1425	9.2521	2.89873	1.26263	2488.1	492652
793	628849	498677257	28.1603	9.2560	2.89927	1.26103	2491.3	493897
794	630436	500566184	28.1780	9.2599	2.89982	1.25944	2494.4	495143
795	632025	502459875	28.1957	9.2638	2.90037	1.25786	2497.6	496391
796	633616	504358336	28.2135	9.2677	2.90091	1.25628	2500.7	497641
797	635209	506261573	28.2312	9.2716	2.90146	1.25471	2503.8	498892
798	636804	508169592	28.2489	9.2754	2.90200	1.25313	2507.0	500145
799	638401	510082399	28.2666	9.2793	2.90255	1.25156	2510.1	501399

# CARNEGIE STEEL COMPANY

## FUNCTIONS OF NUMBERS, 800 TO 849

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No.—Diameter	
							Circum.	Area
800	640000	512000000	28.2843	9.2832	2.90309	1.25000	2513.3	502655
801	641601	513922401	28.3019	9.2870	2.90363	1.24844	2516.4	503912
802	643204	515849608	28.3196	9.2909	2.90417	1.24688	2519.6	505171
803	644809	517781627	28.3373	9.2948	2.90472	1.24533	2522.7	506432
804	646416	519718464	28.3549	9.2986	2.90526	1.24378	2525.8	507694
805	648025	521660125	28.3725	9.3025	2.90580	1.24224	2529.0	508958
806	649636	523606616	28.3901	9.3063	2.90634	1.24069	2532.1	510223
807	651249	525557943	28.4077	9.3102	2.90687	1.23916	2535.3	511490
808	652864	527514112	28.4253	9.3140	2.90741	1.23762	2538.4	512758
809	654481	529475129	28.4429	9.3179	2.90795	1.23609	2541.5	514028
810	656100	531441000	28.4605	9.3217	2.90849	1.23457	2544.7	515300
811	657721	533411731	28.4781	9.3255	2.90902	1.23305	2547.8	516573
812	659344	535387328	28.4956	9.3294	2.90956	1.23153	2551.0	517848
813	660969	537367707	28.5132	9.3332	2.91009	1.23001	2554.1	519124
814	662596	539353144	28.5307	9.3370	2.91062	1.22850	2557.3	520402
815	664225	541343375	28.5482	9.3408	2.91116	1.22699	2560.4	521681
816	665856	543338496	28.5657	9.3447	2.91169	1.22548	2563.5	522962
817	667489	545338513	28.5832	9.3485	2.91222	1.22397	2566.7	524245
818	669124	547343432	28.6007	9.3523	2.91275	1.22246	2569.8	525529
819	670761	549353259	28.6182	9.3561	2.91328	1.22100	2573.0	526814
820	672400	551368000	28.6356	9.3599	2.91381	1.21951	2576.1	528102
821	674041	553387661	28.6531	9.3637	2.91434	1.21803	2579.2	529391
822	675684	555412248	28.6705	9.3675	2.91487	1.21655	2582.4	530681
823	677329	557441767	28.6880	9.3713	2.91540	1.21507	2585.5	531973
824	678976	559476224	28.7054	9.3751	2.91593	1.21359	2588.7	533267
825	680625	561515625	28.7228	9.3789	2.91645	1.21212	2591.8	534562
826	682276	563559976	28.7402	9.3827	2.91698	1.21065	2595.0	535858
827	683929	565609283	28.7576	9.3865	2.91751	1.20919	2598.1	537157
828	685584	567663552	28.7750	9.3902	2.91803	1.20773	2601.2	538456
829	687241	569722789	28.7924	9.3940	2.91855	1.20627	2604.4	539758
830	688900	571787000	28.8097	9.3978	2.91908	1.20482	2607.5	541061
831	690561	573856191	28.8271	9.4016	2.91960	1.20337	2610.7	542365
832	692224	575930368	28.8444	9.4053	2.92012	1.20192	2613.8	543671
833	693889	578009537	28.8617	9.4091	2.92065	1.20048	2616.9	544979
834	695556	580093704	28.8791	9.4129	2.92117	1.19904	2620.1	546288
835	697225	582182875	28.8964	9.4166	2.92169	1.19760	2623.2	547599
836	698896	584277036	28.9137	9.4204	2.92221	1.19617	2626.4	548912
837	700569	586376253	28.9310	9.4241	2.92273	1.19474	2629.5	550226
838	702244	588480472	28.9482	9.4279	2.92324	1.19332	2632.7	551541
839	703921	590589719	28.9655	9.4316	2.92376	1.19190	2635.8	552858
840	705600	592704000	28.9828	9.4354	2.92428	1.19048	2638.9	554177
841	707281	594823321	29.0000	9.4391	2.92480	1.18906	2642.1	555497
842	708964	596947688	29.0172	9.4429	2.92531	1.18765	2645.2	556819
843	710649	599077107	29.0345	9.4466	2.92583	1.18624	2648.4	558142
844	712336	601211584	29.0517	9.4503	2.92634	1.18483	2651.5	559467
845	714025	603351125	29.0689	9.4541	2.92686	1.18343	2654.6	560794
846	715716	605495736	29.0861	9.4578	2.92737	1.18203	2657.8	562122
847	717409	607645423	29.1033	9.4615	2.92788	1.18064	2660.9	563452
848	719104	609800192	29.1204	9.4652	2.92840	1.17925	2664.1	564783
849	720801	611960049	29.1376	9.4690	2.92891	1.17786	2667.2	566116

# MATHEMATICAL TABLES

## FUNCTIONS OF NUMBERS, 850 TO 899

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No. = Diameter	
							Circum.	Area
850	722500	614125000	29.1548	9.4727	2.92942	1.17647	2670.4	567450
851	724201	616295051	29.1719	9.4764	2.92993	1.17500	2673.5	568786
852	725904	618470208	29.1890	9.4801	2.93044	1.17371	2676.6	570124
853	727609	620650477	29.2062	9.4838	2.93095	1.17233	2679.8	571463
854	729316	622835864	29.2233	9.4875	2.93146	1.17096	2682.9	572803
855	731025	625026375	29.2404	9.4912	2.93197	1.16959	2686.1	574146
856	732736	627222016	29.2575	9.4949	2.93247	1.16822	2689.2	575490
857	734449	629422793	29.2746	9.4986	2.93298	1.16686	2692.3	576835
858	736164	631628712	29.2916	9.5023	2.93349	1.16550	2695.5	578182
859	737881	633839779	29.3087	9.5060	2.93399	1.16414	2698.6	579530
860	739600	636056000	29.3258	9.5097	2.93450	1.16279	2701.8	580880
861	741321	638277381	29.3428	9.5134	2.93500	1.16144	2704.9	582232
862	743044	640503928	29.3598	9.5171	2.93551	1.16009	2708.1	583585
863	744769	642735647	29.3769	9.5207	2.93601	1.15875	2711.2	584940
864	746496	644972544	29.3939	9.5244	2.93651	1.15741	2714.3	586297
865	748225	647214625	29.4109	9.5281	2.93702	1.15607	2717.5	587655
866	749956	649461896	29.4279	9.5317	2.93752	1.15473	2720.6	589014
867	751689	651714363	29.4449	9.5354	2.93802	1.15340	2723.8	590375
868	753424	653972032	29.4618	9.5391	2.93852	1.15207	2726.9	591738
869	755161	656234909	29.4788	9.5427	2.93902	1.15075	2730.0	593102
870	756900	658503000	29.4958	9.5464	2.93952	1.14943	2733.2	594468
871	758641	660776311	29.5127	9.5501	2.94002	1.14811	2736.3	595835
872	760384	663054848	29.5296	9.5537	2.94052	1.14679	2739.5	597204
873	762129	665338617	29.5466	9.5574	2.94101	1.14548	2742.6	598575
874	763876	667627624	29.5635	9.5610	2.94151	1.14416	2745.8	599947
875	765625	669921875	29.5804	9.5647	2.94201	1.14286	2748.9	601320
876	767376	672221376	29.5973	9.5683	2.94250	1.14155	2752.0	602696
877	769129	674526133	29.6142	9.5719	2.94300	1.14025	2755.2	604073
878	770884	676836152	29.6311	9.5756	2.94349	1.13895	2758.3	605451
879	772641	679151439	29.6479	9.5792	2.94399	1.13766	2761.5	606831
880	774400	681472000	29.6648	9.5828	2.94448	1.13636	2764.6	608212
881	776161	683797841	29.6816	9.5865	2.94498	1.13507	2767.7	609595
882	777924	686128968	29.6985	9.5901	2.94547	1.13377	2770.9	610980
883	779689	688465387	29.7153	9.5937	2.94596	1.13250	2774.0	612366
884	781456	690807104	29.7321	9.5973	2.94645	1.13122	2777.2	613754
885	783225	693154125	29.7489	9.6010	2.94694	1.12994	2780.3	615143
886	784996	695506456	29.7658	9.6046	2.94743	1.12867	2783.5	616534
887	786769	697864103	29.7825	9.6082	2.94792	1.12740	2786.6	617927
888	788544	700227072	29.7993	9.6118	2.94841	1.12613	2789.7	619321
889	790321	702595369	29.8161	9.6154	2.94890	1.12486	2792.9	620717
890	792100	704969000	29.8329	9.6190	2.94939	1.12360	2796.0	622114
891	793881	707347971	29.8496	9.6226	2.94988	1.12233	2799.2	623513
892	795664	709732288	29.8664	9.6262	2.95036	1.12108	2802.3	624913
893	797449	712121967	29.8831	9.6298	2.95085	1.11982	2805.4	626315
894	799236	714516984	29.8998	9.6334	2.95134	1.11857	2808.6	627718
895	801025	716917375	29.9166	9.6370	2.95182	1.11732	2811.7	629124
896	802816	719323136	29.9333	9.6406	2.95231	1.11607	2814.9	630530
897	804609	721734273	29.9500	9.6442	2.95279	1.11483	2818.0	631938
898	806404	724150792	29.9666	9.6477	2.95328	1.11359	2821.2	633348
899	808201	726572699	29.9833	9.6513	2.95376	1.11235	2824.3	634760

# CARNEGIE STEEL COMPANY

## FUNCTIONS OF NUMBERS, 900 TO 949

No.	Square	Cube	Square Root	Cube Root	Logarithm	1000 x Reciprocal	No.—Diameter	
							Circum.	Area
900	810000	729000000	30.0000	9.6549	2.95424	1.11111	2827.4	636173
901	811801	731432701	30.0167	9.6585	2.95472	1.10988	2830.6	637587
902	813604	733870808	30.0333	9.6620	2.95521	1.10865	2833.7	639003
903	815409	736314327	30.0500	9.6656	2.95569	1.10742	2836.9	640421
904	817216	738763264	30.0666	9.6692	2.95617	1.10619	2840.0	641840
905	819025	741217625	30.0832	9.6727	2.95665	1.10497	2843.1	643261
906	820836	743677416	30.0998	9.6763	2.95713	1.10375	2846.3	644683
907	822649	746142643	30.1164	9.6799	2.95761	1.10254	2849.4	646107
908	824464	748613312	30.1330	9.6834	2.95809	1.10132	2852.6	647533
909	826281	751089420	30.1496	9.6870	2.95856	1.10011	2855.7	648960
910	828100	753571000	30.1662	9.6905	2.95904	1.09890	2858.8	650388
911	829921	756058031	30.1828	9.6941	2.95952	1.09769	2862.0	651818
912	831744	758550528	30.1993	9.6976	2.95999	1.09649	2865.1	653250
913	833569	761048497	30.2159	9.7012	2.96047	1.09520	2868.3	654684
914	835396	763551944	30.2324	9.7047	2.96095	1.09400	2871.4	656118
915	837225	766060875	30.2490	9.7082	2.96142	1.09290	2874.6	657555
916	839056	768575296	30.2655	9.7118	2.96190	1.09170	2877.7	658993
917	840889	771095213	30.2820	9.7153	2.96237	1.09051	2880.8	660433
918	842724	773620632	30.2985	9.7188	2.96284	1.08932	2884.0	661874
919	844561	776151559	30.3150	9.7224	2.96332	1.08814	2887.1	663317
920	846400	778688000	30.3315	9.7259	2.96379	1.08696	2890.3	664761
921	848241	781229961	30.3480	9.7294	2.96426	1.08578	2893.4	666207
922	850084	783777448	30.3645	9.7329	2.96473	1.08460	2896.5	667654
923	851929	786330467	30.3809	9.7364	2.96520	1.08342	2899.7	669103
924	853776	788889024	30.3974	9.7400	2.96567	1.08225	2902.8	670554
925	855625	791453125	30.4138	9.7435	2.96614	1.08108	2906.0	672006
926	857476	794022776	30.4302	9.7470	2.96661	1.07991	2909.1	673460
927	859329	796597983	30.4467	9.7505	2.96708	1.07875	2912.3	674915
928	861184	799178752	30.4631	9.7540	2.96755	1.07759	2915.4	676372
929	863041	801765089	30.4795	9.7575	2.96802	1.07643	2918.5	677831
930	864900	804357000	30.4959	9.7610	2.96848	1.07527	2921.7	679291
931	866761	806954491	30.5123	9.7645	2.96895	1.07411	2924.8	680752
932	868624	809557568	30.5287	9.7680	2.96942	1.07296	2928.0	682216
933	870489	812166237	30.5450	9.7715	2.96988	1.07181	2931.1	683680
934	872356	814780504	30.5614	9.7750	2.97035	1.07066	2934.2	685147
935	874225	817400375	30.5778	9.7785	2.97081	1.06952	2937.4	686615
936	876096	820025866	30.5941	9.7819	2.97128	1.06838	2940.5	688084
937	877969	822656963	30.6105	9.7854	2.97174	1.06724	2943.7	689555
938	879844	825293672	30.6268	9.7889	2.97220	1.06610	2946.8	691028
939	881721	827936019	30.6431	9.7924	2.97267	1.06496	2950.0	692502
940	883600	830584000	30.6594	9.7959	2.97313	1.06383	2953.1	693978
941	885481	833237621	30.6757	9.7993	2.97359	1.06270	2956.2	695455
942	887364	835896888	30.6920	9.8028	2.97405	1.06157	2959.4	696934
943	889249	838561807	30.7083	9.8063	2.97451	1.06045	2962.5	698415
944	891136	841232384	30.7246	9.8097	2.97497	1.05932	2965.7	699897
945	893025	843908625	30.7409	9.8132	2.97543	1.05820	2968.8	701380
946	894916	846590536	30.7571	9.8167	2.97589	1.05708	2971.9	702865
947	896809	849278123	30.7734	9.8201	2.97635	1.05597	2975.1	704352
948	898704	851971392	30.7896	9.8236	2.97681	1.05485	2978.2	705840
949	900601	854670349	30.8058	9.8270	2.97727	1.05374	2981.4	707330

# MATHEMATICAL TABLES

## FUNCTIONS OF NUMBERS, 950 TO 999

No.	Square	Cube	Square Root	Cubic Root	Logarithm	1000 + Reciprocal	No. = Diameter	
							Circum.	Area
950	902500	857375000	30.8221	9.8305	2.97772	1.05263	2984.5	708822
951	904401	860085351	30.8383	9.8339	2.97818	1.05152	2987.7	710315
952	906304	862801408	30.8545	9.8374	2.97864	1.05042	2990.8	711809
953	908209	865523177	30.8707	9.8408	2.97909	1.04932	2993.9	713306
954	910116	868250664	30.8869	9.8443	2.97955	1.04822	2997.1	714803
955	912025	870983875	30.9031	9.8477	2.98000	1.04712	3000.2	716303
956	913936	873722813	30.9192	9.8511	2.98046	1.04603	3003.4	717804
957	915849	876467403	30.9354	9.8546	2.98091	1.04493	3006.5	719306
958	917764	879217912	30.9516	9.8580	2.98137	1.04384	3009.6	720810
959	919681	881974079	30.9677	9.8614	2.98182	1.04275	3012.8	722316
960	921600	884736000	30.9839	9.8648	2.98227	1.04167	3015.9	723823
961	923521	887503681	31.0000	9.8683	2.98272	1.04058	3019.1	725332
962	925444	890277128	31.0161	9.8717	2.98318	1.03950	3022.2	726842
963	927369	893056347	31.0322	9.8751	2.98363	1.03842	3025.4	728354
964	929296	895841344	31.0483	9.8785	2.98408	1.03734	3028.5	729867
965	931225	898632125	31.0644	9.8819	2.98453	1.03627	3031.6	731382
966	933156	901428696	31.0805	9.8854	2.98498	1.03520	3034.8	732899
967	935089	904231063	31.0966	9.8888	2.98543	1.03413	3037.9	734417
968	937024	907039232	31.1127	9.8922	2.98588	1.03306	3041.1	735937
969	938961	909853209	31.1288	9.8956	2.98632	1.03199	3044.2	737458
970	940900	912673000	31.1448	9.8990	2.98677	1.03093	3047.3	738981
971	942841	915498611	31.1609	9.9024	2.98722	1.02987	3050.5	740506
972	944784	918330048	31.1769	9.9058	2.98767	1.02881	3053.6	742032
973	946729	921167317	31.1929	9.9092	2.98811	1.02775	3056.8	743559
974	948676	924010424	31.2090	9.9126	2.98856	1.02669	3059.9	745088
975	950625	926859375	31.2250	9.9160	2.98900	1.02564	3063.1	746619
976	952576	929714176	31.2410	9.9194	2.98945	1.02459	3066.2	748151
977	954529	932574833	31.2570	9.9227	2.98989	1.02354	3069.3	749685
978	956484	935441352	31.2730	9.9261	2.99034	1.02249	3072.5	751221
979	958441	938313739	31.2890	9.9295	2.99078	1.02145	3075.6	752758
980	960400	941192000	31.3050	9.9329	2.99123	1.02041	3078.8	754296
981	962361	944076141	31.3209	9.9363	2.99167	1.01937	3081.9	755837
982	964324	946966168	31.3369	9.9396	2.99211	1.01833	3085.0	757378
983	966289	949862087	31.3528	9.9430	2.99255	1.01729	3088.2	758922
984	968256	952763904	31.3688	9.9464	2.99300	1.01626	3091.3	760466
985	970225	955671625	31.3847	9.9497	2.99344	1.01523	3094.5	762013
986	972196	958585250	31.4006	9.9531	2.99388	1.01420	3097.6	763561
987	974169	961504803	31.4166	9.9565	2.99432	1.01317	3100.8	765111
988	976144	964430272	31.4325	9.9598	2.99476	1.01215	3103.9	766662
989	978121	967361669	31.4484	9.9632	2.99520	1.01112	3107.0	768214
990	980100	970299000	31.4643	9.9666	2.99564	1.01010	3110.2	769769
991	982081	973242271	31.4802	9.9699	2.99607	1.00908	3113.3	771325
992	984064	976191488	31.4960	9.9733	2.99651	1.00806	3116.5	772882
993	986049	979146657	31.5119	9.9766	2.99695	1.00705	3119.6	774441
994	988036	982107784	31.5278	9.9800	2.99739	1.00604	3122.7	776002
995	990025	985074875	31.5436	9.9833	2.99782	1.00503	3125.9	777564
996	992016	988047936	31.5595	9.9866	2.99826	1.00402	3129.0	779128
997	994009	991026973	31.5753	9.9900	2.99870	1.00301	3132.2	780693
998	996004	994011992	31.5911	9.9933	2.99913	1.00200	3135.3	782260
999	998001	997002999	31.6070	9.9967	2.99957	1.00100	3138.5	783828



# CARNEGIE STEEL COMPANY

## NATURAL TRIGONOMETRIC FUNCTIONS

Degrees	SINES							Cosines
	0'	10'	20'	30'	40'	50'	60'	
0	0.00000	0.00291	0.00582	0.00873	0.01164	0.01454	0.01745	89
1	0.01745	0.02036	0.02327	0.02618	0.02908	0.03199	0.03490	88
2	0.03490	0.03781	0.04071	0.04362	0.04653	0.04943	0.05234	87
3	0.05234	0.05524	0.05814	0.06105	0.06396	0.06685	0.06976	86
4	0.06976	0.07266	0.07556	0.07846	0.08136	0.08426	0.08716	85
5	0.08716	0.09005	0.09295	0.09585	0.09874	0.10164	0.10453	84
6	0.10453	0.10742	0.11031	0.11320	0.11609	0.11898	0.12187	83
7	0.12187	0.12476	0.12764	0.13053	0.13341	0.13629	0.13917	82
8	0.13917	0.14205	0.14493	0.14781	0.15069	0.15356	0.15643	81
9	0.15643	0.15931	0.16218	0.16505	0.16792	0.17078	0.17365	80
10	0.17365	0.17651	0.17937	0.18224	0.18509	0.18795	0.19081	79
11	0.19081	0.19366	0.19652	0.19937	0.20222	0.20507	0.20791	78
12	0.20791	0.21076	0.21360	0.21644	0.21928	0.22212	0.22495	77
13	0.22495	0.22778	0.23062	0.23345	0.23627	0.23910	0.24192	76
14	0.24192	0.24474	0.24756	0.25038	0.25320	0.25601	0.25882	75
15	0.25882	0.26163	0.26443	0.26724	0.27004	0.27284	0.27564	74
16	0.27564	0.27843	0.28123	0.28402	0.28680	0.28959	0.29237	73
17	0.29237	0.29515	0.29793	0.30071	0.30348	0.30625	0.30902	72
18	0.30902	0.31178	0.31454	0.31730	0.32006	0.32282	0.32557	71
19	0.32557	0.32832	0.33106	0.33381	0.33655	0.33929	0.34202	70
20	0.34202	0.34475	0.34748	0.35021	0.35293	0.35565	0.35837	69
21	0.35837	0.36108	0.36379	0.36650	0.36921	0.37191	0.37461	68
22	0.37461	0.37730	0.37999	0.38268	0.38537	0.38805	0.39073	67
23	0.39073	0.39341	0.39608	0.39875	0.40142	0.40408	0.40674	66
24	0.40674	0.40939	0.41204	0.41469	0.41734	0.41998	0.42262	65
25	0.42262	0.42525	0.42788	0.43051	0.43313	0.43575	0.43837	64
26	0.43837	0.44098	0.44359	0.44620	0.44880	0.45140	0.45399	63
27	0.45399	0.45658	0.45917	0.46175	0.46433	0.46690	0.46947	62
28	0.46947	0.47204	0.47460	0.47716	0.47971	0.48228	0.48481	61
29	0.48481	0.48735	0.48989	0.49242	0.49495	0.49748	0.50000	60
30	0.50000	0.50252	0.50503	0.50754	0.51004	0.51254	0.51504	59
31	0.51504	0.51753	0.52002	0.52250	0.52498	0.52745	0.52992	58
32	0.52992	0.53238	0.53484	0.53730	0.53975	0.54220	0.54464	57
33	0.54464	0.54708	0.54951	0.55194	0.55436	0.55678	0.55919	56
34	0.55919	0.56160	0.56401	0.56641	0.56880	0.57119	0.57358	55
35	0.57358	0.57596	0.57833	0.58070	0.58307	0.58543	0.58779	54
36	0.58779	0.59014	0.59248	0.59482	0.59716	0.59949	0.60182	53
37	0.60182	0.60414	0.60645	0.60875	0.61107	0.61337	0.61566	52
38	0.61566	0.61795	0.62024	0.62251	0.62479	0.62706	0.62932	51
39	0.62932	0.63158	0.63383	0.63608	0.63832	0.64056	0.64279	50
40	0.64279	0.64501	0.64723	0.64945	0.65166	0.65386	0.65606	49
41	0.65606	0.65825	0.66044	0.66262	0.66480	0.66697	0.66913	48
42	0.66913	0.67129	0.67344	0.67559	0.67773	0.67987	0.68200	47
43	0.68200	0.68412	0.68624	0.68835	0.69046	0.69256	0.69466	46
44	0.69466	0.69675	0.69883	0.70091	0.70298	0.70505	0.70711	45
Sines	60'	50'	40'	30'	20'	10'	0'	Degrees
	COSINES							

# MATHEMATICAL TABLES

## NATURAL TRIGONOMETRIC FUNCTIONS

Degrees	COSINES							Sines
	0'	10'	20'	30'	40'	50'	60'	
0	1.00000	1.00000	0.99998	0.99996	0.99993	0.99989	0.99985	89
1	0.99985	0.99979	0.99973	0.99966	0.99958	0.99949	0.99939	88
2	0.99939	0.99929	0.99917	0.99905	0.99892	0.99878	0.99863	87
3	0.99863	0.99847	0.99831	0.99813	0.99795	0.99776	0.99756	86
4	0.99756	0.99730	0.99714	0.99692	0.99668	0.99644	0.99619	85
5	0.99619	0.99594	0.99567	0.99540	0.99511	0.99482	0.99452	84
6	0.99452	0.99421	0.99390	0.99357	0.99324	0.99290	0.99255	83
7	0.99255	0.99219	0.99182	0.99144	0.99106	0.99067	0.99027	82
8	0.99027	0.98986	0.98944	0.98902	0.98858	0.98814	0.98769	81
9	0.98769	0.98723	0.98676	0.98629	0.98580	0.98531	0.98481	80
10	0.98481	0.98430	0.98378	0.98325	0.98272	0.98218	0.98163	79
11	0.98163	0.98107	0.98050	0.97992	0.97934	0.97875	0.97815	78
12	0.97815	0.97754	0.97692	0.97630	0.97566	0.97502	0.97437	77
13	0.97437	0.97371	0.97304	0.97237	0.97169	0.97100	0.97030	76
14	0.97030	0.96959	0.96887	0.96815	0.96742	0.96667	0.96593	75
15	0.96593	0.96517	0.96440	0.96363	0.96285	0.96206	0.96126	74
16	0.96126	0.96046	0.95964	0.95882	0.95799	0.95715	0.95630	73
17	0.95630	0.95545	0.95459	0.95372	0.95284	0.95195	0.95106	72
18	0.95106	0.95015	0.94924	0.94832	0.94740	0.94646	0.94552	71
19	0.94552	0.94457	0.94361	0.94264	0.94167	0.94068	0.93969	70
20	0.93969	0.93869	0.93769	0.93667	0.93565	0.93462	0.93358	69
21	0.93358	0.93253	0.93148	0.93042	0.92935	0.92827	0.92718	68
22	0.92718	0.92609	0.92499	0.92388	0.92276	0.92164	0.92050	67
23	0.92050	0.91936	0.91822	0.91706	0.91590	0.91472	0.91355	66
24	0.91355	0.91236	0.91116	0.90996	0.90875	0.90753	0.90631	65
25	0.90631	0.90507	0.90383	0.90259	0.90133	0.90007	0.89879	64
26	0.89879	0.89752	0.89623	0.89493	0.89363	0.89232	0.89101	63
27	0.89101	0.88968	0.88835	0.88701	0.88566	0.88431	0.88295	62
28	0.88295	0.88158	0.88020	0.87882	0.87743	0.87603	0.87462	61
29	0.87462	0.87321	0.87178	0.87036	0.86892	0.86748	0.86603	60
30	0.86603	0.86457	0.86310	0.86163	0.86015	0.85866	0.85717	59
31	0.85717	0.85567	0.85418	0.85264	0.85112	0.84959	0.84805	58
32	0.84805	0.84650	0.84495	0.84339	0.84182	0.84025	0.83867	57
33	0.83867	0.83708	0.83549	0.83389	0.83228	0.83066	0.82904	56
34	0.82904	0.82741	0.82577	0.82413	0.82248	0.82082	0.81915	55
35	0.81915	0.81748	0.81580	0.81412	0.81242	0.81072	0.80902	54
36	0.80902	0.80730	0.80558	0.80386	0.80212	0.80038	0.79864	53
37	0.79864	0.79688	0.79512	0.79335	0.79158	0.78980	0.78801	52
38	0.78801	0.78622	0.78442	0.78261	0.78079	0.77897	0.77715	51
39	0.77715	0.77531	0.77347	0.77162	0.76977	0.76791	0.76604	50
40	0.76604	0.76417	0.76229	0.76041	0.75851	0.75661	0.75471	49
41	0.75471	0.75280	0.75088	0.74896	0.74703	0.74509	0.74314	48
42	0.74314	0.74120	0.73924	0.73728	0.73531	0.73333	0.73135	47
43	0.73135	0.72937	0.72737	0.72537	0.72337	0.72136	0.71934	46
44	0.71934	0.71732	0.71529	0.71325	0.71121	0.70916	0.70711	45
Cosines	60'	50'	40'	30'	20'	10'	0'	Degrees
SINES								

# CARNEGIE STEEL COMPANY

## NATURAL TRIGONOMETRIC FUNCTIONS

Degrees	TANGENTS							Cotangents
	0'	10'	20'	30'	40'	50'	60'	
0	0.00000	0.00291	0.00582	0.00873	0.01164	0.01455	0.01746	89
1	0.01746	0.02036	0.02328	0.02619	0.02910	0.03201	0.03492	88
2	0.03492	0.03783	0.04075	0.04366	0.04658	0.04949	0.05241	87
3	0.05241	0.05533	0.05824	0.06116	0.06408	0.06700	0.06993	86
4	0.06993	0.07285	0.07578	0.07870	0.08163	0.08456	0.08749	85
5	0.08749	0.09042	0.09335	0.09629	0.09923	0.10216	0.10510	84
6	0.10510	0.10805	0.11099	0.11394	0.11688	0.11983	0.12278	83
7	0.12278	0.12574	0.12869	0.13165	0.13461	0.13758	0.14054	82
8	0.14054	0.14351	0.14648	0.14945	0.15243	0.15540	0.15838	81
9	0.15838	0.16137	0.16435	0.16734	0.17033	0.17333	0.17633	80
10	0.17633	0.17933	0.18233	0.18534	0.18835	0.19136	0.19438	79
11	0.19438	0.19740	0.20042	0.20345	0.20648	0.20952	0.21256	78
12	0.21256	0.21560	0.21864	0.22169	0.22475	0.22781	0.23087	77
13	0.23087	0.23393	0.23700	0.24008	0.24316	0.24624	0.24933	76
14	0.24933	0.25242	0.25552	0.25862	0.26172	0.26483	0.26795	75
15	0.26795	0.27107	0.27419	0.27732	0.28046	0.28360	0.28675	74
16	0.28675	0.28990	0.29305	0.29621	0.29938	0.30255	0.30573	73
17	0.30573	0.30891	0.31210	0.31530	0.31850	0.32171	0.32492	72
18	0.32492	0.32814	0.33136	0.33460	0.33783	0.34108	0.34433	71
19	0.34433	0.34758	0.35085	0.35412	0.35740	0.36068	0.36397	70
20	0.36397	0.36727	0.37057	0.37388	0.37720	0.38053	0.38386	69
21	0.38386	0.38721	0.39055	0.39391	0.39727	0.40065	0.40403	68
22	0.40403	0.40741	0.41081	0.41421	0.41763	0.42105	0.42447	67
23	0.42447	0.42791	0.43136	0.43481	0.43828	0.44175	0.44523	66
24	0.44523	0.44872	0.45222	0.45573	0.45924	0.46277	0.46631	65
25	0.46631	0.46985	0.47341	0.47698	0.48055	0.48414	0.48773	64
26	0.48773	0.49134	0.49495	0.49858	0.50222	0.50587	0.50953	63
27	0.50953	0.51320	0.51688	0.52057	0.52427	0.52798	0.53171	62
28	0.53171	0.53545	0.53920	0.54296	0.54674	0.55051	0.55431	61
29	0.55431	0.55812	0.56194	0.56577	0.56962	0.57348	0.57735	60
30	0.57735	0.58124	0.58513	0.58905	0.59297	0.59691	0.60086	59
31	0.60086	0.60483	0.60881	0.61280	0.61681	0.62083	0.62487	58
32	0.62487	0.62892	0.63299	0.63707	0.64117	0.64528	0.64941	57
33	0.64941	0.65355	0.65771	0.66189	0.66608	0.67028	0.67451	56
34	0.67451	0.67875	0.68301	0.68728	0.69157	0.69588	0.70021	55
35	0.70021	0.70455	0.70891	0.71329	0.71769	0.72211	0.72654	54
36	0.72654	0.73100	0.73547	0.73996	0.74447	0.74900	0.75355	53
37	0.75355	0.75812	0.76272	0.76733	0.77196	0.77661	0.78129	52
38	0.78129	0.78598	0.79070	0.79544	0.80020	0.80498	0.80978	51
39	0.80978	0.81461	0.81946	0.82434	0.82923	0.83415	0.83910	50
40	0.83910	0.84407	0.84906	0.85408	0.85912	0.86419	0.86929	49
41	0.86929	0.87441	0.87955	0.88473	0.88992	0.89515	0.90040	48
42	0.90040	0.90569	0.91099	0.91633	0.92170	0.92709	0.93252	47
43	0.93252	0.93797	0.94345	0.94896	0.95451	0.96008	0.96569	46
44	0.96569	0.97133	0.97700	0.98270	0.98843	0.99420	1.00000	45
Tangents	COTANGENTS							Degrees
	60'	50'	40'	30'	20'	10'	0'	

# MATHEMATICAL TABLES

## NATURAL TRIGONOMETRIC FUNCTIONS

Degrees	COTANGENTS							Tangents
	0'	10'	20'	30'	40'	50'	60'	
0	∞	343.77371	171.88540	114.58865	85.93979	68.75009	57.28996	89
1	57.28996	49.10388	42.96408	38.18846	34.36777	31.24158	28.63825	88
2	28.63825	26.43160	24.54176	22.90377	21.47040	20.20555	19.08114	87
3	19.08114	18.07498	17.16934	16.34986	15.60478	14.92442	14.30067	86
4	14.30067	13.72674	13.19688	12.70621	12.25051	11.82617	11.43005	85
5	11.43005	11.05943	10.71191	10.38540	10.07803	9.78817	9.51436	84
6	9.51436	9.25530	9.00983	8.77689	8.55555	8.34496	8.14435	83
7	8.14435	7.95302	7.77035	7.59575	7.42871	7.26873	7.11537	82
8	7.11537	6.96823	6.82094	6.69116	6.56055	6.43484	6.31375	81
9	6.31375	6.19703	6.08444	5.97576	5.87080	5.76937	5.67128	80
10	5.67128	5.57638	5.48451	5.39552	5.30928	5.22566	5.14455	79
11	5.14455	5.06584	4.98940	4.91510	4.84300	4.77286	4.70463	78
12	4.70463	4.63825	4.57363	4.51071	4.44942	4.38969	4.33148	77
13	4.33148	4.27471	4.21933	4.16530	4.11256	4.06107	4.01078	76
14	4.01078	3.96165	3.91364	3.86671	3.82083	3.77595	3.73205	75
15	3.73205	3.68909	3.64705	3.60588	3.56557	3.52609	3.48741	74
16	3.48741	3.44651	3.41236	3.37594	3.34023	3.30521	3.27085	73
17	3.27085	3.23714	3.20406	3.17159	3.13972	3.10842	3.07768	72
18	3.07768	3.04749	3.01783	2.98869	2.96004	2.93189	2.90421	71
19	2.90421	2.87700	2.85023	2.82391	2.79802	2.77254	2.74748	70
20	2.74748	2.72281	2.69853	2.67462	2.65109	2.62791	2.60509	69
21	2.60509	2.58261	2.56046	2.53865	2.51715	2.49597	2.47509	68
22	2.47509	2.45451	2.43422	2.41421	2.39449	2.37504	2.35585	67
23	2.35585	2.33693	2.31826	2.29984	2.28167	2.26374	2.24604	66
24	2.24604	2.22857	2.21132	2.19430	2.17749	2.16090	2.14451	65
25	2.14451	2.12832	2.11233	2.09654	2.08094	2.06553	2.05030	64
26	2.05030	2.03526	2.02039	2.00569	1.99116	1.97680	1.96261	63
27	1.96261	1.94858	1.93470	1.92098	1.90741	1.89400	1.88073	62
28	1.88073	1.86760	1.85462	1.84177	1.82907	1.81649	1.80405	61
29	1.80405	1.79174	1.77955	1.76749	1.75556	1.74375	1.73205	60
30	1.73205	1.72047	1.70901	1.69766	1.68643	1.67530	1.66428	59
31	1.66428	1.65337	1.64256	1.63185	1.62125	1.61074	1.60033	58
32	1.60033	1.59002	1.57981	1.56969	1.55966	1.54972	1.53987	57
33	1.53987	1.53010	1.52043	1.51084	1.50133	1.49190	1.48256	56
34	1.48256	1.47330	1.46411	1.45501	1.44598	1.43703	1.42815	55
35	1.42815	1.41934	1.41061	1.40195	1.39336	1.38484	1.37638	54
36	1.37638	1.36800	1.35968	1.35142	1.34323	1.33511	1.32704	53
37	1.32704	1.31904	1.31110	1.30323	1.29541	1.28764	1.27994	52
38	1.27994	1.27230	1.26471	1.25717	1.24969	1.24227	1.23490	51
39	1.23490	1.22758	1.22031	1.21310	1.20593	1.19882	1.19175	50
40	1.19175	1.18474	1.17777	1.17085	1.16398	1.15715	1.15037	49
41	1.15037	1.14363	1.13694	1.13029	1.12369	1.11713	1.11061	48
42	1.11061	1.10414	1.09770	1.09131	1.08496	1.07864	1.07237	47
43	1.07237	1.06613	1.05994	1.05378	1.04766	1.04158	1.03553	46
44	1.03553	1.02952	1.02355	1.01761	1.01170	1.00583	1.00000	45
Cotangents	TANGENTS							Degrees
	60'	50'	40'	30'	20'	10'	0'	

# CARNEGIE STEEL COMPANY

## NATURAL TRIGONOMETRIC FUNCTIONS

Degrees	SECANTS							Cosecants
	0'	10'	20'	30'	40'	50'	60'	
0	1.00000	1.00000	1.00002	1.00004	1.00007	1.00011	1.00015	89
1	1.00015	1.00021	1.00027	1.00034	1.00042	1.00051	1.00061	88
2	1.00061	1.00072	1.00083	1.00095	1.00108	1.00122	1.00137	87
3	1.00137	1.00153	1.00169	1.00187	1.00205	1.00224	1.00244	86
4	1.00244	1.00265	1.00287	1.00309	1.00333	1.00357	1.00382	85
5	1.00382	1.00408	1.00435	1.00463	1.00491	1.00521	1.00551	84
6	1.00551	1.00582	1.00614	1.00647	1.00681	1.00715	1.00751	83
7	1.00751	1.00787	1.00825	1.00863	1.00902	1.00942	1.00983	82
8	1.00983	1.01024	1.01067	1.01111	1.01155	1.01200	1.01247	81
9	1.01247	1.01294	1.01342	1.01391	1.01440	1.01491	1.01543	80
10	1.01543	1.01595	1.01649	1.01703	1.01758	1.01815	1.01872	79
11	1.01872	1.01930	1.01989	1.02049	1.02110	1.02171	1.02234	78
12	1.02234	1.02298	1.02362	1.02428	1.02494	1.02562	1.02630	77
13	1.02630	1.02700	1.02770	1.02842	1.02914	1.02987	1.03061	76
14	1.03061	1.03137	1.03213	1.03290	1.03368	1.03447	1.03528	75
15	1.03528	1.03609	1.03691	1.03774	1.03858	1.03944	1.04030	74
16	1.04030	1.04117	1.04206	1.04295	1.04385	1.04477	1.04569	73
17	1.04569	1.04663	1.04757	1.04853	1.04950	1.05047	1.05146	72
18	1.05146	1.05246	1.05347	1.05449	1.05552	1.05657	1.05762	71
19	1.05762	1.05869	1.05976	1.06085	1.06195	1.06306	1.06418	70
20	1.06418	1.06531	1.06645	1.06761	1.06878	1.06995	1.07115	69
21	1.07115	1.07235	1.07356	1.07479	1.07602	1.07727	1.07853	68
22	1.07853	1.07981	1.08109	1.08239	1.08370	1.08503	1.08636	67
23	1.08636	1.08771	1.08907	1.09044	1.09183	1.09323	1.09464	66
24	1.09464	1.09606	1.09750	1.09895	1.10041	1.10189	1.10338	65
25	1.10338	1.10488	1.10640	1.10793	1.10947	1.11103	1.11260	64
26	1.11260	1.11419	1.11579	1.11740	1.11903	1.12067	1.12233	63
27	1.12233	1.12400	1.12568	1.12738	1.12910	1.13083	1.13257	62
28	1.13257	1.13433	1.13610	1.13789	1.13970	1.14152	1.14335	61
29	1.14335	1.14521	1.14707	1.14896	1.15085	1.15277	1.15470	60
30	1.15470	1.15665	1.15861	1.16059	1.16259	1.16460	1.16663	59
31	1.16663	1.16868	1.17075	1.17283	1.17493	1.17704	1.17918	58
32	1.17918	1.18133	1.18350	1.18569	1.18790	1.19012	1.19236	57
33	1.19236	1.19463	1.19691	1.19920	1.20152	1.20386	1.20622	56
34	1.20622	1.20859	1.21099	1.21341	1.21584	1.21830	1.22077	55
35	1.22077	1.22327	1.22579	1.22833	1.23089	1.23347	1.23607	54
36	1.23607	1.23869	1.24134	1.24400	1.24669	1.24940	1.25214	53
37	1.25214	1.25489	1.25767	1.26047	1.26330	1.26615	1.26902	52
38	1.26902	1.27191	1.27483	1.27778	1.28075	1.28374	1.28676	51
39	1.28676	1.28980	1.29287	1.29597	1.29900	1.30223	1.30541	50
40	1.30541	1.30861	1.31183	1.31509	1.31837	1.32168	1.32501	49
41	1.32501	1.32838	1.33177	1.33519	1.33864	1.34212	1.34563	48
42	1.34563	1.34917	1.35274	1.35634	1.35997	1.36363	1.36733	47
43	1.36733	1.37105	1.37481	1.37860	1.38242	1.38628	1.39016	46
44	1.39016	1.39409	1.39804	1.40203	1.40606	1.41012	1.41421	45
Seconds	COSECANTS							Degrees
	60'	50'	40'	30'	20'	10'	0'	

# MATHEMATICAL TABLES

## NATURAL TRIGONOMETRIC FUNCTIONS

Degrees	COSECANTS							Seconds
	0'	10'	20'	30'	40'	50'	60'	
0	∞	343.77516	171.88831	114.59301	85.94561	68.75736	57.29860	89
1	57.29869	49.11406	42.97571	38.20155	34.38232	31.25758	28.65371	88
2	28.65371	26.45051	24.56212	22.92559	21.49368	20.23028	19.10732	87
3	19.10732	18.10262	17.19843	16.38041	15.63679	14.95788	14.33559	86
4	14.33559	13.76312	13.23472	12.74550	12.29125	11.86837	11.47371	85
5	11.47371	11.10455	10.75849	10.43343	10.12752	9.83912	9.56677	84
6	9.56677	9.30917	9.06515	8.83367	8.61379	8.40466	8.20551	83
7	8.20551	8.01565	7.83443	7.66130	7.49571	7.33719	7.18530	82
8	7.18530	7.03962	6.89979	6.76547	6.63633	6.51208	6.39245	81
9	6.39245	6.27719	6.16607	6.05886	5.95536	5.85530	5.75877	80
10	5.75877	5.66533	5.57493	5.48740	5.40263	5.32040	5.24084	79
11	5.24084	5.16359	5.08863	5.01585	4.94517	4.87649	4.80973	78
12	4.80973	4.74482	4.68167	4.62023	4.56041	4.50210	4.44541	77
13	4.44541	4.39012	4.33622	4.28366	4.23239	4.18238	4.13357	76
14	4.13357	4.08591	4.03938	3.99393	3.94952	3.90613	3.86370	75
15	3.86370	3.82223	3.78166	3.74198	3.70315	3.66515	3.62796	74
16	3.62796	3.59154	3.55587	3.52094	3.48671	3.45317	3.42030	73
17	3.42030	3.38908	3.35649	3.32551	3.29512	3.26531	3.23607	72
18	3.23607	3.20737	3.17920	3.15155	3.12440	3.09774	3.07155	71
19	3.07155	3.04584	3.02057	2.99574	2.97135	2.94737	2.92380	70
20	2.92380	2.90063	2.87785	2.85545	2.83342	2.81175	2.79043	69
21	2.79043	2.76945	2.74881	2.72850	2.70851	2.68884	2.66947	68
22	2.66947	2.65040	2.63162	2.61313	2.59491	2.57698	2.55930	67
23	2.55930	2.54190	2.52474	2.50784	2.49119	2.47477	2.45859	66
24	2.45859	2.44264	2.42692	2.41142	2.39614	2.38107	2.36620	65
25	2.36620	2.35154	2.33708	2.32282	2.30875	2.29487	2.28117	64
26	2.28117	2.26760	2.25432	2.24116	2.22817	2.21535	2.20269	63
27	2.20269	2.19019	2.17786	2.16568	2.15366	2.14178	2.13005	62
28	2.13005	2.11847	2.10704	2.09574	2.08458	2.07356	2.06267	61
29	2.06267	2.05191	2.04128	2.03077	2.02039	2.01014	2.00000	60
30	2.00000	1.98998	1.98008	1.97029	1.96062	1.95106	1.94160	59
31	1.94160	1.93226	1.92302	1.91388	1.90485	1.89591	1.88709	58
32	1.88709	1.87834	1.86970	1.86116	1.85271	1.84435	1.83608	57
33	1.83608	1.82790	1.81981	1.81180	1.80388	1.79604	1.78829	56
34	1.78829	1.78062	1.77303	1.76552	1.75808	1.75073	1.74345	55
35	1.74345	1.73624	1.72911	1.72205	1.71506	1.70815	1.70130	54
36	1.70130	1.69452	1.68782	1.68117	1.67460	1.66809	1.66164	53
37	1.66164	1.65526	1.64894	1.64268	1.63648	1.63035	1.62427	52
38	1.62427	1.61825	1.61229	1.60639	1.60054	1.59475	1.58902	51
39	1.58902	1.58333	1.57771	1.57213	1.56661	1.56114	1.55572	50
40	1.55572	1.55036	1.54504	1.53977	1.53455	1.52938	1.52425	49
41	1.52425	1.51918	1.51415	1.50916	1.50422	1.49933	1.49448	48
42	1.49448	1.48967	1.48491	1.48019	1.47551	1.47087	1.46628	47
43	1.46628	1.46173	1.45721	1.45274	1.44831	1.44391	1.43956	46
44	1.43956	1.43524	1.43096	1.42672	1.42251	1.41835	1.41421	45
Cosecants	SECANTS							Degrees
	00'	50'	40'	30'	20'	10'	0'	

# CARNEGIE STEEL COMPANY

## BIRMINGHAM WIRE GAGE

### EQUIVALENTS IN INCHES

### CORRESPONDING WEIGHTS OF FLAT ROLLED STEEL

Gage Number	Thickness, Inches	Pounds per Square Foot	Thickness, Inches		Pounds per Square Foot
			Fractional	Decimal	
.....	.....	.....	$\frac{1}{2}$	.5	20.4
0000	.454	18.5232	$\frac{11}{16}$	.46875	19.125
000	.425	17.34	$\frac{5}{8}$	.4375	17.85
.....	.....	.....	$\frac{3}{4}$	.40625	16.575
00	.380	15.504	$\frac{7}{8}$	.375	15.3
0	.340	13.872	$\frac{15}{16}$	.34375	14.025
1	.300	12.24	$\frac{1}{8}$	.3125	12.75
2	.284	11.5872	$\frac{1}{4}$	.296875	12.1125
3	.259	10.5672	$\frac{3}{8}$	.28125	11.475
.....	.....	.....	$\frac{1}{2}$	.265625	10.8375
4	.238	9.7104	$\frac{5}{8}$	.25	10.2
5	.220	8.976	$\frac{3}{4}$	.234375	9.5625
6	.203	8.2824	$\frac{7}{8}$	.21875	8.925
7	.180	7.344	$\frac{15}{16}$	.203125	8.2875
8	.165	6.732	$\frac{1}{8}$	.1875	7.65
9	.148	6.0384	$\frac{1}{4}$	.171875	7.0125
10	.134	5.4672	$\frac{3}{8}$	.15625	6.375
11	.120	4.896	$\frac{1}{2}$	.140625	5.7375
12	.109	4.4472	$\frac{5}{8}$	.125	5.1
13	.095	3.876	$\frac{3}{4}$	.109375	4.4625
14	.083	3.3864	$\frac{7}{8}$	.09375	3.825
15	.072	2.9376	$\frac{15}{16}$	.078125	3.1875
16	.065	2.652	..	.....	.....
17	.058	2.3664	$\frac{1}{8}$	.0625	2.55
18	.049	1.9902	..	.....	.....
19	.042	1.7136	$\frac{1}{4}$	.046875	1.0125
20	.035	1.428	..	.....	.....
21	.032	1.3056	..	.....	.....
22	.028	1.1424	$\frac{3}{8}$	.03125	1.275
23	.025	1.02	..	.....	.....
24	.022	0.8976	..	.....	.....
25	.020	0.816	..	.....	.....
26	.018	0.7344	..	.....	.....
27	.016	0.6528	$\frac{1}{2}$	.015625	0.0375
28	.014	0.5712	..	.....	.....
29	.013	0.5304	..	.....	.....
30	.012	0.4896	..	.....	.....
31	.010	0.408	..	.....	.....
32	.009	0.3672	..	.....	.....
33	.008	0.3264	$\frac{1}{16}$	.0078125	0.31875
34	.007	0.2856	..	.....	.....
35	.005	0.2040	..	.....	.....
36	.004	0.1632	$\frac{1}{32}$	.00390625	0.159375

Unless otherwise specified, all orders for flat rolled steel in gages will be executed by Carnegie Steel Company to Birmingham Wire Gage.

# MEASURES AND WEIGHTS

## UNITED STATES STANDARD GAGE

For

### SHEET AND PLATE IRON AND STEEL

Gage Number	Approximate Thickness			Weight per Square Foot, Ounces, Avoirdupois	Weight per Square Foot, Pounds, Avoirdupois	Weight per Square Meter, Kilograms
	Fractional Inches	Decimal Inches	Millimeters			
0000000	$\frac{1}{16}$	.5	12.7	320	20.00	97.65
0000000	$\frac{1}{8}$	.46875	11.90625	300	18.75	91.55
000000	$\frac{3}{16}$	.4375	11.1125	280	17.50	85.44
0000	$\frac{1}{4}$	.40625	10.31875	260	16.25	79.33
000	$\frac{5}{16}$	.375	9.525	240	15.00	73.24
00	$\frac{3}{8}$	.34375	8.73125	220	13.75	67.13
0	$\frac{1}{2}$	.3125	7.9375	200	12.50	61.03
1	$\frac{5}{8}$	.28125	7.14375	180	11.25	54.93
2	$\frac{3}{4}$	.250625	6.46875	170	10.625	51.88
3	$\frac{7}{8}$	.25	6.35	160	10.00	48.82
4	$\frac{1}{2}$	.234375	5.953125	150	9.375	45.77
5	$\frac{9}{16}$	.21875	5.55625	140	8.75	42.72
6	$\frac{11}{16}$	.203125	5.159375	130	8.125	39.67
7	$\frac{1}{2}$	.1875	4.7625	120	7.50	36.62
8	$\frac{13}{16}$	.171875	4.365625	110	6.875	33.57
9	$\frac{3}{4}$	.15625	3.96875	100	6.25	30.52
10	$\frac{7}{8}$	.140625	3.571875	90	5.625	27.46
11	$\frac{15}{16}$	.125	3.175	80	5.00	24.41
12	$\frac{1}{2}$	.109375	2.778125	70	4.375	21.36
13	$\frac{5}{8}$	.09375	2.38125	60	3.75	18.31
14	$\frac{11}{16}$	.078125	1.984375	50	3.125	15.26
15	$\frac{3}{4}$	.0703125	1.7859375	45	2.8125	13.73
16	$\frac{13}{16}$	.0625	1.5875	40	2.50	12.21
17	$\frac{7}{8}$	.05625	1.42875	36	2.25	10.99
18	$\frac{15}{16}$	.05	1.27	32	2.00	9.765
19	$\frac{1}{2}$	.04375	1.11125	28	1.75	8.544
20	$\frac{9}{16}$	.0375	.9525	24	1.50	7.324
21	$\frac{11}{16}$	.034375	.87125	22	1.375	6.713
22	$\frac{13}{16}$	.03125	.79375	20	1.25	6.103
23	$\frac{3}{4}$	.028125	.714375	18	1.125	5.493
24	$\frac{7}{8}$	.025	.635	16	1.00	4.882
25	$\frac{15}{16}$	.021875	.555625	14	.875	4.272
26	$\frac{1}{2}$	.01875	.47625	12	.75	3.662
27	$\frac{11}{16}$	.0171875	.4365625	11	.6875	3.357
28	$\frac{3}{4}$	.015625	.396875	10	.625	3.052
29	$\frac{13}{16}$	.0140625	.3571875	9	.5625	2.746
30	$\frac{7}{8}$	.0125	.3175	8	.50	2.441
31	$\frac{15}{16}$	.0109375	.2778125	7	.4375	2.136
32	$\frac{1}{2}$	.01015625	.25796875	6 $\frac{1}{2}$	.40625	1.983
33	$\frac{9}{16}$	.009375	.238125	6	.375	1.831
34	$\frac{11}{16}$	.00859375	.21828125	5 $\frac{1}{2}$	.34375	1.678
35	$\frac{3}{4}$	.0078125	.1984375	5	.3125	1.526
36	$\frac{13}{16}$	.00703125	.17859375	4 $\frac{1}{2}$	.28125	1.373
37	$\frac{7}{8}$	.006640625	.168671875	4 $\frac{1}{4}$	.265625	1.297
38	$\frac{15}{16}$	.00625	.15875	4	.25	1.221

The United States Standard Gage is a weight gage based upon the weights per square foot in ounces avoirdupois and approximate thickness based upon 480 pounds per cubic foot.

In the practical use and application of the United States Standard Gage, a weight variation of  $2\frac{1}{4}$  per cent either way may be allowed.

Unless otherwise specified, all orders for flat rolled steel in gages will be executed by Carnegie Steel Company to Birmingham Wire Gage.



# CARNEGIE STEEL COMPANY

## STANDARD GAGES

### COMPARATIVE TABLE

Gage Number	Thickness in Decimals of an Inch					
	Birmingham Wire (B. W. G.) also known as Stub's Iron Wire	American Wire Browne & Sharpe	American Steel & Wire Co. formerly Washburn & Moen	Trenton Iron Company	British Imperial Standard Wire (B. W. G.)	Standard Birmingham Sheet and Hoop (B. G.)
0000000	.....	.....	.4900	.....	.500	.....
000000	.....	.580000	.4615	.....	.464	.....
00000	.500	.516500	.4305	.450	.432	.....
0000	.454	.460000	.3938	.400	.400	.....
000	.425	.409642	.3625	.360	.372	.5000
00	.380	.364796	.3310	.330	.348	.4452
0	.340	.324861	.3005	.305	.324	.3964
1	.300	.289297	.2830	.285	.300	.3532
2	.284	.257627	.2625	.265	.276	.3147
3	.259	.229423	.2437	.245	.252	.2804
4	.238	.204307	.2253	.225	.232	.2500
5	.220	.181940	.2070	.205	.212	.2225
6	.203	.162023	.1920	.190	.192	.1981
7	.180	.144285	.1770	.175	.176	.1764
8	.165	.128490	.1620	.160	.160	.1570
9	.148	.114423	.1483	.145	.144	.1398
10	.134	.101897	.1350	.130	.128	.1250
11	.120	.090742	.1205	.1175	.116	.1113
12	.109	.080808	.1055	.105	.104	.0991
13	.095	.071962	.0915	.0925	.092	.0882
14	.083	.064084	.0800	.0806	.080	.0785
15	.072	.057098	.0720	.070	.072	.0699
16	.065	.050821	.0625	.061	.064	.0625
17	.058	.045257	.0540	.0525	.056	.0556
18	.049	.040303	.0475	.045	.048	.0495
19	.042	.035890	.0410	.040	.040	.0440
20	.035	.031961	.0348	.035	.036	.0392
21	.032	.028462	.03175	.031	.032	.0349
22	.028	.025346	.0286	.028	.028	.03125
23	.025	.022572	.0258	.025	.024	.02782
24	.022	.020101	.0230	.0225	.022	.02476
25	.020	.017900	.0204	.020	.020	.02204
26	.018	.015941	.0181	.018	.018	.01961
27	.016	.014195	.0173	.017	.0164	.01745
28	.014	.012641	.0162	.016	.0148	.015625
29	.013	.011257	.0150	.015	.0136	.0139
30	.012	.010025	.0140	.014	.0124	.0123
31	.010	.008928	.0132	.013	.0116	.0110
32	.009	.007950	.0128	.012	.0108	.0098
33	.008	.007080	.0118	.011	.0100	.0087
34	.007	.006305	.0104	.010	.0092	.0077
35	.005	.005615	.0095	.0095	.0084	.0069
36	.004	.005000	.0090	.009	.0076	.0061
37	.....	.004453	.0085	.0085	.0068	.0054
38	.....	.003965	.0080	.008	.0060	.0048
39	.....	.003531	.0075	.0075	.0052	.....
40	.....	.003144	.0070	.007	.0048	.....

Unless otherwise specified, all orders for flat rolled steel in gages will be executed by Carnegie Steel Company to Birmingham Wire Gage.

# MEASURES AND WEIGHTS

## DECIMAL OF AN INCH AND OF A FOOT

Fractions of Inch or Foot	Inch Equivalents to Foot Fractions	Fractions of Inch or Foot	Inch Equivalents to Foot Fractions	Fractions of Inch or Foot	Inch Equivalents to Foot Fractions	Fractions of Inch or Foot	Inch Equivalents to Foot Fractions
.0052	$\frac{1}{192}$	.2552	$3\frac{1}{8}$	.5052	$6\frac{1}{8}$	.7552	$9\frac{1}{8}$
.0104	$\frac{1}{96}$	.2604	$3\frac{1}{8}$	.5104	$6\frac{1}{8}$	.7604	$9\frac{1}{8}$
.015625	$\frac{1}{64}$	.265625	$3\frac{1}{8}$	.515625	$6\frac{1}{8}$	.765625	$9\frac{1}{8}$
.0208	$\frac{1}{48}$	.2708	$3\frac{1}{8}$	.5208	$6\frac{1}{8}$	.7708	$9\frac{1}{8}$
.0260	$\frac{1}{38}$	.2760	$3\frac{1}{8}$	.5260	$6\frac{1}{8}$	.7760	$9\frac{1}{8}$
.03125	$\frac{1}{32}$	.28125	$3\frac{1}{8}$	.53125	$6\frac{1}{8}$	.78125	$9\frac{1}{8}$
.0365	$\frac{1}{27}$	.2865	$3\frac{1}{8}$	.5365	$6\frac{1}{8}$	.7865	$9\frac{1}{8}$
.0417	$\frac{1}{24}$	.2917	$3\frac{1}{8}$	.5417	$6\frac{1}{8}$	.7917	$9\frac{1}{8}$
.046875	$\frac{3}{64}$	.296875	$3\frac{1}{8}$	.546875	$6\frac{1}{8}$	.796875	$9\frac{1}{8}$
.0521	$\frac{1}{19}$	.3021	$3\frac{1}{8}$	.5521	$6\frac{1}{8}$	.8021	$9\frac{1}{8}$
.0573	$\frac{1}{17}$	.3073	$3\frac{1}{8}$	.5573	$6\frac{1}{8}$	.8073	$9\frac{1}{8}$
.0625	$\frac{1}{16}$	.3125	$3\frac{1}{8}$	.5625	$6\frac{1}{8}$	.8125	$9\frac{1}{8}$
.0677	$\frac{1}{15}$	.3177	$3\frac{1}{8}$	.5677	$6\frac{1}{8}$	.8177	$9\frac{1}{8}$
.0729	$\frac{1}{14}$	.3229	$3\frac{1}{8}$	.5729	$6\frac{1}{8}$	.8229	$9\frac{1}{8}$
.078125	$\frac{1}{13}$	.328125	$3\frac{1}{8}$	.578125	$6\frac{1}{8}$	.828125	$9\frac{1}{8}$
.0833	$\frac{1}{12}$	.3333	$3\frac{1}{8}$	.5833	$6\frac{1}{8}$	.8333	$9\frac{1}{8}$
.0885	$\frac{1}{11}$	.3385	$3\frac{1}{8}$	.5885	$6\frac{1}{8}$	.8385	$9\frac{1}{8}$
.09375	$\frac{1}{10}$	.34375	$3\frac{1}{8}$	.59375	$6\frac{1}{8}$	.84375	$9\frac{1}{8}$
.0990	$\frac{1}{9}$	.3490	$3\frac{1}{8}$	.5990	$6\frac{1}{8}$	.8490	$9\frac{1}{8}$
.1042	$\frac{1}{8}$	.3542	$3\frac{1}{8}$	.6042	$6\frac{1}{8}$	.8542	$9\frac{1}{8}$
.109375	$\frac{7}{64}$	.359375	$3\frac{1}{8}$	.609375	$6\frac{1}{8}$	.859375	$9\frac{1}{8}$
.1146	$\frac{1}{7}$	.3646	$3\frac{1}{8}$	.6146	$6\frac{1}{8}$	.8646	$9\frac{1}{8}$
.1198	$\frac{1}{6}$	.3698	$3\frac{1}{8}$	.6198	$6\frac{1}{8}$	.8698	$9\frac{1}{8}$
.1250	$\frac{1}{5}$	.3750	$3\frac{1}{8}$	.6250	$6\frac{1}{8}$	.8750	$9\frac{1}{8}$
.1302	$\frac{1}{4}$	.3802	$3\frac{1}{8}$	.6302	$6\frac{1}{8}$	.8802	$9\frac{1}{8}$
.1354	$\frac{1}{3}$	.3854	$3\frac{1}{8}$	.6354	$6\frac{1}{8}$	.8854	$9\frac{1}{8}$
.140625	$\frac{1}{2}$	.390625	$3\frac{1}{8}$	.640625	$6\frac{1}{8}$	.890625	$9\frac{1}{8}$
.1458	$\frac{1}{2}$	.3958	$3\frac{1}{8}$	.6458	$6\frac{1}{8}$	.8958	$9\frac{1}{8}$
.1510	$\frac{1}{2}$	.4010	$3\frac{1}{8}$	.6510	$6\frac{1}{8}$	.9010	$9\frac{1}{8}$
.15625	$\frac{1}{2}$	.40625	$3\frac{1}{8}$	.65625	$6\frac{1}{8}$	.90625	$9\frac{1}{8}$
.1615	$\frac{1}{2}$	.4115	$3\frac{1}{8}$	.6615	$6\frac{1}{8}$	.9115	$9\frac{1}{8}$
.1667	$\frac{1}{2}$	.4167	$3\frac{1}{8}$	.6667	$6\frac{1}{8}$	.9167	$9\frac{1}{8}$
.171875	$\frac{1}{2}$	.421875	$3\frac{1}{8}$	.671875	$6\frac{1}{8}$	.921875	$9\frac{1}{8}$
.1771	$\frac{1}{2}$	.4271	$3\frac{1}{8}$	.6771	$6\frac{1}{8}$	.9271	$9\frac{1}{8}$
.1823	$\frac{1}{2}$	.4323	$3\frac{1}{8}$	.6823	$6\frac{1}{8}$	.9323	$9\frac{1}{8}$
.1875	$\frac{1}{2}$	.4375	$3\frac{1}{8}$	.6875	$6\frac{1}{8}$	.9375	$9\frac{1}{8}$
.1927	$\frac{1}{2}$	.4427	$3\frac{1}{8}$	.6927	$6\frac{1}{8}$	.9427	$9\frac{1}{8}$
.1979	$\frac{1}{2}$	.4479	$3\frac{1}{8}$	.6979	$6\frac{1}{8}$	.9479	$9\frac{1}{8}$
.203125	$\frac{1}{2}$	.453125	$3\frac{1}{8}$	.703125	$6\frac{1}{8}$	.953125	$9\frac{1}{8}$
.2083	$\frac{1}{2}$	.4583	$3\frac{1}{8}$	.7083	$6\frac{1}{8}$	.9583	$9\frac{1}{8}$
.2135	$\frac{1}{2}$	.4635	$3\frac{1}{8}$	.7135	$6\frac{1}{8}$	.9635	$9\frac{1}{8}$
.21875	$\frac{1}{2}$	.46875	$3\frac{1}{8}$	.71875	$6\frac{1}{8}$	.96875	$9\frac{1}{8}$
.2240	$\frac{1}{2}$	.4740	$3\frac{1}{8}$	.7240	$6\frac{1}{8}$	.9740	$9\frac{1}{8}$
.2292	$\frac{1}{2}$	.4792	$3\frac{1}{8}$	.7292	$6\frac{1}{8}$	.9792	$9\frac{1}{8}$
.234375	$\frac{1}{2}$	.484375	$3\frac{1}{8}$	.734375	$6\frac{1}{8}$	.984375	$9\frac{1}{8}$
.2396	$\frac{1}{2}$	.4896	$3\frac{1}{8}$	.7396	$6\frac{1}{8}$	.9896	$9\frac{1}{8}$
.2448	$\frac{1}{2}$	.4948	$3\frac{1}{8}$	.7448	$6\frac{1}{8}$	.9948	$9\frac{1}{8}$
.2500	$\frac{1}{2}$	.5000	$3\frac{1}{8}$	.7500	$6\frac{1}{8}$	1.0000	$9\frac{1}{8}$

# CARNEGIE STEEL COMPANY

## SUBJECT INDEX

	Page
American Bridge Co. . . . .	154-160
A. S. T. M. . . . .	4-54
boiler and fire box steel . . . . .	36-40
boiler rivet steel . . . . .	41-44
nickel steel, structural . . . . .	45-50
reinforcement bars, billet steel . . . . .	51-54
ship rivet steel . . . . .	31-35
structural steel for bridges . . . . .	4-9
" " " buildings . . . . .	10-15
" " " cars . . . . .	21-25
" " " locomotives . . . . .	16-20
" " " ships . . . . .	26-30
Anchors . . . . .	243
Angles . . . . .	167, 178-183
profiles, dimensions and weights . . . . .	86-93
safe loads, explanatory notes . . . . .	206
safe load tables . . . . .	230-234
standard connections . . . . .	240, 241
structural details for punching and riveting . . . . .	246-248
tension values . . . . .	254-256
Angles, Back to Back . . . . .	169, 194-196
Arches, Floor Arches . . . . .	320-322
terra cotta, safe load tables and weights . . . . .	323-326
Areas . . . . .	394-413
circles, diameters 1 to 909 . . . . .	388-391
circular segments . . . . .	56
method of increasing sectional areas . . . . .	254-256
net areas of angles . . . . .	385
plane figures . . . . .	112-114
rectangular sections . . . . .	248
reduction of area for rivet holes . . . . .	118, 119
square and round bars . . . . .	170-189
structural shapes . . . . .	392, 393
surface of solids . . . . .	110
Band Edge Flats . . . . .	120
Bars . . . . .	120-128
cold twisted square bars, sizes and weights . . . . .	146
concrete reinforcement bars, sizes and weights . . . . .	129
eye bars, sizes and dimensions . . . . .	158
hanger bars, sizes and weights . . . . .	110, 111
lattice bars, dimensions for columns . . . . .	118, 119
merchant bars, list of sizes . . . . .	134, 135
rounds and squares, weights and areas . . . . .	4-54
splice bars, profiles, dimensions and weights . . . . .	257
standard test bars, see A. S. T. M. Specifications . . . . .	144, 145
tension values, rounds and squares . . . . .	
upset screw ends, sizes and dimensions . . . . .	

# INDEX

	Page
<b>Beams, H-Beams</b> .....	see H-Beams..... 68, 174, 224, 290
<b>Beams, I-Beams</b> .....	bending moments, tables..... 213, 214
	common dimensions..... 57
	details, connection angles..... 240, 241
	" bearing plates..... 244
	" separators..... 242
	" standard gages for punching..... 237, 238
	elements of sections..... 166, 170, 171
	grillage, notes and calculations..... 258-262
	profiles, weights and dimensions..... 58-67
	safe loads, explanation of tables..... 206-212
	safe load tables..... 216-223
	web resistance, tables..... 213, 214
<b>Beam Columns</b> .....	safe load tables..... 290
<b>Beam Girders</b> .....	explanatory notes..... 263
	safe load tables..... 264, 265
<b>Beam Stresses</b> .....	explanatory notes..... 197-199, 206-212
	bending stresses..... 197, 198
	buckling stresses..... 210, 211
	deflection, lateral..... 156, 198, 208
	" vertical..... 202-207
	flexure formulas for various loading conditions..... 200-205
	impact stresses..... 208, 209
	shearing stresses, longitudinal and vertical..... 198, 209, 210
	tensile and compressive stresses..... 198
<b>Bearing Plates</b> .....	explanatory notes..... 244
	safe resistance..... 245
	standard for beams..... 244
<b>Bearing Values</b> .....	pins and rivets, explanatory notes..... 249
	pins, tables..... 252
	rivets, tables..... 250, 251
<b>Bending Moments</b> .....	explanatory notes..... 107
	beams, tables..... 213, 214
	channels, tables..... 215
	pins, tables..... 253
	various loading conditions, formulas..... 202-205
<b>Bolts</b> .....	standard dimensions..... 140, 141
	screw threads, standard dimensions..... 140, 141
	weights, bolts with hexagon heads and nuts..... 143
	weights, bolts with square heads and nuts..... 142
<b>Bolt Heads and Nuts</b> .....	standard dimensions..... 140, 141
	weights..... 142, 143
<b>Buckle Plates</b> .....	explanatory notes..... 334
	safe load table..... 334
	sizes and dimensions..... 335
<b>Buckling of Webs</b> .....	explanatory notes..... 210-212
	web resistance of beams and channels, tables..... 213-215
<b>Building Laws</b> .....	extract, from building laws of various cities..... 318
<b>Bulb Sections</b> .....	bulb angles, bulb beams..... 60-76, 175-177
	angles, elements..... 175-177
	" profiles, weights and dimensions..... 70-76
	beams, elements..... 175
	" profiles, weights and dimensions..... 69

# CARNEGIE STEEL COMPANY

	PAGE
<b>Cast Iron Columns</b> . . . . .	allowable unit stresses . . . . . 314
	hollow round and square, elements . . . . . 192, 193
	“ “ “ safe loads . . . . . 315, 316
<b>Ceilings</b> . . . . .	deflection of plastered ceilings . . . . . 206, 207
	weight of ceilings . . . . . 326
<b>Center of Gravity</b> . . . . .	see Neutral Axis . . . . . 161-167, 172-191
<b>Channels, Ship and Car</b> . . . . .	elements of sections . . . . . 173, 174
	profiles, weights and dimensions . . . . . 81-85
<b>Channels, Structural</b> . . . . .	bending moments, table . . . . . 215
	common dimensions . . . . . 57
	details, standard gages for punching . . . . . 239
	elements of sections . . . . . 166, 172-174
	profiles, weights and dimensions . . . . . 77-85
	safe loads, explanation of tables . . . . . 206-212
	safe load tables . . . . . 225-229
	web resistance, table . . . . . 215
<b>Checkered Plates</b> . . . . .	elements and safe loads . . . . . 338
	profiles, weights and dimensions . . . . . 106
<b>Circles</b> . . . . .	areas and circumferences, dia. 1 to 999 . . . . . 394-413
	properties of the circle . . . . . 384
<b>Circular Plates</b> . . . . .	extreme sizes, carbon steel . . . . . 107, 108
<b>Circular Segments</b> . . . . .	areas, tables of coefficients . . . . . 388-391
<b>Cleaves</b> . . . . .	sizes and weights . . . . . 148
<b>Coefficients</b> . . . . .	circular segments . . . . . 389-391
	deflection under uniform load . . . . . 207
	expansion due to heat . . . . . 371
<b>Cold Twisted Squares</b> . . . . .	sizes and weights . . . . . 120
<b>Columns, Cast Iron</b> . . . . .	allowable unit stresses . . . . . 314
	hollow round and square, elements . . . . . 192, 193
	“ “ “ safe loads . . . . . 315, 316
<b>Columns, Steel</b> . . . . .	explanatory notes . . . . . 285, 287
	calculation of elements . . . . . 168, 169
	“ “ stresses . . . . . 287
	compression formulas . . . . . 288, 289
	elements, angle and plate columns . . . . . 303-310
	“ channel and plate columns . . . . . 291-302
	“ miscellaneous beam columns . . . . . 290
	safe loads, angle and plate columns . . . . . 303-310
	“ “ channel and plate columns . . . . . 291-302
	“ “ miscellaneous beam columns . . . . . 290
	typical details for mill and office buildings . . . . . 311-313
<b>Columns, Wood</b> . . . . .	allowable unit stresses . . . . . 361
	square and round, safe loads . . . . . 362, 363
<b>Compound Sections</b> . . . . .	calculation of elements . . . . . 168, 169
<b>Concrete, Masonry</b> . . . . .	strength, unit fiber stresses . . . . . 370
	specific gravity and weight . . . . . 365
<b>Concrete, Reinforced</b> . . . . .	explanatory notes . . . . . 327-331
	beams and slabs, formulas . . . . . 327-330
	bending moments of slabs . . . . . 332
	columns, formulas . . . . . 330
	reinforcements, deformed bars, etc. . . . . 120-128
	“ round and square bars . . . . . 118, 119
	“ triangle mesh . . . . . 333

# INDEX

	Page
Connection Angles..... standard for beams.....	240, 241
Construction Specifications..... American Bridge Company.....	154, 160
Conversion Tables..... measures, metric and U. S. Standard.....	372-383
Corrugated Plates..... elements of sections.....	188
..... profiles, weights and dimensions.....	105
..... assembled sections, elements and safe loads..	337
Corrugated Sheets..... explanatory notes.....	346
..... sizes and weights.....	347
Cotter Pins..... sizes and dimensions.....	150
Cross Tie Sections..... elements of sections.....	187
..... profiles, weights and dimensions.....	130, 131
..... safe load tables.....	224
Cubes and Cube Roots..... numbers 1 to 999.....	394-413
Decimal Table..... equivalents of an inch and of a foot.....	423
Deflection, Lateral..... explanatory notes and formula.....	156, 198, 208
Deflection, Vertical..... explanatory notes.....	198, 206
..... coefficients, calculation and table.....	207
..... coefficients for beams and channels.....	216-220, 224-227
..... limit for plastered ceilings.....	206
..... formulas for loading under various conditions.....	202-205
Deformed Bars..... sizes and weights.....	120-127
Elasticity..... elastic limit of substances.....	368-369
..... modulus of elasticity of substances.....	200, 353, 368-370
Elements of Sections..... explanatory notes.....	161
..... formulas for calculation of elements.....	162-169
..... structural shapes.....	170-196
Equivalent Measures..... metric and U. S. standard.....	372-383
Expansion, Heat..... table of coefficients.....	371
Eye Bars..... sizes, dimensions and weights.....	146
Fiber Stresses..... concrete, reinforced concrete.....	370
..... masonry, stone.....	370
..... metals, alloys.....	368, 369
..... miscellaneous substances.....	370
..... structural steel.....	154, 155, 369
..... structural timber.....	353
Fireproof Floors..... see Floor Construction.....	317-333
Flat Rolled Steel..... list of sizes.....	107-110
..... tables of weights.....	115-117
Flexure of Beams..... explanatory notes and formulas.....	197-205
Floor Construction..... explanatory notes.....	317-322
..... fireproof floor systems.....	319, 320
..... live loads, various building laws.....	318
..... reinforced concrete beams and slabs.....	327-333
..... terra cotta arches, safe loads and weights.....	323-326
..... thrust in arches.....	320-322
Floor Plates..... buckle plates.....	334, 335
..... checkered plates.....	338
..... corrugated plates, assembled.....	337
..... trough plates, assembled.....	336

# CARNEGIE STEEL COMPANY

	Page
<b>Formulas</b> .....	bending moments and deflection..... 200-205
	elements of sections..... 162-169
	geometric and trigonometric..... 384-387, 392, 393
	roof trusses, stresses and length of members..... 342-345
	stresses in beams, bending..... 198-200
	"    "    "    buckling..... 210, 211
	"    "    "    impact..... 208, 209
	"    "    "    shearing..... 209, 210
	stresses in columns, cast iron..... 314
	"    "    "    structural steel..... 288, 289
	"    "    "    structural timber..... 353
	stresses in bearing plates and steel slabs..... 244, 258, 259
<b>Functions</b> .....	numbers 1 to 999..... 394-413
	trigonometric..... 414-419
<b>Gages</b> .....	specific gravity and weight..... 364
<b>Gages</b> .....	angles, for punching..... 240, 241
	beams, for punching..... 237, 238
	Birmingham wire gage..... 420
	channels, for punching..... 239
	comparative table of various gages..... 422
	United States standard gage..... 421
<b>Gage Variation</b> .....	steel plates, see A. S. T. M. Specifications..... 4-54
<b>Girders</b> .....	explanatory notes..... 263
	angle and plate girders, safe loads..... 266-284
	beam and plate girders, safe loads..... 264, 265
	elements of compound sections..... 168, 169
	grillage foundations..... 258-262
<b>Grillage Foundations</b> ..	explanatory notes and calculation..... 258-262
<b>Grips of Rivets</b> .....	length of field rivets..... 152
<b>H-Beams</b> .....	beam safe load tables..... 224
	column safe load tables..... 290
	elements of sections..... 174
	profiles, dimensions and weights..... 68
<b>Half Rounds</b> .....	list of sizes..... 111
<b>Hexagons</b> .....	list of sizes..... 111
<b>Hollow Sections</b> .....	rounds and squares, elements..... 192, 193
	cast iron columns..... 314-316
<b>Impact Stresses</b> .....	effect on beams..... 208, 209
<b>Increase of Sections</b> ..	method of rolling..... 56
<b>Lateral Deflection</b> .....	explanatory notes and formula..... 156, 198, 208
<b>Lattice Bars</b> .....	dimensions for columns..... 158
<b>Liquids</b> .....	coefficients of expansion..... 371
	specific gravity and weight..... 364
<b>Live Loads, Floors</b> .....	building laws of various cities..... 318
<b>Logarithms</b> .....	numbers 1 to 999..... 394-413
<b>Longitudinal Shear</b> .....	explanation and formula..... 209, 210
<b>Loop Rods</b> .....	sizes and dimensions..... 147

## INDEX

	Page
Masonry and Stone . . . coefficients of expansion . . . . .	371
	specific gravity and weight . . . . . 365
	strength, unit fiber stresses . . . . . 370
Materials . . . . . coefficients of expansion . . . . .	371
	specific gravity and weight . . . . . 364-367
	strength, unit fiber stresses . . . . . 368-370
Measures and Weights . . . equivalents of U. S. and metric . . . . .	372-383
Mensuration . . . . . mathematical formulas . . . . .	384-393
Metals and Alloys . . . . . coefficients of expansion . . . . .	371
	specific gravity and weight . . . . . 364
	strength, unit fiber stresses . . . . . 368, 369
Metric Tables . . . . . weights and measures . . . . .	372-383
Minerals . . . . . specific gravity and weight . . . . .	365
Modulus of Elasticity . . . various substances . . . . .	200, 353, 368-370
Moments of Inertia . . . definition and formulas . . . . .	161-167
	structural sections, tables . . . . . 170-191
Neutral Axis . . . . . definition and formulas . . . . .	161-167
	structural shapes, tables . . . . . 172-191
Nuts . . . . . dimensions and weights . . . . .	140-143
	recessed pin nuts, sizes and dimensions . . . . . 150
	sleeve nuts, sizes and dimensions . . . . . 149
Nut Steel Flats . . . . . list of sizes . . . . .	110
Ordering Materials . . . general instructions . . . . .	55
Piling, Steel Sheet . . . explanatory notes . . . . .	348-350
	elements, rolled and assembled sections . . . . . 188, 351
	profiles, rolled sections . . . . . 104
Pins . . . . . explanatory notes . . . . .	249
	bearing values, tables . . . . . 252
	bending moments, tables . . . . . 253
	cotter pins, sizes and dimensions . . . . . 150
Pipe . . . . . black and galvanized . . . . .	138, 139
Plate Girders . . . . . see Girders . . . . .	168, 169, 258-284
Plates, Flat Rolled Steel . . extrusion sizes . . . . .	107-109
	carbon steel, sheared, rectangular and circular . . . . . 107, 108
	" " , universal rectangular . . . . . 107
	nickel steel, sheared, rectangular . . . . . 109
	" " , universal, rectangular . . . . . 109
Plates, Floor Plates . . . buckle plates, explanatory notes and sizes . . . . . 334, 335	
	cheekered plates, elements and safe loads . . . . . 338
	" " profiles, weights, dimensions . . . . . 106
	corrugated plates, elements and safe loads . . . . . 188, 337
	" " profiles, weights, dimensions . . . . . 105
	trough plates, elements and safe loads . . . . . 188, 336
	" " profiles, weights, dimensions . . . . . 105
Plates, Wall Plates . . . see Bearing Plates . . . . .	244, 245
Profiles of Sections . . . dimensions and weights . . . . .	58-106, 120-137
Punching . . . . . details for punching and riveting . . . . .	246-248
	construction specifications . . . . . 159
Purlins . . . . . explanatory notes . . . . .	341



# CARNEGIE STEEL COMPANY

	Page
<b>Radius of Gyration</b> . . . . . definition . . . . .	161
angles back to back, tables . . . . .	194-196
formulas for elements of sections . . . . .	162-169
structural shapes, tables . . . . .	170-180
<b>Rails</b> . . . . . elements of A. R. A. and A. S. C. E. sections . . . . .	189
profiles, weights and dimensions . . . . .	132, 133
<b>Rails and Accessories</b> . . . . . weights and dimensions . . . . .	136
<b>Rail Clips</b> . . . . . profiles, dimensions and weights . . . . .	137
<b>Ratio of Slenderness</b> . . . . . definition . . . . .	285
unit stresses for compression formulas . . . . .	288
<b>Recessed Pin Nuts</b> . . . . . sizes and dimensions . . . . .	150
<b>Reciprocals</b> . . . . . numbers 1 to 999 . . . . .	394-413
<b>Rectangular Plates</b> . . . . . extreme sizes, carbon and nickel steel . . . . .	107-109
<b>Rectangular Sections</b> . . . . . areas . . . . .	112-114
moments of inertia . . . . .	100, 101
<b>Reinforced Concrete</b> . . . . . see Concrete, Reinforced . . . . .	118-128, 327-333
<b>Riveting</b> . . . . . construction specifications . . . . .	157, 158
details for punching and riveting . . . . .	246-248
<b>Rivets</b> . . . . . areas of rivet holes . . . . .	248
conventional signs . . . . .	246
dimensions . . . . .	151
lengths for various grips . . . . .	152
stresses, shearing and bearing values . . . . .	249-251
structural details for riveting . . . . .	246-248
weights . . . . .	153
<b>Roofs</b> . . . . . explanatory notes . . . . .	339-341
live loads, building laws of various cities . . . . .	318
snow and wind loads . . . . .	339
trusses, stresses and length of members . . . . .	342-345
weights, roof covering and roof trusses . . . . .	340, 341
<b>Screw Threads</b> . . . . . Franklin Institute, U. S. and A. B. Co. standards . . . . .	140
<b>Section Modulus</b> . . . . . definition and formulas . . . . .	161-169
structural shapes . . . . .	170-189
<b>Segments, Circular</b> . . . . . coefficients of areas . . . . .	389-391
<b>Separators</b> . . . . . standard for beams . . . . .	242
<b>Shearing Stresses</b> . . . . . longitudinal and vertical . . . . .	198, 209, 210
<b>Sheared Plates</b> . . . . . extreme sizes, carbon and nickel steel . . . . .	107-109
<b>Shearing Values, Rivets</b> . . . . . tables . . . . .	250, 251
<b>Ship and Car Channels</b> . . . . . see Channels, Ship and Car . . . . .	81-85, 173, 174
<b>Skelp</b> . . . . . list of sizes . . . . .	110
<b>Sleeve Nuts</b> . . . . . sizes and dimensions . . . . .	149
<b>Snow Loads</b> . . . . . roofs and trusses . . . . .	339
<b>Specifications</b> . . . . . American Bridge Company . . . . .	154-160
American Society for Testing Materials . . . . .	4-54
<b>Specific Gravity</b> . . . . . various substances . . . . .	364, 365
<b>Splice Bars</b> . . . . . elements of A. R. A. and A. S. C. E. sections . . . . .	189
profiles, dimensions and weights . . . . .	134, 135
<b>Square and Round Bars</b> . . . . . area and weight . . . . .	118, 119
<b>Square Edge Flats</b> . . . . . list of sizes . . . . .	110
<b>Squares, Square Roots</b> . . . . . numbers 1 to 999 . . . . .	394-413
<b>Strength of Materials</b> . . . . . unit fiber stresses . . . . .	368, 370
<b>Stresses</b> . . . . . see Beam Stresses . . . . .	156, 197-212

# INDEX

	Page
<b>Tees</b> .....	elements of sections ..... 169, 184, 185
	profiles, weights and dimensions ..... 94-101
	safe load tables ..... 235
<b>Terra Cotta</b> .....	arches, ceilings, furring, partition, roofing ..... 320-326
<b>Test Bars</b> .....	standard, see A. S. T. M. Specifications ..... 4-54
<b>Threads</b> .....	length of bolt threads ..... 141
	standard dimensions of screw thread ..... 140
<b>Thrust in Arches</b> .....	effect in floor construction ..... 320-322
<b>Tie Rods</b> .....	length and weight ..... 243
	spacing ..... 322
<b>Timber, Structural</b> ....	A. R. E. A. unit stresses and explanatory notes. 352, 353
	beams, deflections, limiting loads and spans... 355
	“ explanatory notes ..... 354
	“ safe load tables ..... 356-360
	coefficients of expansion ..... 371
	columns, explanatory notes ..... 361
	“ safe load tables ..... 362, 363
	specific gravity and weight ..... 364
<b>Triangle Mesh</b> .....	concrete reinforcement ..... 333
<b>Trigonometric Formulas</b>	functions of angles and triangles ..... 386, 387
<b>Trigonometric Functions</b>	natural ..... 414-419
<b>Trough Plates</b> .....	elements of sections ..... 188
	profiles, weights and dimensions ..... 105
	riveted sections, elements and safe loads ..... 336
<b>Trusses</b> .....	explanatory notes ..... 341
	stresses and length of members ..... 342-345
	weights of trusses ..... 341
<b>Turnbuckles</b> .....	size and dimensions ..... 149
<b>Unit Stresses</b> .....	see Fiber Stresses ..... 154, 155, 353, 368-370
<b>Universal Mill Plates</b> ...	extreme sizes, carbon- and nickel steel ..... 107, 109
<b>Upset Screw Ends</b> ....	square and round bars ..... 144, 145
<b>Vertical Shear</b> .....	explanation ..... 209
	formulas for various conditions of loading ..... 201-205
<b>Volume and Surface</b> ...	solids ..... 392, 393
<b>Web Resistances</b> .....	beams and channels ..... 213-215
<b>Weights</b> .....	flat rolled steel, tables ..... 115-117
	rounds and squares ..... 118, 119
	shapes ..... 58-106, 120-137
	various substances ..... 364-367
<b>Weights and Measures</b> ..	metric and U. S. Standard ..... 372-385
<b>Wind Loads, Pressure</b> ..	building specifications of various cities ..... 318
	roofs and trusses ..... 339
<b>Wire and Sheet Metal</b> ..	standard gages ..... 420-422
<b>Wooden Beams, Columns</b>	see Timber, Structural ..... 354-361
<b>Zee Bars</b> .....	elements of sections ..... 166, 186
	profiles, weights and dimensions ..... 102, 103
	safe load tables ..... 236

**CARNEGIE STEEL COMPANY**

**PRODUCTS**

**PIG IRON AND FURNACE PRODUCTS**

**FERRO-MANGANESE AND SPIEGELEISEN**

**OPEN-HEARTH AND BESSEMER STEEL, ALLOY STEELS**

**INGOTS, BILLETS, BLOOMS, SLABS, SHEET BARS**

**ARMOR AND VAULT PLATE**

**PLATES FOR BRIDGES, SHIPS, TANKS, BOILERS, AND CARS**

**ROLLED STRUCTURAL SHAPES**

**BEAMS, CHANNELS, ANGLES, TEES, ZEES**

**STEEL MINE TIMBERS AND STEEL SHEET PILING**

**BAR MILL PRODUCTS**

**CONCRETE REINFORCEMENT BARS, AGRICULTURAL SHAPES**

**MISCELLANEOUS AND SPECIAL SHAPES**

**MERCHANT BARS**

**SQUARES, ROUNDS, HALF ROUNDS, HEXAGONS, OVALS, HALF OVALS**

**FLATS, SKELP, BANDS, HOOPS, COTTON TIES**

**HOOPS FOR SLACK BARREL COOPERAGE**

**TIRE AND VEHICLE SPRING STEEL**

**TRACK MATERIAL**

**RAILS AND SPLICE BARS, DUQUESNE RAIL JOINTS,**

**TRACK ACCESSORIES**

**STEEL CROSS TIES**

**FORGINGS**

**STANDARD FORGED AND HEAT-TREATED AXLES**

**CONNECTING RODS, CRANK SHAFTS, AND ARCH BARS**

**FORGED AND ROLLED WHEELS, GEAR BLANKS,**

**AUTOMOBILE FLY WHEELS, PIPE FLANGES, SHAFT COUPLINGS**

**DERRICKS AND DRILLING RIGS**

## CARNEGIE STEEL COMPANY

### WORKS

DUQUESNE STEEL WORKS AND FURNACES.....	South Duquesne, Pa.
EDGAR THOMSON STEEL WORKS AND FURNACES.....	Bessemer, Pa.
HOMESTEAD STEEL WORKS.....	Munhall, Pa.
CARRIE FURNACES.....	Rankin, Pa.
EDITH FURNACE.....	Pittsburgh, N. S., Pa.
ISABELLA FURNACES.....	Etna, Pa.
LUCY FURNACES.....	Pittsburgh, Pa.
NEVILLE FURNACE.....	Neville Island, Pa.
CLARK MILLS.....	Pittsburgh, Pa.
McCUTCHEON MILLS.....	Pittsburgh, N. S., Pa.
PAINTER MILLS.....	Pittsburgh, S. S., Pa.
LOWER UNION MILLS.....	Pittsburgh, Pa.
UPPER UNION MILLS.....	Pittsburgh, Pa.
HOWARD AXLE WORKS.....	Homestead, Pa.
SCHOEN STEEL WHEEL WORKS.....	McKees Rocks, Pa.
BELLAIRE STEEL WORKS AND FURNACES.....	Bellaire, O.
CLAIRTON STEEL WORKS AND FURNACES.....	Clairton, Pa.
COLUMBUS STEEL WORKS AND FURNACES.....	Columbus, O.
MINGO STEEL WORKS AND FURNACES.....	Mingo Junction, O.
NEW CASTLE STEEL WORKS AND FURNACES.....	New Castle, Pa.
OHIO STEEL WORKS AND FURNACES.....	Youngstown, O.
SHARON STEEL WORKS AND FURNACE.....	Sharon, Pa.
FARRELL STEEL WORKS AND FURNACES.....	Farrell, Pa.
GREENVILLE MILLS.....	Greenville, Pa.
MONESSEN MILLS.....	Monessen, Pa.
LOWER UNION MILLS.....	Youngstown, O.
UPPER UNION MILLS.....	Youngstown, O.
NILES FURNACE.....	Niles, O.
STEBENVILLE FURNACE.....	Stebenville, O.
ZANESVILLE FURNACE.....	Zanesville, O.
PITTSBURGH WAREHOUSE.....	Pittsburgh, Pa.
BALTIMORE WAREHOUSE.....	Baltimore, Md.
CLEVELAND WAREHOUSE.....	Cleveland, O.
NEW ENGLAND WAREHOUSE.....	Allston, Mass.
WAVERLY WAREHOUSES.....	Waverly, N. J.

**CARNEGIE STEEL COMPANY**

**OFFICES**

**GENERAL OFFICES:**

**Pittsburgh, Carnegie Building.**

**DISTRICT OFFICES:**

**Birmingham, Brown-Marx Building,  
Boston, 120 Franklin Street,  
Buffalo, Marine National Bank Building,  
Chicago, 208 South La Salle Street,  
Cincinnati, Union Trust Building,  
Cleveland, Rockefeller Building,  
Denver, First National Bank Building,  
Detroit, Ford Building,  
New Orleans, Maison Blanche,  
New York, Hudson Terminal, 30 Church Street,  
Philadelphia, Widener Building,  
Pittsburgh, Carnegie Building,  
St. Louis, Third National Bank Building,  
St. Paul, Pioneer Building.**

**EXPORT REPRESENTATIVES:**

**UNITED STATES STEEL PRODUCTS CO.,**

**New York, Hudson Terminal, 30 Church Street.**

**PACIFIC COAST REPRESENTATIVES:**

**UNITED STATES STEEL PRODUCTS CO., PACIFIC COAST DEPT.**

**Los Angeles, Jackson Street and Central Avenue,  
Portland, Selling Building,  
San Francisco, Rialto Building,  
Seattle, Fourth Ave. South and Connecticut Ave.**

